Characterization of Fuel Cell Materials

Karren More, Chad Parish, Kelly Perry,
Miaofang Chi, and Shawn Reeves

Oak Ridge National Laboratory
Oak Ridge, TN

June 9, 2010

Project ID FC020

This presentation does not contain any proprietary, confidential, or otherwise restricted information

Project Overview

Timeline

- **Project initiated in FY2000**
- **Continuous - fundamental research on microstructural characterization to improve MEA durability**

Budget

- **Funding in FY09 - $500k**
- **Funding in FY10 - $583k**

Barriers

- **Fuel Cell Barriers Addressed**
  - **A: Durability**
  - **C: Performance**
  - **G: Start-up/Shut-down Time and Energy/Transient Operation**

Partners

- **Los Alamos National Laboratory**
- **Argonne National Laboratory**
- **3M Company**
- **UTC Power**
- **Cabot Superior Micropowders**
- **Naval Research Laboratory**
- **Honda Research Institute**
- **Jet Propulsion Laboratory**
- **University of Houston**
- **University of Illinois - Chicago**
- **Rensselaer Polytechnic Institute**

Relevance - ORNL Research Objectives

- Identify and optimize novel high-resolution imaging and compositional/chemical analysis techniques, and unique specimen preparation methodologies, for the μm-Å-scale characterization of the material constituents comprising fuel cells (catalyst, support, membrane)
- Apply advanced analytical and imaging techniques for the evaluation of microstructural and microchemical changes that correlate with fuel cell performance
- Elucidate microstructure-related degradation mechanisms contributing to fuel cell performance loss
- MAKE TECHNIQUES AND EXPERTISE AVAILABLE TO FC RESEARCHERS OUTSIDE OF ORNL!

Approach: Use Advanced Imaging and Compositional Analysis Techniques to Evaluate μm-Å-Scale MEA Microstructures

- Apply state-of-the-art electron microscopy techniques for the analysis of MEA material constituents:
  - Catalyst nanoparticles
  - Membranes
  - Carbon supports
  - GDLs/MPLs
- Collaborate with industry, academia, and national laboratories to make these techniques (and expertise) available to correlate structure/composition with MEA processing and/or life-testing studies

Milestones

- FY09 Milestones:
  - Publish results for AC-STEM analyses of Pt-based catalyst stability during in-situ heating *Completed*
  - Complete study of the mechanisms of carbon support oxidation/corrosion under relevant PEMFC operating conditions and report results *Completed*
- FY10 Milestones:
  - Establish “baseline” design for window/chips for *in-situ* electrochemical cell for STEM imaging/analysis *Completed*
  - Publish results of preliminary *in-situ* STEM catalyst degradation study *In Progress*

Technical Accomplishments and Progress

- Investigated carbon-support corrosion mechanisms in electrochemically-aged MEAs
- Studied Pt migration as a function of aging protocols
- Applied advanced statistical analysis techniques to evaluate Å-scale elemental/compositional analyses of catalyst nanoparticles (Multivariate Statistical Analysis – Principal Component Analysis)
- Continued development of liquid STEM technique to characterize PEMFC materials constituents during operation – many obstacles encountered!

Technical Accomplishments and Progress
Understanding Mechanisms of Carbon Corrosion at Cathode

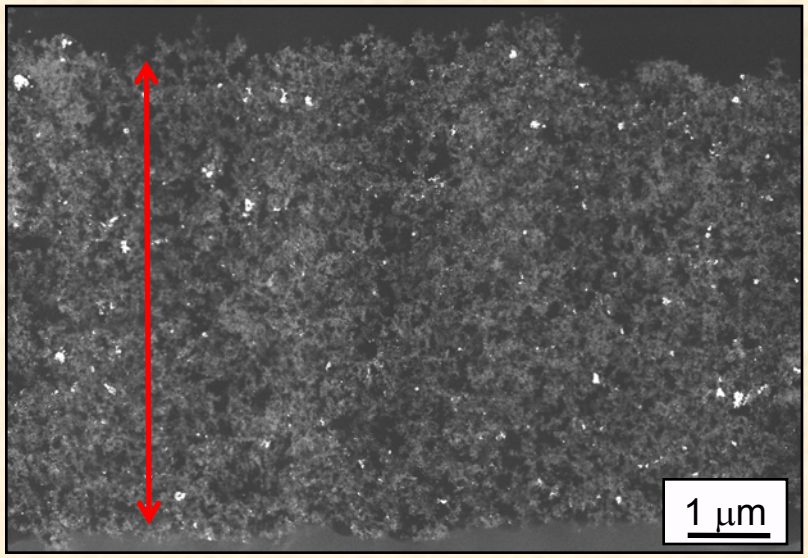

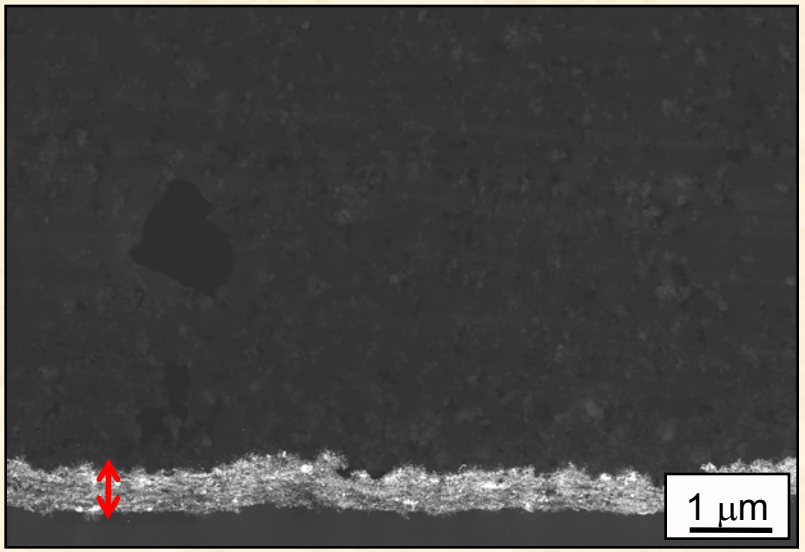

During electrochemical aging under adverse conditions (>OCV; start-up/shut-down cycles; H_2 fuel starvation), the cathode can collapse/compress/thin resulting in major implications for:

- loss of catalyst electrochemically active surface area (Pt EASA)
- loss of catalyst support (carbon) due to enhanced electrochemical oxidation
- loss of porosity for gas transport to reactive sites
- implications for water management

Recent publications suggest that:

- severe oxidation of carbon results in LITTLE/NO carbon support remaining in cathode
  $C + 2H_2O \rightarrow CO_2 + 4H^+ + 4e^-$ (carbon loss and CO_2 evolution)
- Pt is “detached” from support

Technical Accomplishments and Progress

Understanding Mechanisms of Carbon Corrosion at Cathode

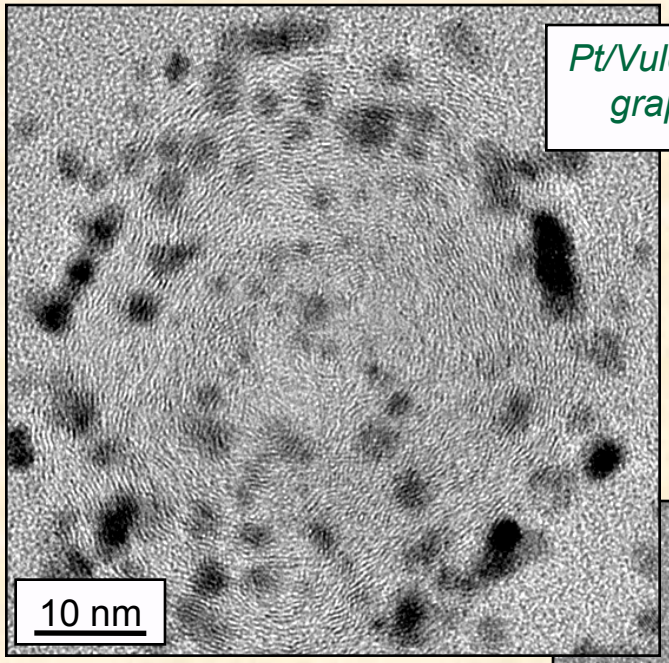

Pt/Vulcan – virgin MEA graphitic structure

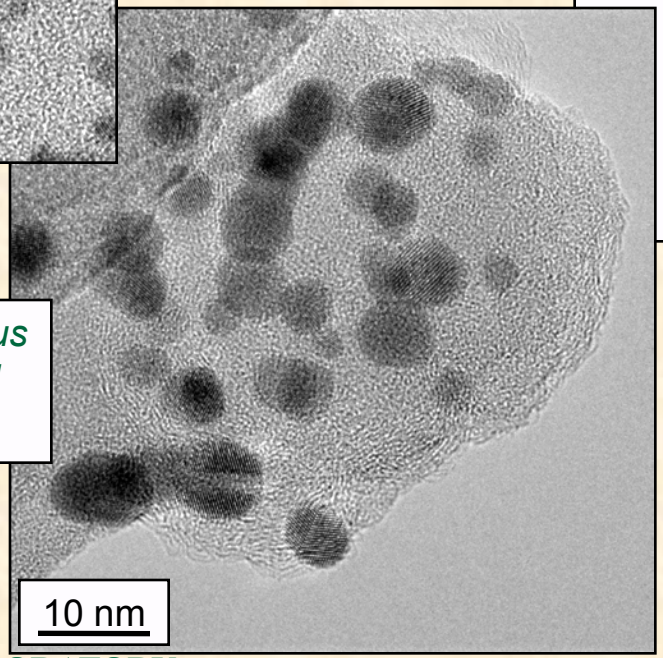

Pt/Vulcan –amorphous carbon in collapsed cathode

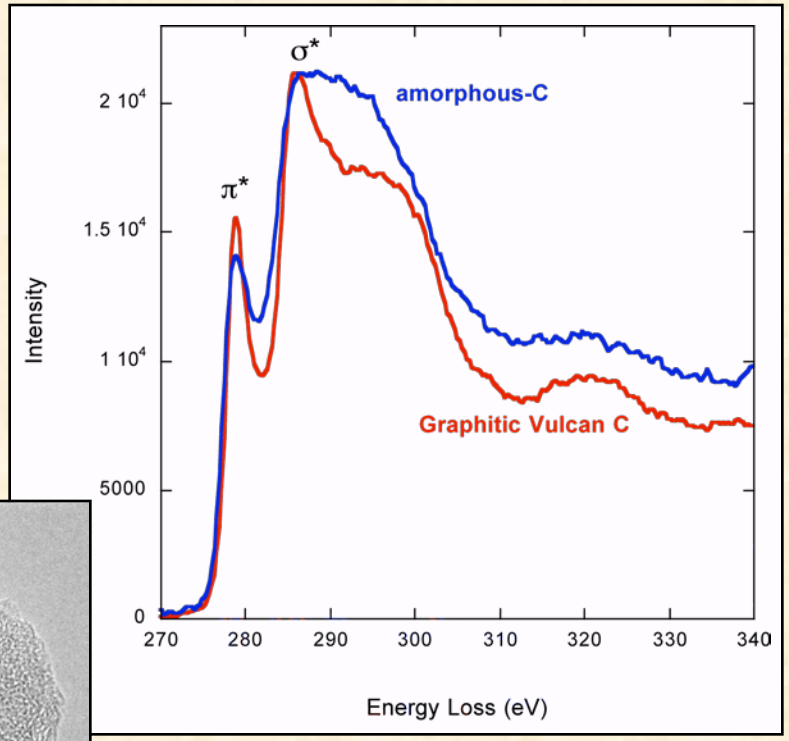

Corrosion of carbon black at cathode:

- *some loss of carbon via oxidation to CO_2*
- *oxidation resulting in amorphous "glassy" carbon*
- *sintering of glassy carbon particles*
- *extreme Pt coarsening – Pt particles remain attached to glassy carbon*

Technical Accomplishments and Progress

Understanding Mechanisms of Carbon Corrosion at Cathode

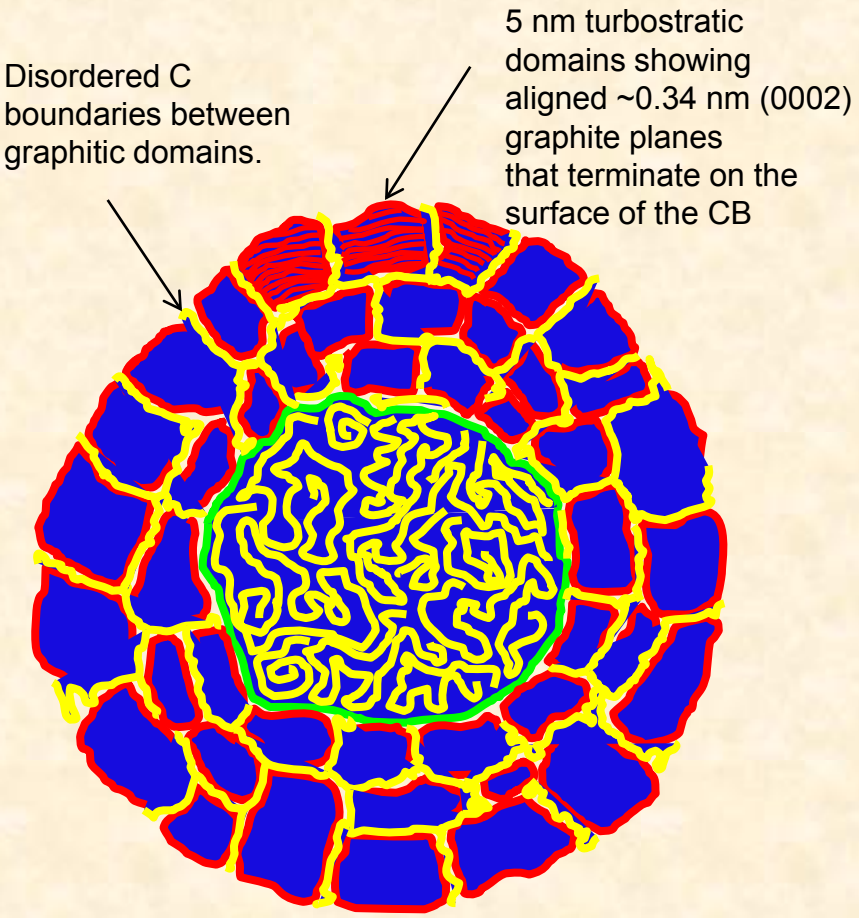

Structure Of Vulcan Support

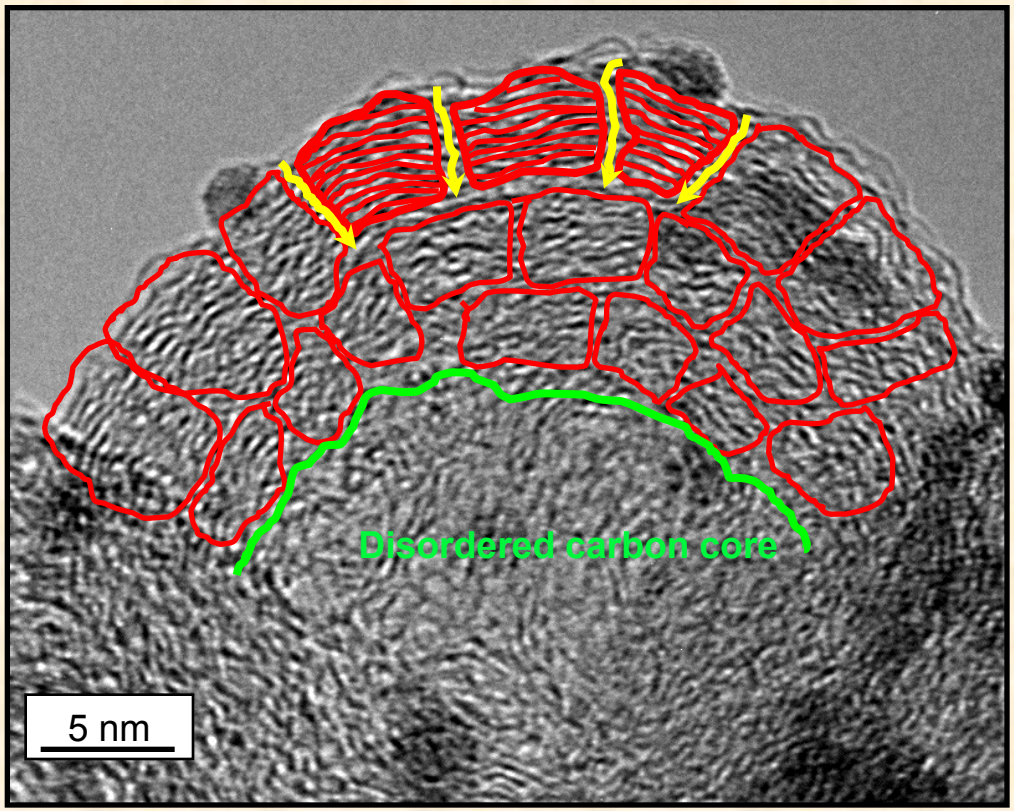

The amount of disordered carbon within a CB particle is ~20% for both the domain boundaries + central core (Zerda, et. al., *Carbon* **38** (2000) 355). The surface roughness is limited to 1-2 graphite $d_{(0002)}$ (~0.6 nm) where domains meet at the disordered boundaries.

"Mosaic-domain structure"
Oberlin, in Chemistry and Physics of Carbon **22** (1965) 1
Huttepain and Oberlin, *Carbon* **28**[1] (1990) 103

Technical Accomplishments and Progress

Understanding Mechanisms of Carbon Corrosion at Cathode

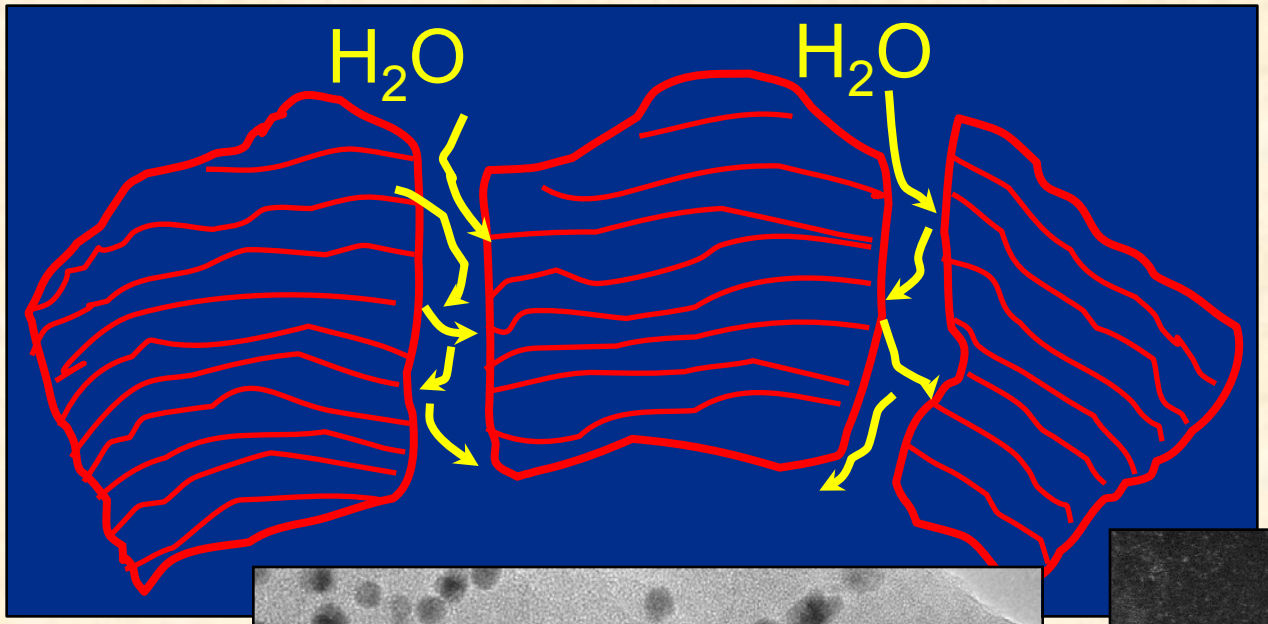

Reactivity on basal plane surface-terminating sites is very low

Reactivity of disordered carbon between graphitic domains (singly-bonded carbon end sites) is much higher.

Carbon oxidation results in a fully densified cathode

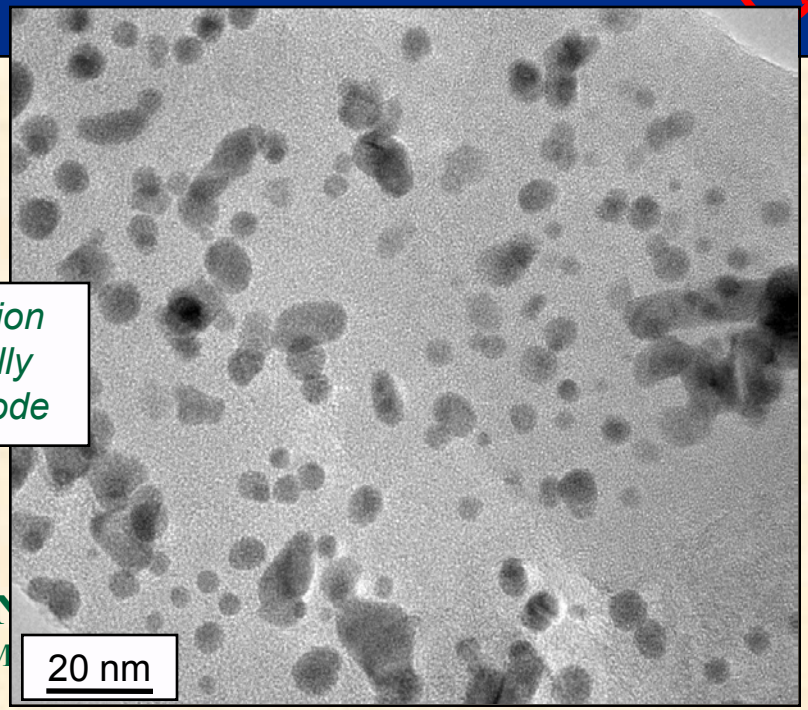

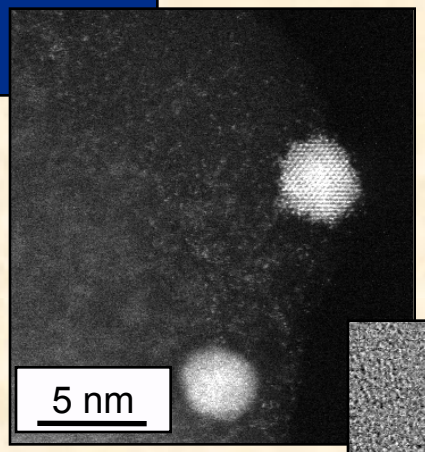

Impurities (glass-formers such as Ca, Si) can accelerate amorphization/sintering

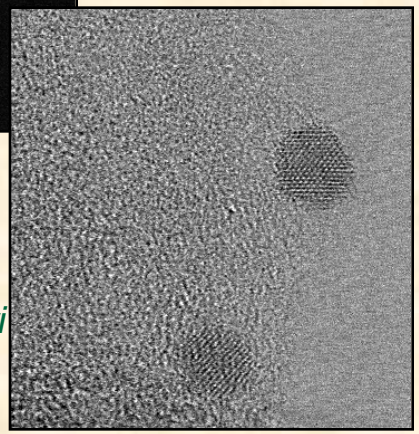

Technical Accomplishments and Progress

Understanding Mechanisms of Carbon Corrosion at Cathode

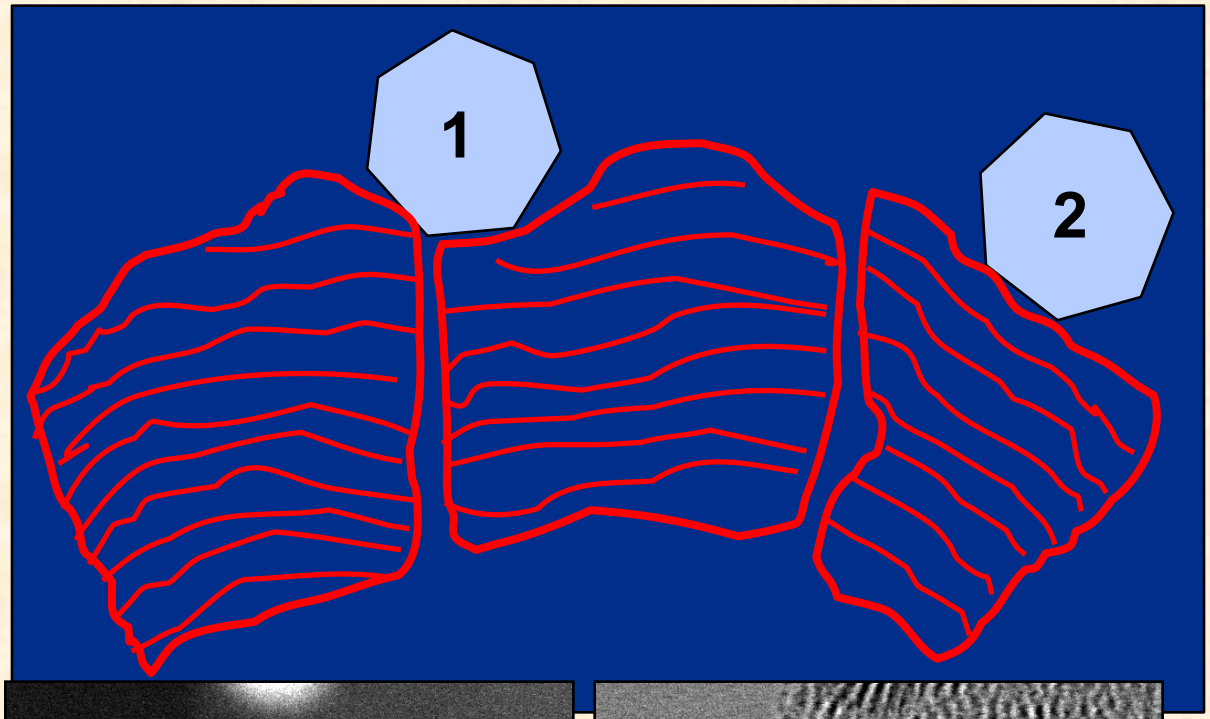

Nucleation of Pt On Vulcan Surface

1 – *Pt nucleates preferentially at disordered regions between graphitic domains:*

- *Pt anchored by oxygen-containing functional groups on basal plane edges*

2 – *Pt nucleates preferentially on surfaces of graphitic domains*

- *Pt anchored by π sites on basal plane surfaces*

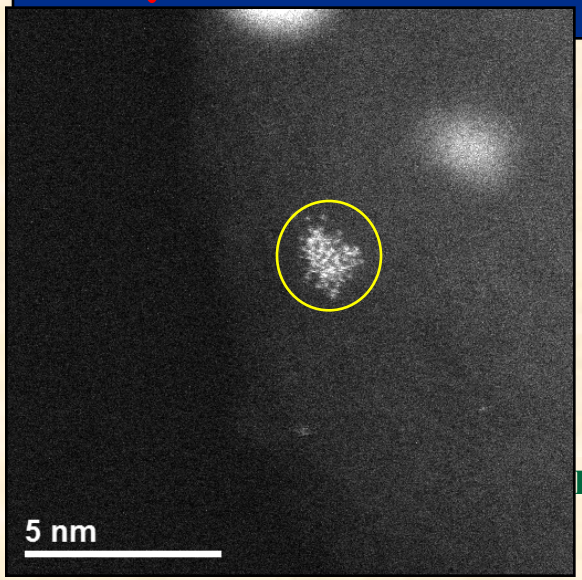

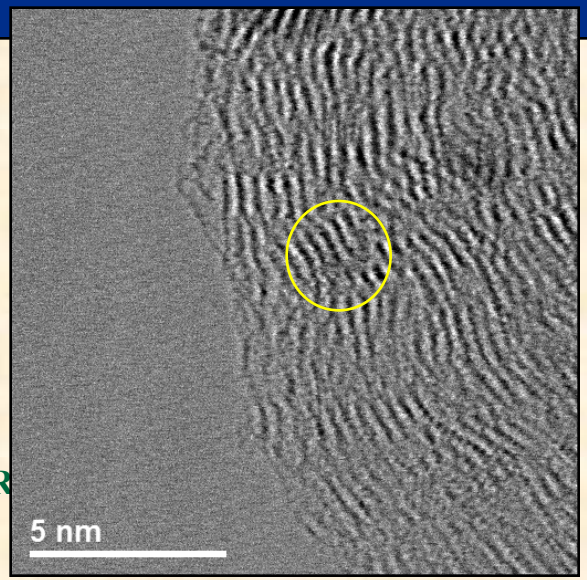

Indications are that Pt nucleates on the π sites on basal plane surfaces, which would leave disordered channels open to surface

UT-BATTELLE

Technical Accomplishments and Progress

Using Statistical Data Analysis Methods For Nanoparticle Analysis

Multivariate Statistical Analysis – Principal Component Analysis

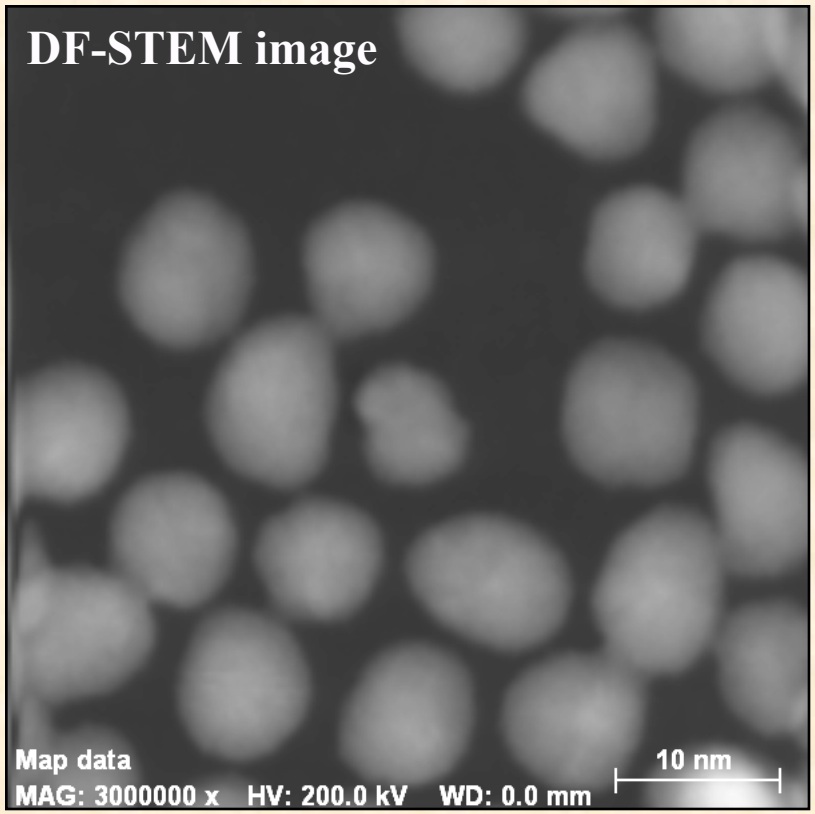

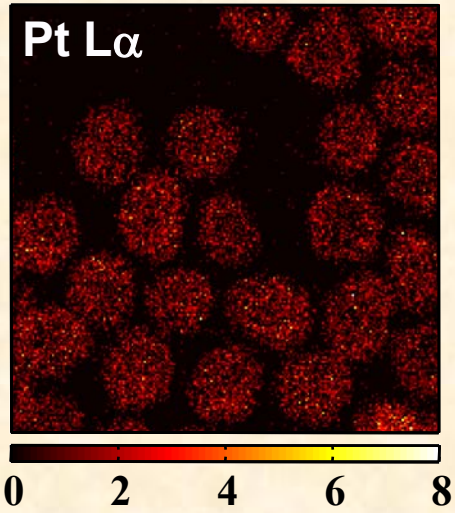

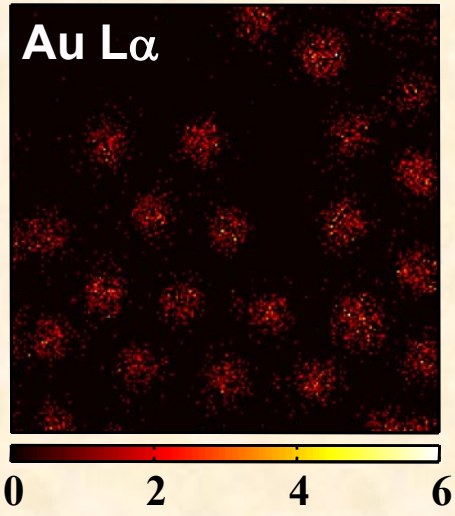

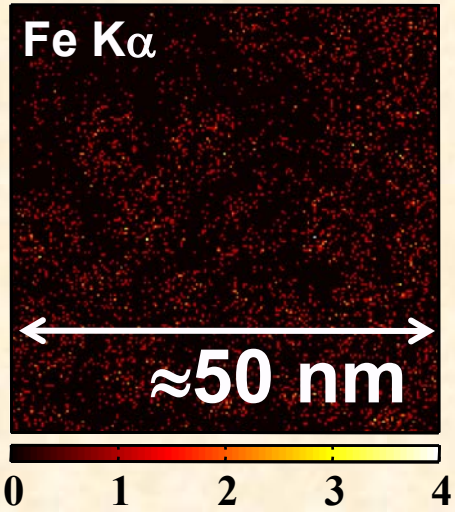

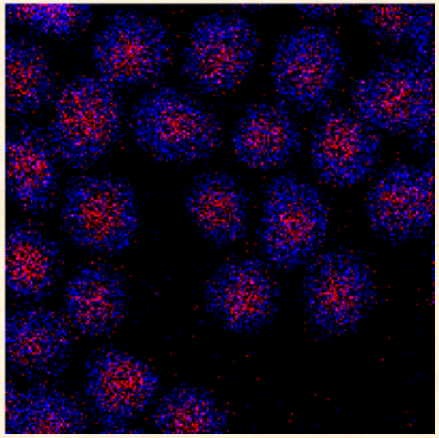

Pt-Lα counts
Au-Lα counts

"Raw" EDS data
Pt-shell/Au-core structure evident but association of Fe not clear

Technical Accomplishments and Progress

Using Statistical Data Analysis Methods For Nanoparticle Analysis

Multivariate Statistical Analysis – Principal Component Analysis

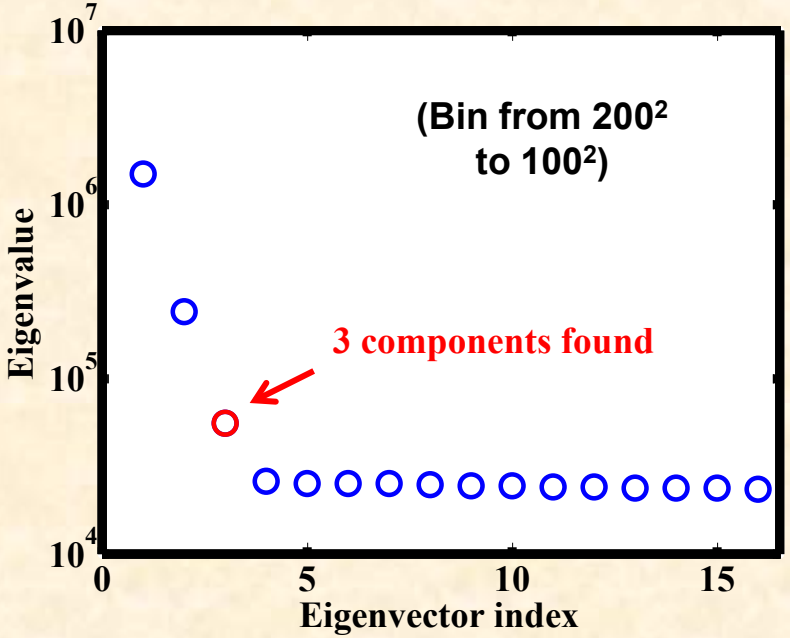

PCA/MVSA allows for an "unbiased" analysis of the data to extract the primary elements and their primary lociation within the structure of the nanoparticle

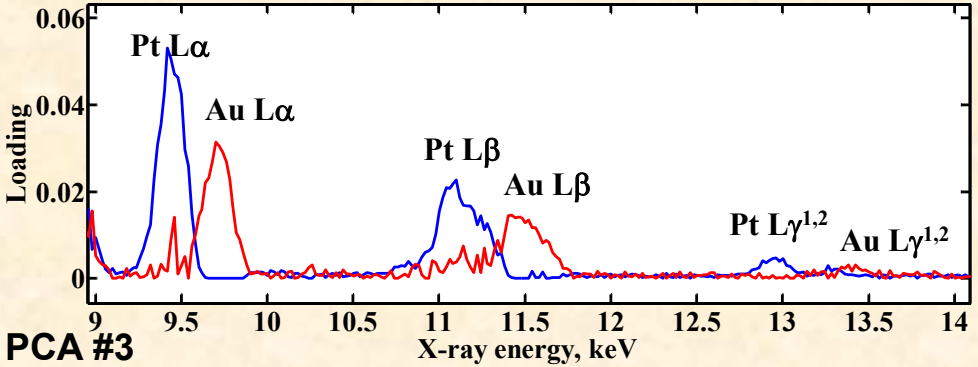

PCA #1
Mostly C

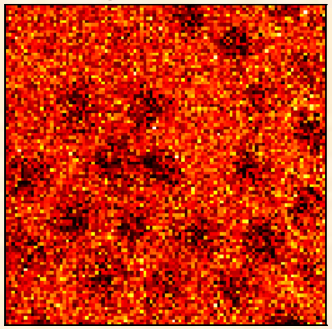

PCA #2
Pt-Fe

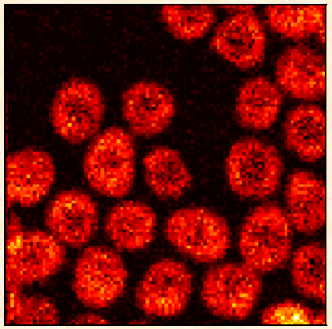

PCA #3
Essentially pure Au

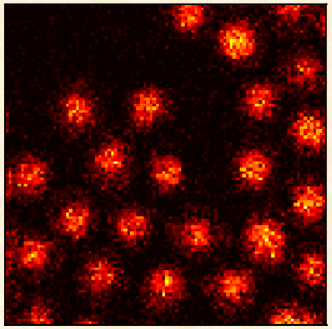

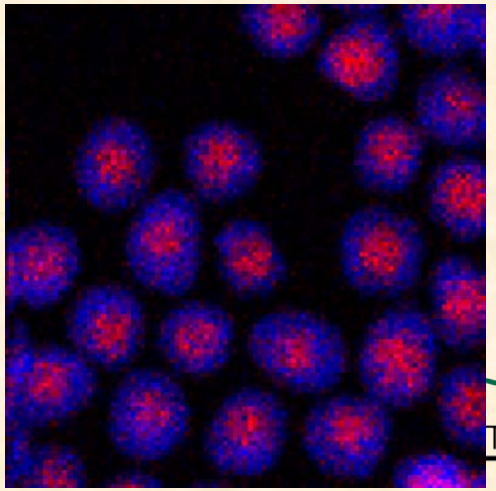

Technical Accomplishments and Progress

Pt Migration From Cathode Into Membrane

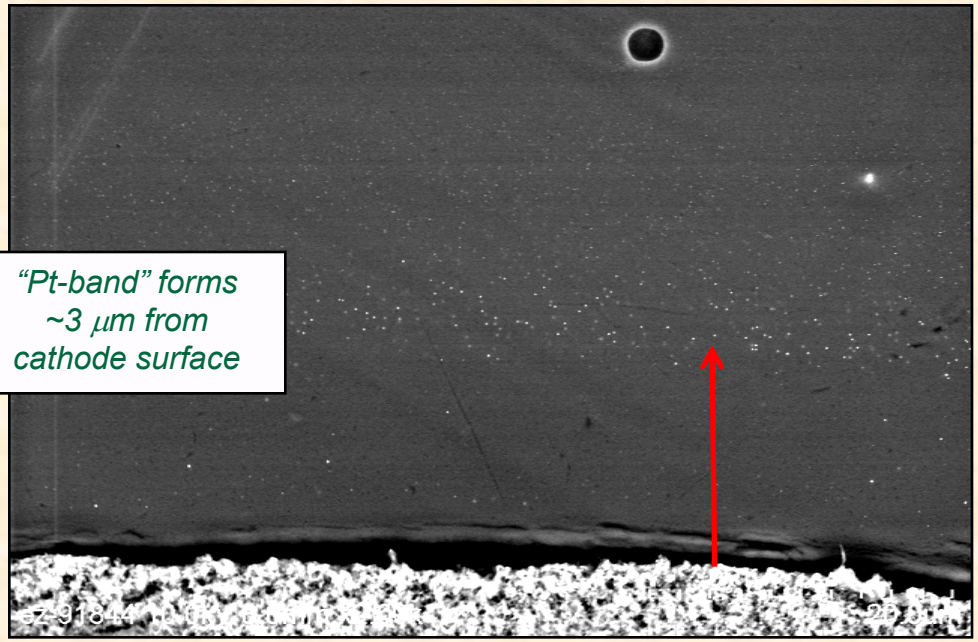

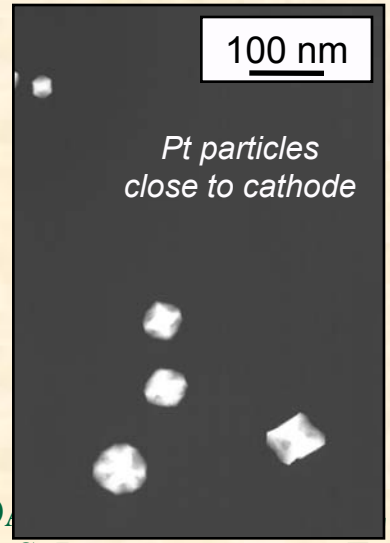

So-called "Pt-band" refers to the highest concentration of Pt particles that precipitate out in membrane at some distance from cathode surface: *Pt migration profiles are much more complicated and are comprised of numerous "Pt-bands" of different size Pt particles distributed across the membrane*

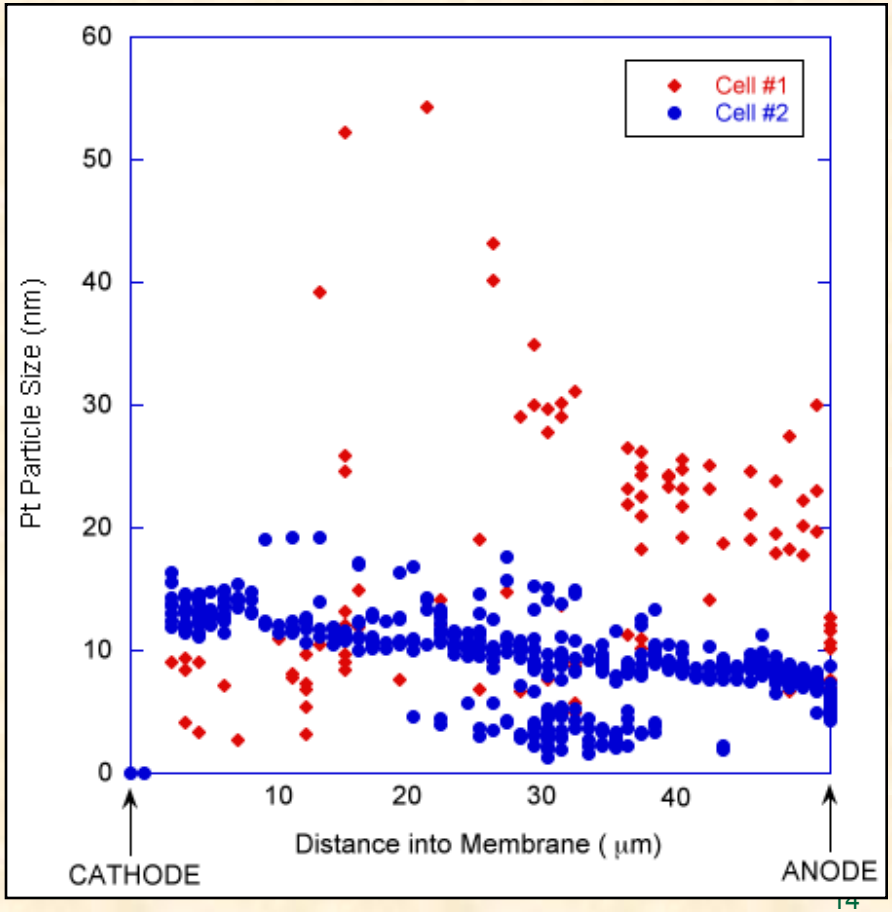

Future Work

- Correlate microstructural/compositional observations with AST protocols (automotive and stationary), especially related to catalyst coarsening & migration, carbon corrosion, membrane degradation
- Apply novel statistical analysis techniques to new catalyst compositions, both as-processed and aged/tested
- Continue to evaluate and add capabilities to the *in situ* liquid holder for near live-time, nm-scale microscopy of PEM fuel cell material constituents operated under relevant operating conditions – liquid electrolytes, temperature, potential cycling, etc.
- Continue to establish collaborations with industries, universities, and national laboratories (including access via ORNL User Facilities) to facilitate “transfer” of unique capabilities.
- Support new DOE projects with microstructural characterization and advanced characterization techniques.

Summary

- Several new collaborations have been established during the past year that have "taken advantage of" the unique imaging (microscopy) capabilities at ORNL:
  - Work-for-Others (proprietary research)
  - Shared Research Equipment (SHaRE) User Program (non-proprietary research) - University of Houston, University of Texas, University of Connecticut, Rensselaer Polytechnic Institute
  - Baseline PEM-MEA Characterization Program (non-proprietary)
- MVSA/PCA is being applied "routinely" to analyzing compositions/distributions of elements comprising catalysts
- New insight into understanding carbon corrosion mechanisms and Pt migration will enable strategies for improved material stability to be studied/implemented