



New Concepts for Optimized Hydrogen Storage in MOFs

Omar M. Yaghi and Adam J. Matzger
Department of Chemistry
University of Michigan
Ann Arbor, MI 48109

May 23, 2005

This presentation does not contain any proprietary or confidential information

Project ID #
STP52 Yaghi



Overview

Timeline

- Project start date
1/1/2005
- Project end date
12/31/2008
- Percent complete
2%

Budget

- Total project funding
 - DOE share: \$1.60M
 - Contractor share: \$0.35M
- Funding received in FY04
 - \$0.00
- Funding for FY05
 - \$37,500 (estimated)

Barriers

- Technical barriers addressed
 - B) Weight and Volume
 - C) Efficiency
 - M) Hydrogen Capacity and Reversibility
- Technical targets by YR 2010
 - Gravimetric capacity: 6.0%
 - Volumetric capacity: 4.5%
 - Operating ambient temp.: -30/50 °C

Partners (planned FY06)

- Juergen Eckert (Los Alamos)
- Randall Q. Snurr (Northwestern University)
- Joseph T. Hupp (Northwestern University)



Objectives

To develop next generation, highly porous metal-organic framework materials (MOFs) that meet or exceed DOE targets for on-board H₂ storage.

- Improve mass and volumetric H₂ density in MOFs.
 - Utilize strategies for design of materials with high thermal stability and architectural stability.
 - Utilize new concepts for synthesis of materials with extraordinary surface areas (>2000 m²/g)
 - Develop strategies for synthesis of MOFs having minimal open space but very high surface areas.
- Employ MOFs in reversible H₂ storage systems.
 - Measure H₂ uptakes under full range of temperatures and pressures as specified in the DOE freedomCAR guidelines.
 - Down-select best materials for scale-up.




Design and Approach

- Implement three major strategies that minimizes open space while increasing total surface area for H₂ binding.
 - Increase surface areas by increasing exposed edges in framework comprising MOF.
 - Use catenated networks.
 - Impregnation of large pores to produce new internal sorption sites and higher surface area.
- Equilibrium H₂ uptake as a function of structure.
 - Measure H₂ uptakes under full range of conditions designated in DOE YR 2010 targets.
 - Use Raman spectroscopy to elucidate H₂ interaction with new materials.




MOFs as H₂ Storage Materials

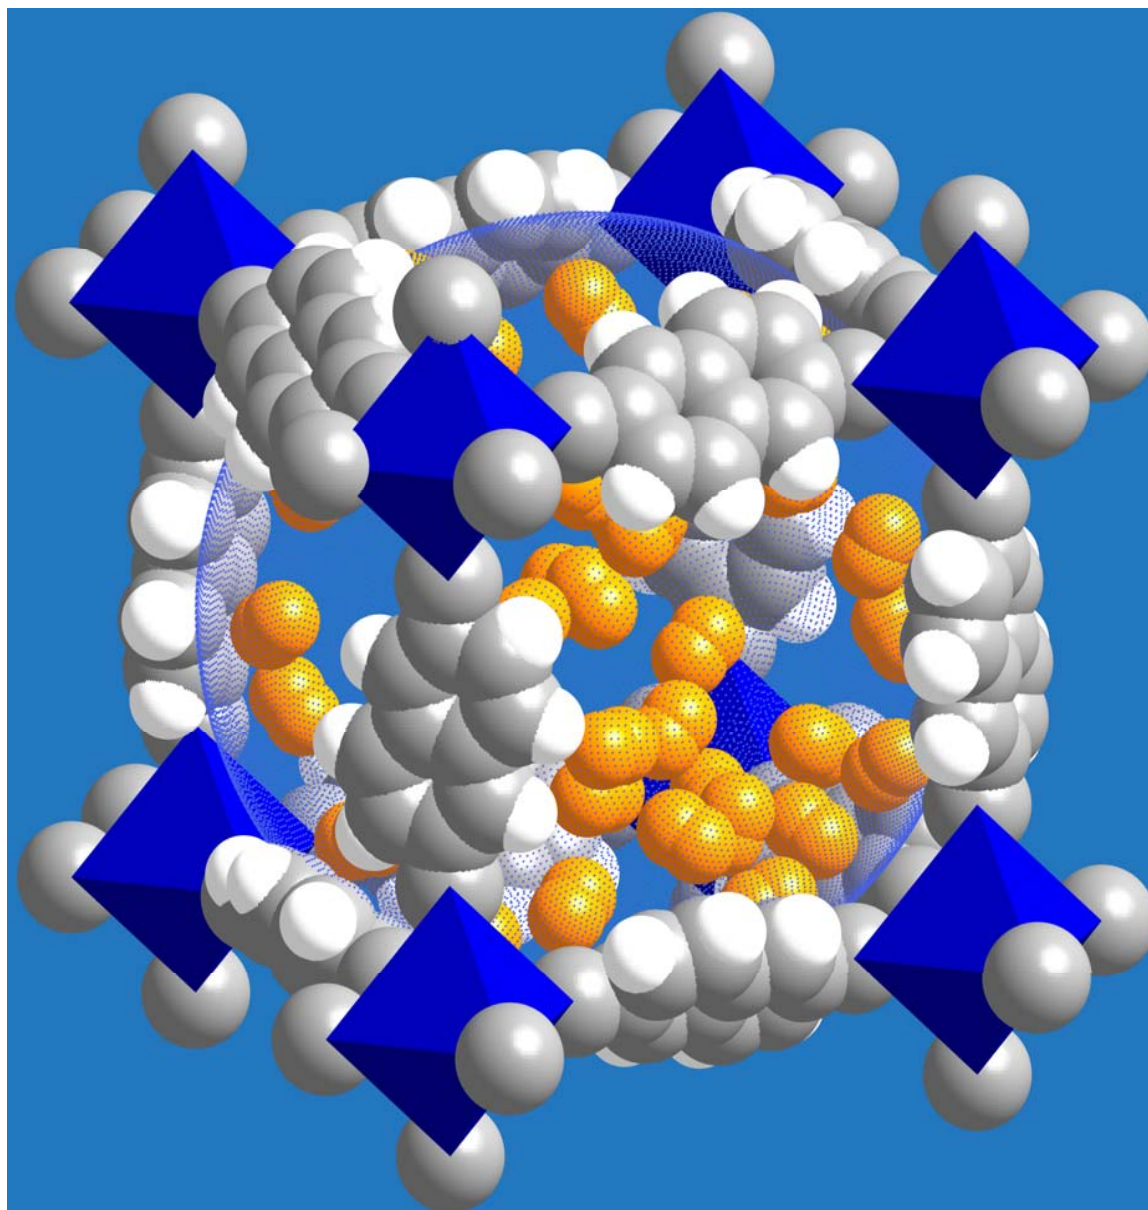




Synthetic Strategy to High Surface Area MOFs


Exposing latent edges dramatically increases surface area.

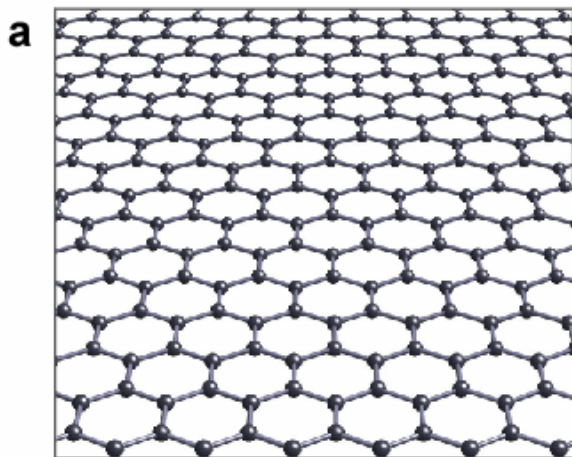


2,965 m²/g

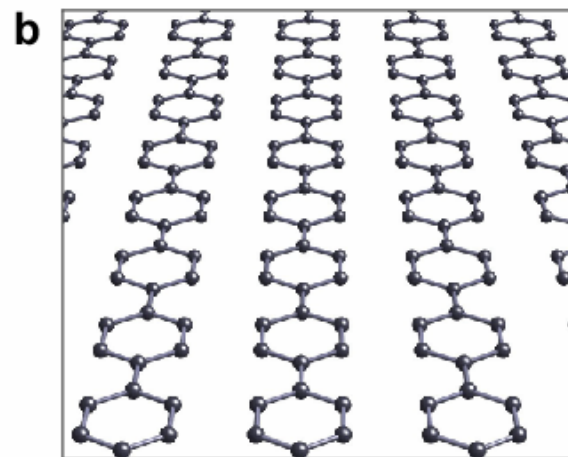

5,683 m²/g

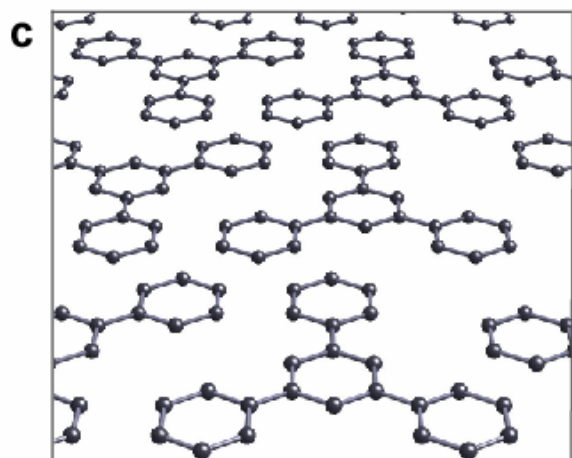

6,200 m²/g

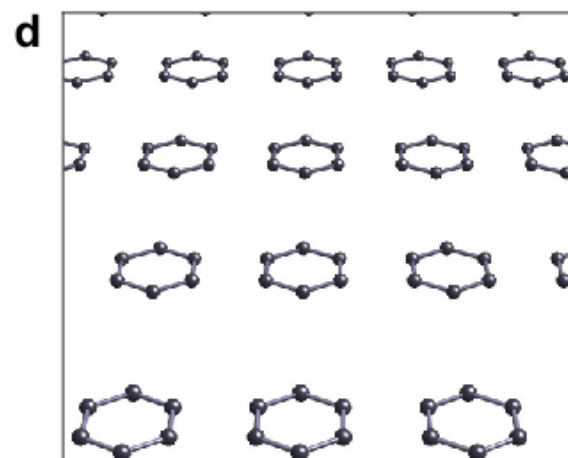


7,745 m²/g



H₂ Storage Capacity at RT & 10 bar


Volumetric Apparatus [mg H₂/g]

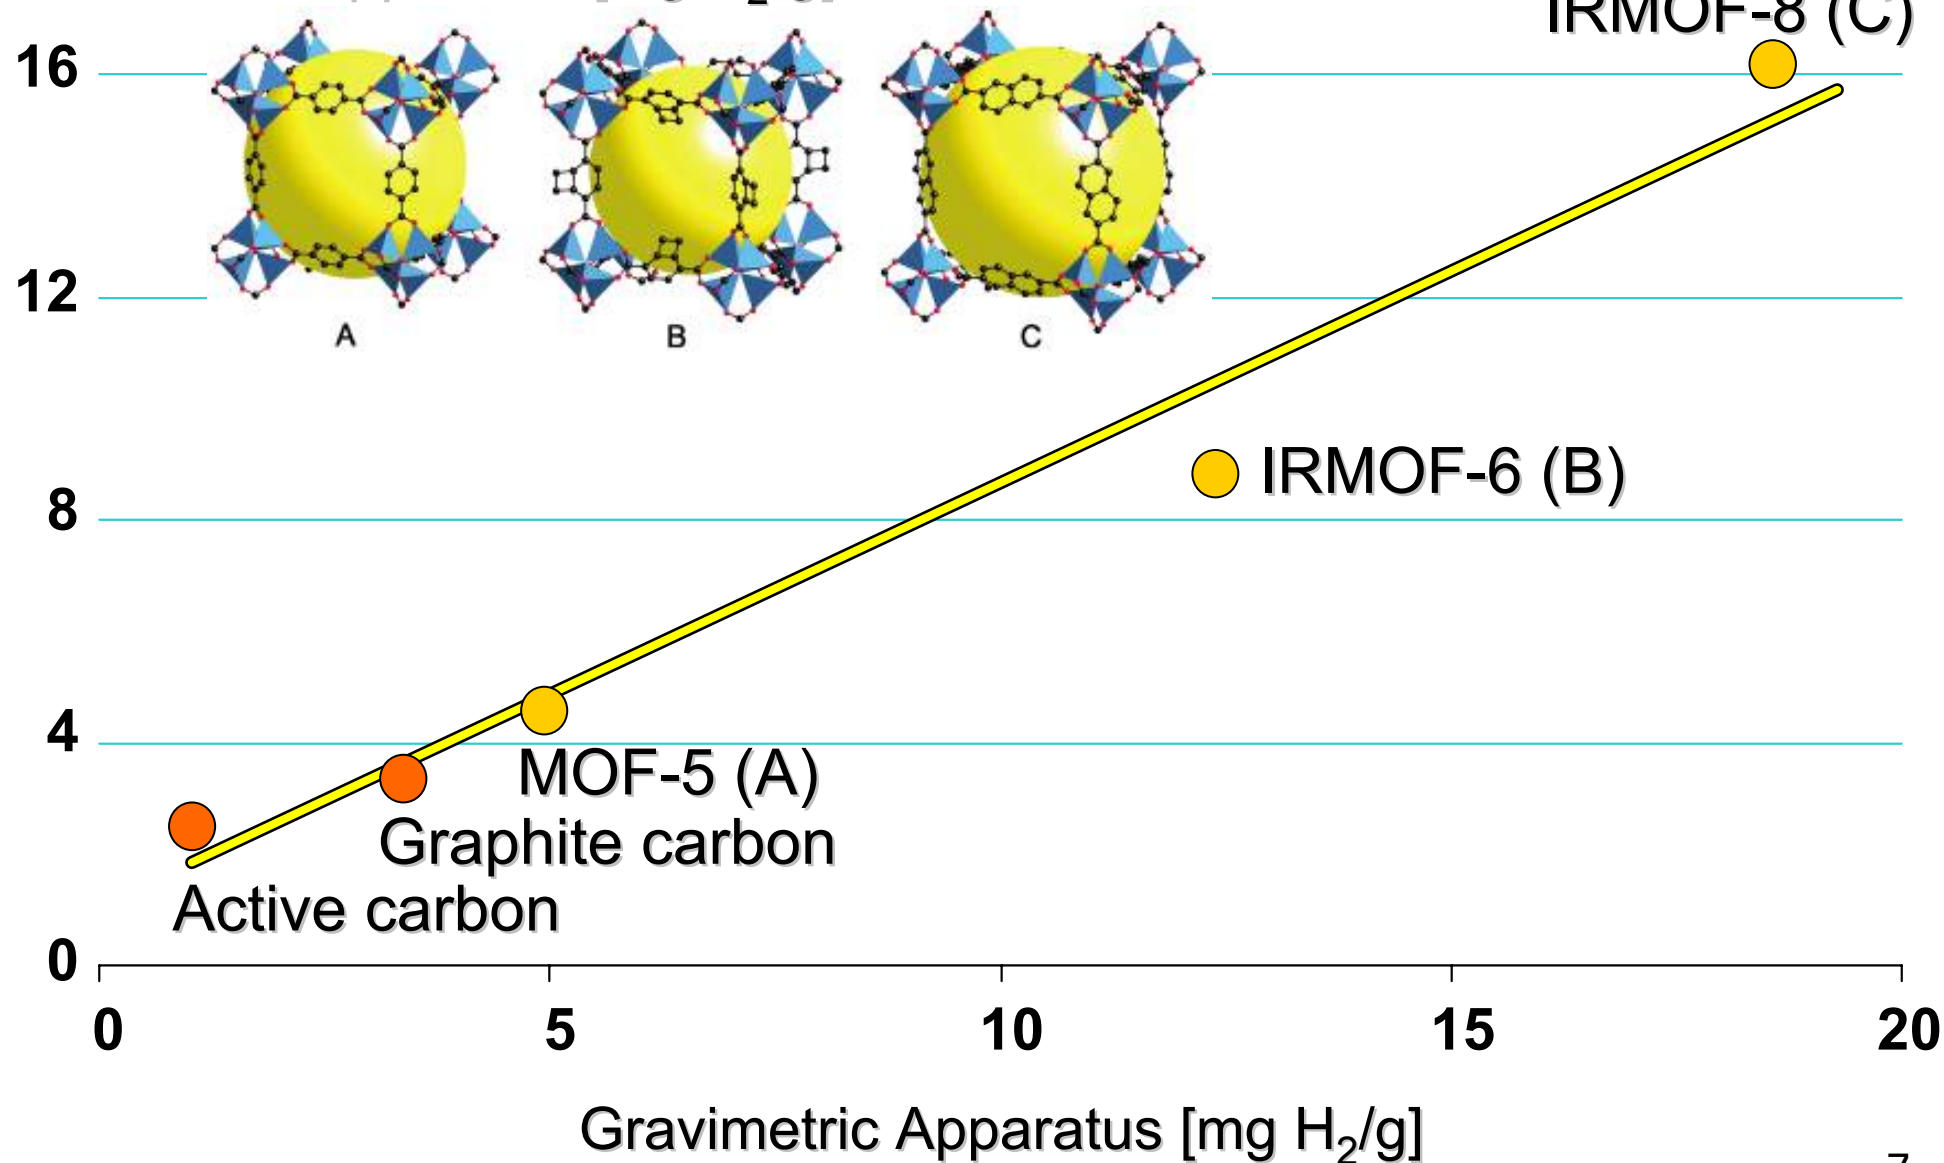




Structure of $\text{Zn}_4\text{O}(1,3,5\text{-benzenetribenzoate})_3$

MOF-177: S_A (Langmuir) = 4,500 m²/g, V_p = 1.59 cm³/g

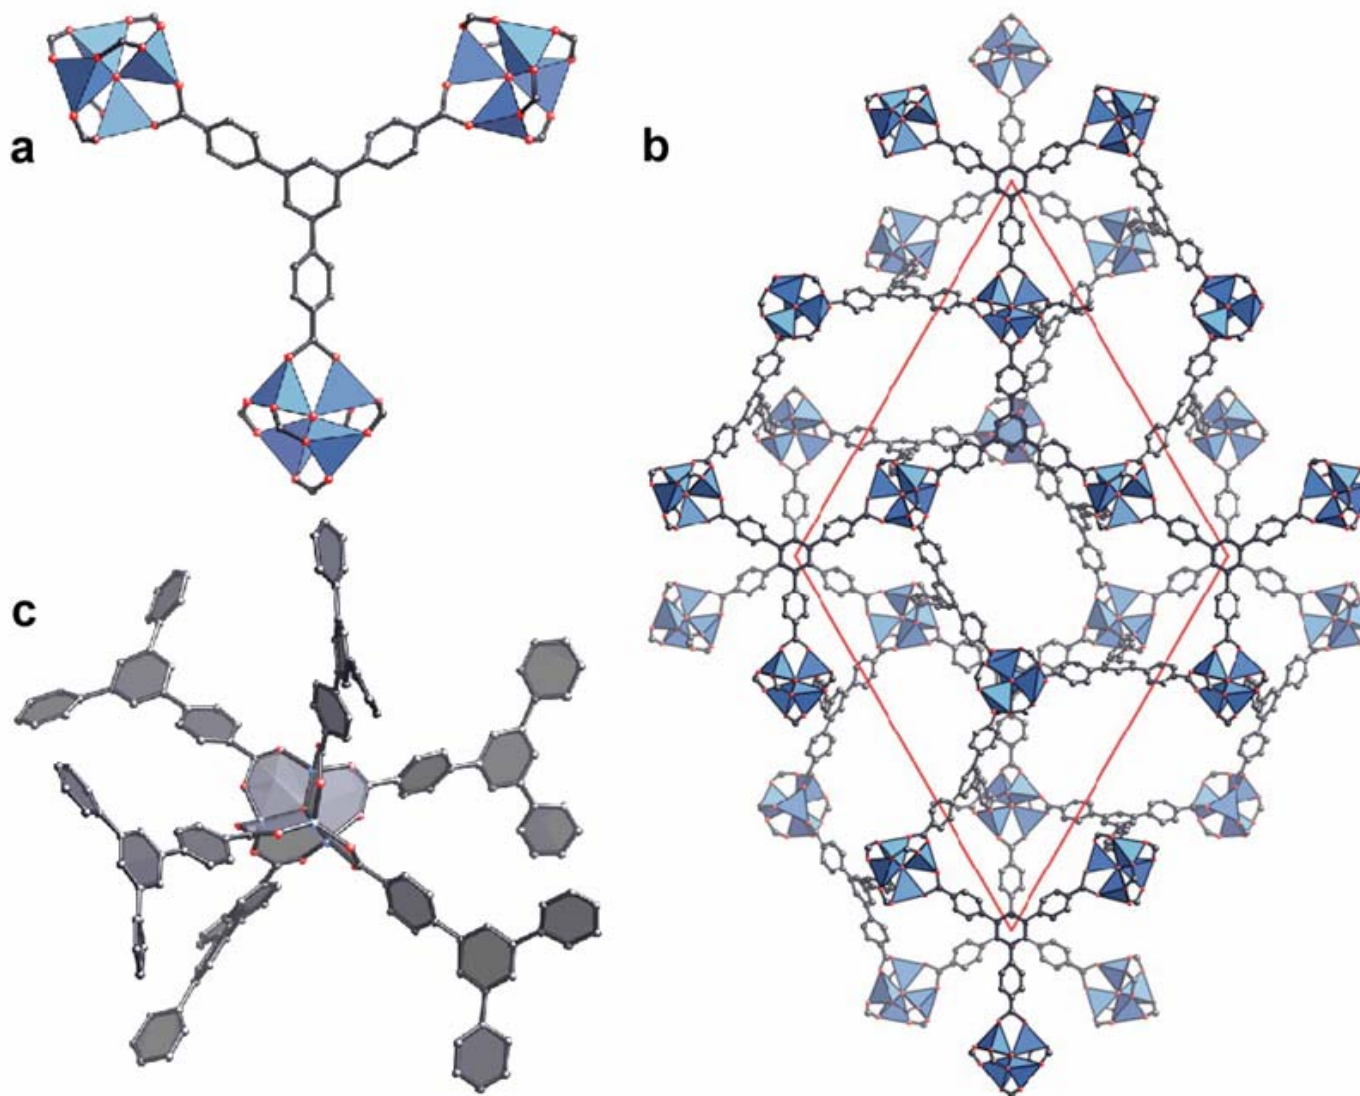




Low Pressure, Low Temperature H₂ Sorption

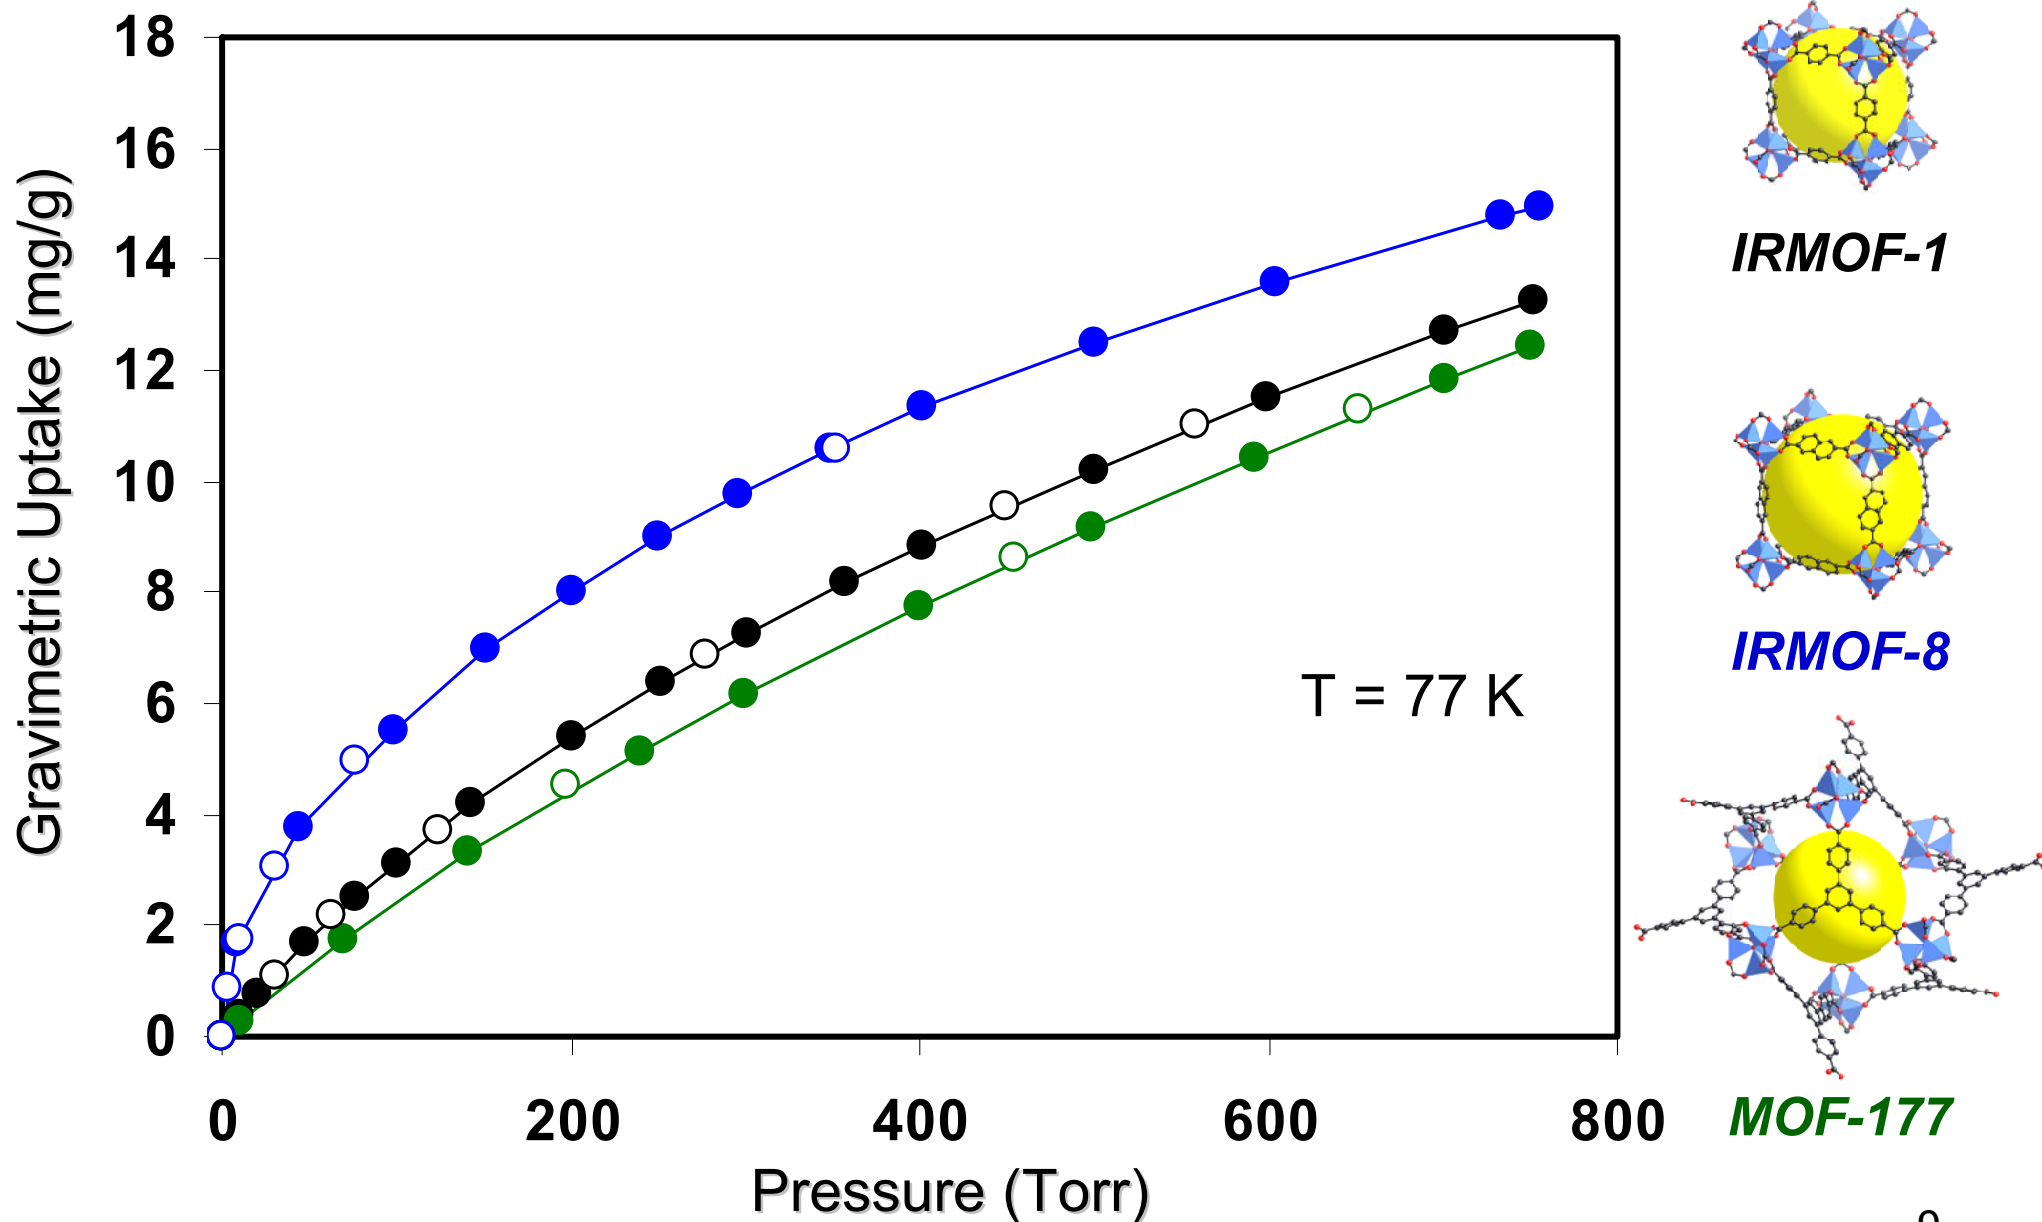




Large Free Volume in Catenated Networks: The role of Secondary Building Units

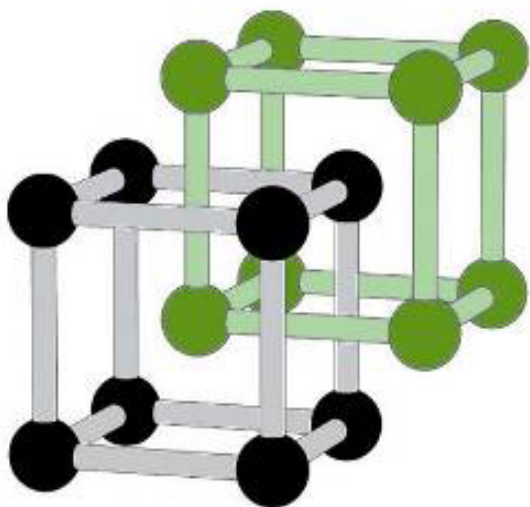


Cell edge: $a = d + l$
 van der Waals Radius of SBU = $\delta / 2$
 For n frameworks to interpenetrate with centers of the SBUs aligned along the body diagonal:
 $n(d + \delta) \leq \sqrt{3} a$ thus $n \leq \sqrt{3} (d + l) / (d + \delta)$

Volume of the cell = $(d + l)^3$
 Volume occupied by SBUs / cell = $n(\pi / 6)d^3$
 Volume of the linkers / cell = $3n(\pi r^2)l$
 Free Volume = $(d + l)^3 - (n(\pi / 6)d^3 + 3n(\pi r^2)l)$

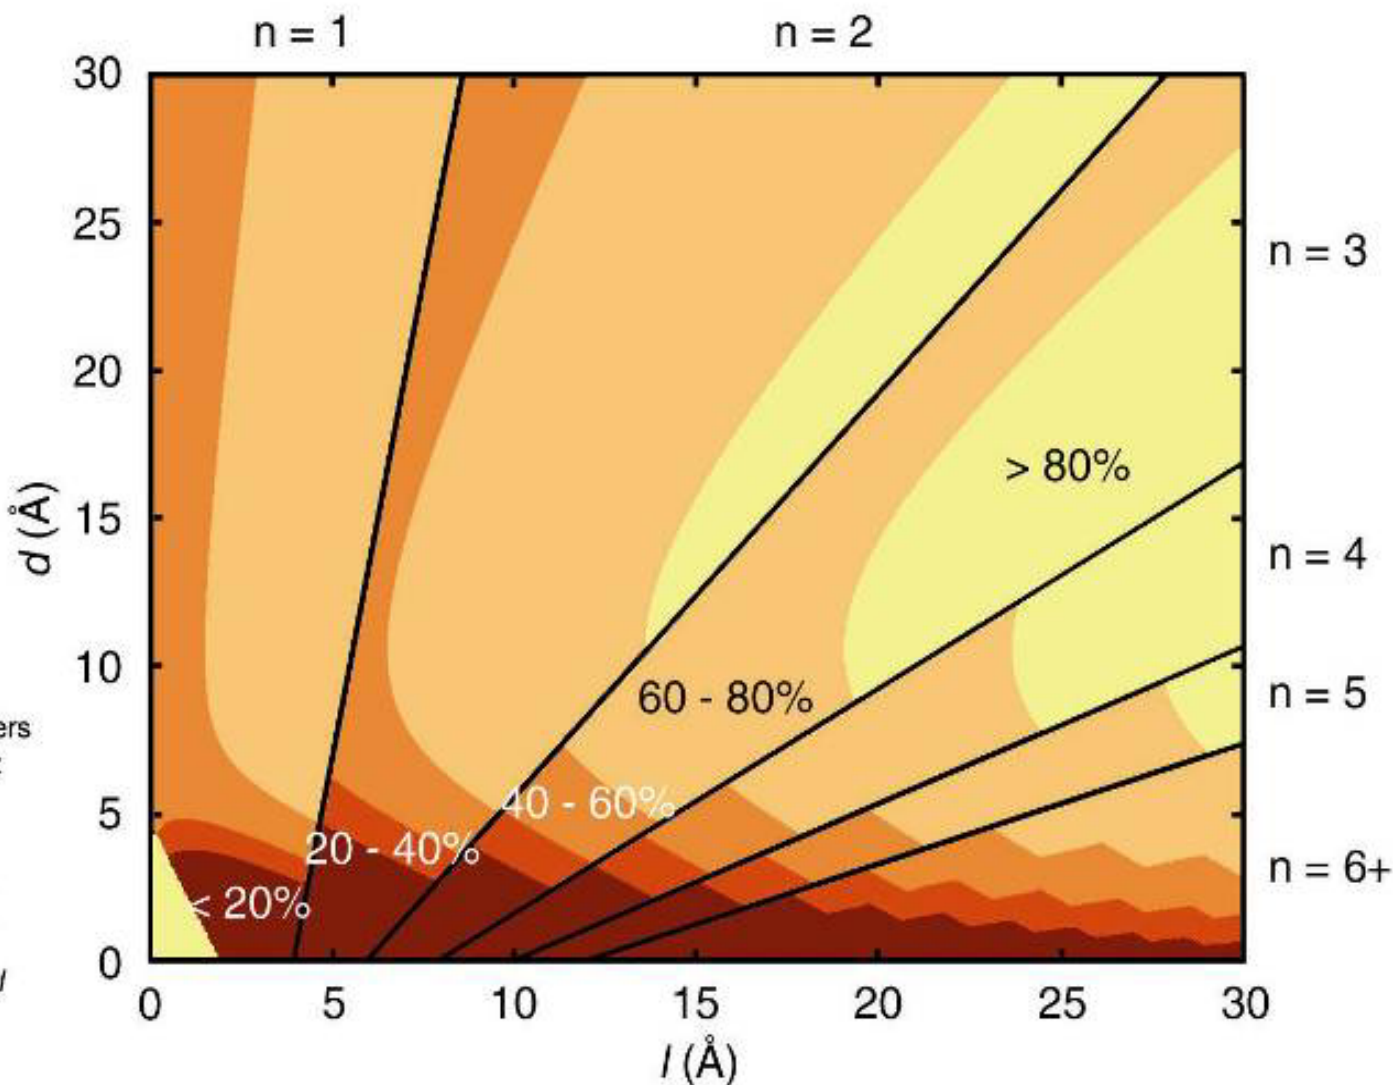




Types of Catenation

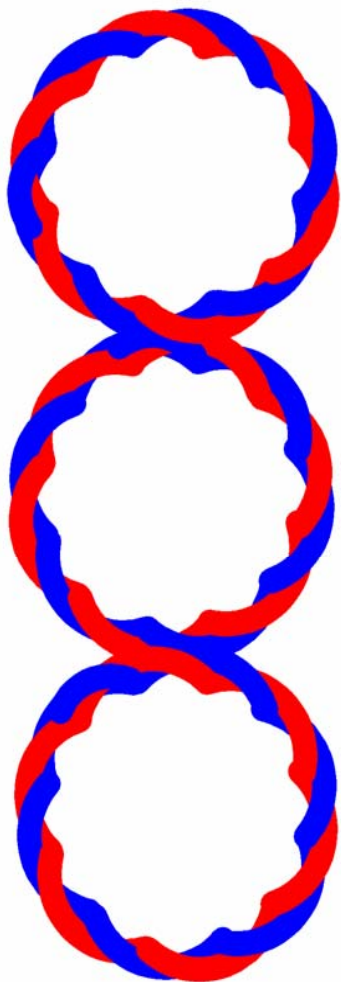

Interweaving

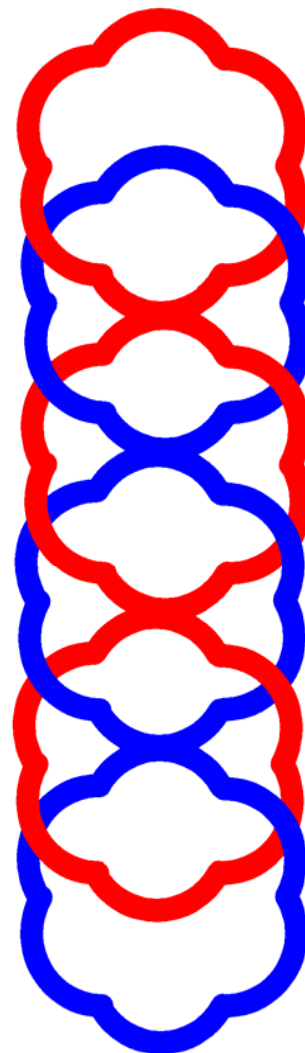


Interpenetrated



Structure of Interwoven $\text{Cu}_3(1,3,5\text{-benzenetribenzoate})_2(\text{H}_2\text{O})_3$


MOF-14: S_A (Langmuir) = 1,502 m^2/g ; V_p = 0.53 cm^3/g

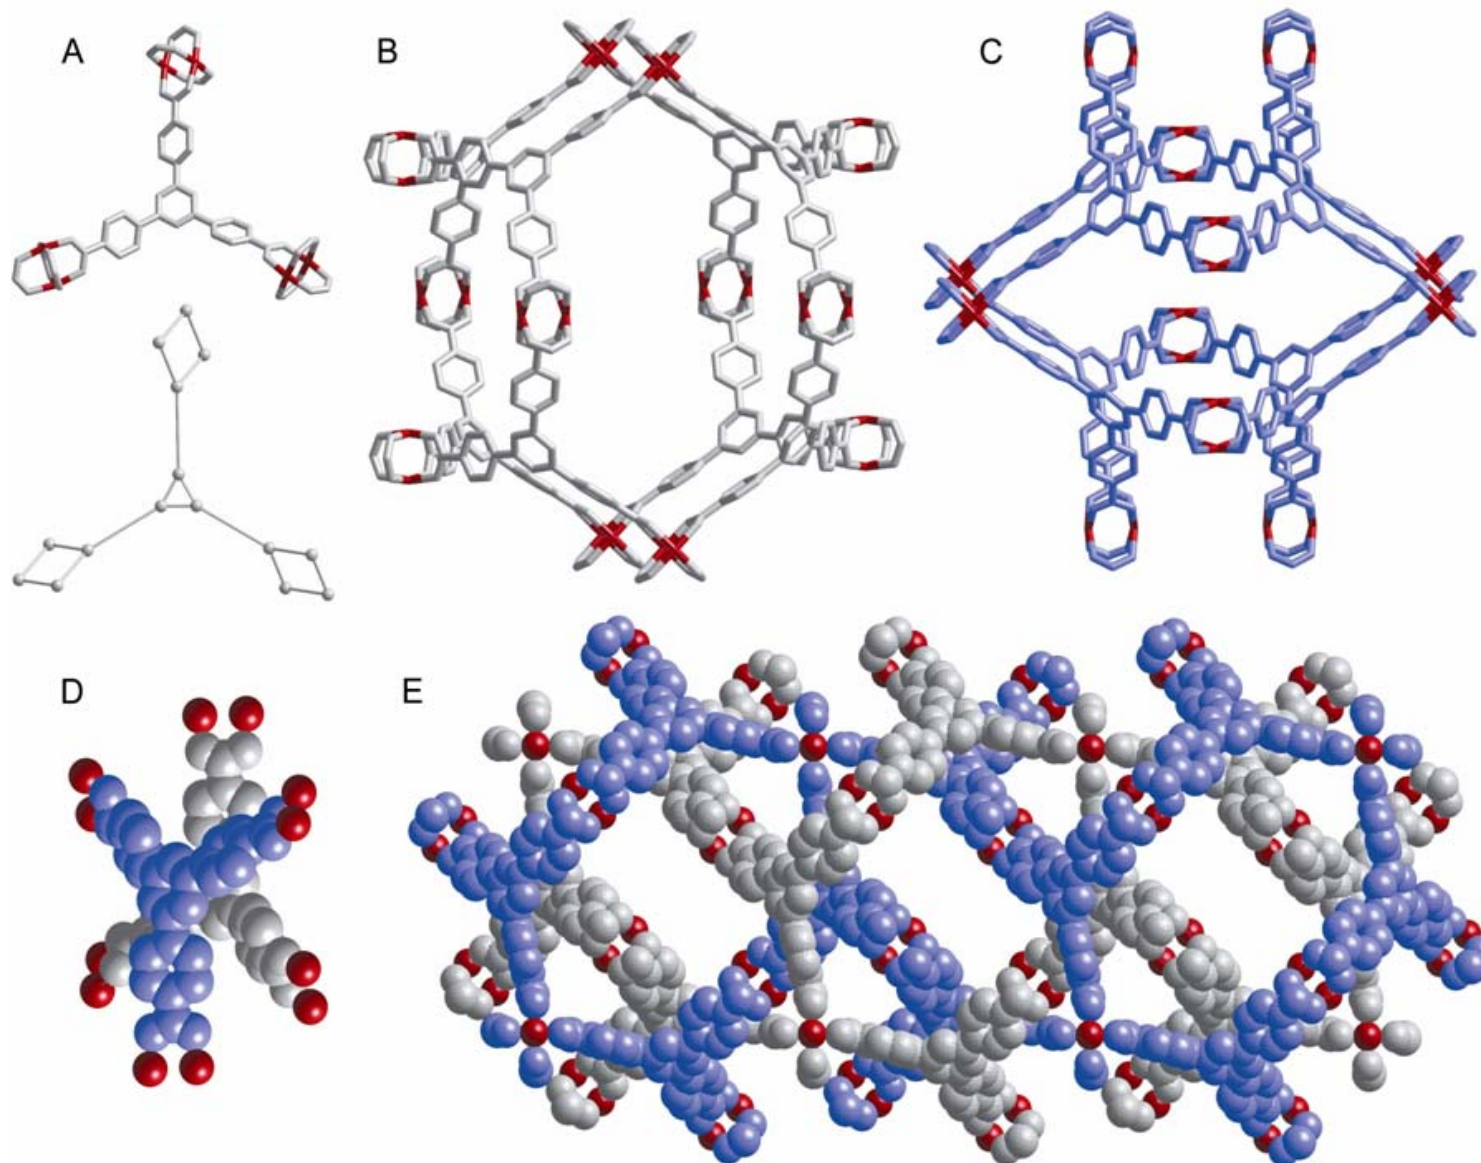




Structure of Interpenetrated $\text{Tb}_2(4,4'\text{-azodibenzoate})_3[(\text{CH}_3)_2\text{SO}]_3$

MOF-9: $V_{\text{Free}} = 71\% V_{\text{Crystal}}$; 16 $[(\text{CH}_3)_2\text{SO}]/\text{unit cell}$

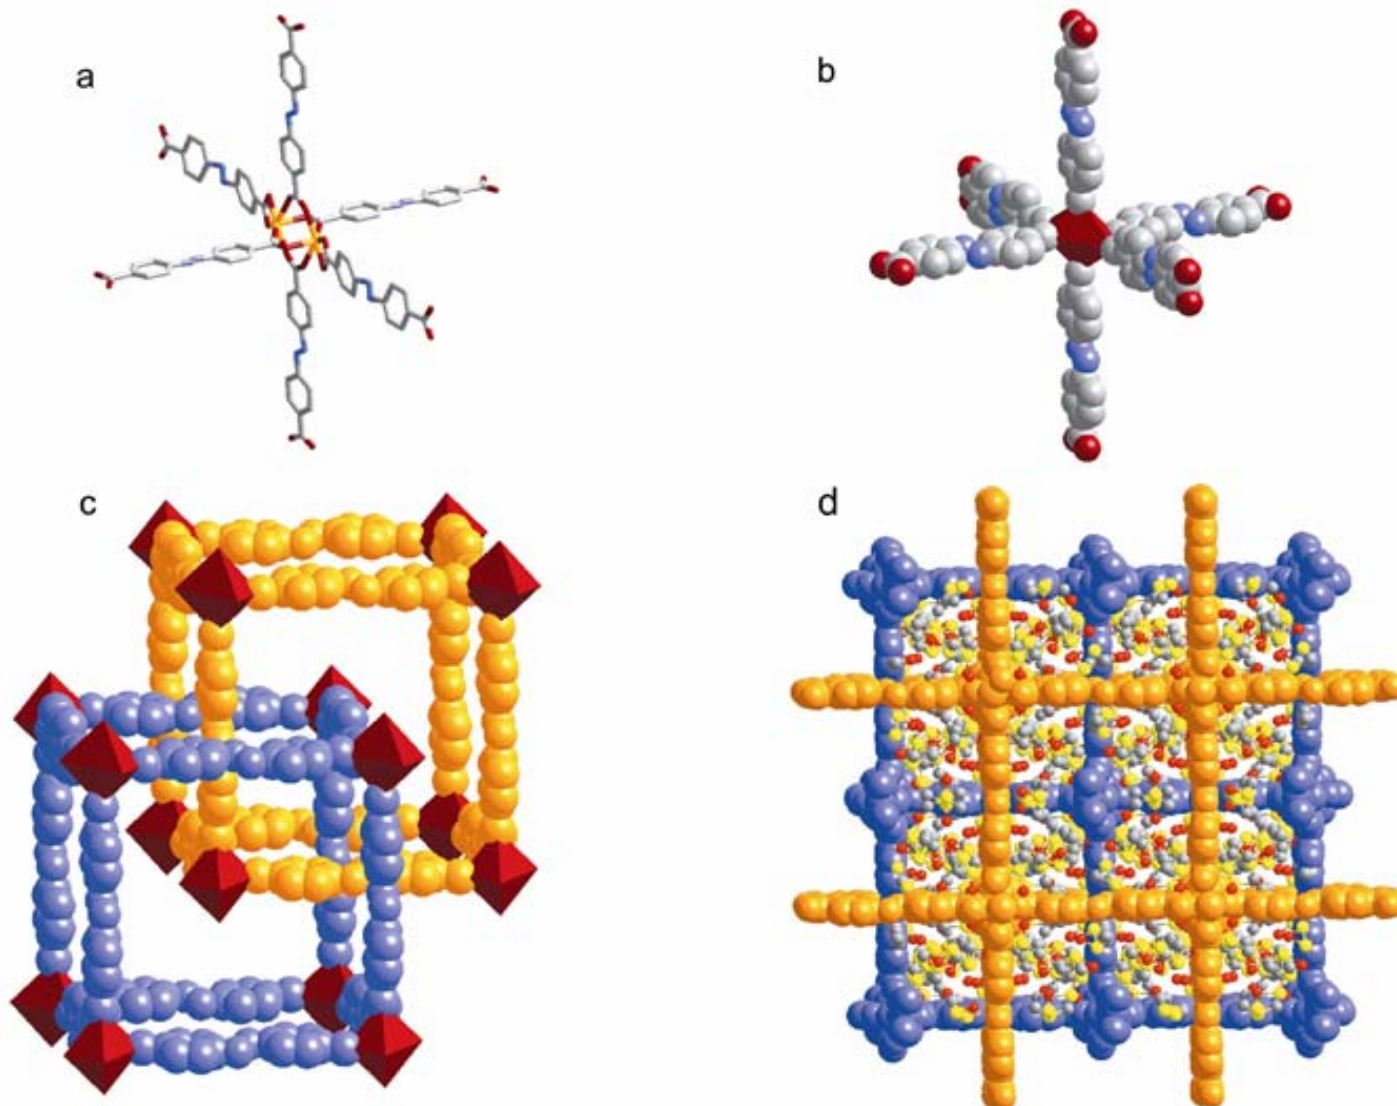





Interpenetrated Isoreticular MOFs

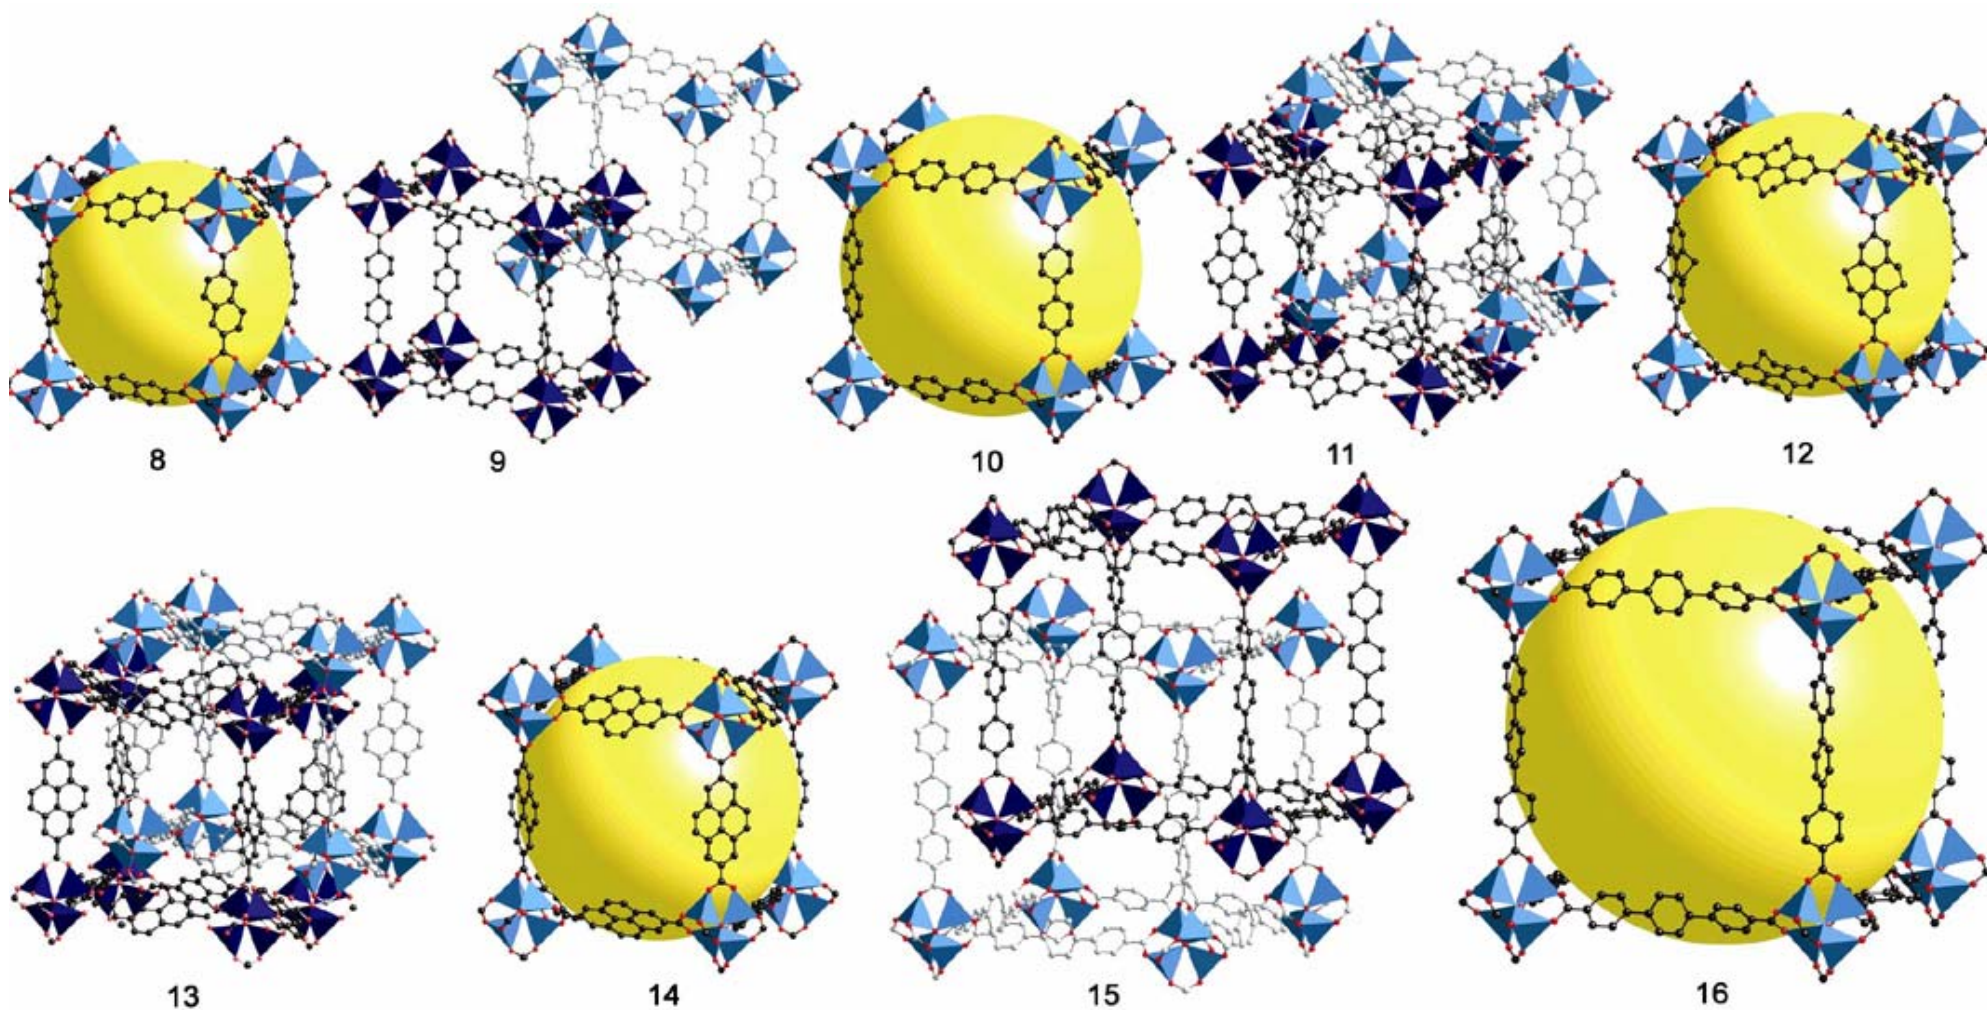





Low Pressure, Low Temperature H₂ Sorption

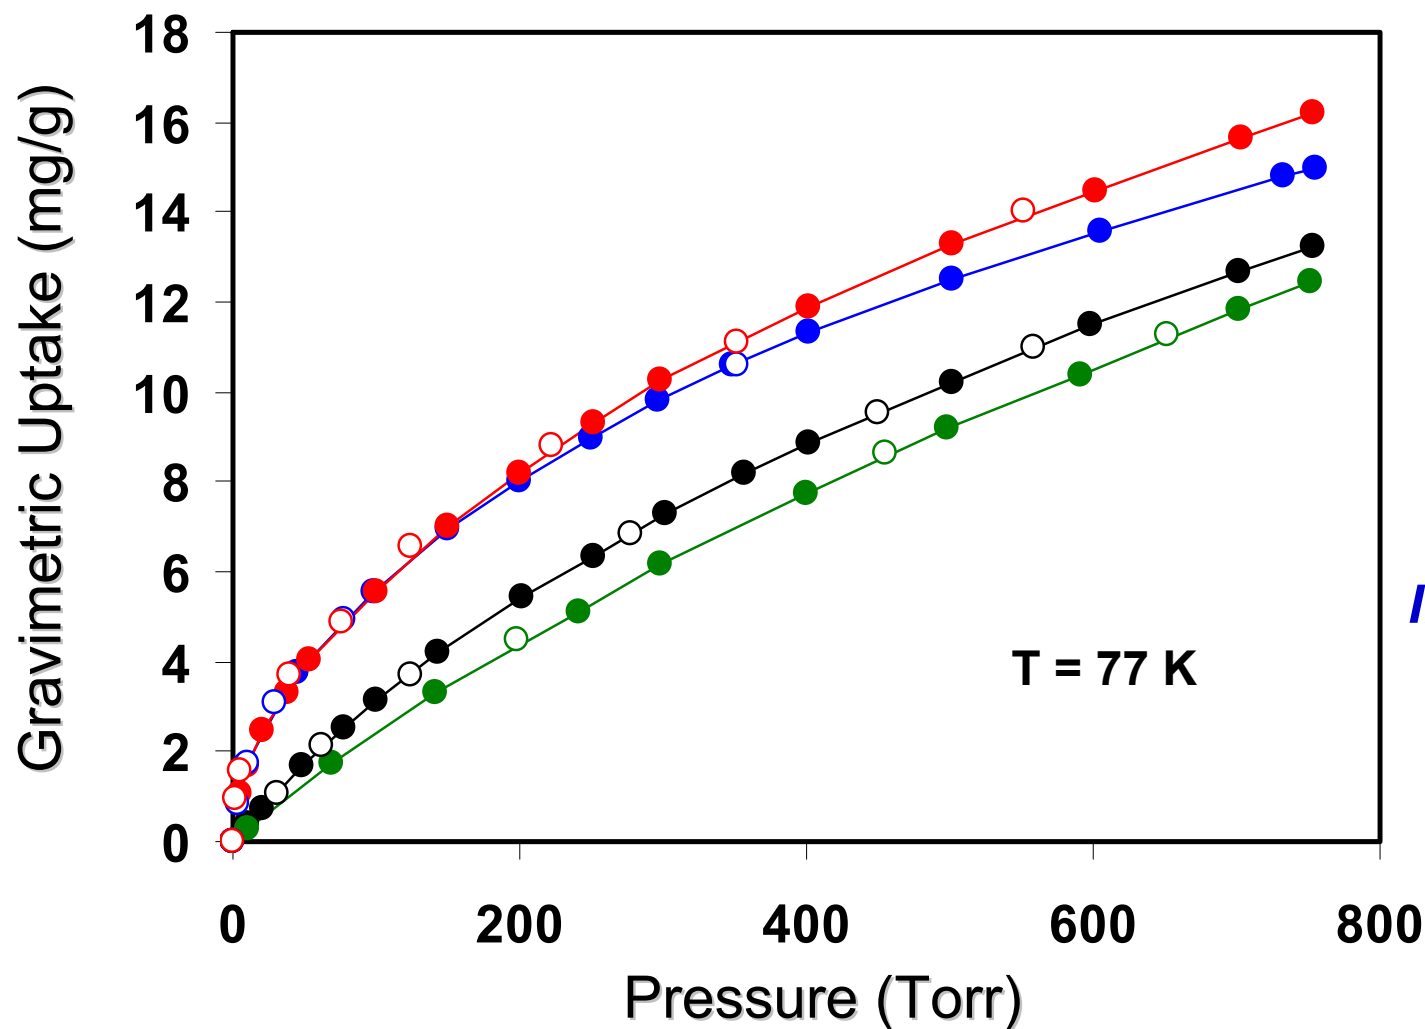


IRMOF-1

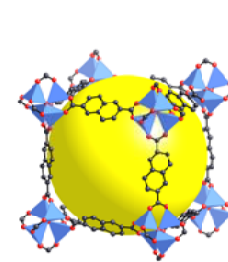

IRMOF-8

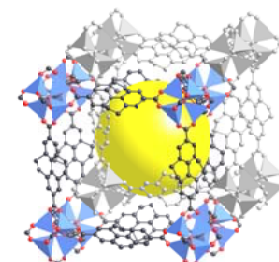


IRMOF-11

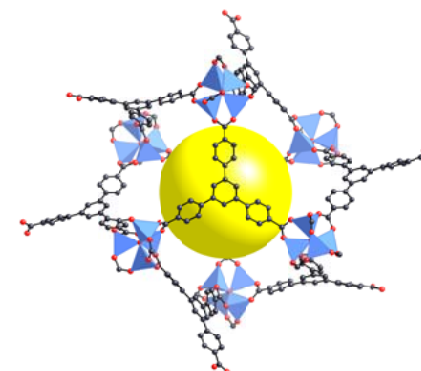

MOF-177




Reversible H₂ sorption in IRMOF-11 at 77K

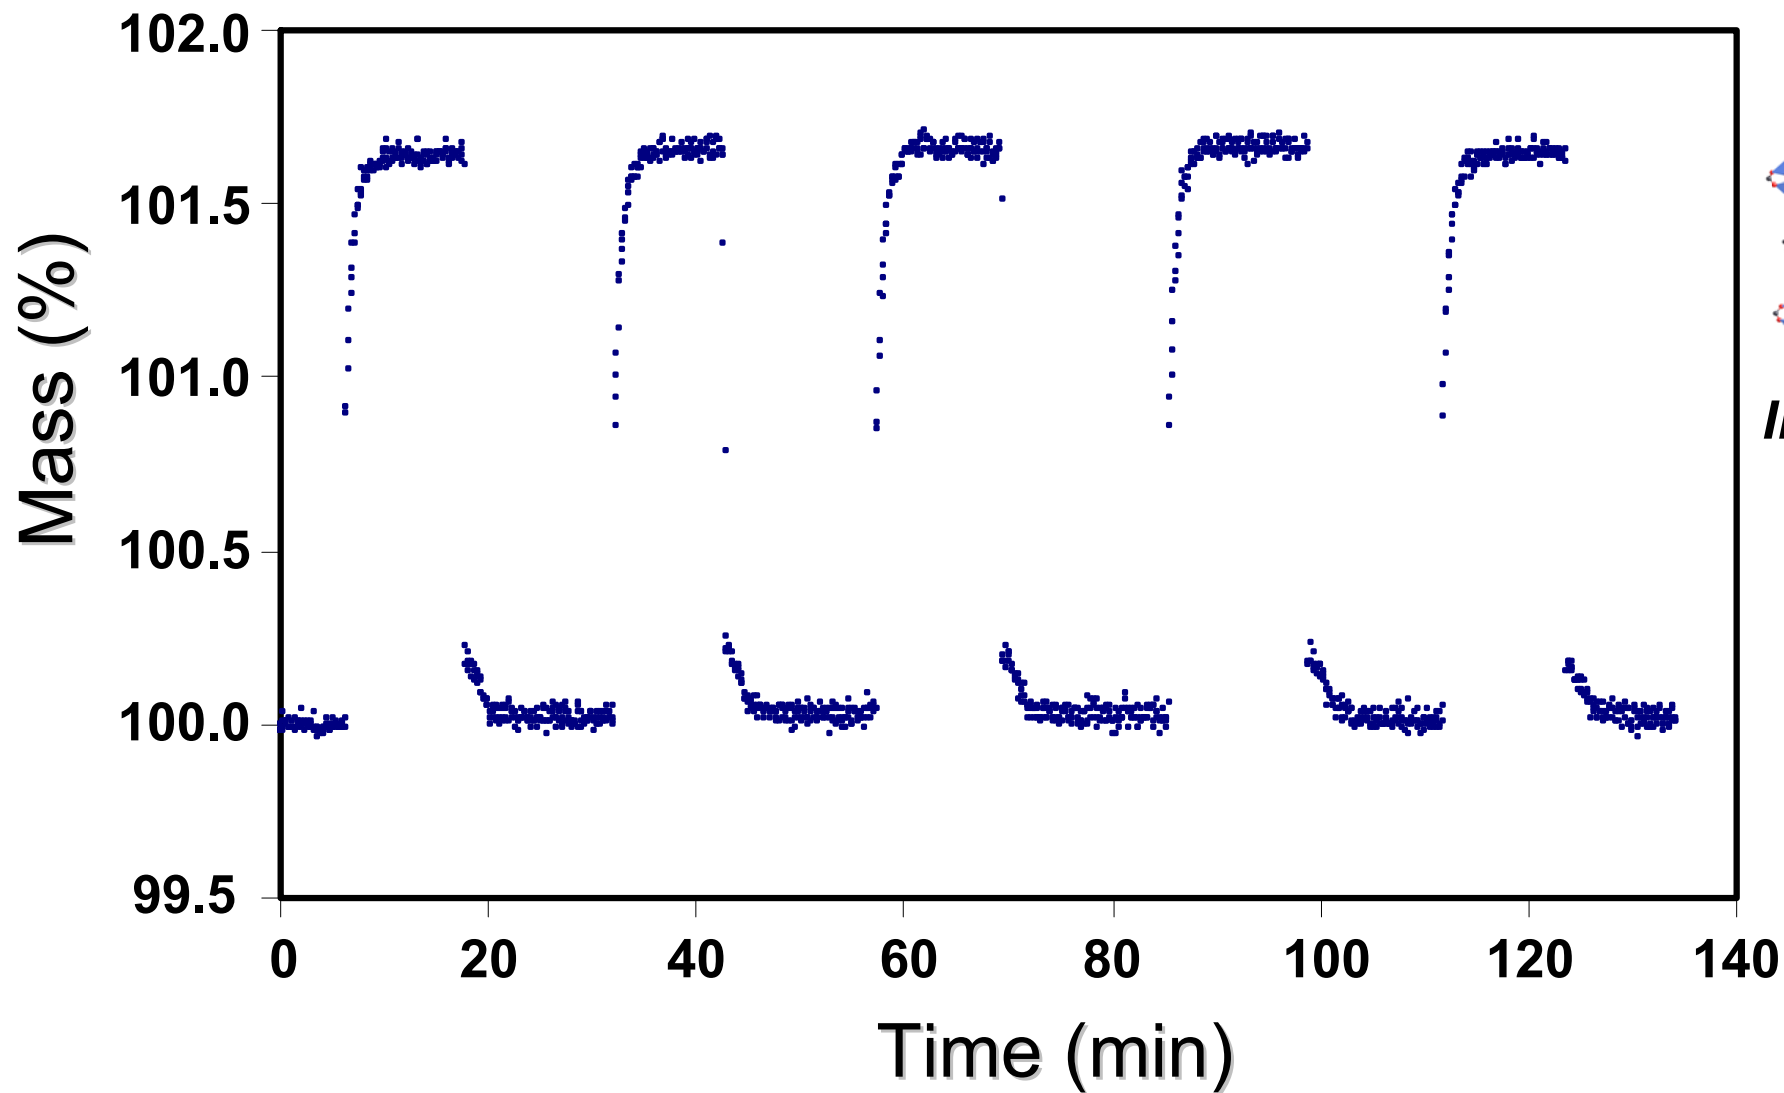





Impregnation of MOF-177

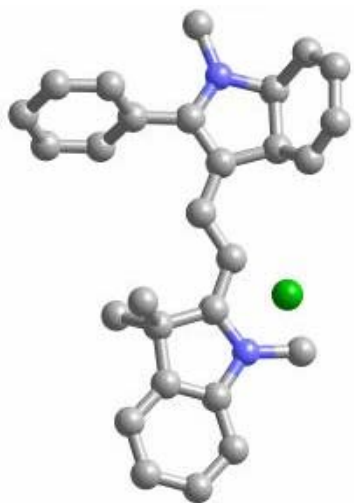


Astrazon orange

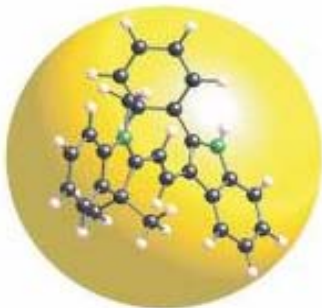


Astrazon Orange R
16 molecules
per unit cell

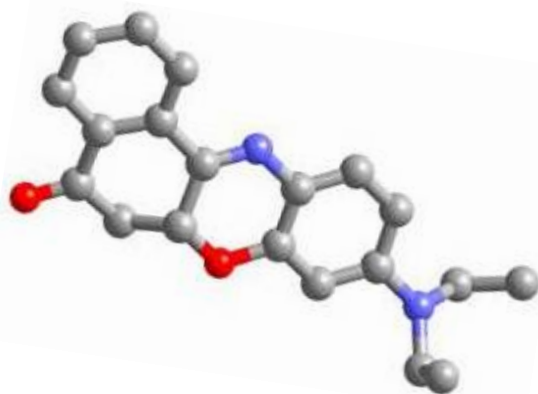


Nile red

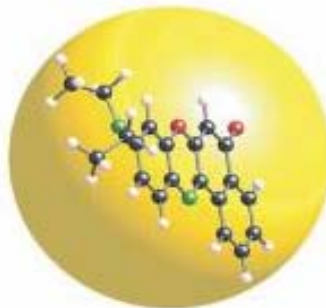

Nile Red
2 molecules
per unit cell

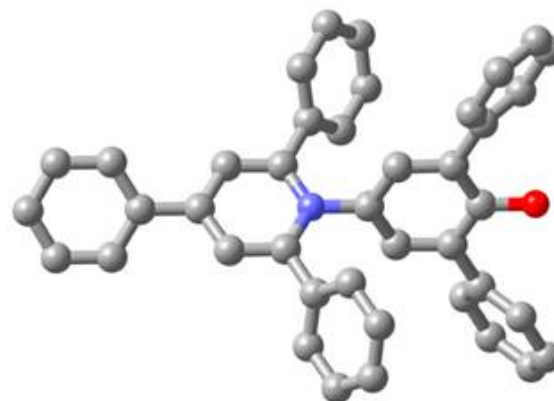



Reichardt's dye

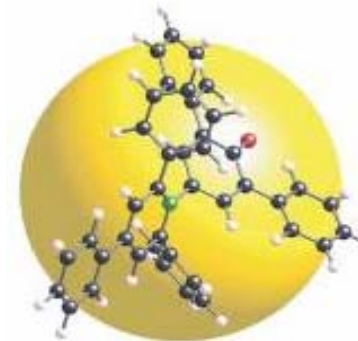

Reichardt's dye
1 molecule
per unit cell



Inclusion of C_{60} in MOF-177

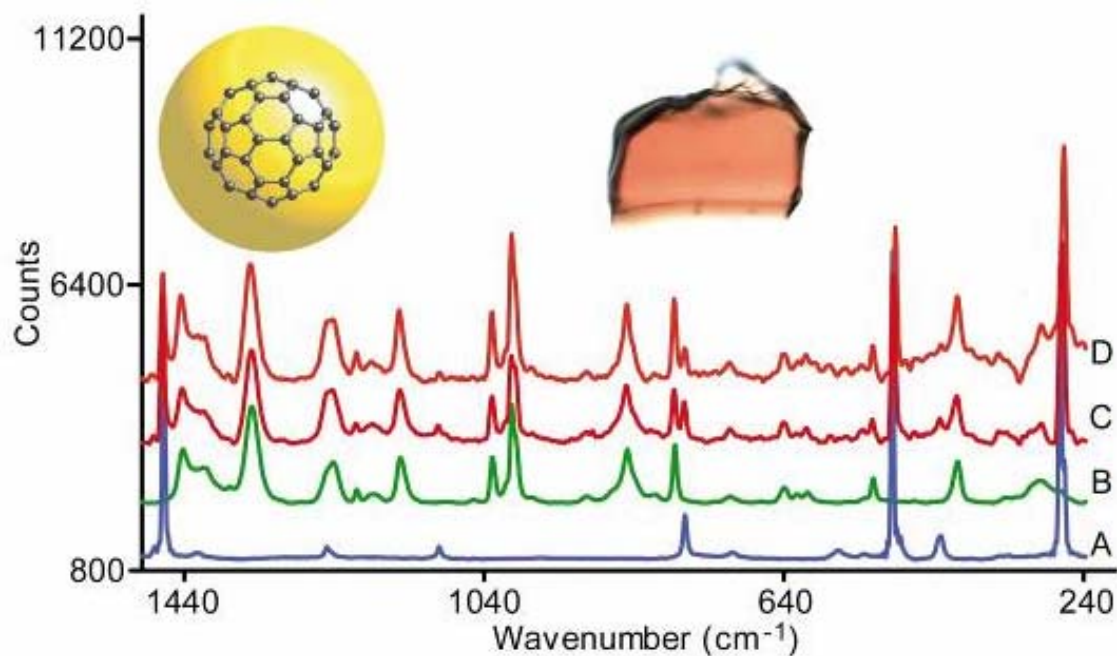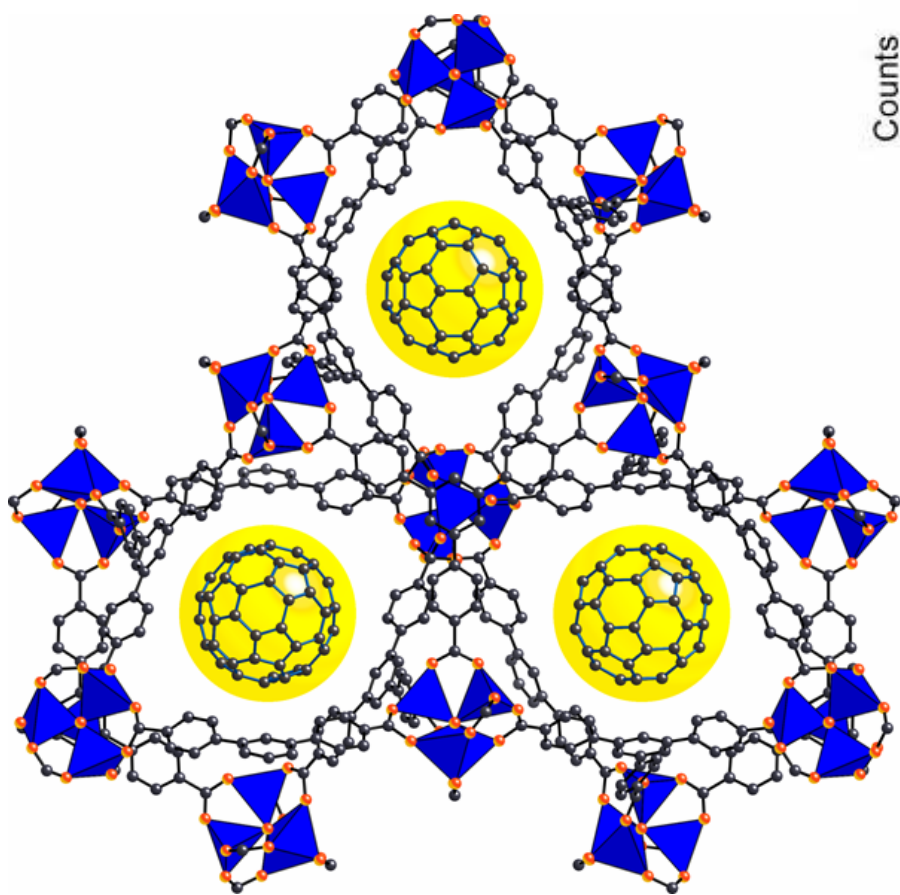

Raman Spectroscopy

- A) Bulk C_{60}
- B) Evacuated MOF-177
- C) Single crystal with C_{60}
- D) Single crystal with C_{60} cleaved in half



Future Work

TASK	2005	2006	2007	2008
Task 1: High Surface Area MOFs				
Synthesize new polycyclic organic links	[Yellow bar from 2005 to 2007]			
Synthesize MOFs with minimal fused edges	[Yellow bar from 2005 to 2007]			
Reduce pore dead volume by forming catenated nets	[Yellow bar from 2005 to 2008]			
Reduce open space in pores by inclusion of guests with sites for H ₂ binding	[Yellow bar from 2006 to 2008]			
		●	●	
		Go/No-Go points		
Task 2: Polarization Effects				
Functionalization of MOFs with group of varying polarity	[Blue bar from 2006 to 2008]			
Correlate H ₂ uptake to electron donating/withdrawing ability of groups	[Blue bar from 2006 to 2008]			
Task 3: Modeling H₂ Uptake (Northwestern)				
Quantitate charge density of organic linker, compare to nanotubes	[Green bar from 2006 to 2008]			
Screen promising candidates for inclusion	[Green bar from 2006 to 2008]			
Quantitate H ₂ interaction in MOFs	[Green bar from 2007 to 2008]			
Predict H ₂ isotherms	[Green bar from 2007 to 2008]			
Task 4: Characterization & Testing	[Brown bar from 2005 to 2008]			



Publications and Presentations

Please list any publications and presentations that have resulted from work on this project.

No publications resulting from current funding.



Hydrogen Safety

The most significant hydrogen hazard associated with this project is:

- High exposure to H₂ gas with possibility of personal injury due to decreased oxygen content in the atmosphere.
- High concentrations of H₂ may pose a fire or explosion in and around instrumentation.



Hydrogen Safety

Our approach to deal with this hazard:

- ❑ Dedicated a single laboratory for all H₂ experiments.
- ❑ Installed active ventilation snorkles from laboratory hoods to all instrumentation consuming/ releasing H₂.
- ❑ Installed atmospheric H₂ detector (% level detection) outfitted with an alarm in the dedicated laboratory.



Acknowledgements

