


# Basic Research for the Hydrogen Fuel Initiative

## Control of Hydrogen Release and Uptake in Condensed Phases


Nancy Hess, John Linehan, Wendy Shaw,  
John Fulton, Luke Daemen, Maciej  
Gutowski, Tom Autrey  
PNNL, LANL (LANSCE)

# Hydrogen-rich ammonia borane (AB)

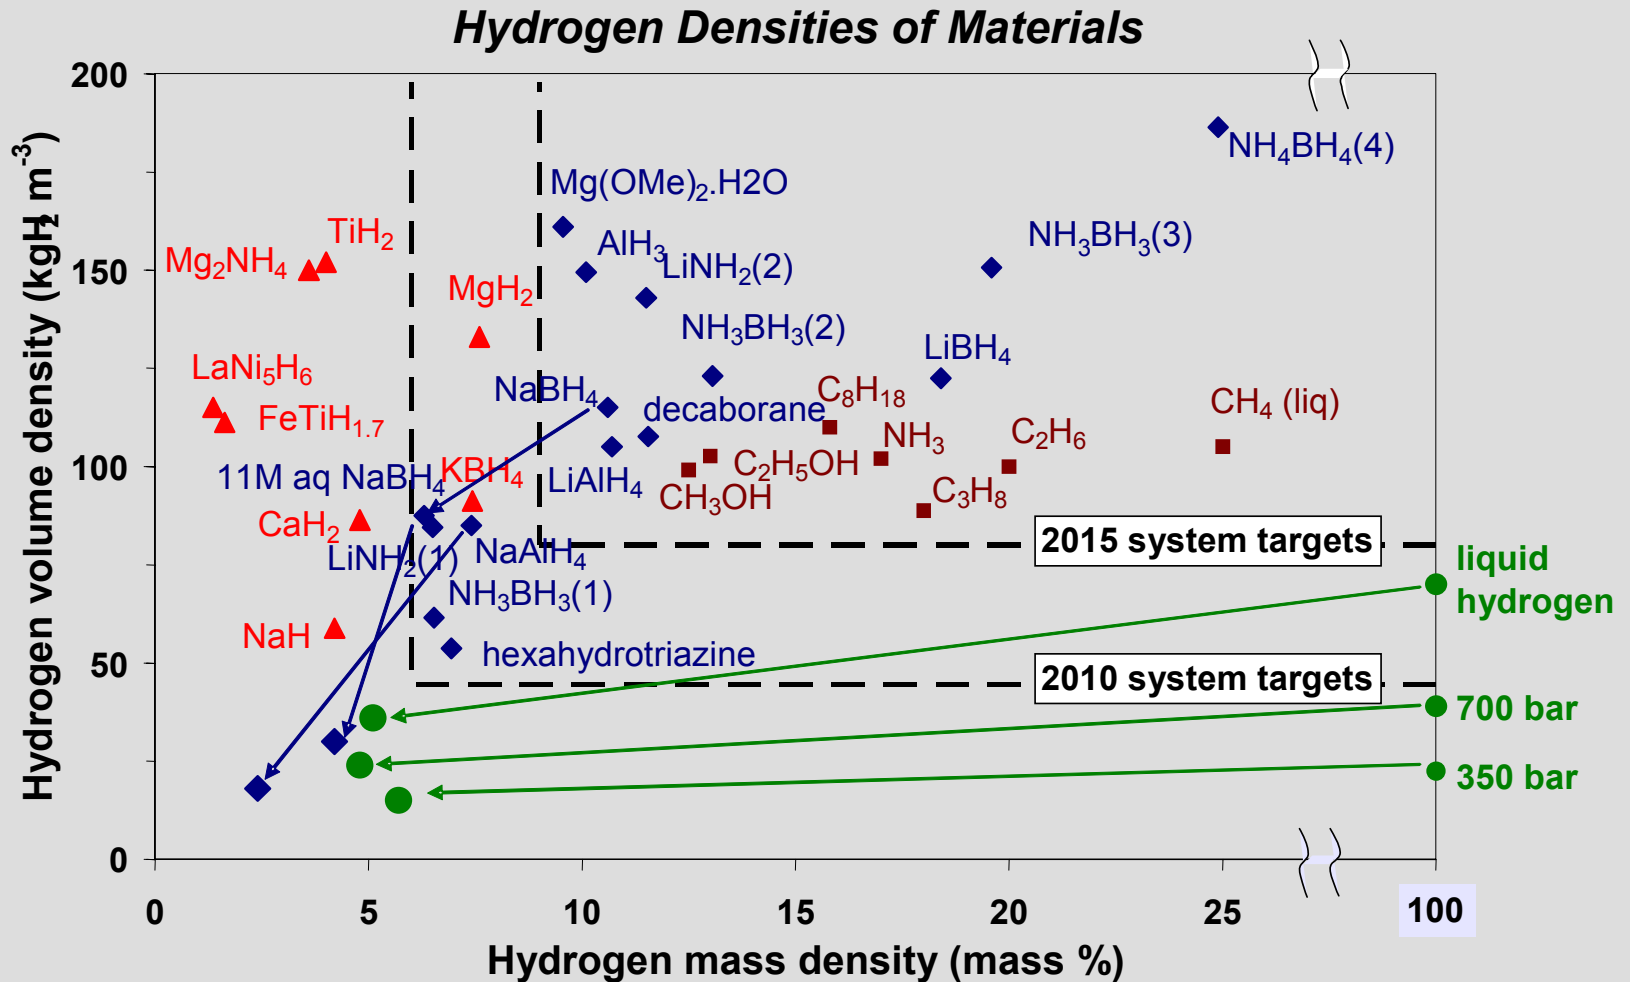

George Thomas

# What we know...

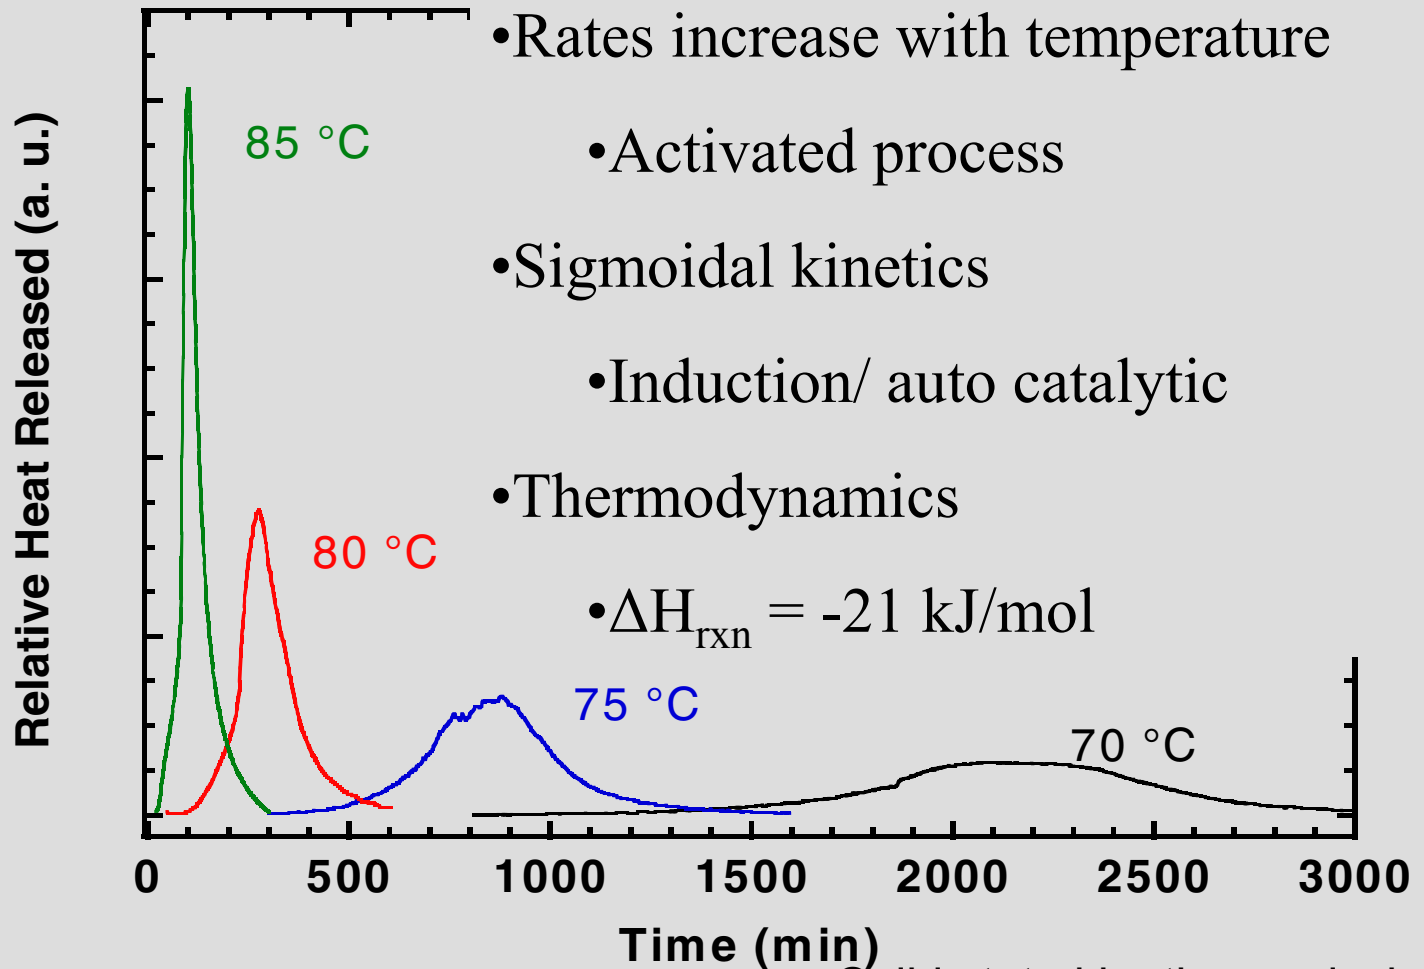

- Rates increase with temperature

- Activated process



- Sigmoidal kinetics

- Induction/ auto catalytic

- Thermodynamics

- $\Delta H_{\text{rxn}} = -21 \text{ kJ/mol}$

# ... and on scaffolds

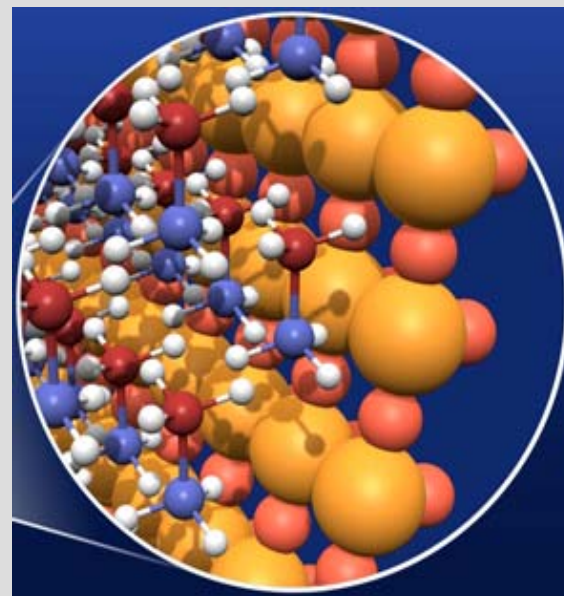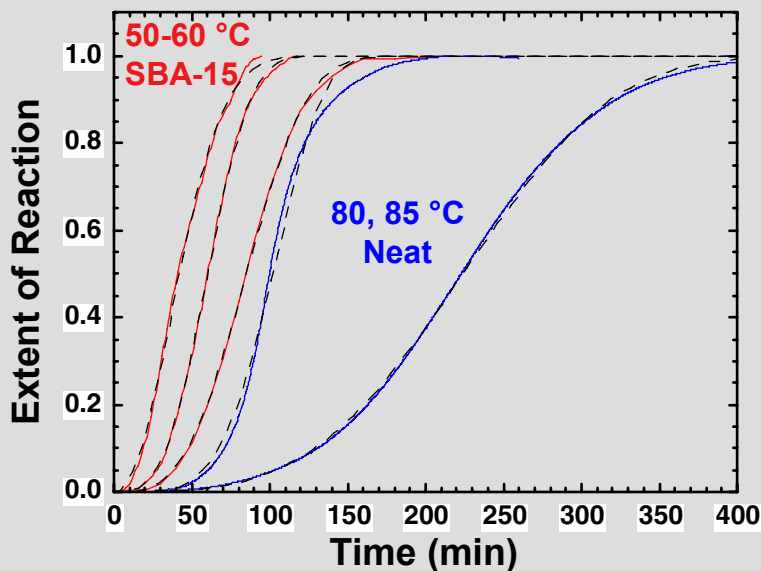


*Ammonia borane in SBA-15*


## Scaffolds:

- enhance rates of H<sub>2</sub> release
- enhance purity of H<sub>2</sub> (little borazine)
- thermodynamics

Angew. Chem. Int. Ed. **2005**, 44, 3578.

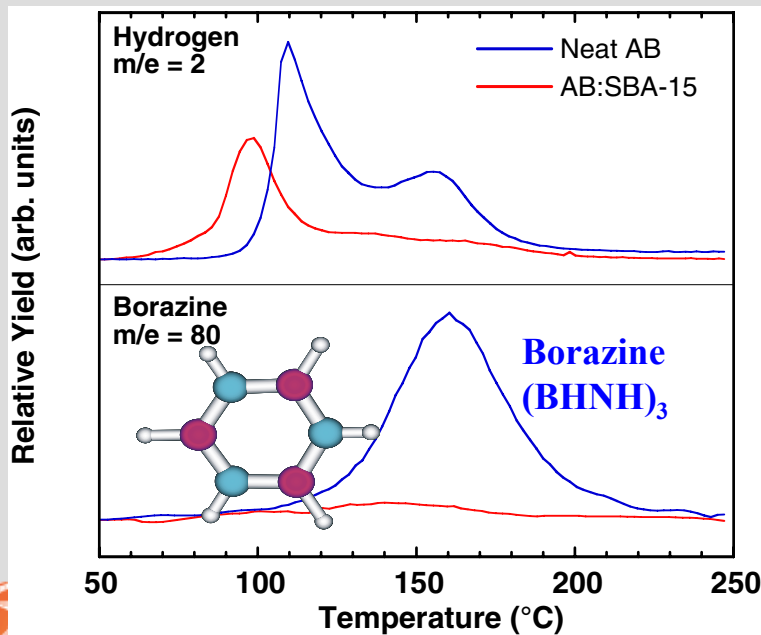

# Summary of AB chemistry

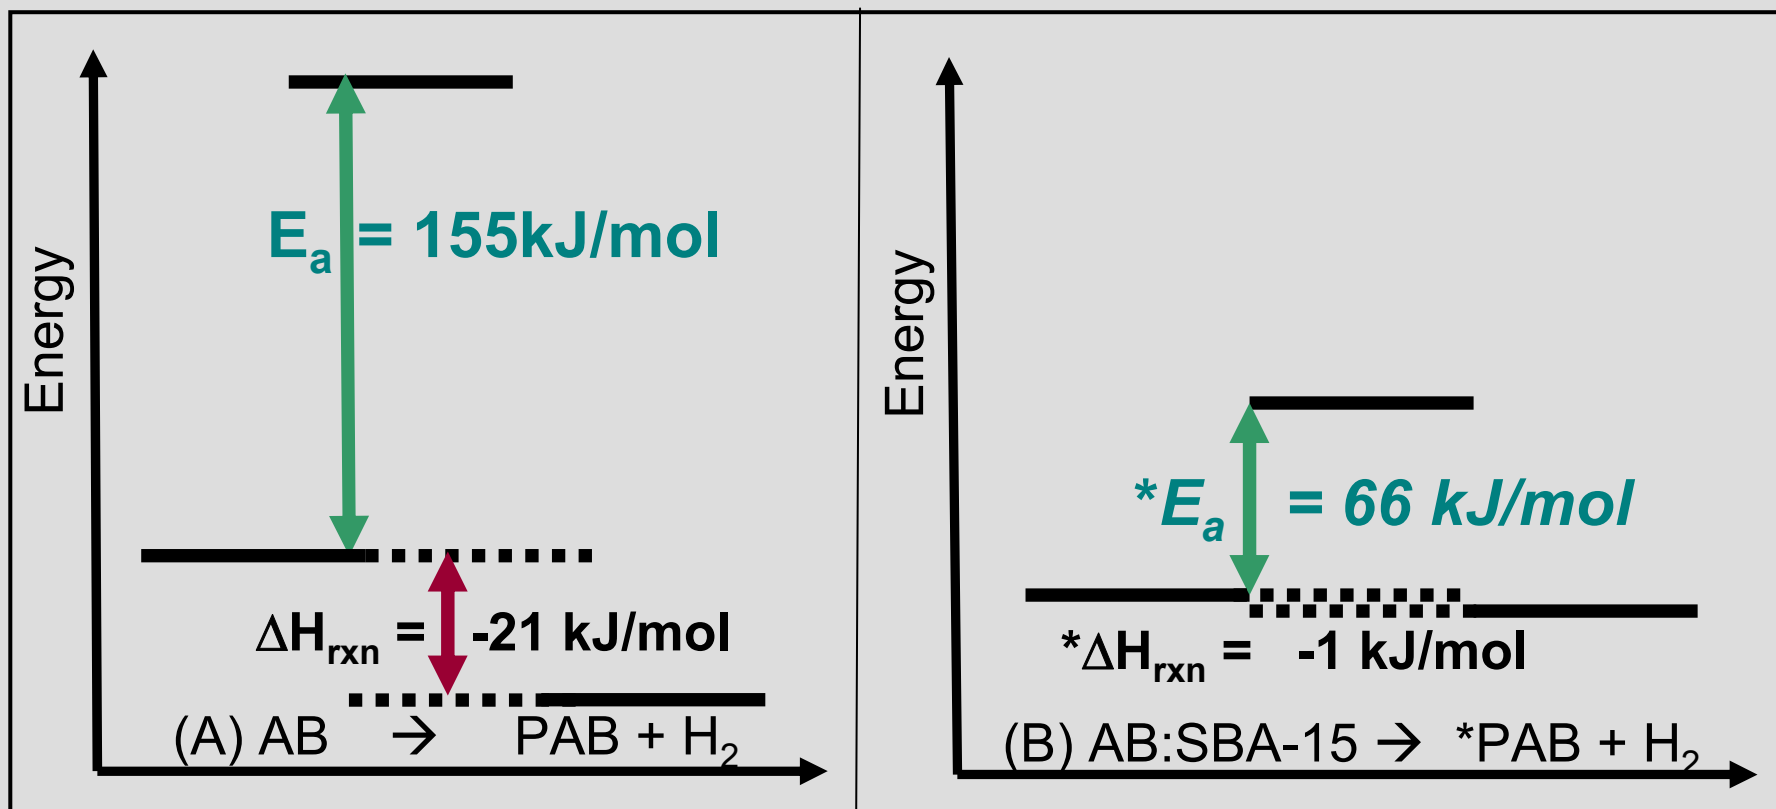

## ► Selectivity of $\text{H}_2$ release from AB


- No borazine seen in volatile products or left behind in scaffold.
- No cyclized products observed in NMR and DSC data show process is less exothermic

## ► Reactivity for $\text{H}_2$ release from AB

- 1-2 orders of magnitude faster!

# Fundamental Questions

---



How is the H<sub>2</sub> released?

Why is there an induction period?

What is the role of the dihydrogen bond?

Can we control the decomposition pathways?

What materials catalyze hydrogen release?

Does the reaction proceed by ionic or neutral pathways?

How does the scaffold interface change reactivity?

What is hydrogen doing before it is released?

# Approaches


---

- ▶ Multi-nuclear NMR and Raman spectroscopy
    - Solid state to study phase transitions and molecular dynamics
    - Variable temperature for in-situ kinetic investigations
  
  - ▶ Neutron spectroscopy
    - QENS (for dynamics of H motion)
    - INS (for structure and spectroscopic studies)
  
  - ▶ EXAFS spectroscopy
    - Operando (in-situ) catalysis studies. Gives x-ray like data for structural studies of catalytic induced transformations.
- 

**Combination of experiment & theory to gain fundamental understanding of interactions between protic/hydric hydrogen**

# Molecular $\text{NH}_3\text{BH}_3$

- ▶  $\text{H}_3\text{B} \leftarrow \text{NH}_3$  Electron donor-acceptor (dative) bond. The lone electron pair of  $\text{NH}_3$  delocalizes over an unoccupied 2p orbital of B.

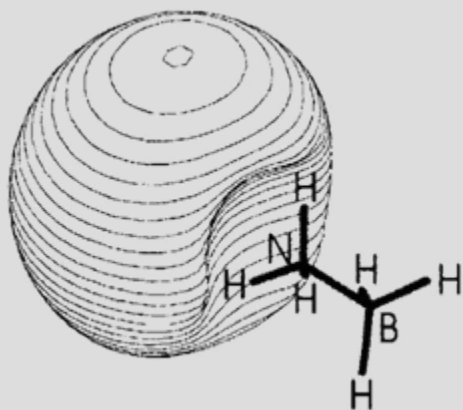


-Large dipole moment (5.3 D) illustrated by effective atomic charges: -0.46 (N), 0.27 (H(N)), 0.39 (B), -0.25 (H(B))

-the length of the dative BN bond 1.67 Å. A barrier for rotation around the BN bond less than 9 kJ/mol

- ▶ The calculated dissociation energy for  $\text{NH}_3\text{BH}_3 \rightarrow \text{BH}_3 + \text{NH}_3$  is 109 kJ/mol. The dative BN bond is stronger than a hydrogen bond but weaker than a valence bond



# Crystalline $\text{NH}_3\text{BH}_3$

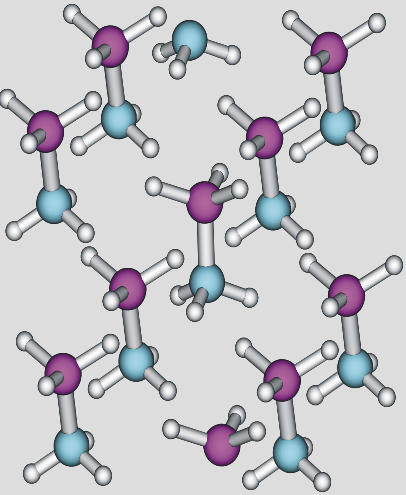


- **Synthesis by Shore and Parry in 1955**
- **Density  $0.74 \text{ g/cm}^3$ , mp  $124 \text{ }^\circ\text{C}$ ,  $19.5\text{wt}\%$   $\text{H}_2$**
- **$\text{NH}_3\text{BH}_3 \rightarrow \text{H}_2 + \text{polyaminoborane}$  at  $< 100 \text{ }^\circ\text{C}$ .**
- **AB in equilibrium with diammoniate of diborane**





• **First order-disorder phase transition at  $225 \text{ K}$ , the low  $T$  structure is orthorhombic, the high  $T$  tetragonal**

• **Electrostatic bonding between  $\text{H}^+$  and  $\text{H}^-$  (dihydrogen bond)**

• **The calculated cohesive energy is  $74 \text{ kJ/mol}$**

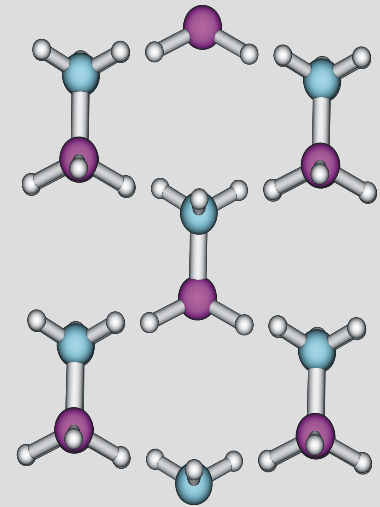

# Dihydrogen Bonds

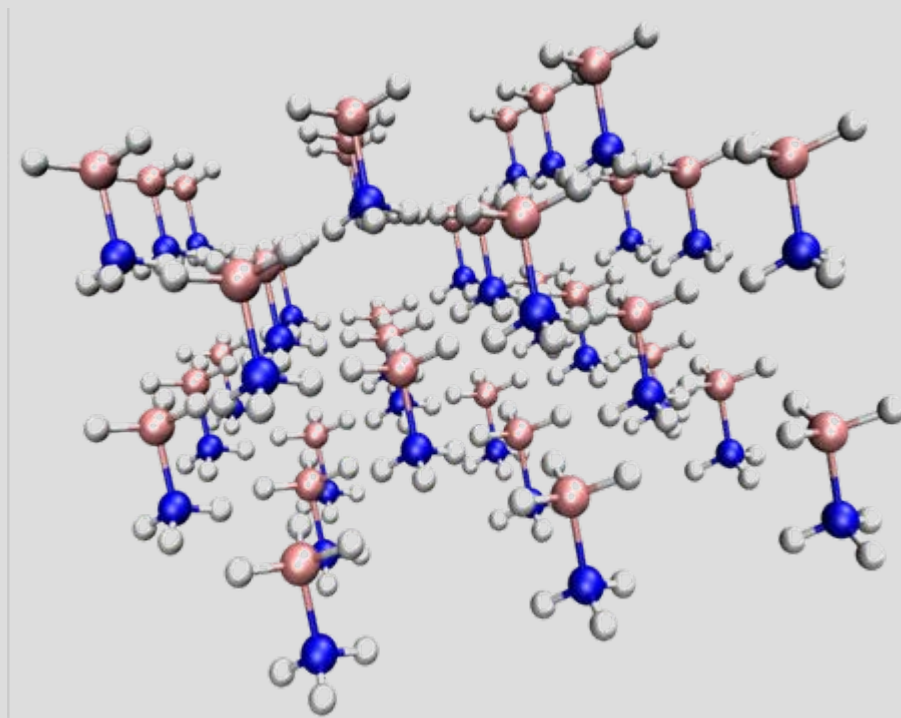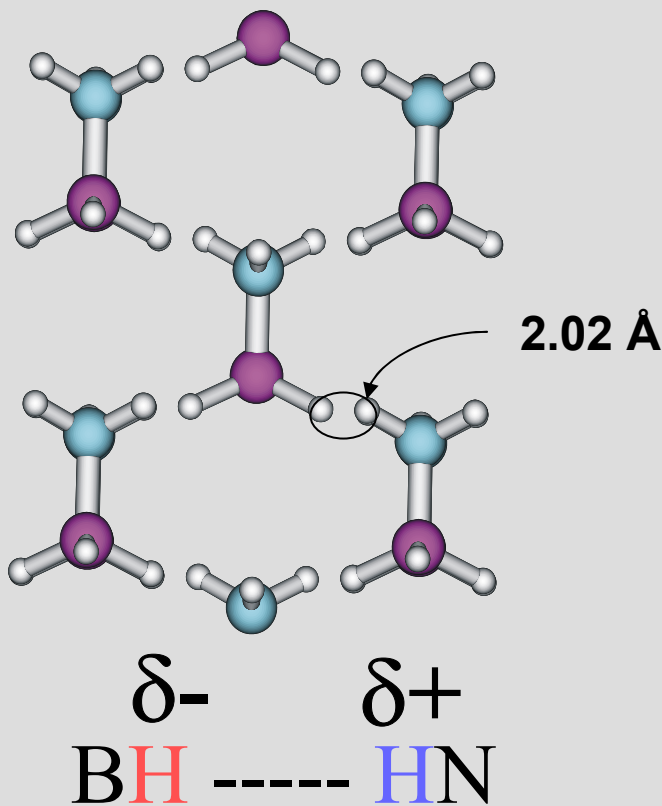



Dihydrogen bond

**Hydride** atoms act as **Proton** acceptor

**Soft vibration modes, where are they?**



Klooster, et. al. *JACS*, 1999, 121, 6337)

# Vibrational studies of dihydrogen bonding

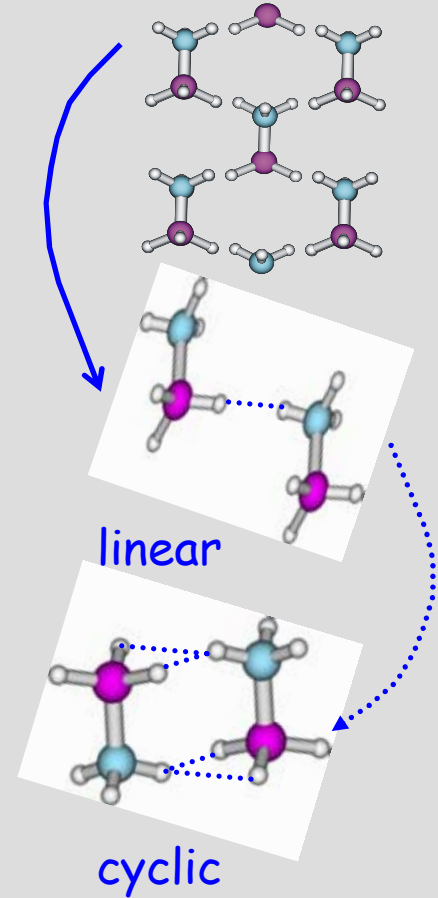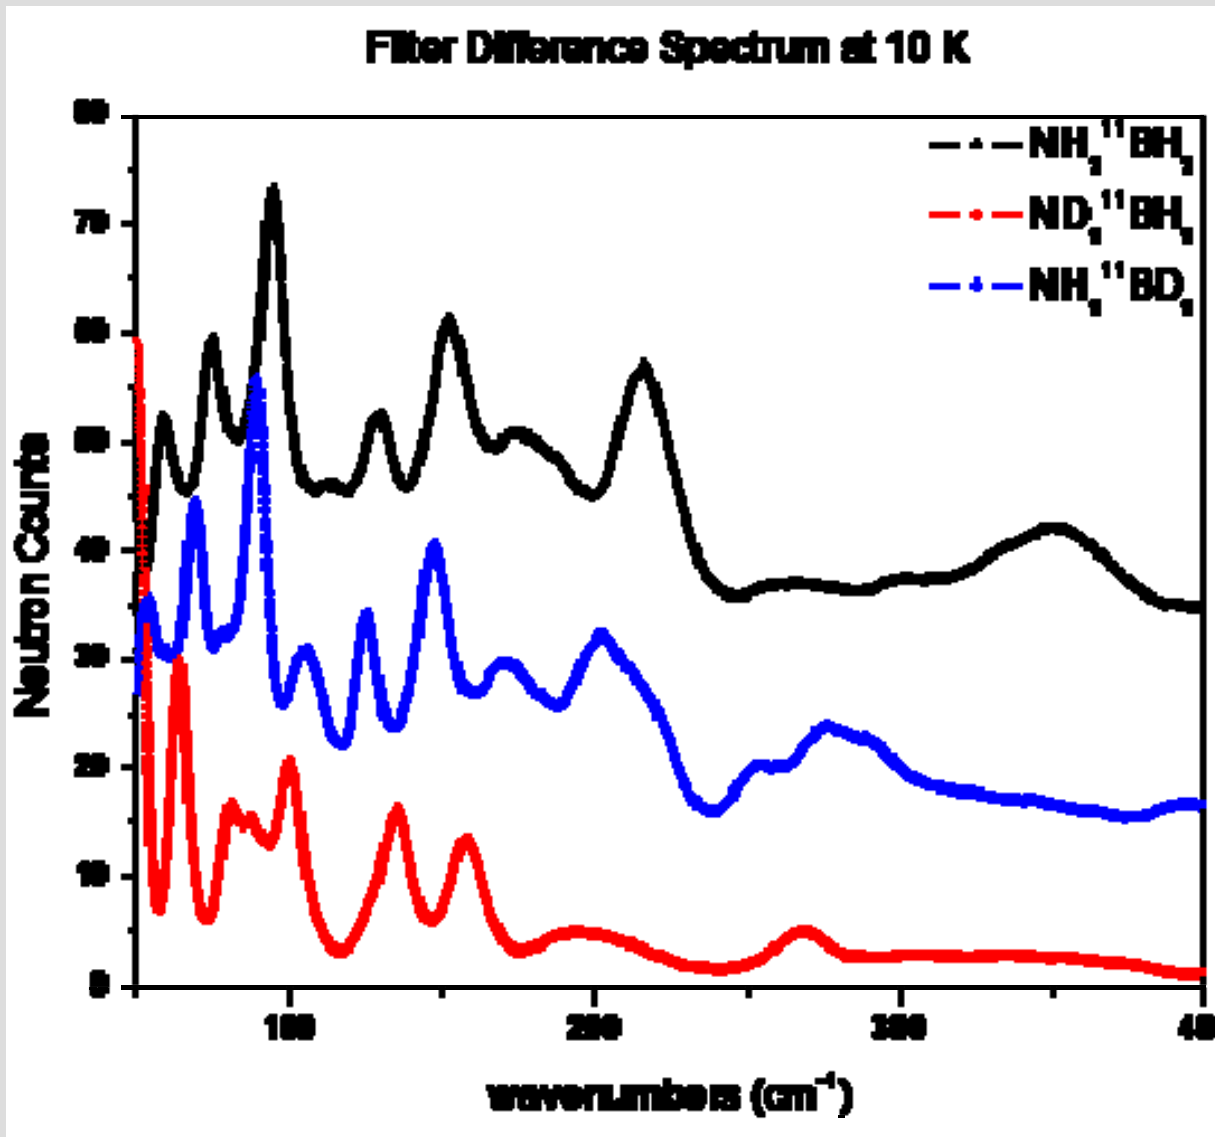



# Computational analysis of dihydrogen bonding

	mode	Calculations on AB dimer (MP2)				FDS spectra at 10K (tentative assignments)		
		linear		cyclic		NH3BH3	ND3BH3	NH3BD3
motion		NH3BH3	NH3BH3	ND3BH3	NH3BD3	NH3BH3	ND3BH3	NH3BD3
molecular rock		52				59	64	53
rock		74				75	81	69
bend	A <sub>u</sub>		93	86 [-7]*	84 [-9.5]	94 (+1)	87 [-8]	89 [-5]
						110		105
torsion	B <sub>g</sub>		132	101 [-23]	117 [-11]	129 (-3)	99 [-23]	125 [-3]
rock	A <sub>g</sub>		150	139 [-8]	141 [-7]	152 (+2)	135 [-11]	147 [-3]
torsion	A <sub>u</sub>		193	142 [-26]	168 [-13]	180 (-13)	158 [-13]	170 [-6]
stretch	A <sub>g</sub>	122	204	201 [-2]	191 [-6]	211 (+7)	198 [-6]	202 [-4]
rock	B <sub>u</sub>		242	224 [-7]	218 [-10]	261 (+19)	-----	218 [-17]
torsion	A <sub>u</sub>	256	295	283 [-4]	241 [-18]	298 (+3)	269 [-10]	253 [-15]
						327		
torsion	B <sub>g</sub>	284	327	304 [-7]	265 [-19]	350 (+23)	317 [-10]	275 [-22]
v(B-N)						764 (782)	725 (737)	756 (747)

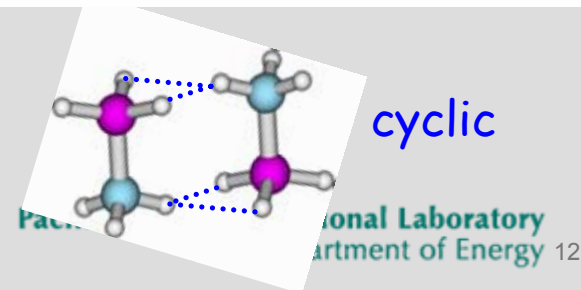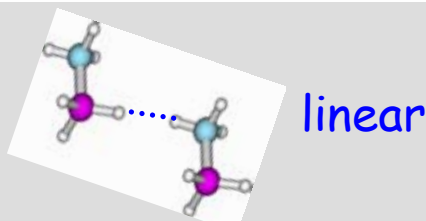

# Dynamics of $\text{-BH}_3$ and $\text{-NH}_3$ motion in AB


Cohesive energy (dihydrogen bonding) 74 kJ/mol...

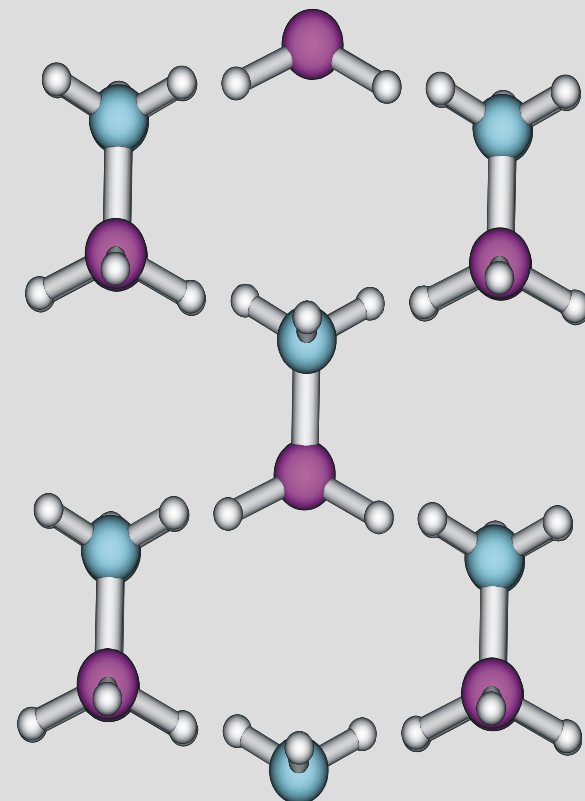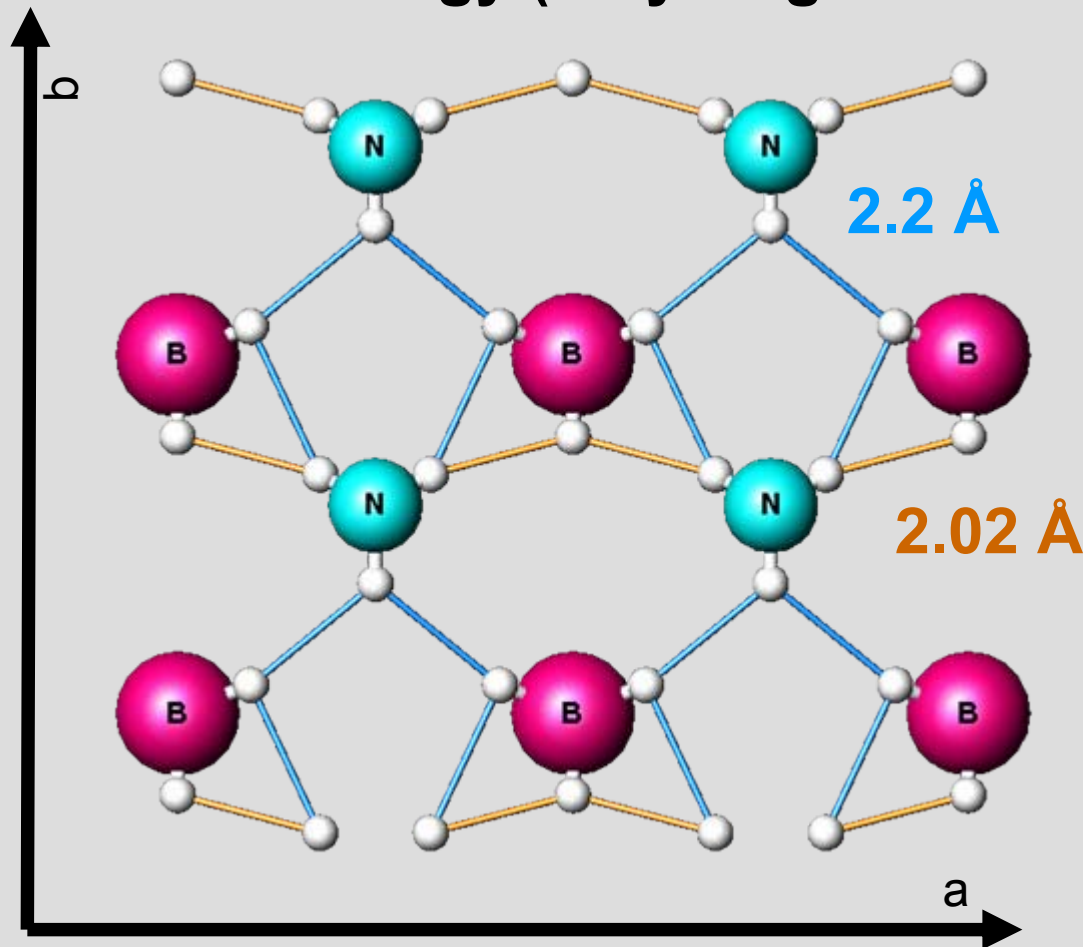



Are hydrogens locked into place?

H-H 2.4 Å


# $^2\text{H}$ nuclear magnetic resonance (D-NMR)

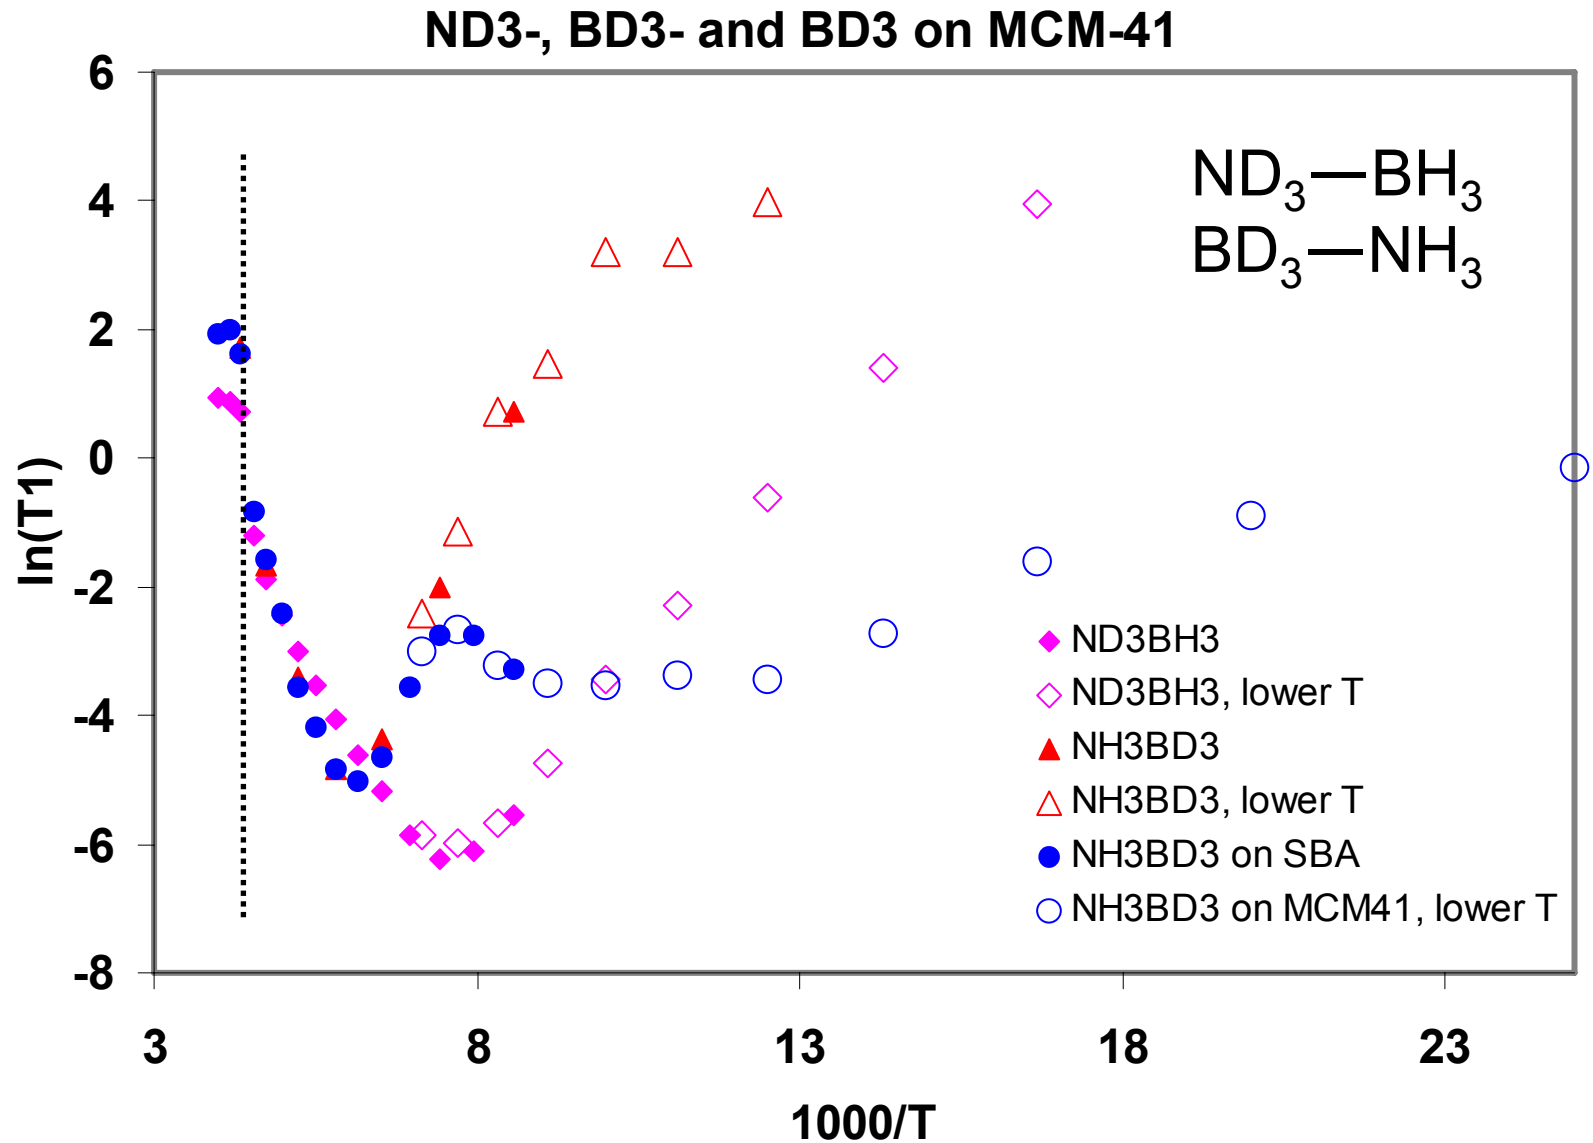

# quasi-elastic neutron scattering (QENS)

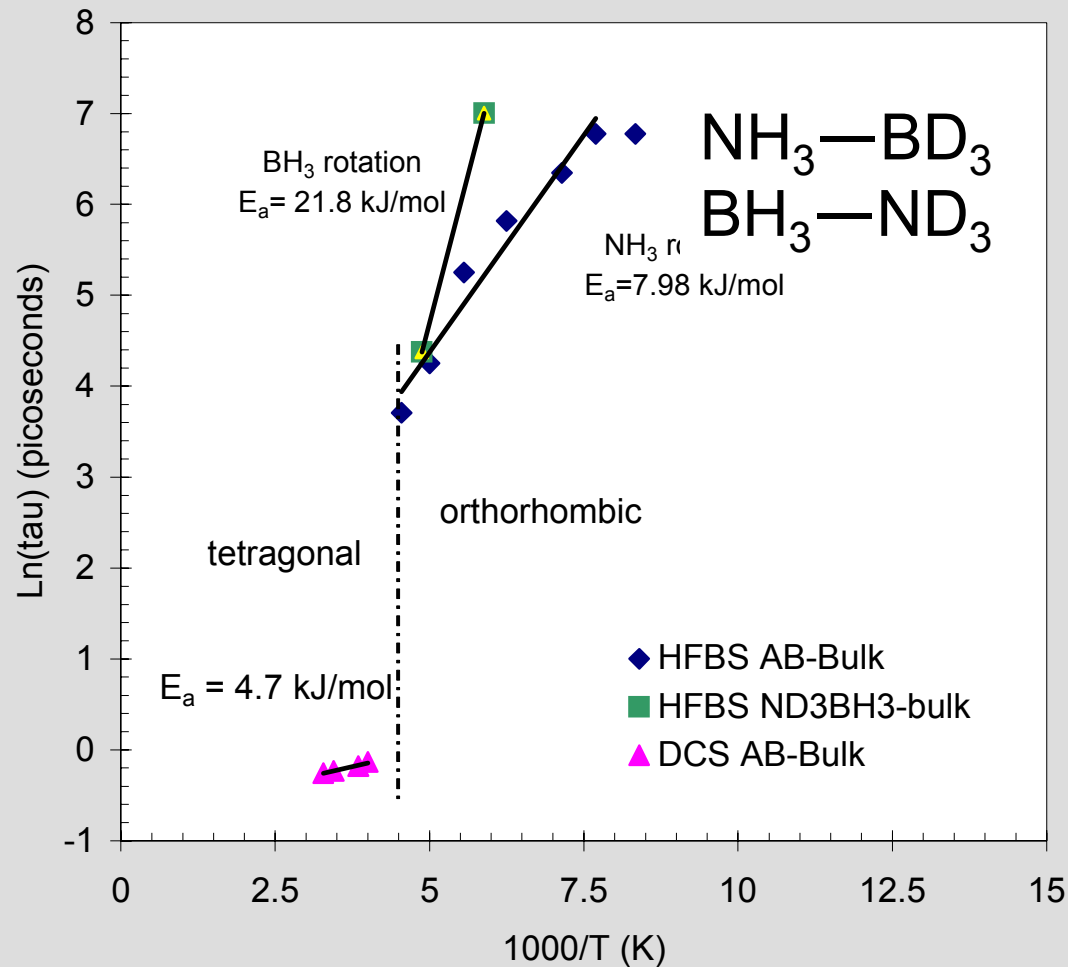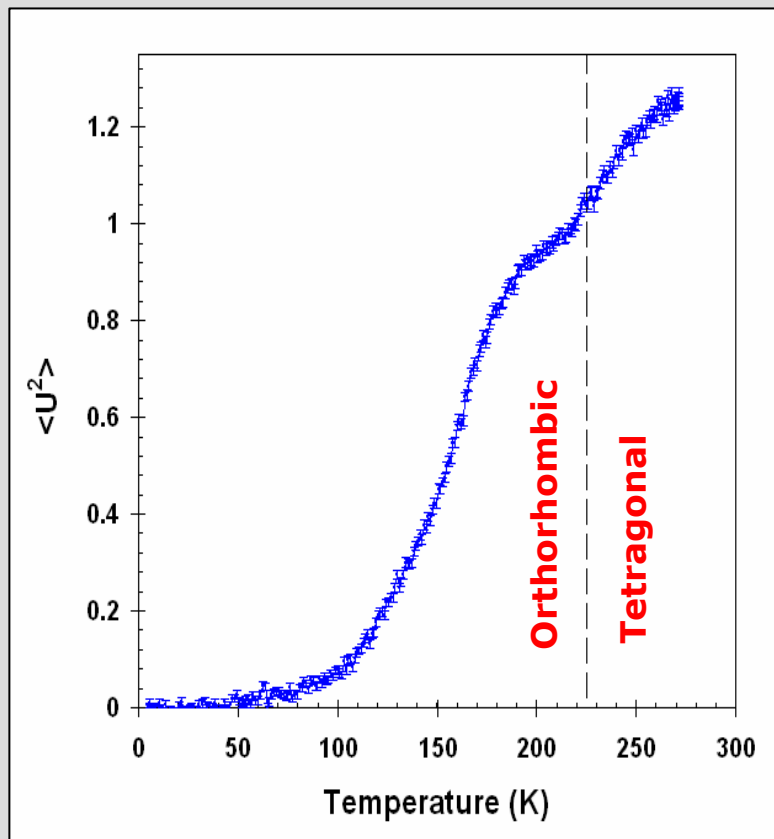

# Rotational energy barriers

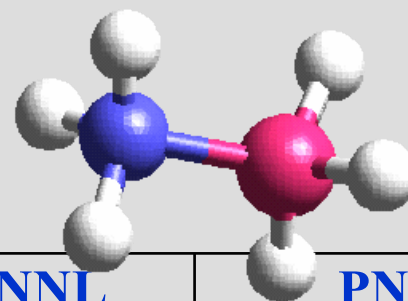

	Reynhardt and Hoon	Penner et al	PNNL NMR	PNNL QENS
<b>Solution</b>				
$E_a$ (kJ/mol)		11.7		
<b>Orthorhombic</b>				<b>HFBS</b>
$\text{NH}_3/\text{ND}_3$				$\text{NH}_3\text{BH}_3$
$E_a$ (kJ/mol)	9.6	13.7 ( $\text{ND}_3$ )	14.6 ( $\text{ND}_3$ )	8 ( $\text{NH}_3$ )
$\text{BH}_3/\text{BD}_3$				$\text{ND}_3\text{BH}_3$
$E_a$ (kJ/mol)	25	25.4 ( $\text{BD}_3$ )	22.7±2 ( $\text{BD}_3$ )	21 ( $\text{BH}_3$ )
<b>Tetragonal</b>				<b>DCS</b>
$\text{NH}_3/\text{ND}_3$				
$E_a$ (kJ/mol)		7.3 ( $\text{ND}_3$ )	5.8 ( $\text{ND}_3$ )	
$\text{BH}_3/\text{BD}_3$				
$E_a$ (kJ/mol)	5.9	5.9 ( $\text{BD}_3$ )		4.7 ( $\text{BH}_3$ )
<b>Gas phase</b>	9			



# Summary

---

$\text{NH}_3\text{BH}_3$ : Strong electrostatic interactions between hydridic and protic hydrogens, however hydrogen is very mobile.

---

**Goal: Understanding dihydrogen bonding interactions. How universal are these interactions in H storage materials?**



**M is electropositive (Li, Mg, Ca, Na, Al, B)**

**Y is electronegative (N, O, P, etc.)**

---

$\text{NH}_x\text{BH}_x$  materials have both hydridic and protic hydrogen. These materials will react with itself or with other hydridic and/or protic hydrogen. E.g.,  $\text{MgH}_2 \text{ --- } \text{H}_3\text{NBH}_3 \text{ --- } \text{H}_2\text{NLi}$

What are thermodynamics of alternative reactions?

# Contributors



## PNNL

Anna Gutowska  
Yongsoon Shin  
Liyu Li  
Scott Smith  
Bruce Kay  
Don Camaioni  
Ashley Stowe  
Abhi Karkamkar  
Dave Heldebrant  
Greg Schenter  
Shawn Kathmann  
Andrew Lipton  
Paul Ellis  
Jesse Sears

## LANSCE

Thomas Proffen  
Monika Hartl

## NCNR

Craig Brown  
Terry Udovic  
Teresa Jacques  
Eugene Mamontov

## Visitors

Benjamin Schmid (UO)  
Mark Bowden (IRL)  
Rene Schellenberg (TUBF)

*This work was supported by the Office of Basic Energy Sciences of the Department of Energy. Pacific Northwest National Laboratory is operated by Battelle for the US Department of Energy.*