



2006 DOE Hydrogen Program

Cost-Effective Method for Producing Self-Supporting Pd Alloy Membrane for Use in the Efficient Production of Coal-derived Hydrogen

James Arps, Ph.D.

Southwest Research Institute

May 17, 2006

Project ID #PD14



This presentation does not contain any proprietary or confidential information





Overview



Timeline

- Project start: Sep. 09, 2003
- Project end: Sep. 08, 2006
- Percent complete: ~85%

Budget

- Total project funding (3 year)
 - DOE share: \$775,771
 - Contractor share: \$194,200
- Funding received in FY05*
 - \$258,606
- Funding for FY06*
 - \$263,671

Barriers

- Barriers addressed
 - N. Defects (high yield, large area)
 - O. Selectivity (>99.9%)
 - Q. Flux (>100 sctH/ft²)
 - S. Cost (<\$1500/ft²)

Partners

- Colorado School of Mines (D. Way)
 - H₂ permeation measurements
 - Membrane characterization
- IdaTech (W. Pledger)
 - Large-scale testing
 - Sealing
 - Module demonstration




Project Objectives



Overall DOE Goal: Develop technologies that effectively and economically separate hydrogen from mixed gas streams that would be produced by coal gasification

- **Develop a process methodology for the cost-effective manufacturing of thin, dense, self-supporting palladium (Pd) alloy membranes for hydrogen separation from the mixed gas streams of coal gasification processes,**
- **Reduce Pd membrane thickness by >50% over current state-of-art, and show potential to meet DOE 2010 technical targets.**
- **Demonstrate viability of using large-area vacuum processing to “engineer” a membrane microstructure that optimizes hydrogen permeability, separation efficiency, and lifetime,**
- **Demonstrate efficacy of large-batch and/or continuous roll-to-roll manufacturing of membrane material with performance and yields within pre-defined tolerance limits**
- **Demonstrate separation efficiency of thin palladium membrane in commercial-type fuel processor using mixed gas streams.**

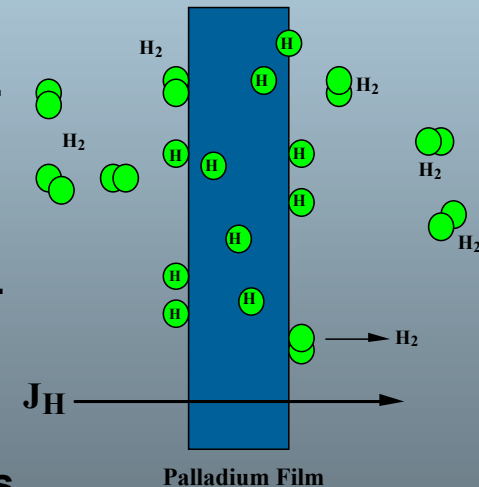





Plan and Approach



- Year 1 (Complete)
 - Task 1: Magnetron Sputter Deposition of Pd-Cu Alloys on Small Samples
 - Task 2: Development of Backing Removal Techniques
 - Task 3: Materials Characterization of Sputtered Pd-alloy Membranes
 - Task 4: Pressure and Purification Testing
 - Task 5: Prototype Module Design
- Year 2 (Complete)
 - Task 1: Fabrication of Larger Area Membranes
 - Task 2: Optimization of Membrane Composition/Microstructure
 - Task 3: Refinement and Down-selection of Backing Removal Methods
 - Task 4: Production of Membranes at least 75 in² in Area
 - Task 5: Prototype Module Construction
- Year 3
 - Task 1: Final Optimization/Selection of Membrane Alloy Composition (Complete)
 - Task 2: Pressure and Purification Testing Pilot-Scale Membranes (50% Complete)
 - Task 3: Prototype Module Final Assembly and Testing (50% Complete)
 - Task 4: Develop Cost Estimates for Production of Pd Membranes (25% Complete)

- Six large chambers utilize a variety of vacuum based coatings and surface treatments.
- Recent DOE projects in:
 - Boiler tube coatings
 - SOFC interconnects
 - PEMFC catalysts

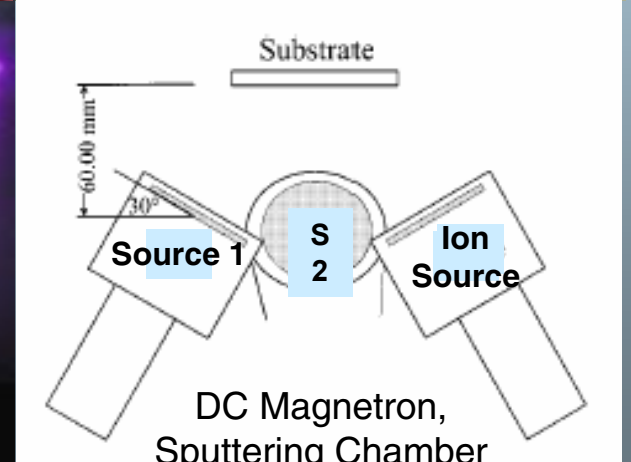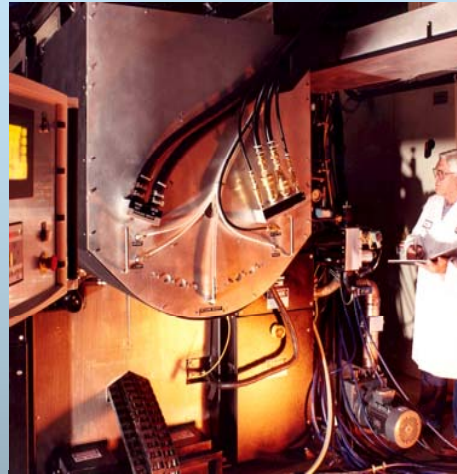



Membrane Fabrication – Flexible Substrates



- Concurrent and sequential e-beam evaporation
 - Utilized DOE approach to screen variables (dep/feed rates, drum temperature, etc)
 - Established level of significance with EIES (optical) control
 - Typical deposition rates between 0.8-1.2 nm/sec at feed rate of 0.12 m/sec

Co-Evap

Pros Simple, Fast (High Rate)


Cons Compositional control over large areas

Sequential

Compositional Control over large areas, Fast

Multiple Steps Post Treatment

- Magnetron Sputtering (60/40 alloy target)
 - Good composition (tiling) /strain control
 - Control of density
- Successful deposition on PS, PI, PVA, PE, and PET
 - Over 200 linear feet of material produced
 - Demonstration over large areas (75 in²)
 - Issues with defects and stress control at thicknesses less than 12 μ m

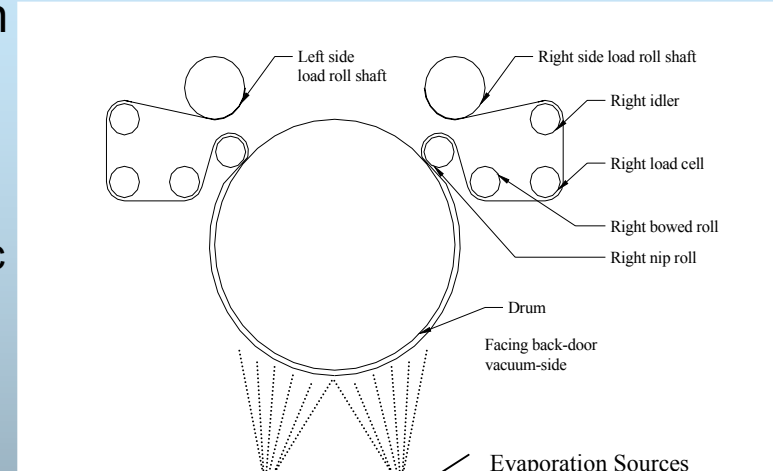

Web roll coater with evaporation sources







Membrane Fabrication – Rigid Substrates





- Formation of free-standing, gas impermeable Pd-Cu membranes up to 110 in² in area and less than 5 μm thick, using rigid backing materials such as glass and silicon.
- Formation of free-standing, Pd-Cu membranes as thin as 1 μm with minimal defects.

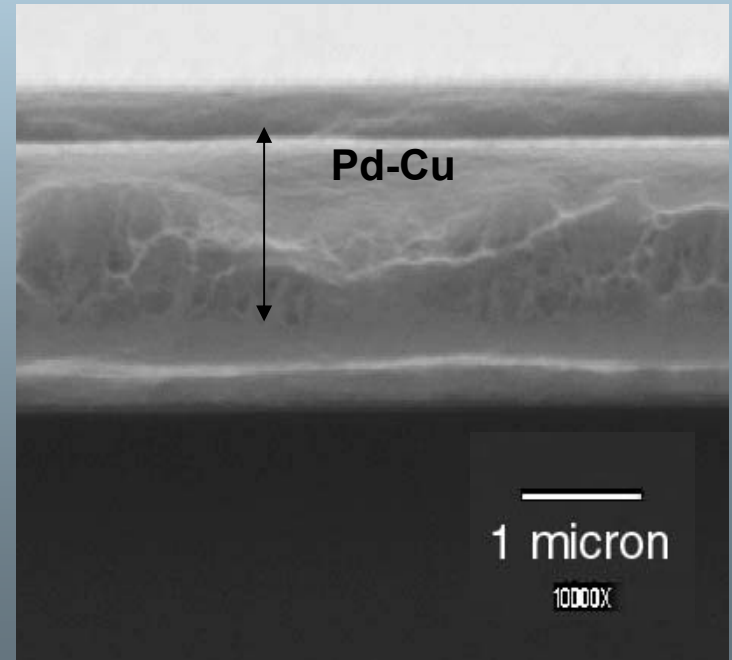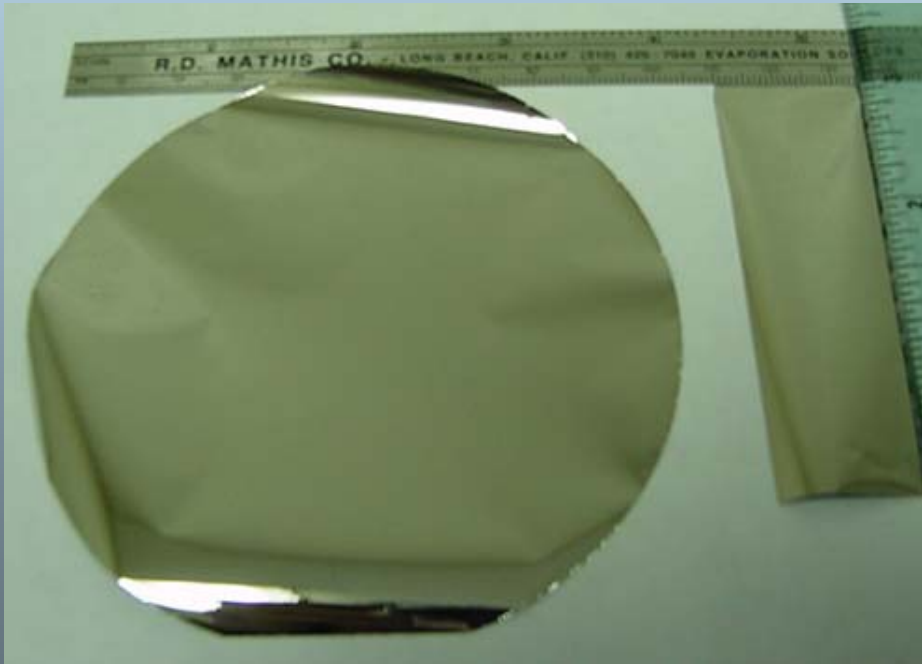


- Conducted statistical DOE to identify conditions for production of defect-free films on silicon wafers with easy release (neutral film stress)

<i>Power (kW)</i>	<i>Flow (sccm)</i>	<i>Press (mtorr)</i>	<i>Angle (deg)</i>	<i>Ion</i>
0.27	21.3	0.3	0	
0.28	24	0.24	10	Assist Clean
0.28	27	0.3	10	Clean

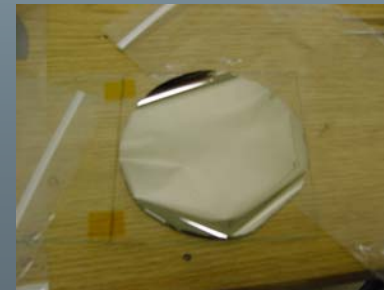


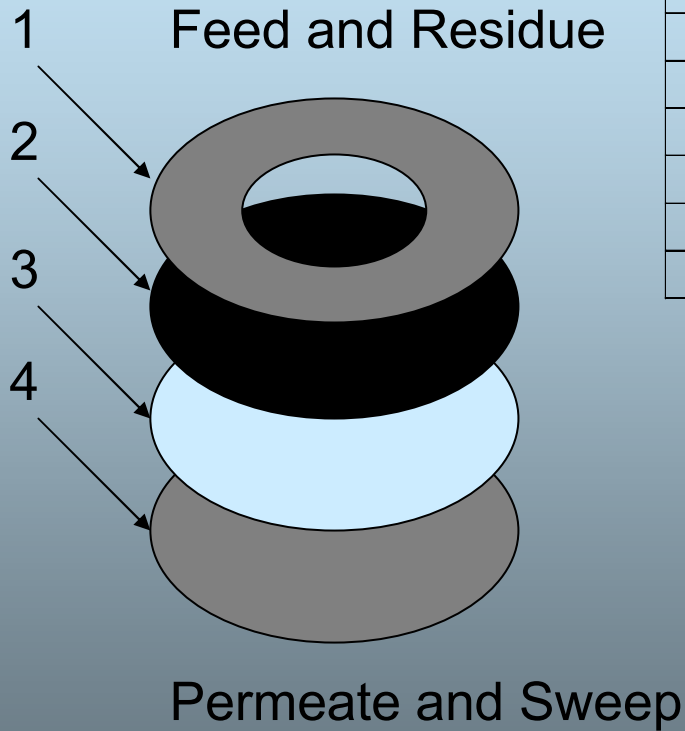


Part Number	Description
1	Graphite Gasket for Sealing
2	Membrane
3	Ceramic Paper (Diffusion barrier)
4	Porous Stainless Steel Support
5	Feed and Residue attachment
6	Permeate and Sweep attachment

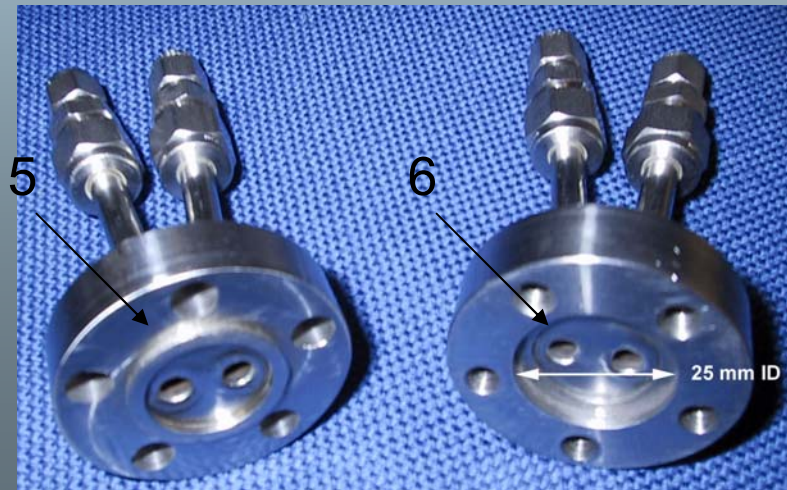

CSM Permeation Apparatus

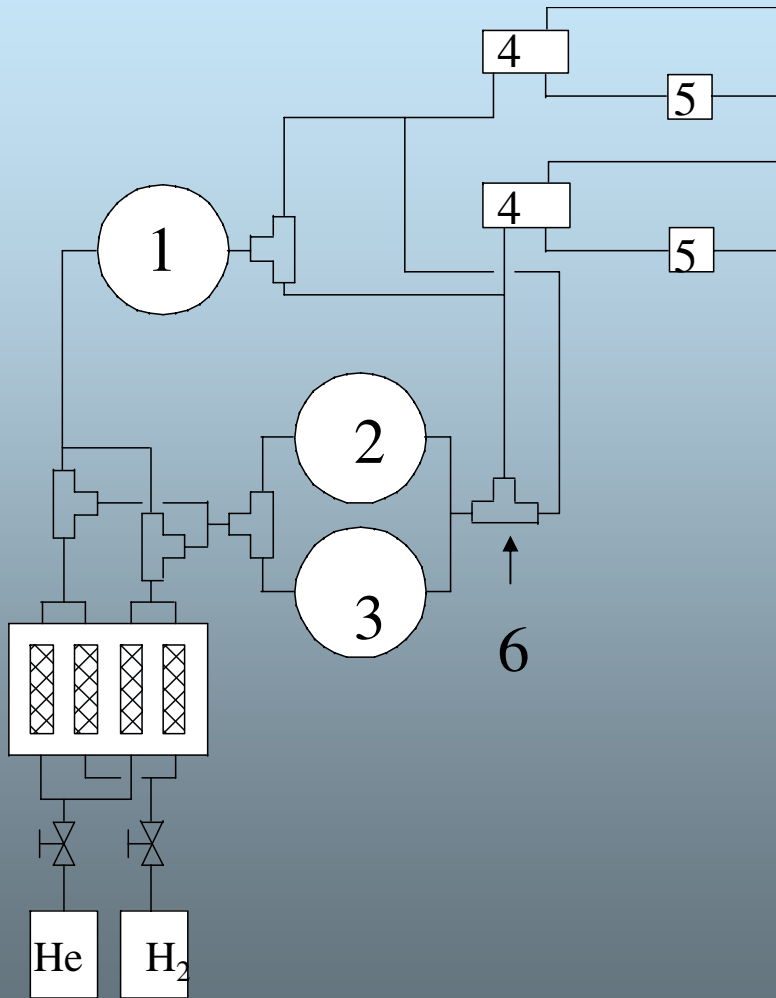

Part Number	Description
1	Idle Pressure Gauge
2	High Pressure Test Gauge
3	Low Pressure Test Gauge
4	Membrane Housing
5	Back Pressure Regulator
6	3-way valves

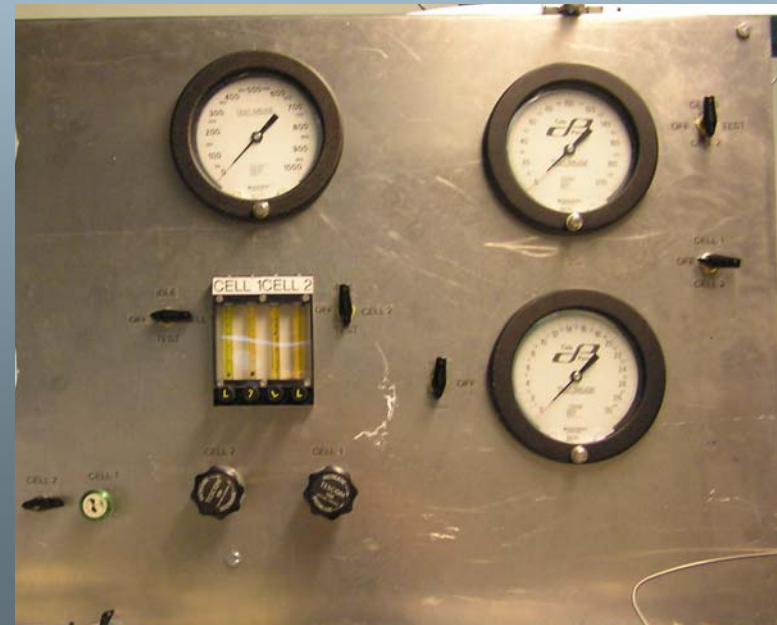



Test Conditions




- Feed Conditions
 - Pure hydrogen at 20 psig or pure helium at 20 psig
- Permeate Conditions
 - Gauge pressure of 0 for all runs
 - Atmospheric pressure in Golden, CO = 12 psia
- Temperatures
 - Most permeation measurements are taken at 400°C
 - Membranes are run at temperatures ranging from 250°C to 550°C



Measured H₂ Flux Has Surpassed Program Goals




- Best performance data @ 400 °C shown for a 2.5 μm Pd-Cu alloy foil, area = 2.6 cm²
 - Pure H₂ permeability = $8 \cdot 10^{-5} \text{ cm}^3 \cdot \text{cm} / \text{cm}^2 \cdot \text{s} \cdot \text{cmHg}^{0.5}$
 - H₂ Flux = 124 cm³/cm²·min = **242 scfh/ft²**
 - Feed pressure = 20 psig
- Exceeds DOE Hydrogen Program and 2010 DOE Fossil Energy targets

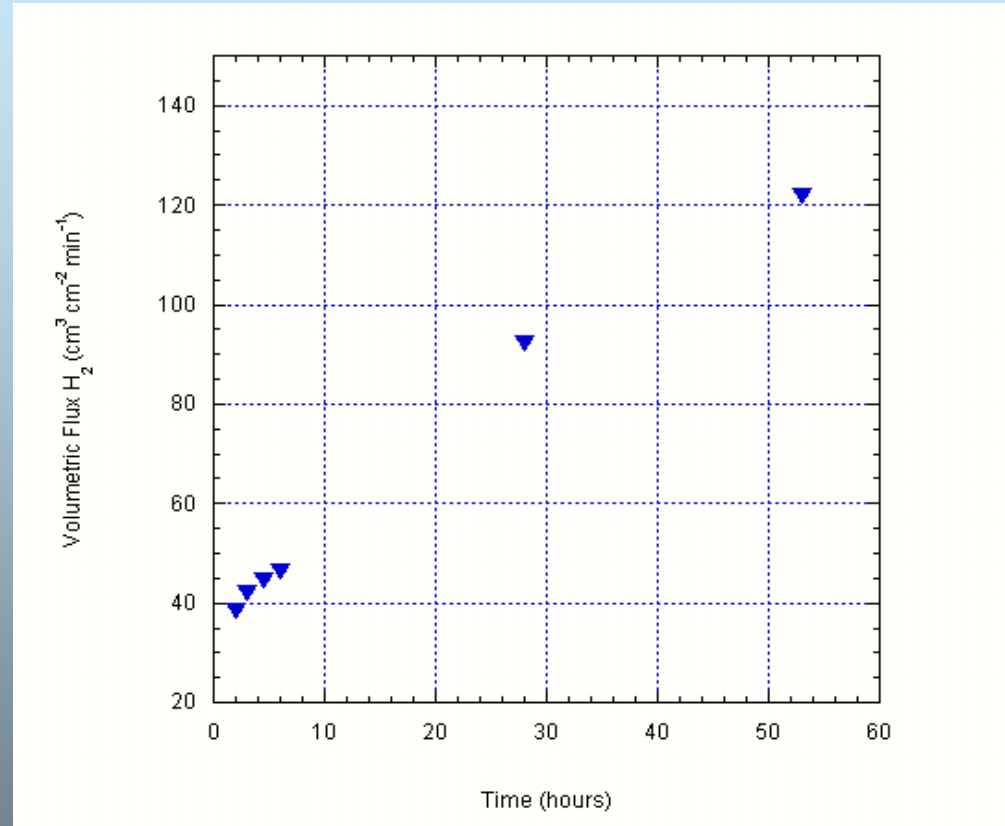

Performance Criteria	SwRI Membrane	2007 Target	2010 Target	2015 Target
Flux scfh/ft ² @ 100 psi DP H ₂ partial pressure & 50 psid	564	100	200	300



- Demonstrated separation of >99.95% pure hydrogen from helium
- Perfect H₂ selectivity measured throughout the test (i.e. no pinholes or other defects)
- Short term testing at 50 psig differential pressure without rupture
- Hydrogen permeability = $1.09\text{E-}4 \text{ cm}^3(\text{STP})\cdot\text{cm}/\text{cm}^2\cdot\text{s}\cdot\text{cmHg}^{1/2}$

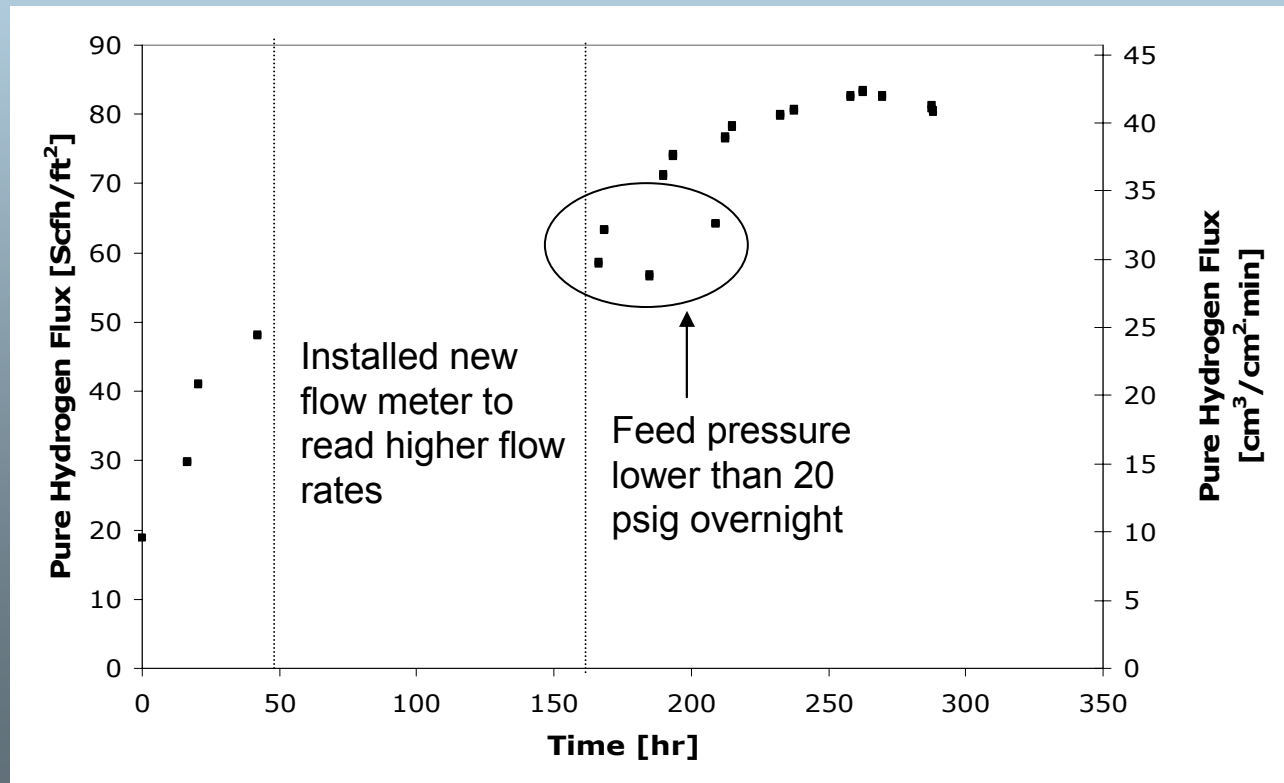




Influence of Temperature on Permeability of 60 wt% Pd Foil



- Demonstrated maximum permeability at 400 C
- SwRI membranes match the Wilkinson and McKinley data both in permeability and composition
- 60-40wt% PdCu composition has been verified by EDX


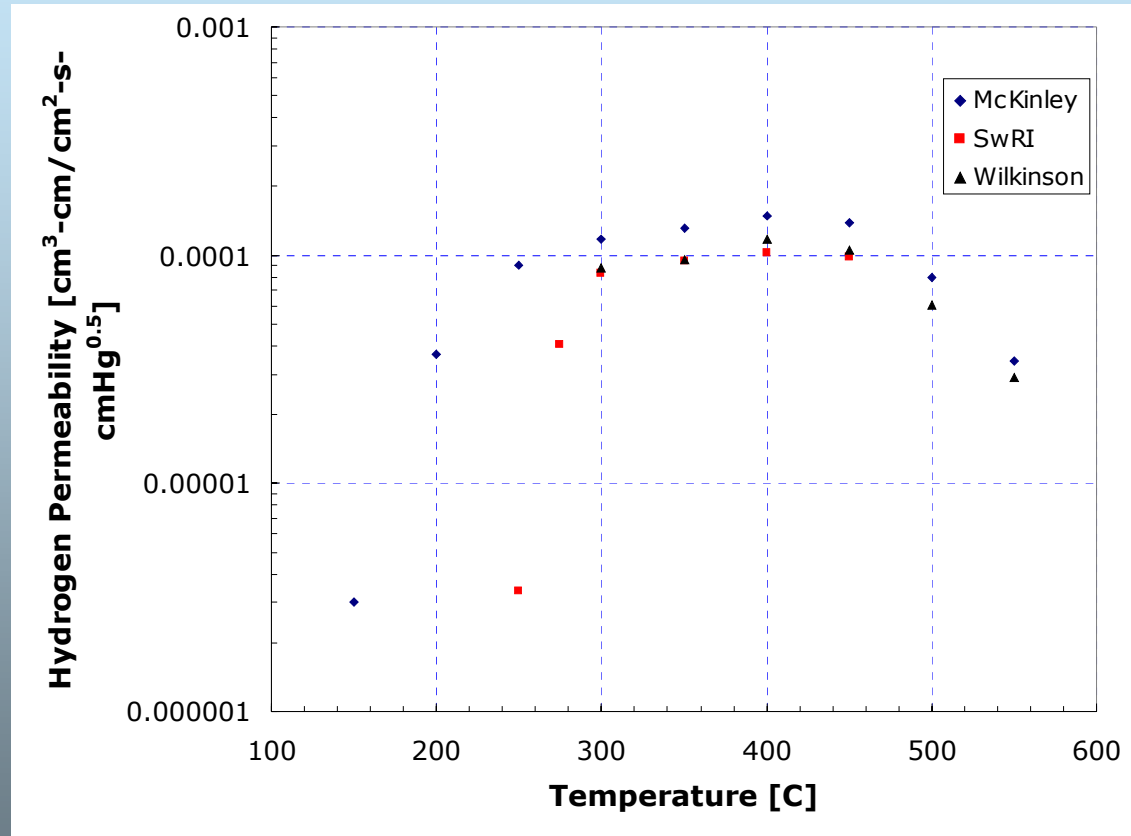




Module Development and Testing at Idatech




- Measured H₂ flux of 420 SCFH/ft² (400°C and 100 psig) on smaller samples provided by SwRI.
- Investigating gasketing arrangements to reliably seal thin membranes.
- First full-scale module test expected in coming weeks
- More than a dozen full-size prototype membranes have been delivered to Idatech

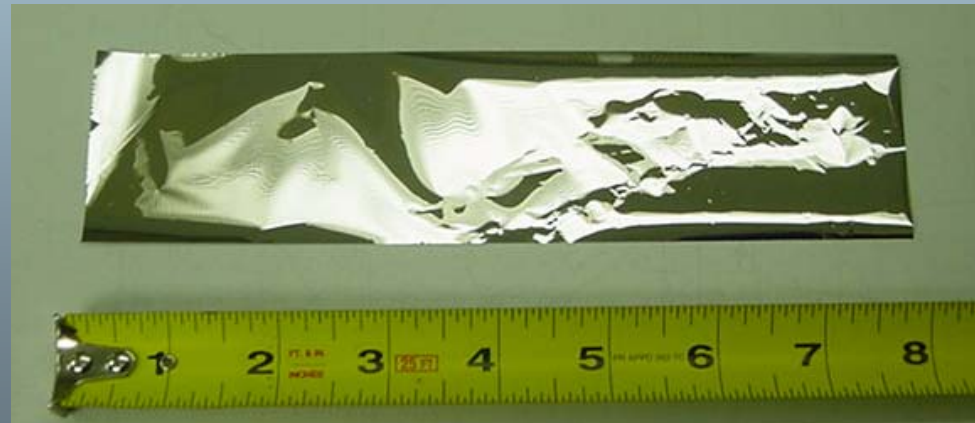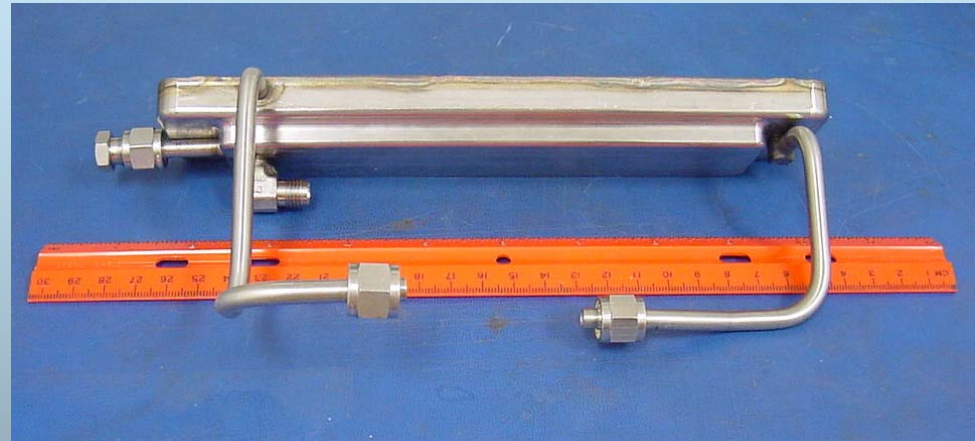

Cost Projections

- Off-the-shelf semiconductor equipment should be adaptable for large-scale membrane production
 - Estimated throughput of $\sim 25 \text{ ft}^2/\text{hr}$ with a single cluster tool
- Currently costs SwRI $\sim \$1500/\text{ft}^2$ to produce Pd alloy membranes in small quantities (few ft^2 per day)
- Raw materials cost is not the most significant factor
 - $3\mu\text{m}$ thick 60wt% membrane, has $\sim \$21/\text{ft}^2$ of Pd (assuming $\$350/\text{oz}$)

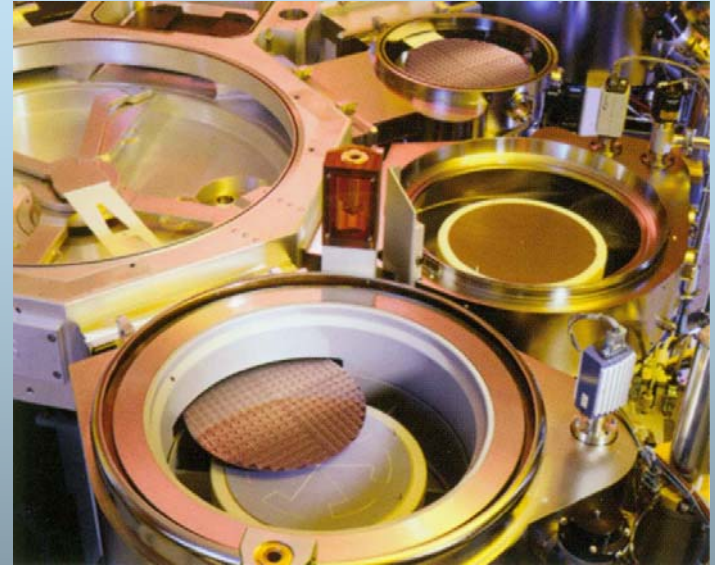

Novellus INOVA xT



Future Work



- Continue efforts to establish reliable sealing methods for ultra-thin membranes
- Ternary alloy development (Pd-Cu-X)
 - Early-stage collaborations with LANL (Steve Paglieri) and CMU (David Sholl)
- Full-Scale Prototype Module Demonstration
 - Target production rate of $50 \text{ cm}^3/\text{cm}^2\text{-min}$ of 99.95% pure hydrogen
- Prepare a more detailed cost analysis of membrane production process



Project Summary



- Relevance
 - Robust, high efficiency methods to extract pure hydrogen from coal gas and other sources is critical to the development of a hydrogen economy
- Approach
 - Use a novel, scalable vacuum deposition method to fabricate free standing Pd alloy hydrogen separation membranes and evaluate their performance
- Accomplishments
 - Produced some of the thinnest (3 μm), largest area (110 in^2), highest performance separation membranes ever reported



Summary (Cont'd)



	2005 DOE Target	2010 DOE Target	SwRI
Flux (scfh/ft ²)	100	200	242
Cost (\$/ft ²)	1500	1000	1500
Hydrogen Quality	99.9	99.95	99.95
DP Operating Capability	200	400	100

- Collaborations
 - Strong commercial partner in Idatech, long track record testing hydrogen membranes at CSM, new interactions with LANL and CMU
- Future R&D
 - Test under more aggressive conditions, develop new ternary alloy formulations with increased durability, demonstrate low-cost pilot production



Backup Slides



Reviewer's Comments



- Future work should include some lifetime tests to evaluate the stability of the membrane over time.
 - Membranes have been tested up to 300 hours at 400°C
 - A lot of bottled hydrogen is needed for these tests
- With better matrix experiment design, approach should lead to significant results
 - Statistic DOE has been implemented in optimization of membrane stress, release, and defect density.
- Hydrogen purity levels derived in recent tests (99.95%) would be insufficient for direct use in fuel cell vehicles
 - Further increases in purity are possible, Idatech has demonstrated membrane purification to <1 ppm CO and <5 ppm CO₂.



Publications and Presentations



- Fabrication of Self-Supported Pd Alloy Membranes Using Vacuum Deposition Methods, International Conference on Metallurgical Coatings and Thin Films, San Diego, CA, May, 2005
- Ultra-thin Palladium Alloy Membrane for Hydrogen Gas Separation, J. Arps, B. Lanning, G. Dearnaley, *Technology Today*, April 2006
- Development of Ultra-Thin, Large-Area, Self-Supported Palladium Alloy Membranes for use in Efficient Production of Coal Derived Hydrogen, 9th International Conference on Inorganic Membranes, Lillehammer, Norway, June, 2006



Critical Assumptions and Issues



- Performance and durability in more realistic syngas environments
 - bcc Pd alloys are known to be sensitive to sulfur
- Demonstrate ability of vacuum deposition method to produce membranes at low cost and in large quantity
 - Several industrial examples prove such methods can be cost effective
- Pressure and sealing issues for thin membranes can be overcome with advanced designs