

Advanced Boron and Metal Loaded High Porosity Carbons



T. C. Mike Chung

**(Other Members in PSU Team:
Vince Crespi, Peter Eklund, Hank Foley)**

The Pennsylvania State University

April 18, 2008

Project ID#: STP 11

Overview

Timeline

- Project start: 2/1/05
- Project end: 1/31/10
- % complete: 60%

Budget

- Total funding for PSU team
 - DOE share: \$1.2M
 - Contractor share: \$0.3M
- FY06 \$ 225,000
- FY07 \$ 333,000

Partners

- Dispersed throughout HSCoE:
NIST (neutron), NREL (TPD),
Air Products (vol. ads.),
UNC (NMR)

Barriers

A: *System Wt & Vol*: Hydrogen volumetric (1.5 kWh/L) and gravimetric (6wt%) storage density goals for 2010

B: *System Cost*: High-volume low-cost synthesis routes (via pyrolysis, arc)

C: *Energy Efficiency*: Low pressure, moderate temperature operation (via enhanced binding energy through chemical modification)

E: *Charge/discharge rate*: via Mixed micro/mesopore structures through precursor design

J: *Thermal management*: via designed moderate binding energies of mixed physi/chemi-sorption

P: *Improved understanding*: via calculations in close coupling with fundamental measurements on well-characterized, well-ordered systems



Project Objectives and Approaches

6 wt% H_2 storage goal by increasing binding energy (10-30 kJ/mol) and SSA ($> 2000 \text{ m}^2/\text{g}$)

*Micro-porous
B Substitution C
(B/C) Materials*



*Microporous
Metal Intercalation
M/B/C Materials*

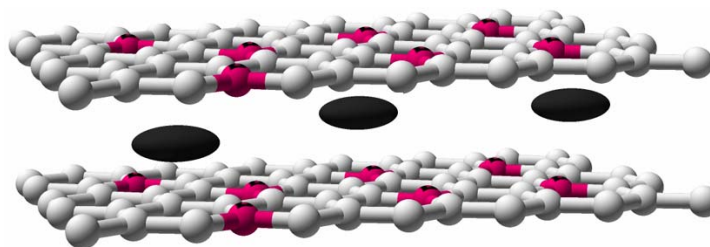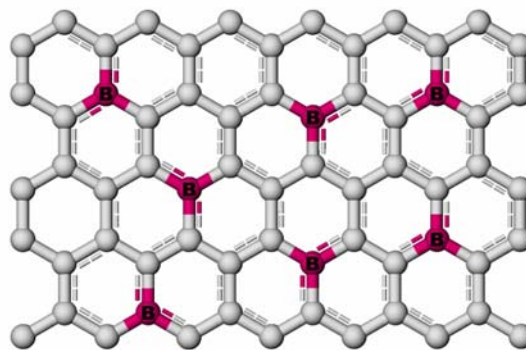

B in C Structures





- ✓ Lightness of Boron
- ✓ Enhancing H_2 interaction
- ✓ No serious structural distortions
- ✓ Catalyzing carbonization
- ✓ Stabilizing atomic metal

Project Activities and Schedule

- FY06**
 - Developing synthesis routes and processes to prepare B/C (**B-substitution**) materials.
 - Characterizing new B/C materials and structure-property-H₂ adsorption relationship.
- FY07**
 - Synthesizing the desirable B/C materials with high B content and high SSA, and their H₂ adsorption.
 - Investigating synthesis routes to prepare atomic metal dispersion (**M-intercalation**) in B/C materials.
- FY08**
 - Synthesizing the desirable B/C and M/B/C materials with B content (>10 mol%), M content (>3 mol%), and SSA (>2000 m²/g).
 - Studying structure-property relationship.

Technical Accomplishments



Synthesis of B/C Materials by B-containing Precursors

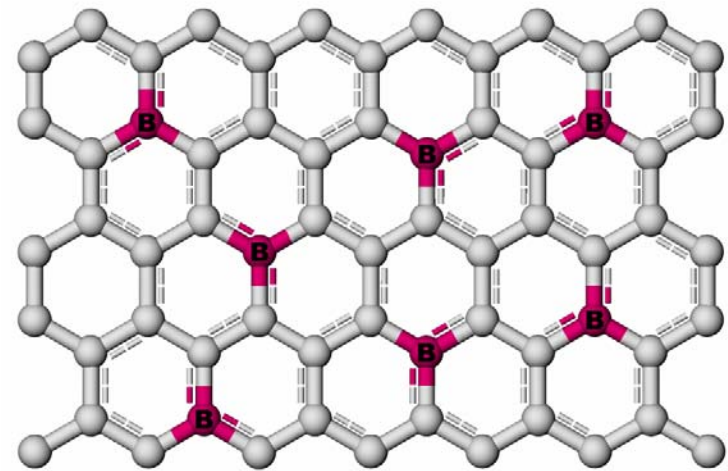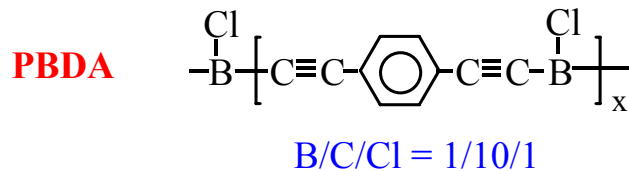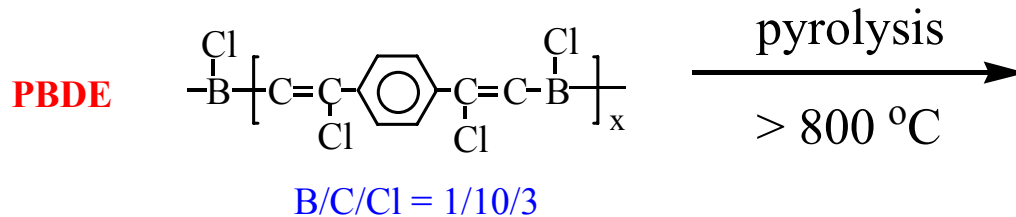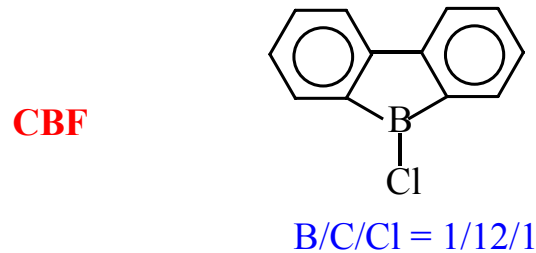

- Conjugated B-C bonds
- Reactive B-Cl for stabilization

- Simple process
- Large scale production
- Varying pyrolysis temp.
- Control Crystal structure
- Control B content (up to 10%)


Synthesis of Micro-porous C/B Material

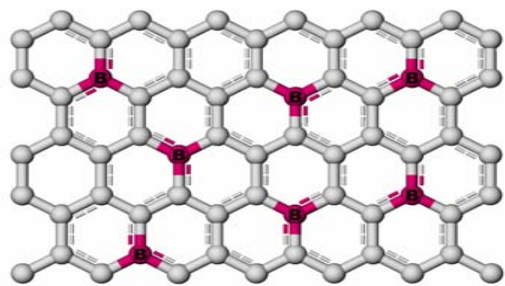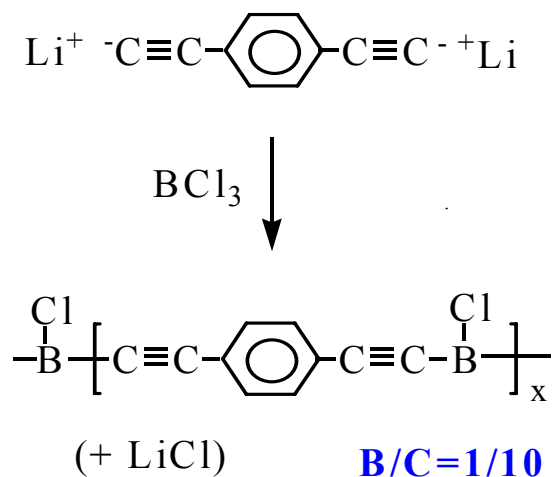

Micro-porous B/C


Pyrolysis temp. (°C)	B content ^a (wt%)	B content ^b (wt%)	Surface area ^c (m ² /g)
600	7.2	7.6	780
800	5.7	7.1	528
1500	3.8	3.0	33

- a. Prompt Gamma-ray Activation Analysis (NIST).
- b. ¹¹B MAS-NMR measurement (UNC).
- c. BET method using N₂ gas at liquid N₂.

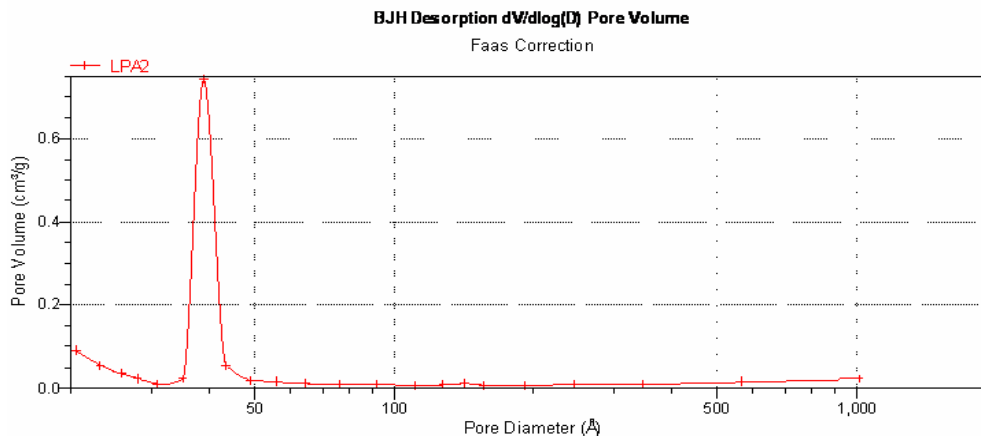


Technical Accomplishments

Solid State ^{11}B MAS-NMR spectra of B/C materials

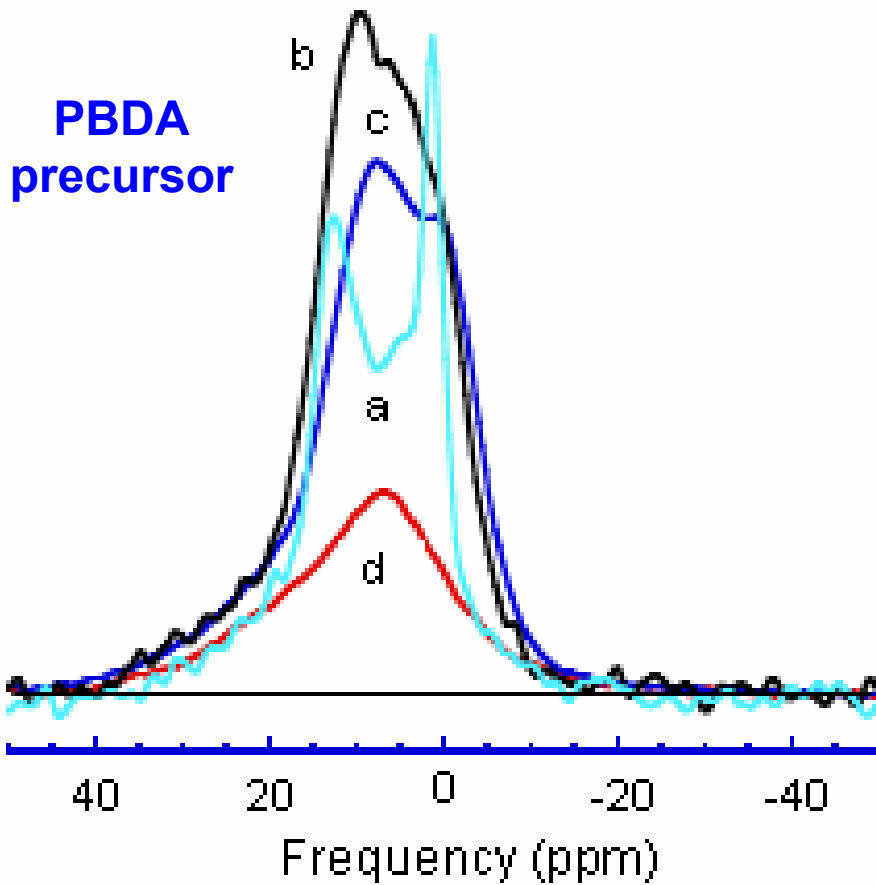

(a) 150, (b) 600, (c) 800, (d) 1000 °C

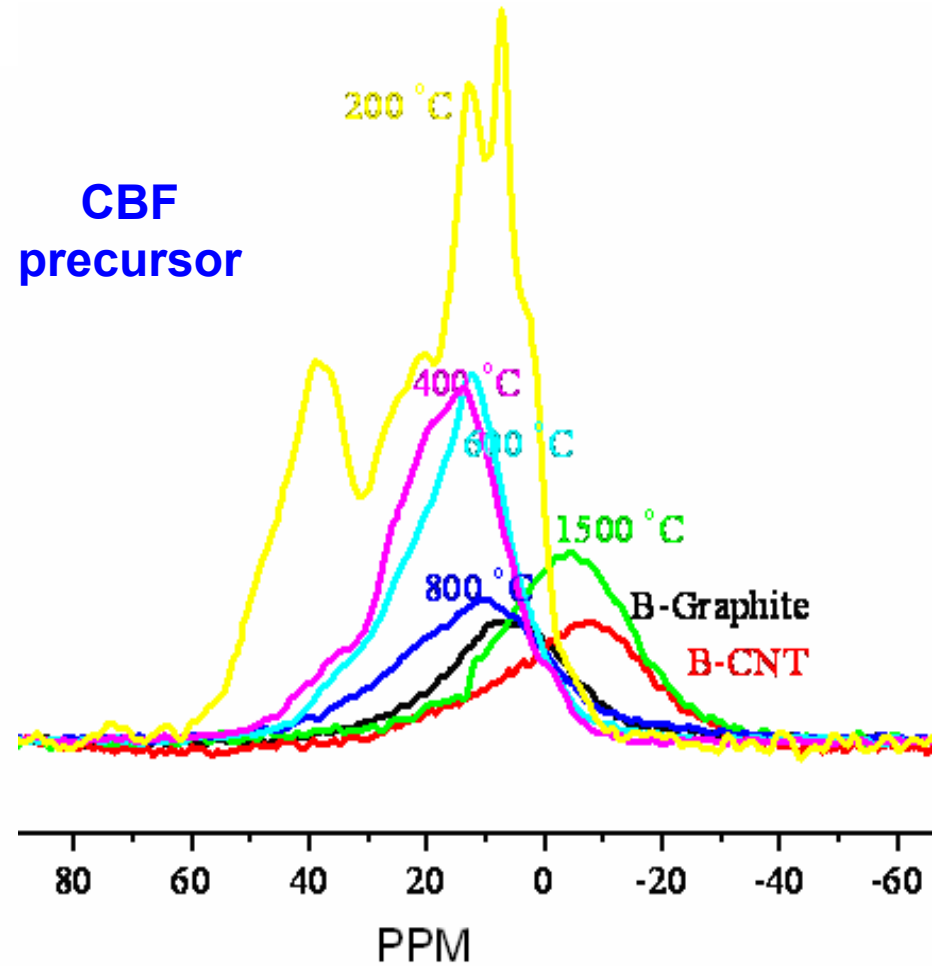


Yue Wu (UNC) and Mike Chung

Technical Accomplishments

XRD Patterns of C/B materials

**Pyrolysis
Temp.**

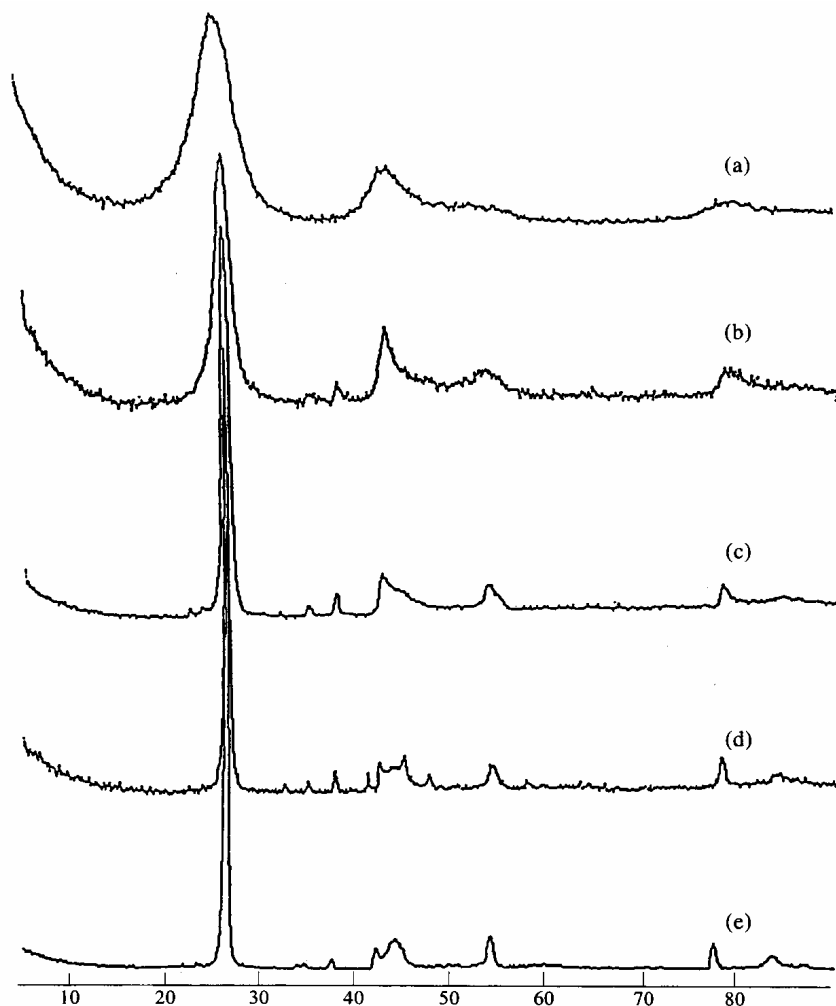

**D-Spacing
(002) (A)**

**Boron
Content**

800°C

3.461

7.65%

1500°C

3.411

7.58%
(PGAA,
NIST)

1800°C

3.383

7.42%

2100°C

3.363

6.96%

2300°C

3.347

3.46%₈

Technical Accomplishments

Evolution of B/C Structure during Pyrolysis

600 °C



1000 °C





>1500 °C



B/C materials with various B site structures that are controlled by pyrolysis temperatures

Technical Accomplishments



Hydrogen Uptake in Micro-porous B/C (SSA: 780 m²/g)

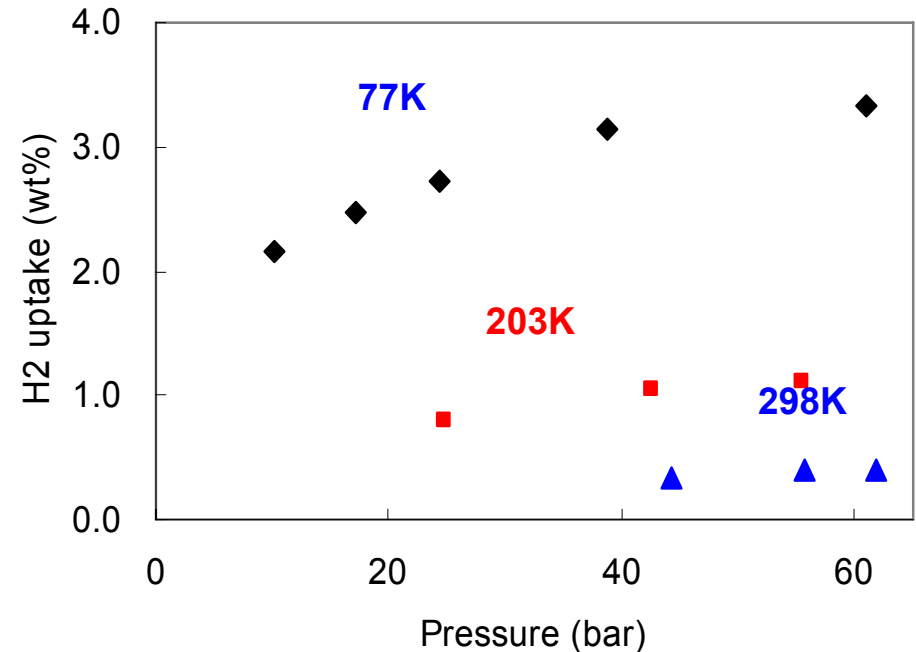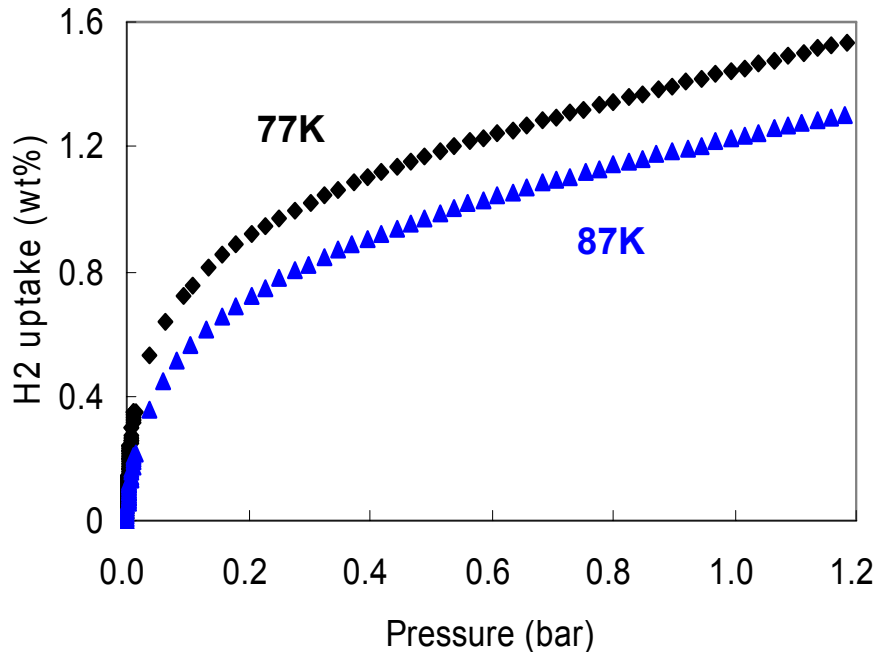

- Initial heat of adsorption for the B/C material is **12.47 kJ/mol**
- **About 2 times H₂ adsorption capacity** (vs. C having similar SSA)

Technical Accomplishments

^1H NMR spectrum of H_2 Gas in Porous B/C Material

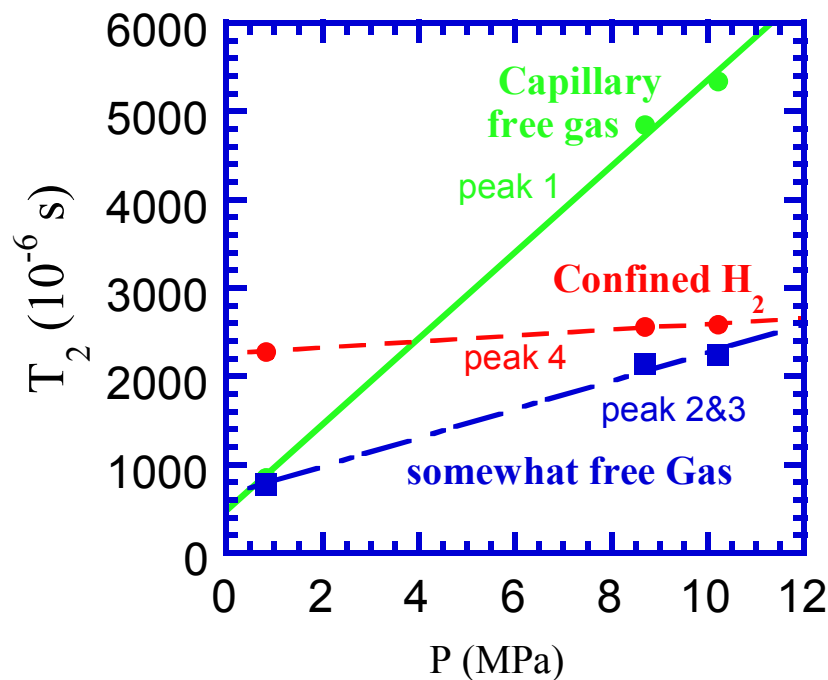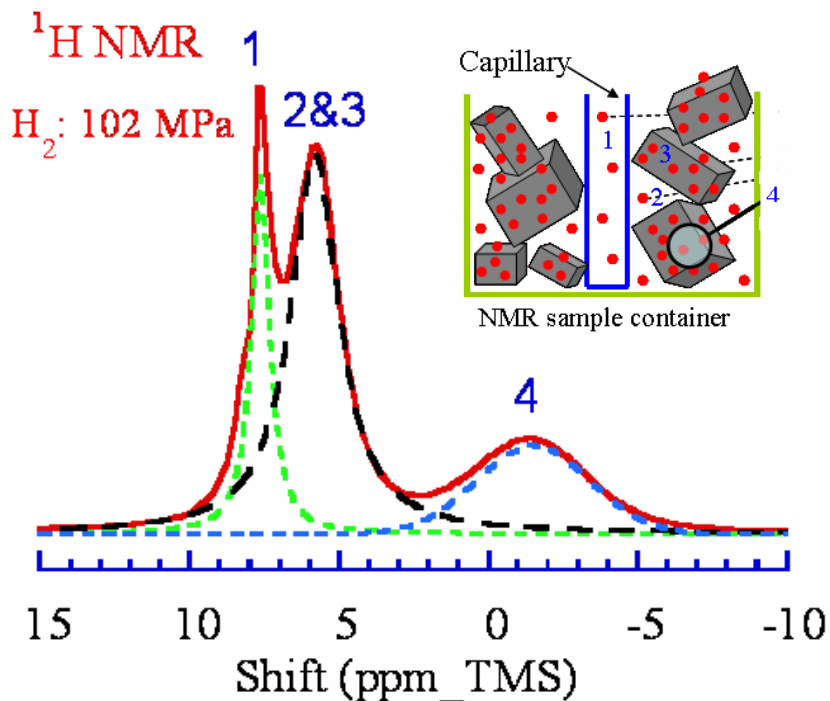


Peak 1 and peak 2&3 depend linearly on pressure as expected for free H_2 gas
 Peak 4 shows nonlinear pressure dependence. Using the Langmuir equation, an estimate of binding energy $E_{\text{ads}} = 11$ kJ/mol.

Boron significantly enhances H_2 binding energy

Technical Accomplishments

Metal-loading in B/C Materials

Graphitic C

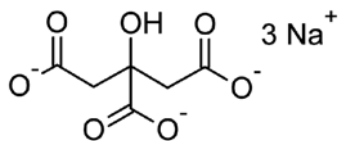


in Water



chemical
reduction

**Pt(0) particles
in C material**

B/C material



Homogeneous
Toluene solution

Washing
then Drying



600 °C

Zr/B/C Material

Technical Accomplishments

Comparison of Metal Loading onto C and B/C Materials

Metal Containing Reagents	Activated C (200 mg, 600 m ² /g)	B/C Material (200 mg, 500 m ² /g)
	After metal loading (mg)	After metal loading (mg)
H ₂ PtCl ₆ ^a	230	234
Cp ₂ TiCl ₂ ^b	200	309
Cp* ₂ ZrCl ₂ ^b	205	222
[(<i>n</i> ⁵ -Cp*)SiMe ₂ (<i>n</i> ¹ -NCMe ₃)]TiCl ₂ ^b	203	272



a. Loading in surfactant/water emulsion

b. Loading in toluene solvent (without surfactant)


Substitutional B in C structure enhances metal intercalation

Technical Accomplishments

High resolution TEM Image of Zr/B/C Material

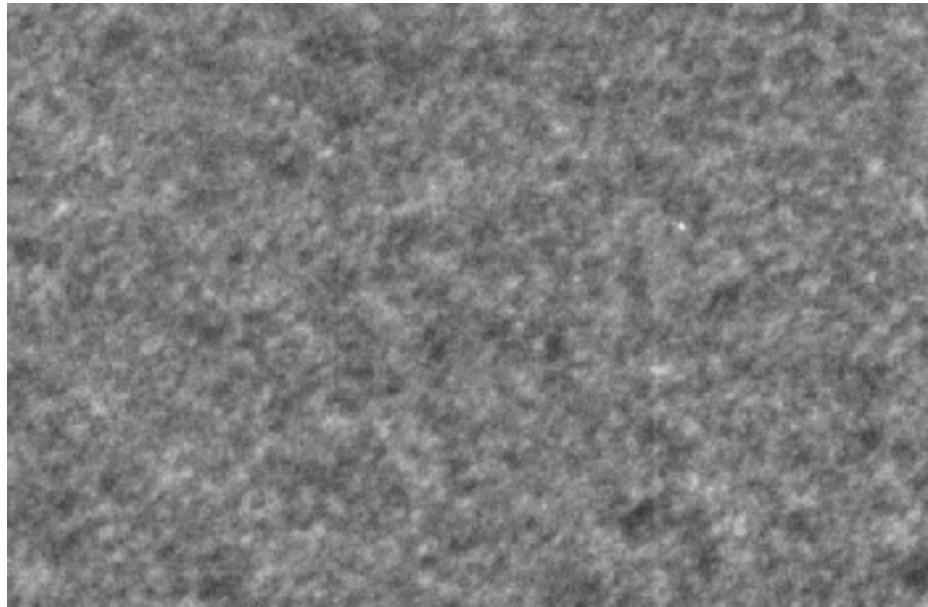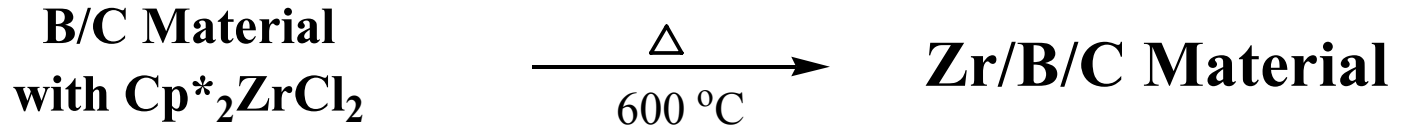

Wave-like B/C structure

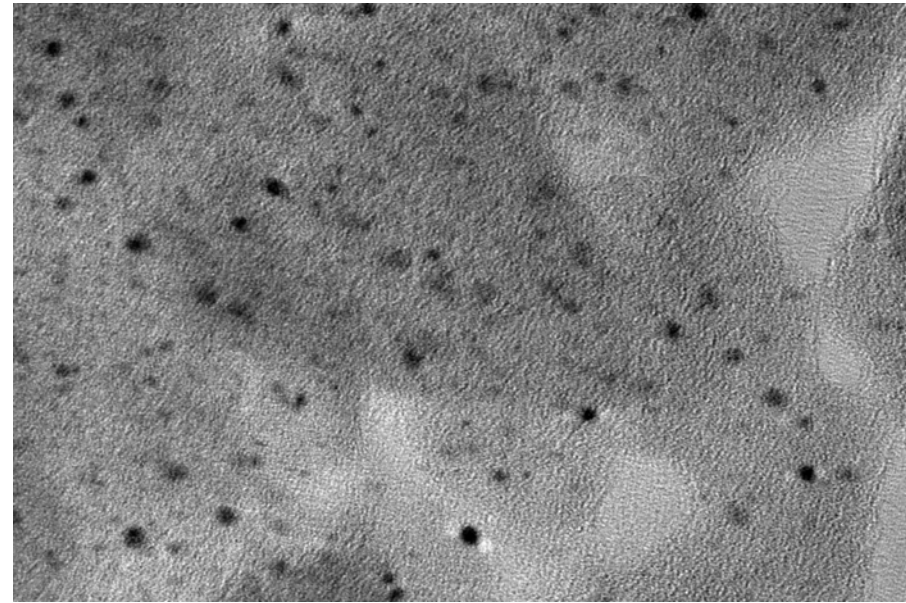


Uniform Zr particles (size < 2nm)

**Intercalating uniform metal nanoparticles
without surfactant**

Technical Accomplishments

H₂ adsorption at 77K

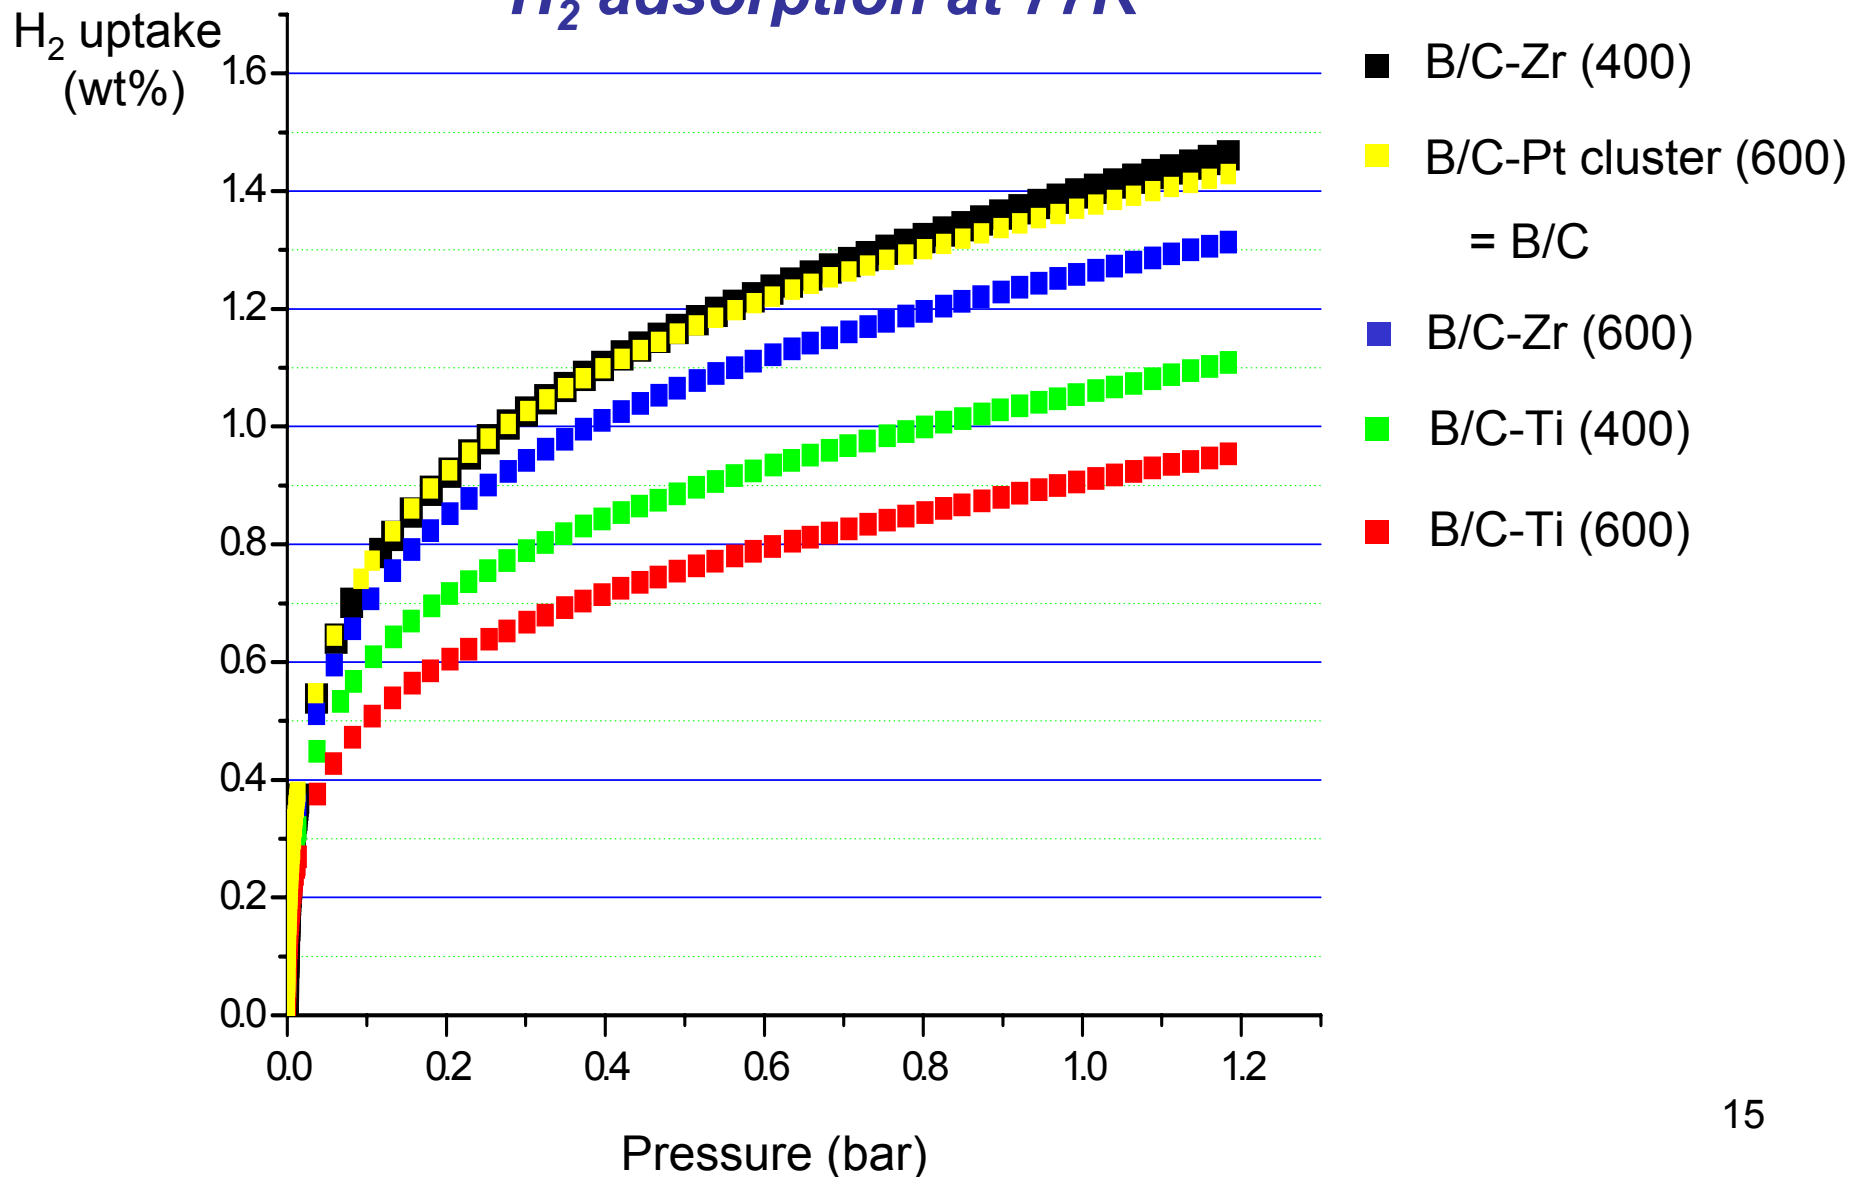

Summary

- **Micro-porous B/C Materials (B ~8%, SSA ~800 m²/g)** has been prepared by B-precursor and pyrolysis
- **B/C Structure Changes with Pyrolysis Temp**
B moiety gradually immerses in graphitic structure
- **B/C Shows H₂ Binding Energy (~12 KJ/mol) and Double Adsorption Capacity (vs. C)**
- **New M/B/C Materials Have Been Prepared with Intercalated Nano-Metal Particles**

Future Work

Year 08

- **Increase Surface Area of B/C Materials**
H₂ adsorption could reach 6 wt% if B/C material would contain > 10% B and >2000 m²/g
- **Increase Binding Energy of M/B/C Materials**
H₂ adsorption at ambient temperature requires higher binding energy (15-30 KJ/mole)
Finding right M species
Well-dispersed metal atoms or neat atomic particles
- **Spill-over on M/B/C Materials**