



# A Synergistic Approach to the Development of New Hydrogen Storage Materials, Part I

Jean M. J. Fréchet, Martin Head-Gordon, Jeffrey R. Long,  
Thomas J. Richardson, and Samuel S. Mao

*Department of Chemistry, University of California, Berkeley and  
Division of Environmental Energy Technologies,  
Lawrence Berkeley National Laboratory*

May 22, 2009

Project ID # ST\_32\_Long

# Overview

## Timeline

- Project start: 12/1/04
- Project end: 11/30/09
- Percent complete: 70%

## Budget

- Total funding expected: \$2.9M
  - \$1.8M from DOE to UC Berkeley
  - \$600k from DOE to LBNL
  - \$500k in cost-sharing
- Funding FY08: \$600k
- Funding FY09: \$567k

## Barriers

- Identify new materials enabling a hydrogen storage system achieving:
  - 2 kWh/kg (6 wt %)
  - 1.5 kWh/L (0.045 kg/L)
  - 4 \$/kWh

## Partners

- ChevronTexaco
- General Motors Corporation
- Electric Power Research Institute

# Overall Program

Synthesis of porous polymers (Fréchet)

Synthesis of porous coordination solids (Long)

Calculations of H<sub>2</sub> binding energies (Head-Gordon)

Synthesis of destabilized hydrides (Richardson)

H<sub>2</sub> storage characterization instrumentation (Mao)

Metal/metal hydride nanocrystals (Alivisatos)

Synthesis of nanostructured boron nitrides (Zettl)



Theory for boron nitride materials (Cohen and Louie)

**Part I\***  
**(EERE)**


**Part II**  
**(BES)**

\*Note that the results presented here are solely from Part I, which is funded through EERE


# H<sub>2</sub> Adsorption in a Hypercrosslinked Polymer

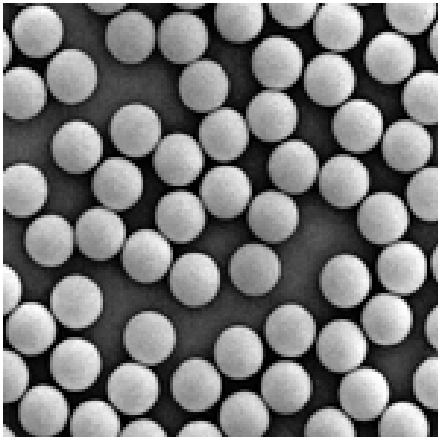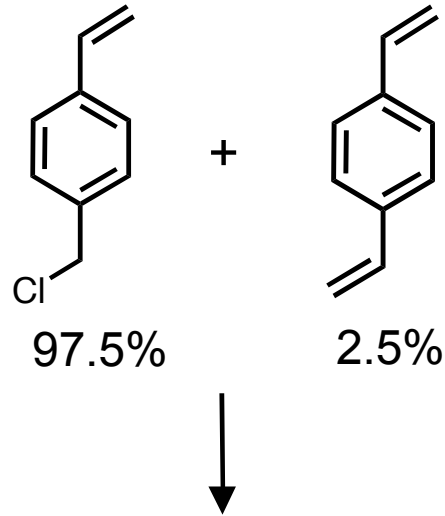

poly(chloromethylstyrene-co-divinylbenzene)

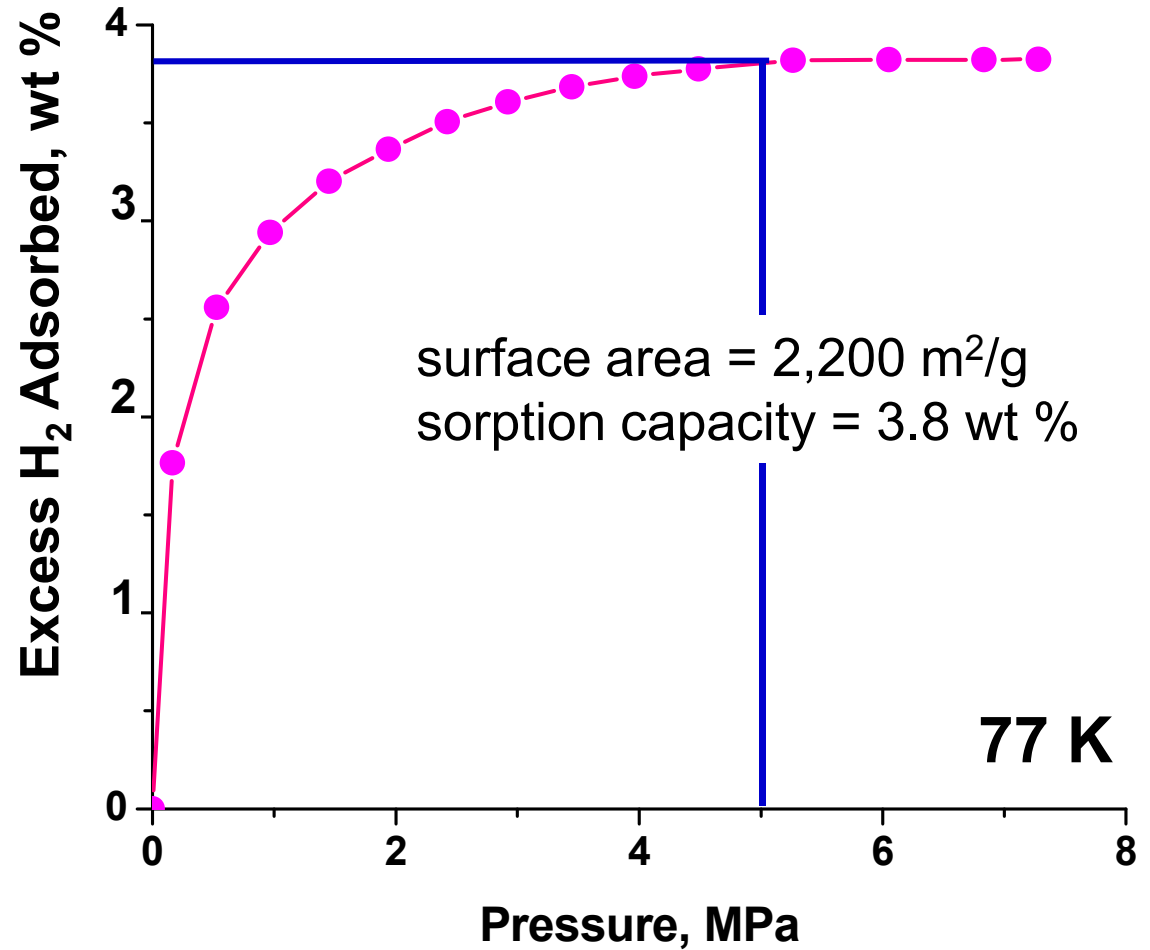


# Hypercrosslinked Polyaniline

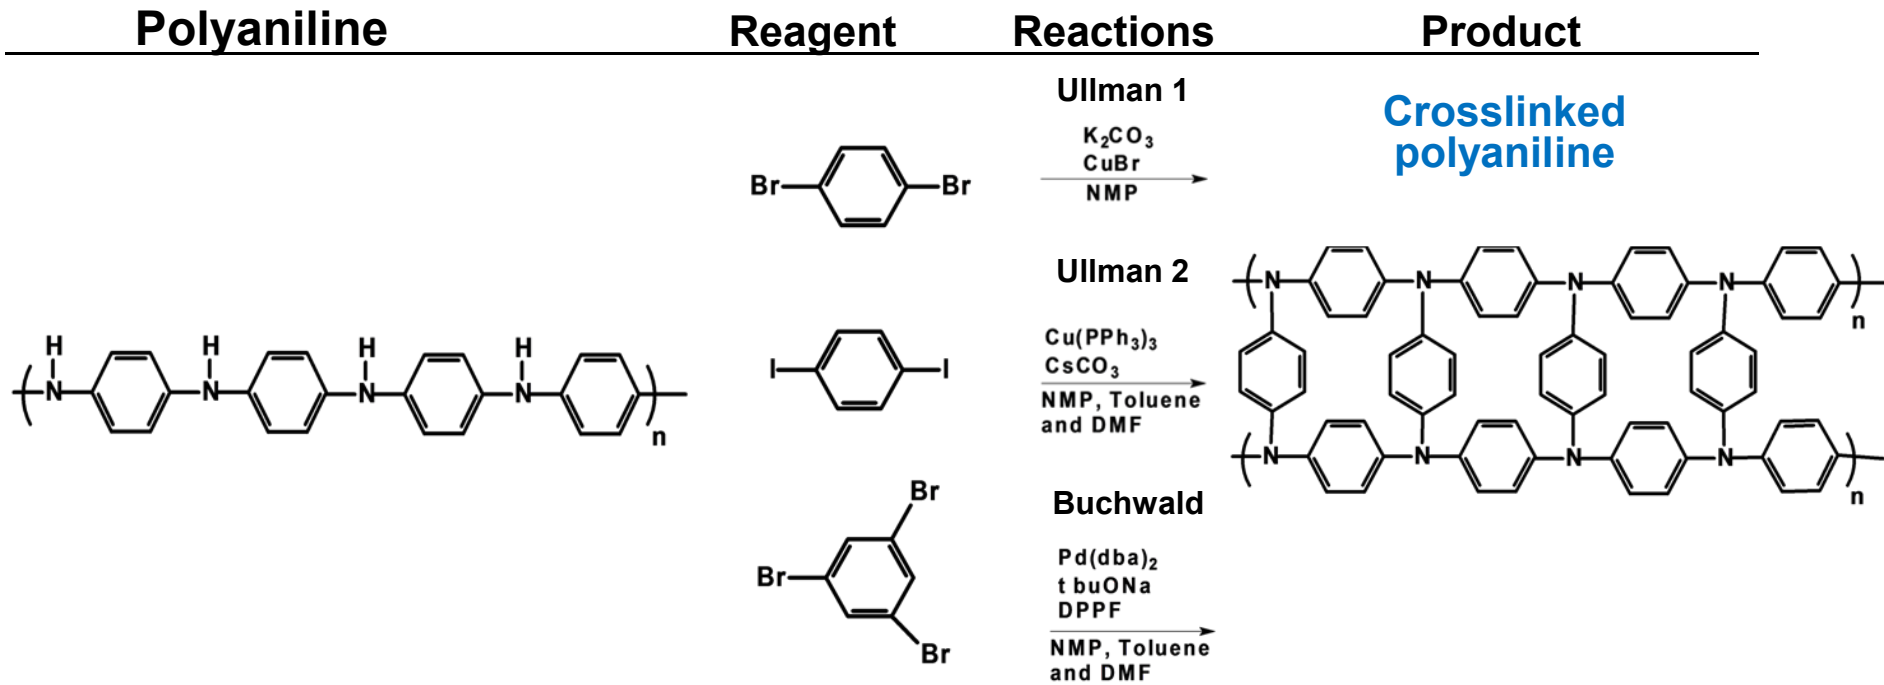


Reaction	Surf. area, m <sup>2</sup> /g Langmuir	Pore volume, mL/g	
		Total	Nano
Ullman 1 (dibromo)	156	0.13	0.03
Ullman 2 (diiodo)	96	0.04	0.01
Buchwald (diiodo)	343	0.25	0.13
Buchwald (tribromo)	368	0.25	0.11

# Size Exclusion of Gases in Ultrananopores

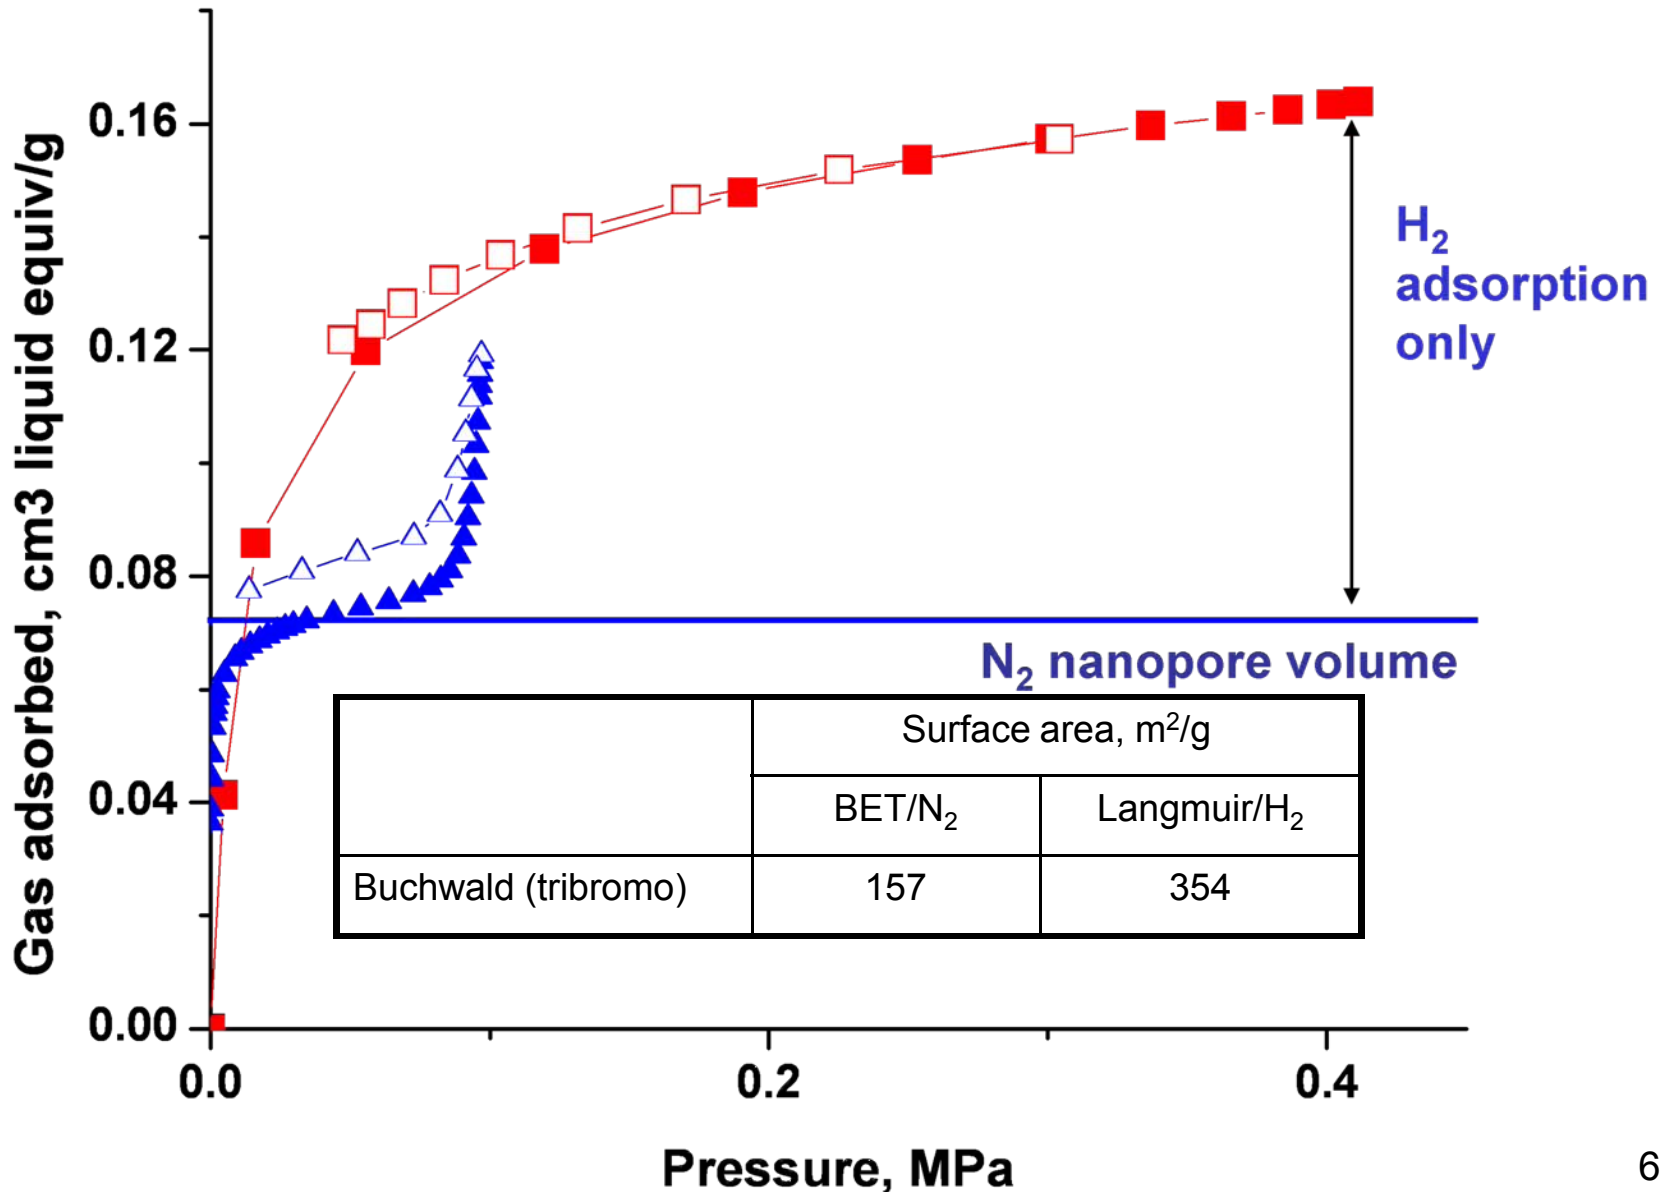


# Nanoporous Nitrogen-Containing Polymers

1,4-Diaminobenzene

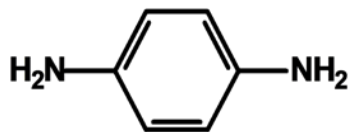

Reagent

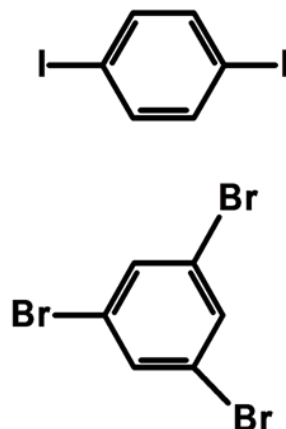


Reaction

Buchwald




Product

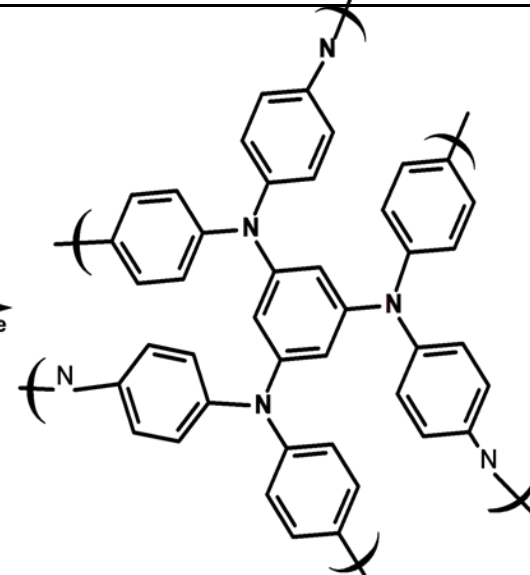

Crosslinked aromatic rings

Reagent	Surf. area, m <sup>2</sup> /g Langmuir	Pore volume, mL/g		
		Total	Nano	Ultra
Diiodobenzene	192	0.01	0.01	0.09
Tribromobenzene	384	0.13	0.11	0.06


# Stronger H<sub>2</sub> Adsorption

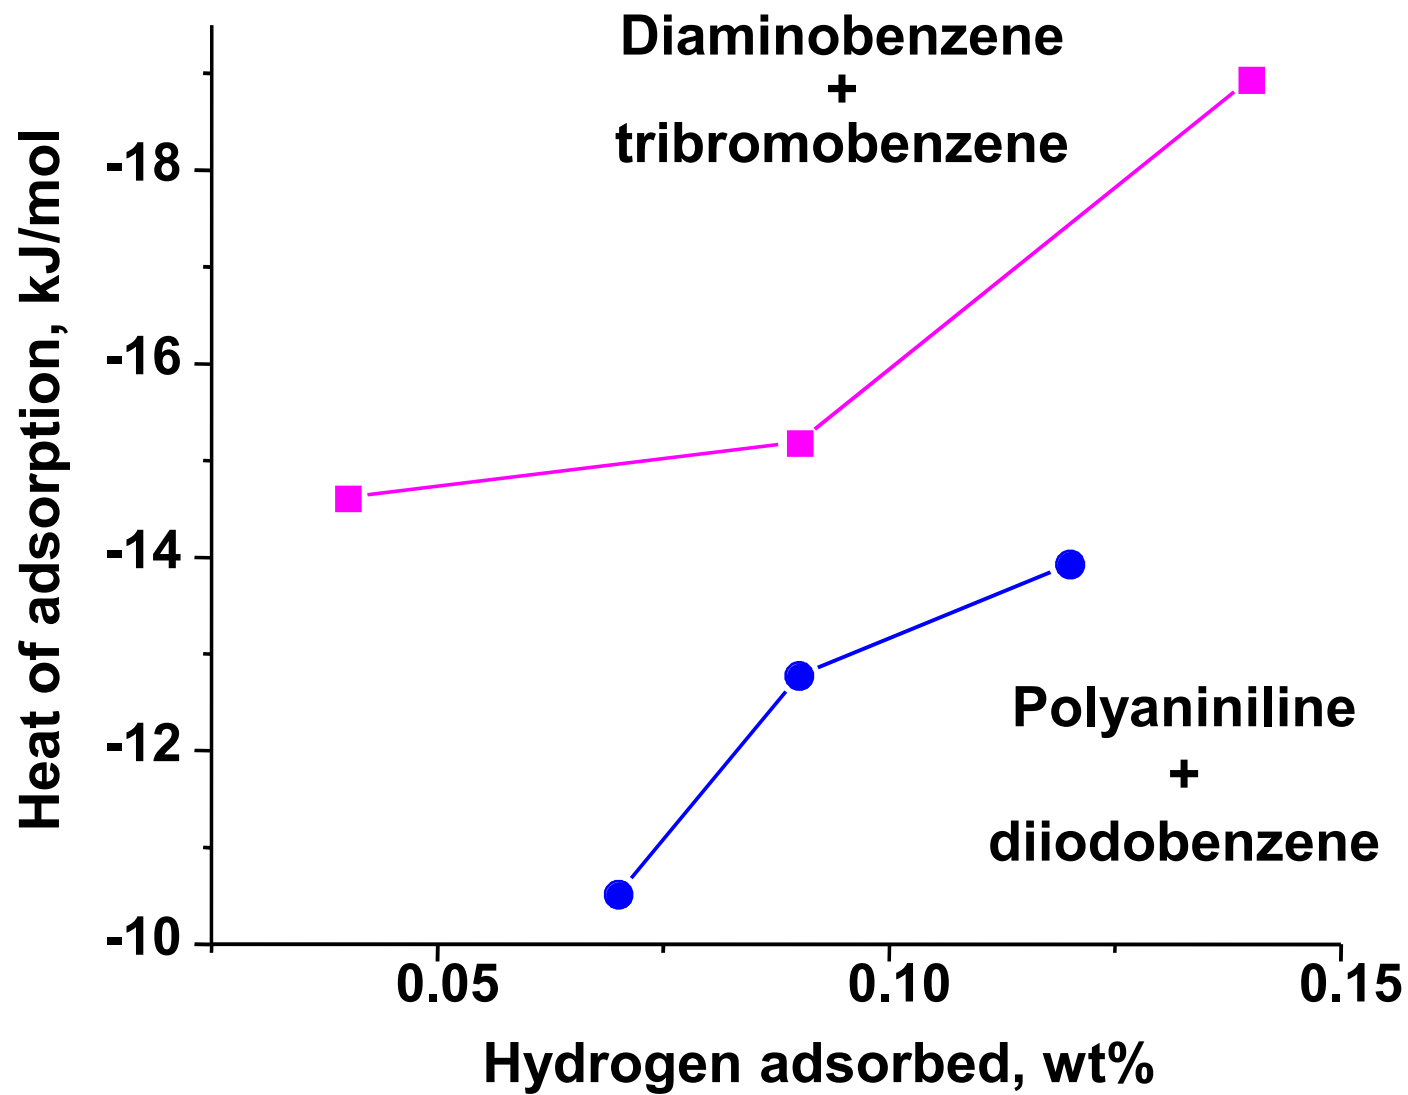




# Hypercrosslinked Polypyrrole




Crosslinking with alkyl groups:

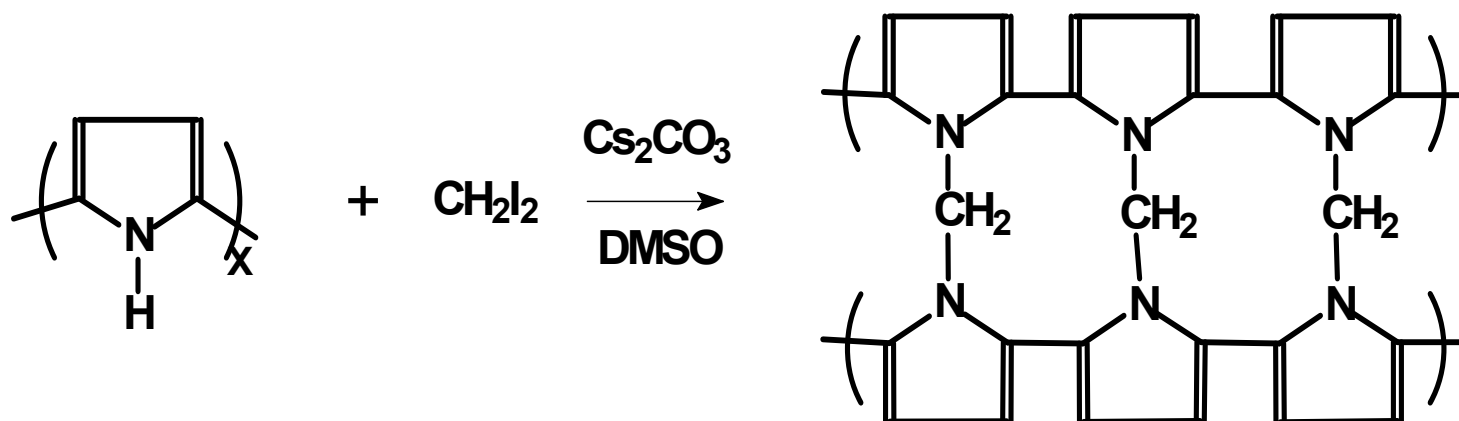

Crosslinking with boron:

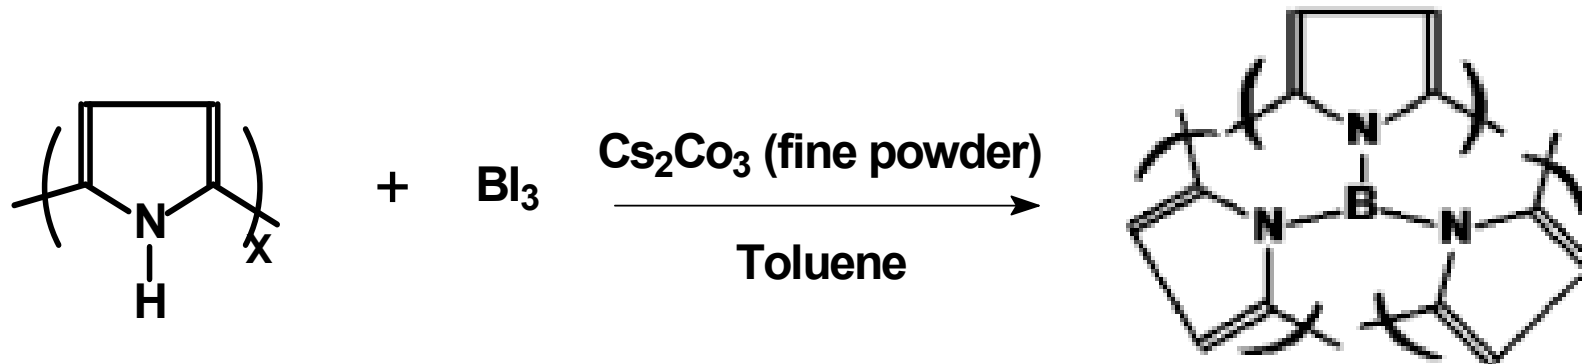


# Increased H<sub>2</sub> Adsorption Capacity

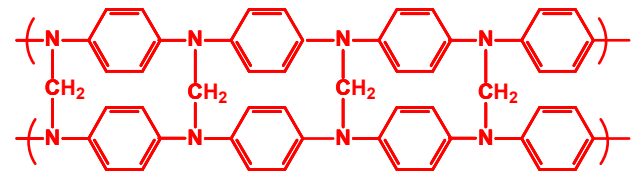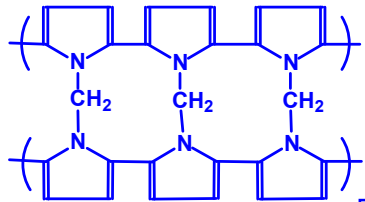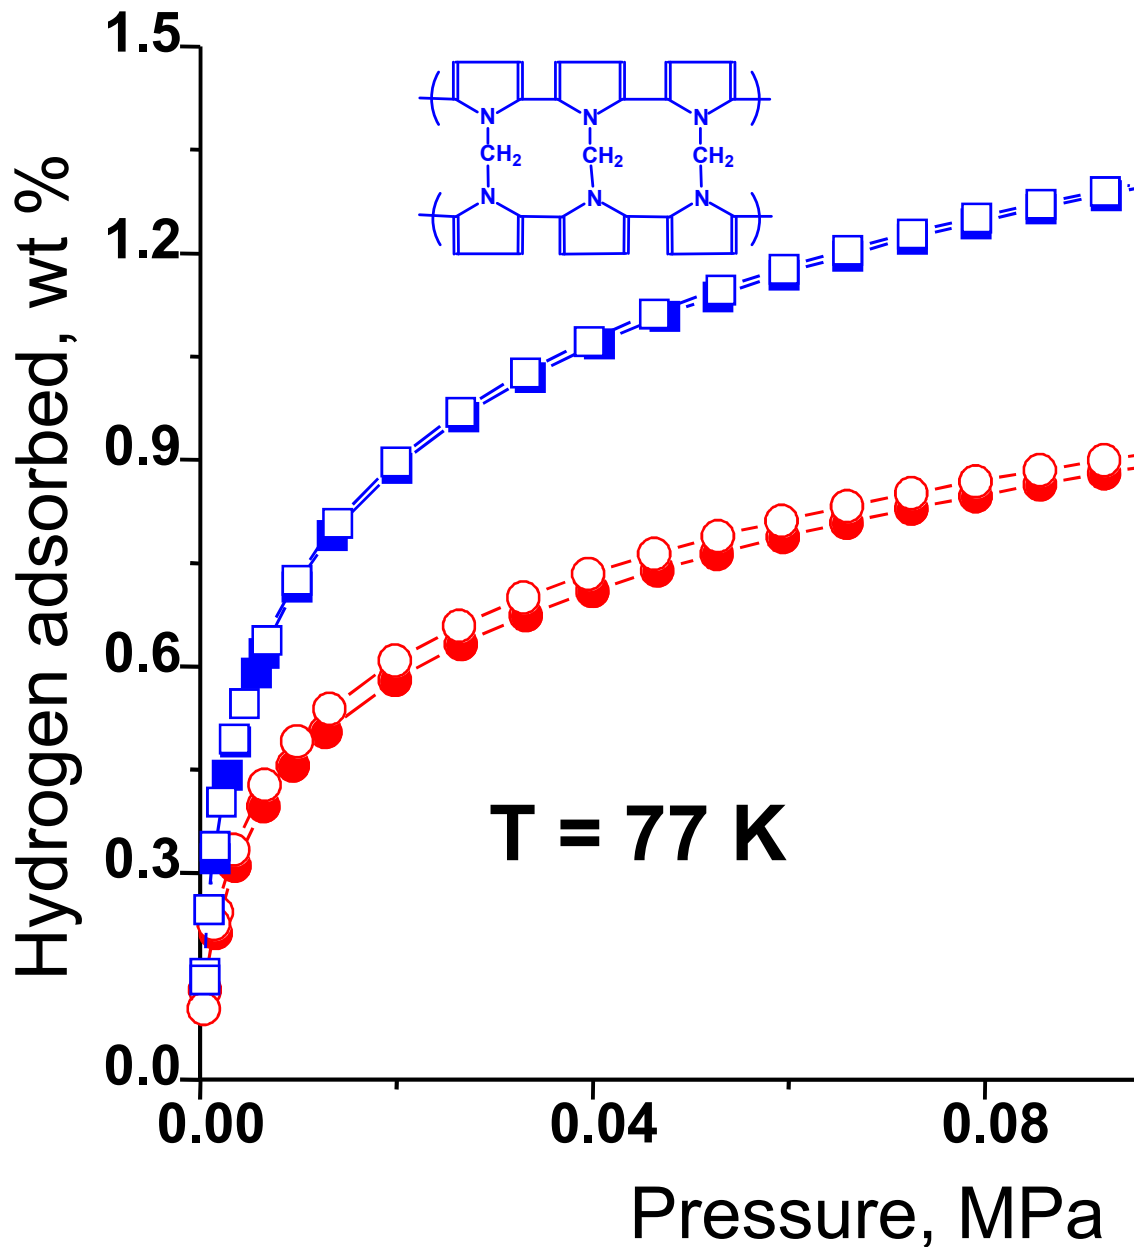




	Surface Area	
	BET/N <sub>2</sub>	Langmuir/H <sub>2</sub>
Ppy	738 m <sup>2</sup> /g	558 m <sup>2</sup> /g
Pani	630 m <sup>2</sup> /g	400 m <sup>2</sup> /g

# Size Exclusion of Gases in Ultrananopores



## No ultrananopores

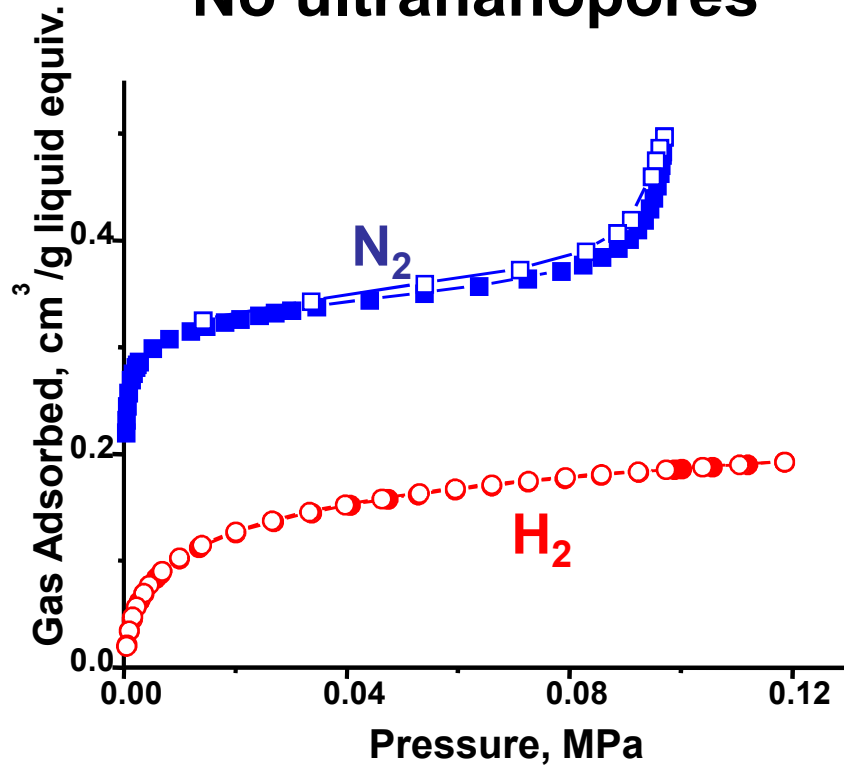

## Ultrananopores

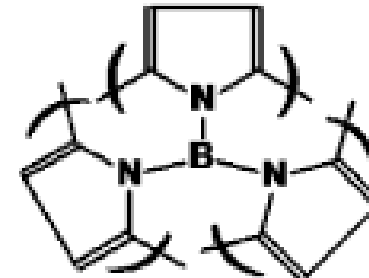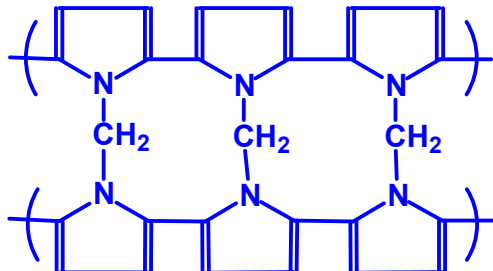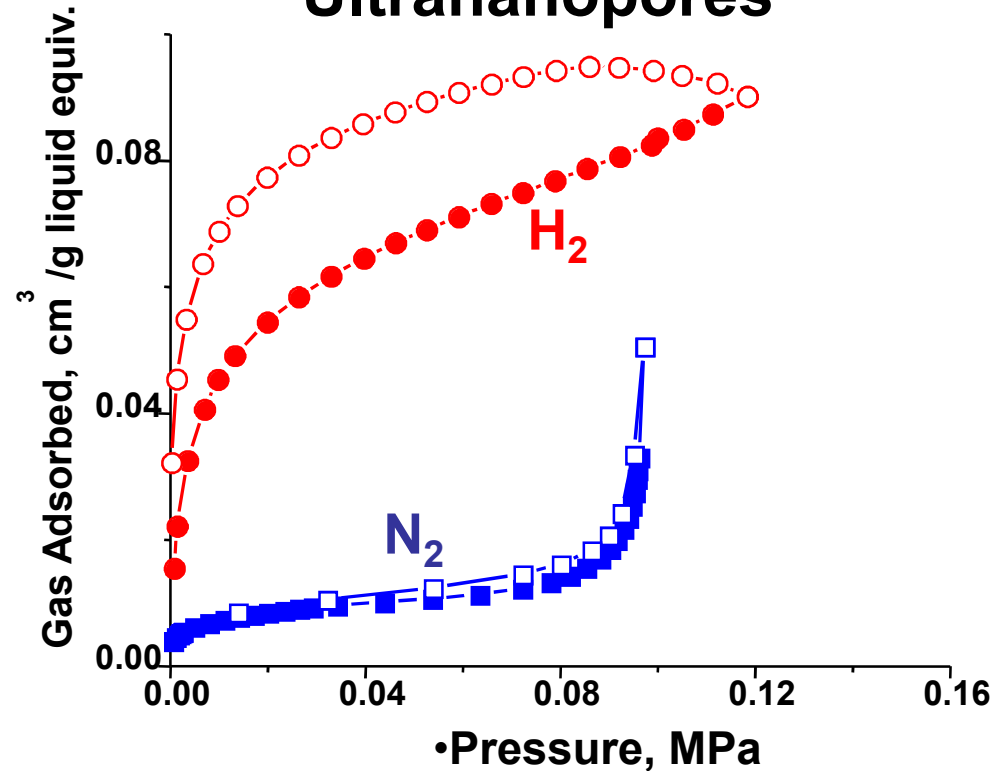


# Hydrogen Storage in Completely-Activated MOF-5

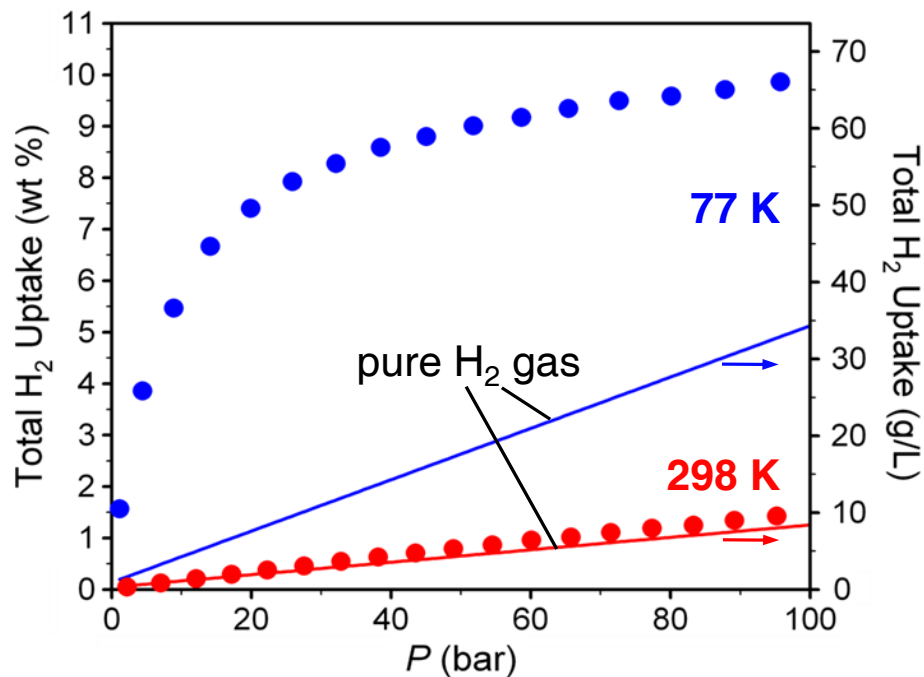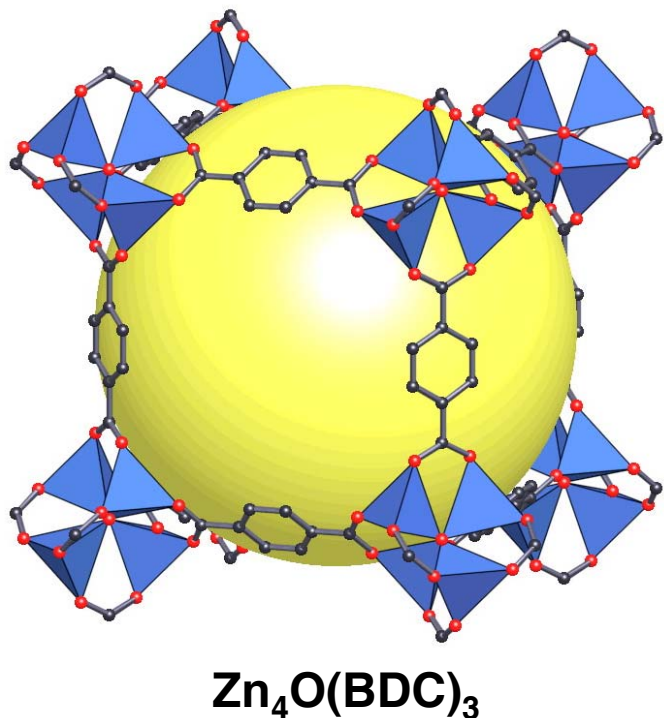



- Currently best known material for cryogenic hydrogen storage at 77 K
- Performance at 298 K is poor owing to weak interaction of H<sub>2</sub> with surface

# A Beryllium-Based Metal-Organic Framework

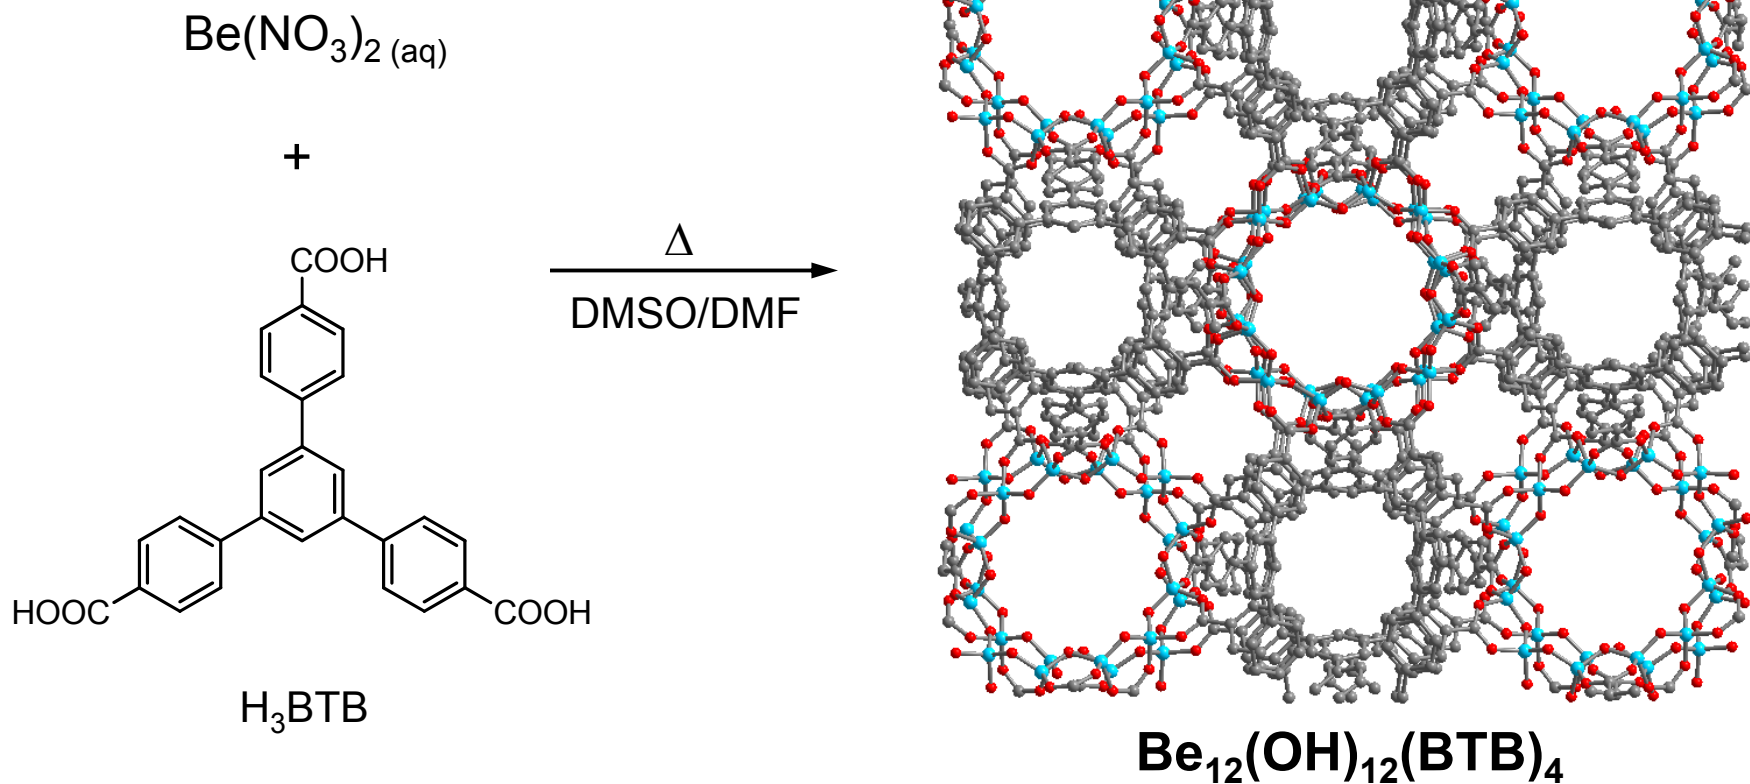


- Unprecedented structure with  $\text{Be}_{12}(\text{OH})_{12}$  rings and 12 and 15 Å channels
- Nitrogen adsorption isotherm affords BET surface area of 4020 m<sup>2</sup>/g

# Low-Pressure H<sub>2</sub> Uptake in Be<sub>12</sub>(OH)<sub>12</sub>(BTB)<sub>4</sub>

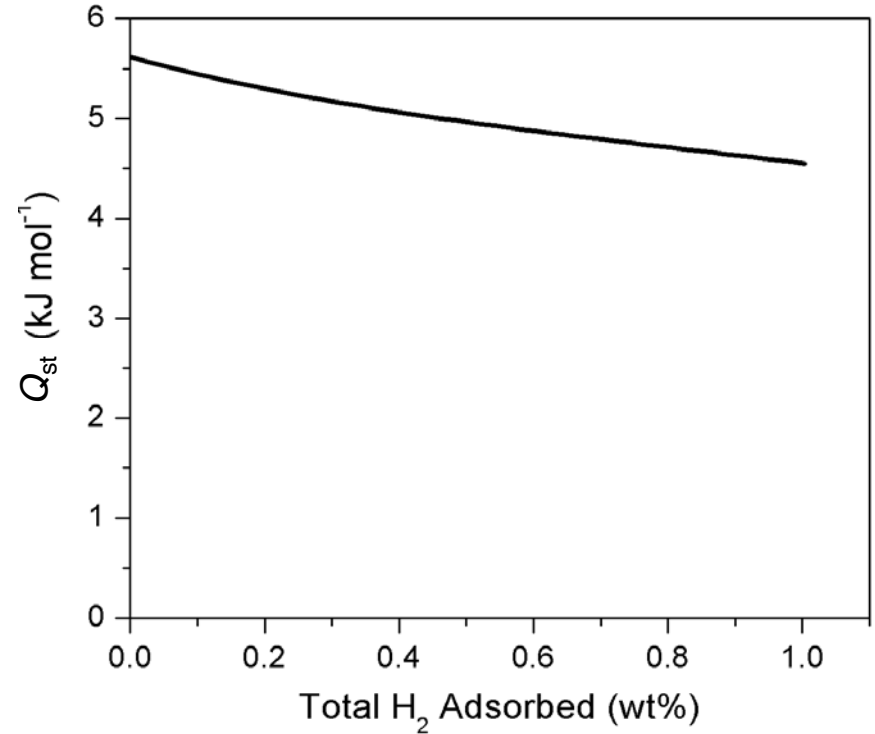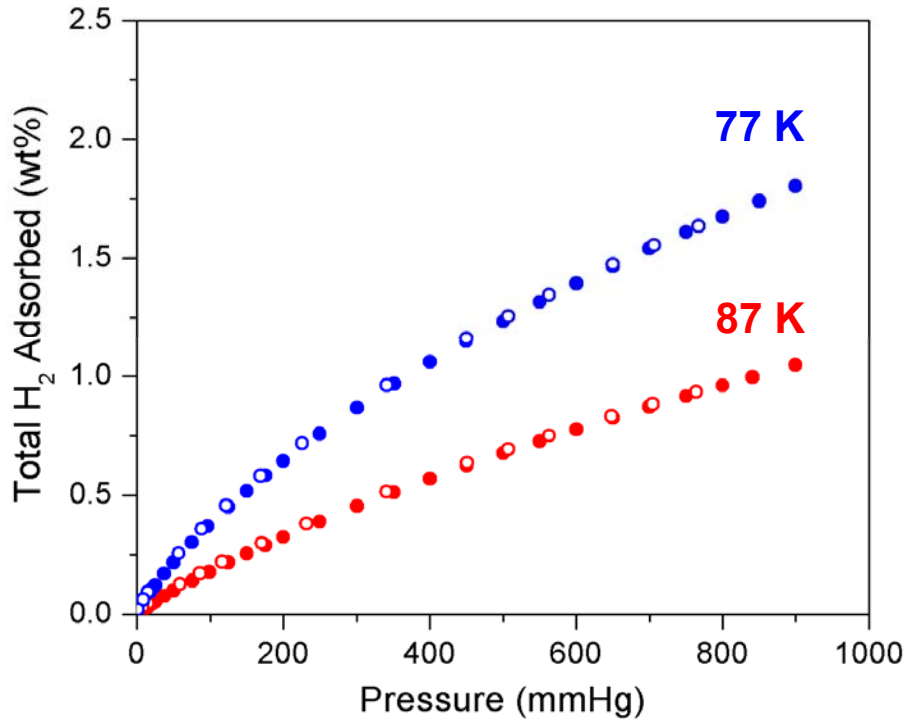



- Weak interaction of H<sub>2</sub> with surface, as desired for cryogenic storage
- At pressures up to 100 bar, expect gravimetric storage above MOF-5

# Strong H<sub>2</sub> Binding in MOF-5 Functionalized with Cr<sup>0</sup>

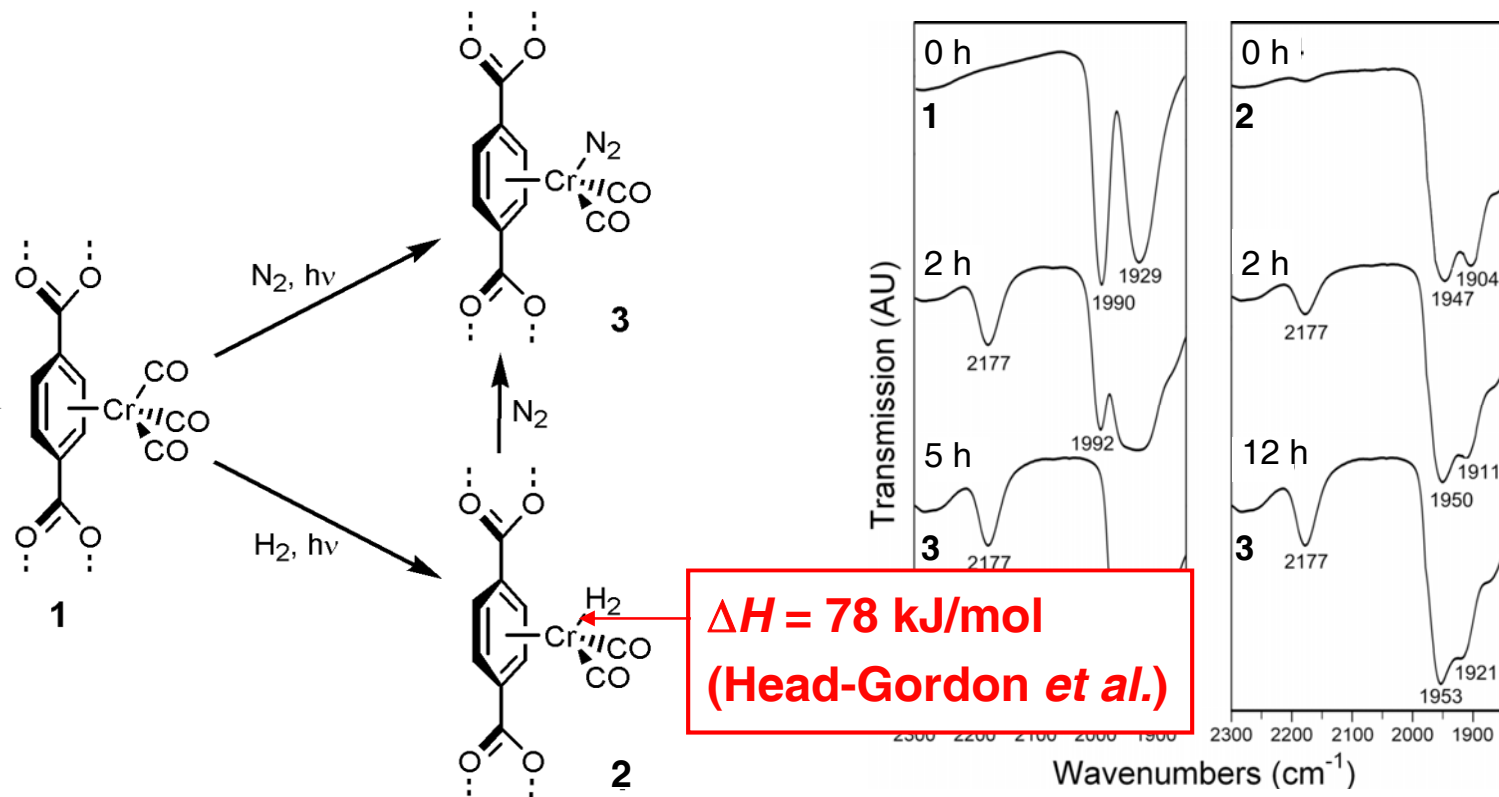

- Orbital interactions lead to strongly-bound H<sub>2</sub> complex that is too stable
- Need to generate charge-induced dipole interaction of 15-20 kJ/mol


# Room Temperature H<sub>2</sub> Uptake in Mn-BTT\*

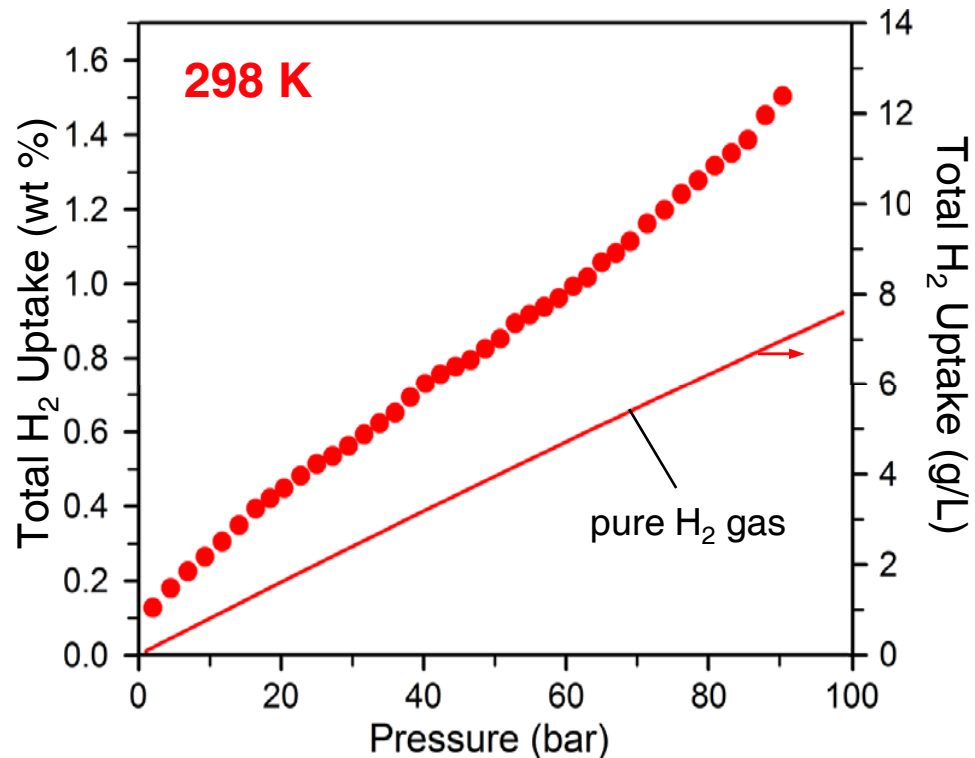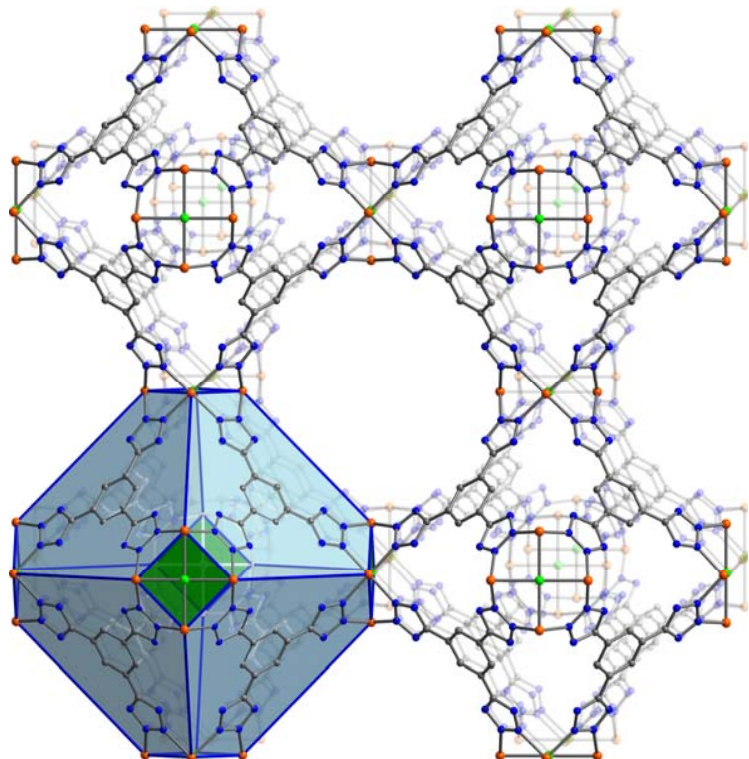

- Exposed Mn<sup>2+</sup> sites lead to isosteric heat of adsorption of up to 10.1 kJ/mol
- Need to increase strength of binding and concentration of open metal sites



# Paddlewheel Frameworks

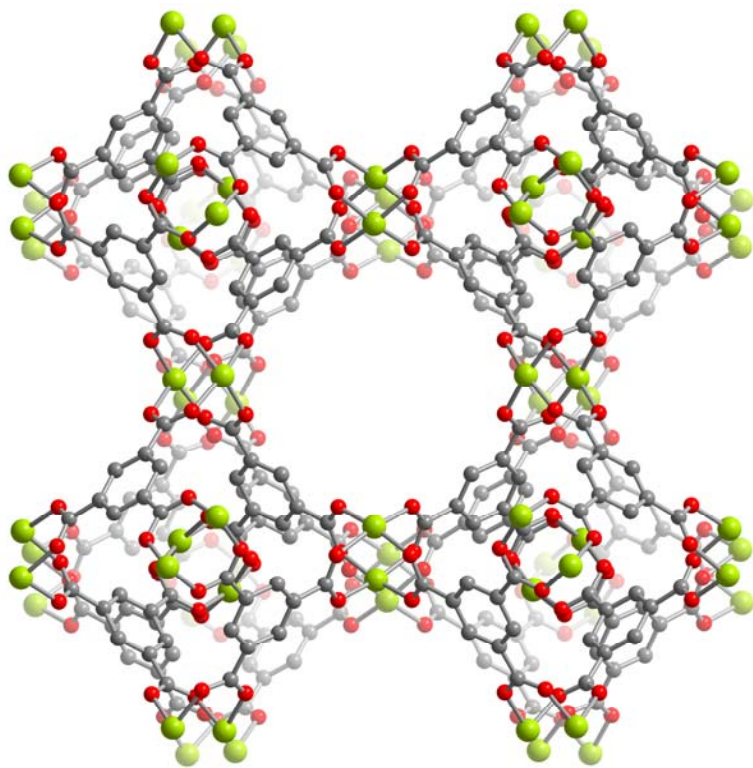

$M_3(\text{BTC})_2$  ( $M = \text{Cr, Cu, Zn, Mo}$ )



- Preparation of  $\text{Cr}_3(\text{BTC})_2$  is new and activation of  $\text{Mo}_3(\text{BTC})_2$  is improved
- Enables comparison of  $\text{H}_2$  binding at the open  $M^{\text{II}}$  coordination sites

	surface area ( $\text{m}^2/\text{g}$ )	
	BET	Langmuir
$\text{Cr}_3(\text{BTC})_2$	2340	2720
$\text{Cu}_3(\text{BTC})_2^a$	1944	2260
$\text{Zn}_3(\text{BTC})_2$	<i>collapsed</i>	
$\text{Mo}_3(\text{BTC})_2^b$	1280	2010
$\text{Mo}_3(\text{BTC})_2$	1800	2100

<sup>a</sup> *J. Am. Chem. Soc.* **2006**, 128, 3494


<sup>b</sup> *J. Mater. Chem.* **2006**, 16, 2245

# H<sub>2</sub> Uptake in M<sub>3</sub>(BTC)<sub>2</sub> (M = Cr, Mo)

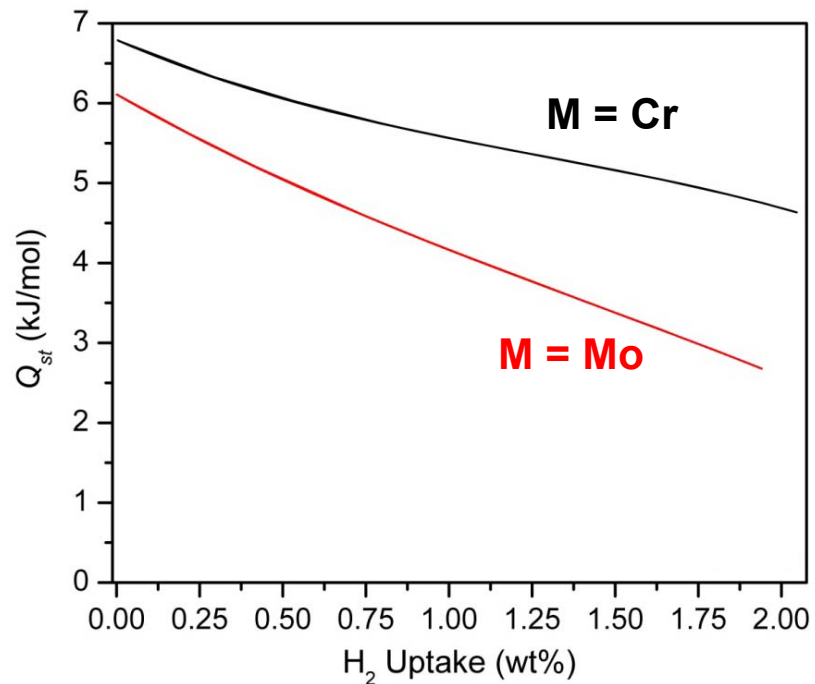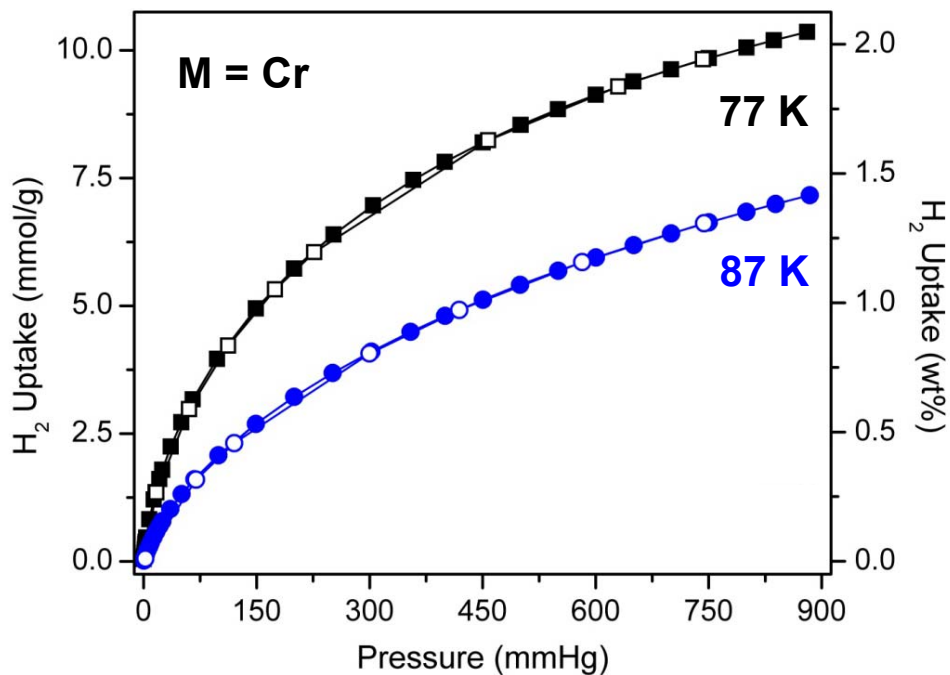


- First assessment of strength of H<sub>2</sub> binding to a Cr<sup>2+</sup> center
- Expect better results for Co<sup>2+</sup> and Ni<sup>2+</sup> owing to a smaller ionic radius
- Attempts to synthesize analogues with other metal ions are underway

# H<sub>2</sub> Uptake in Mg<sub>2</sub>(DOBDC)

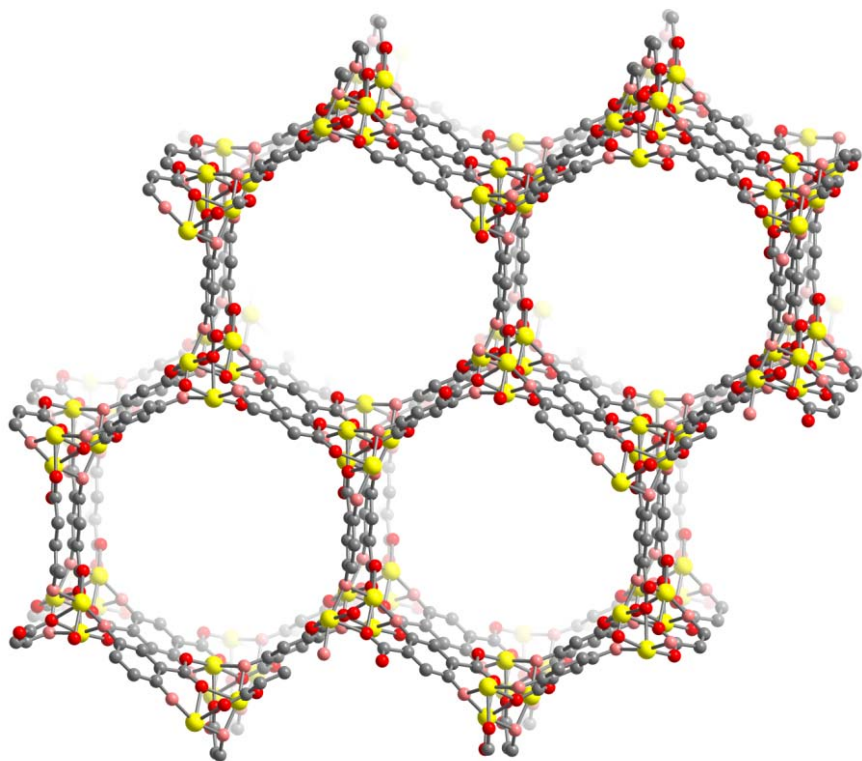

**Mg<sub>2</sub>(DOBDC)**



Matzger *et al.* *J. Am. Chem. Soc.* **2008**, *130*, 10870

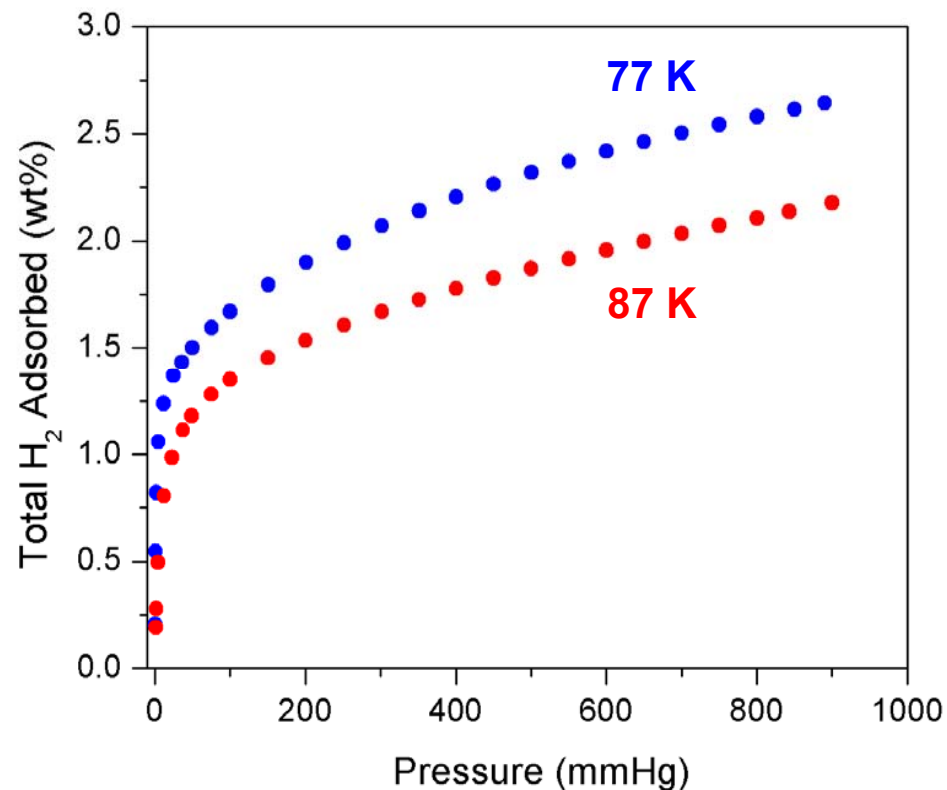


- Open Mg<sup>2+</sup> sites lead to an isosteric heat of adsorption as high as 12.8 kJ/mol
- Neutron diffraction (Craig Brown, NIST) shows Mg···D<sub>2</sub> distance of 2.5 Å

# Calculation of Substituent Effects

Metal chosen as Cr<sup>0</sup>

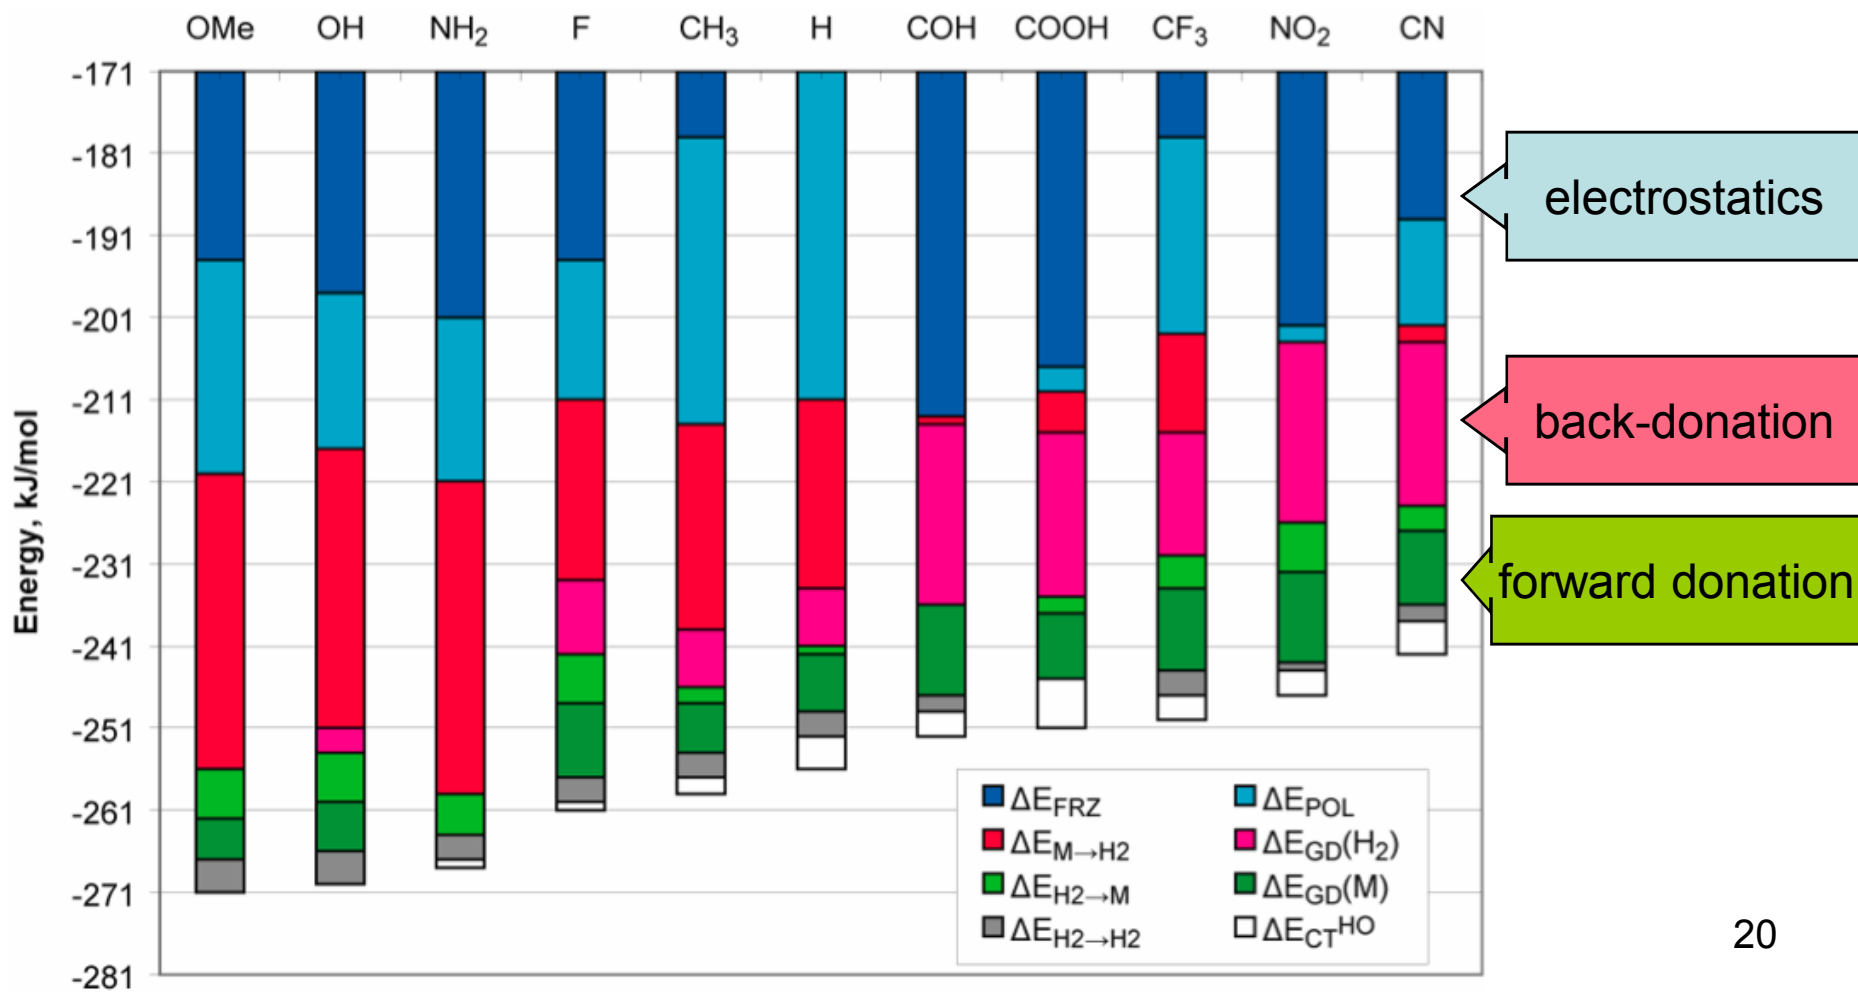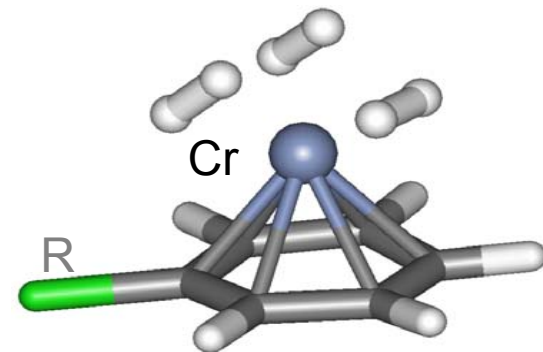


# Effect of Substituent (R)

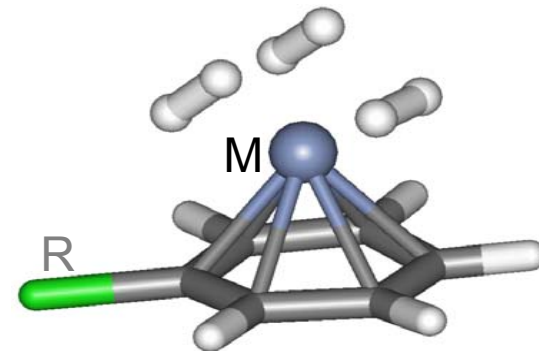

- Electron-donating groups enhance binding, while electron-withdrawing groups reduce binding
  - Tunability is 7% of binding
  - Energies are for three bound H<sub>2</sub> molecules
- Correlates with back-donation, electrostatics
- Quantitative information; qualitative insight
  - BDC<sup>2-</sup> substituents can fine-tune binding
  - Coarse-tuning must come from different metals

# Effect of Metal Substitution

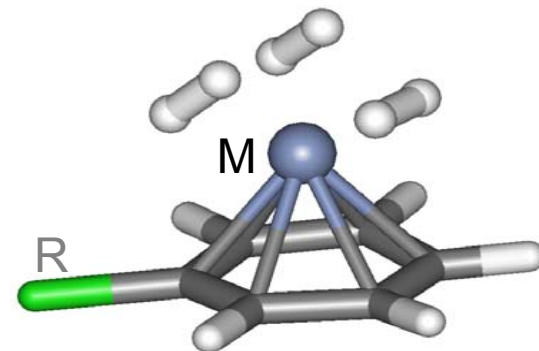

- Heavier isoelectronic elements:

$(C_6H_6)Cr(H_2)_3$       binding per  $H_2$  of 68 kJ/mol

$(C_6H_6)Mo(H_2)_3$       binding per  $H_2$  of 84 kJ/mol

- Lighter transition elements:


$(C_6H_6)Cr(H_2)_3$       binding per  $H_2$  of 68 kJ/mol

$(C_6H_6)Ti(H_2)_4$       binding per  $H_2$  of 32 kJ/mol

- Shows coarse tuning is possible

Still need to examine synergy of these effects

# Computational Study of H<sub>2</sub> Binding in Cu-BTT

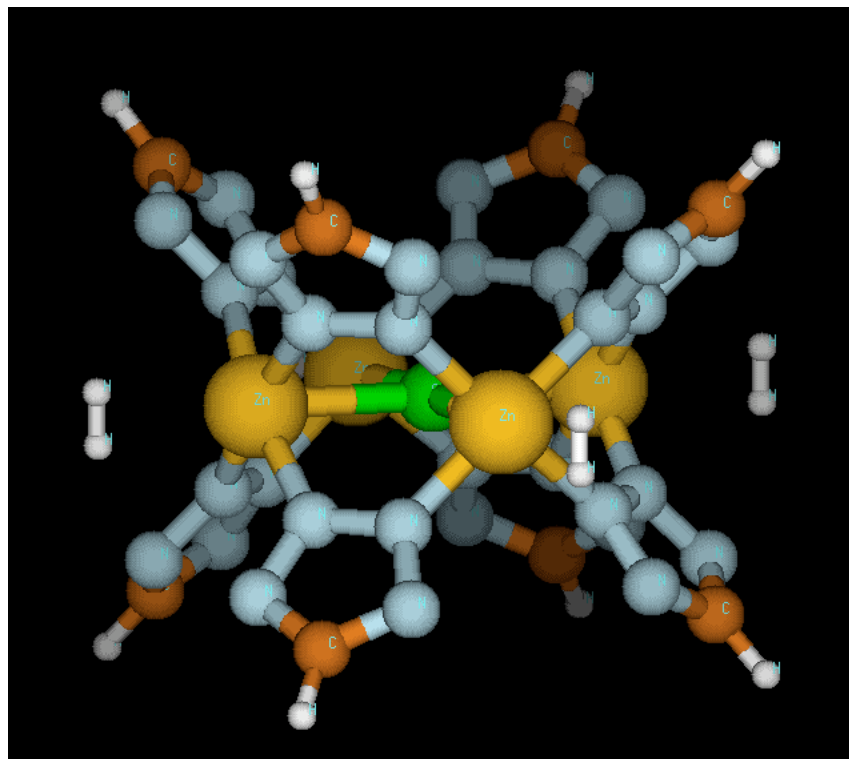


[Cu<sub>4</sub>X(N<sub>4</sub>CH)<sub>8</sub>]<sup>-</sup> fragment

$\omega$ B97X-D/6-31G\*  
calculations:

X	E/kJ/mol
F	-10.9
Cl	-10.9
Br	-13.0
I	--

- Measurements of H<sub>2</sub> binding energy within HCu[(Cu<sub>4</sub>Cl)<sub>3</sub>(BTT)<sub>8</sub>] underway
- We will attempt to synthesize HCu[(Cu<sub>4</sub>Br)<sub>3</sub>(BTT)<sub>8</sub>]

# Computational Study of H<sub>2</sub> Binding in “Zn-BTT”

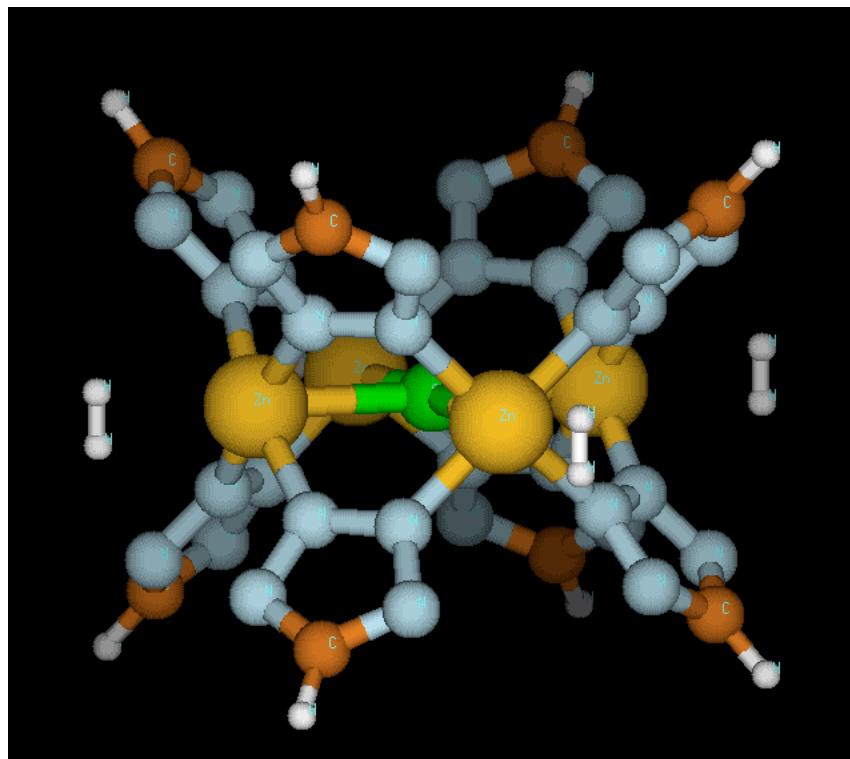

[Zn<sub>4</sub>X(N<sub>4</sub>CH)<sub>8</sub>]<sup>-</sup> fragment


$\omega$ B97X-D/6-31G\*  
calculations:

X	E <sub>Cu</sub> /kJ/mol	E <sub>Zn</sub> /kJ/mol
F	-10.9	-13.8
Cl	-10.9	-15.9
Br	-13.0	-16.3
I	--	--

- Suggests significant improvement in binding energy for Zn-BTT frameworks
- We will therefore attempt to synthesize Zn<sub>3</sub>[(Zn<sub>4</sub>Cl)<sub>3</sub>(BTT)<sub>8</sub>]<sub>2</sub>




# Destabilization of Metal Hydrides

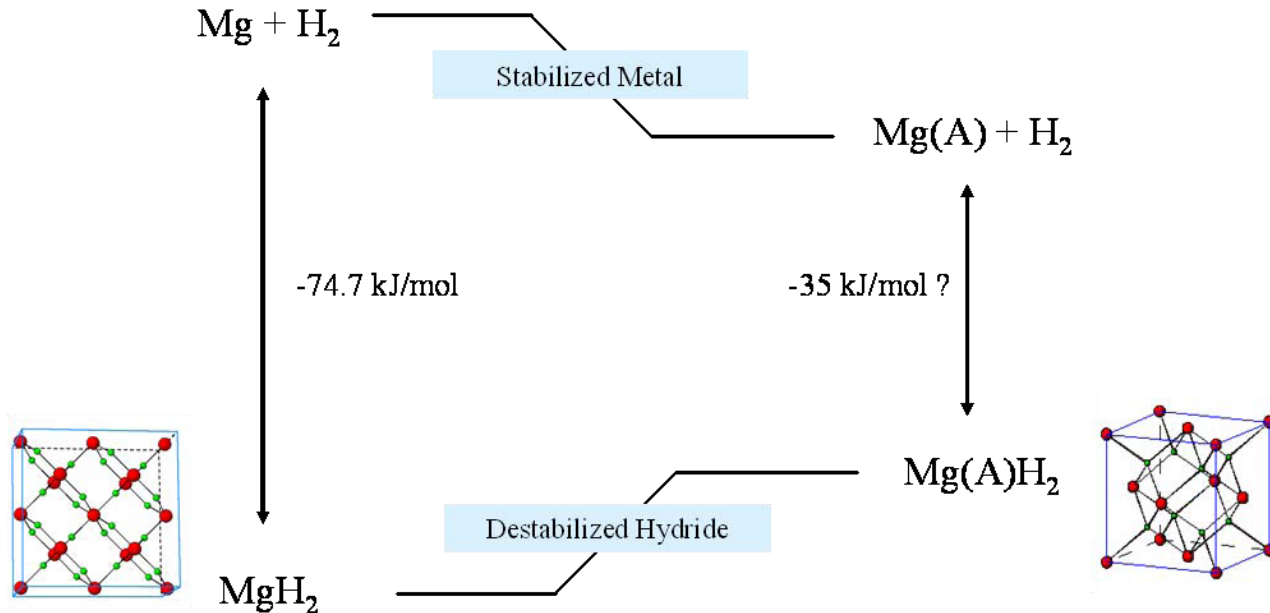


- Attempts at alloying of Mg in order to reduce  $\Delta H$
- Success in partial substitution to form  $\text{Mg}_{1-x}\text{A}_x$  ( $\text{A} = \text{Mn, Fe, Ni}$ )
- Some increases in plateau pressures, but poor kinetics
- Attempts to substitute Na and Li for Mg are underway

# Addition of $\text{MgF}_2$ Enhances Utilization of $\text{MgH}_2$

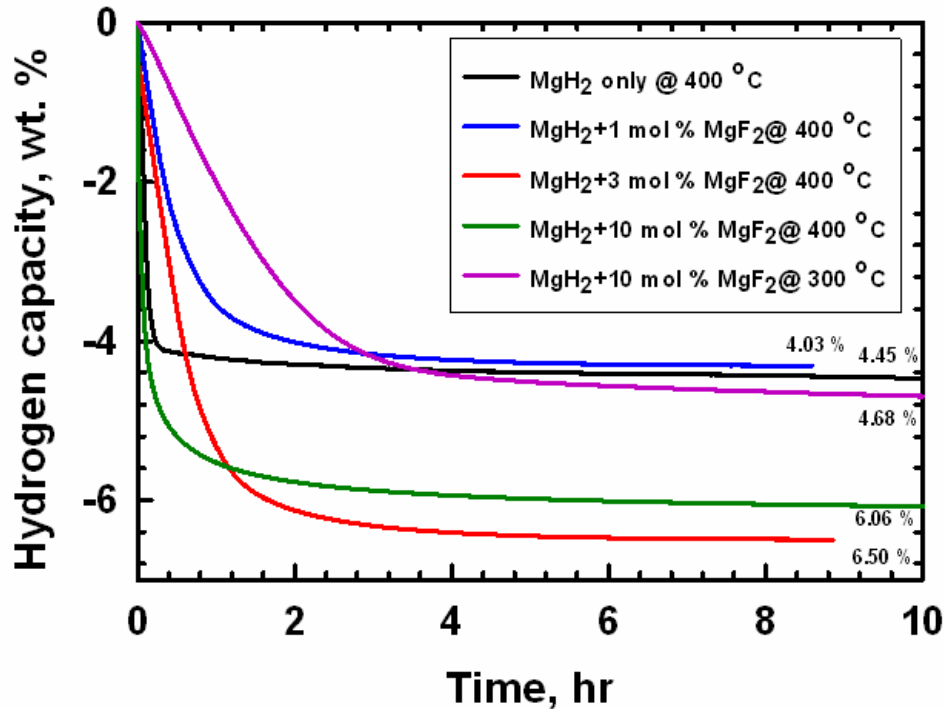


## Elemental Mapping (EELS)

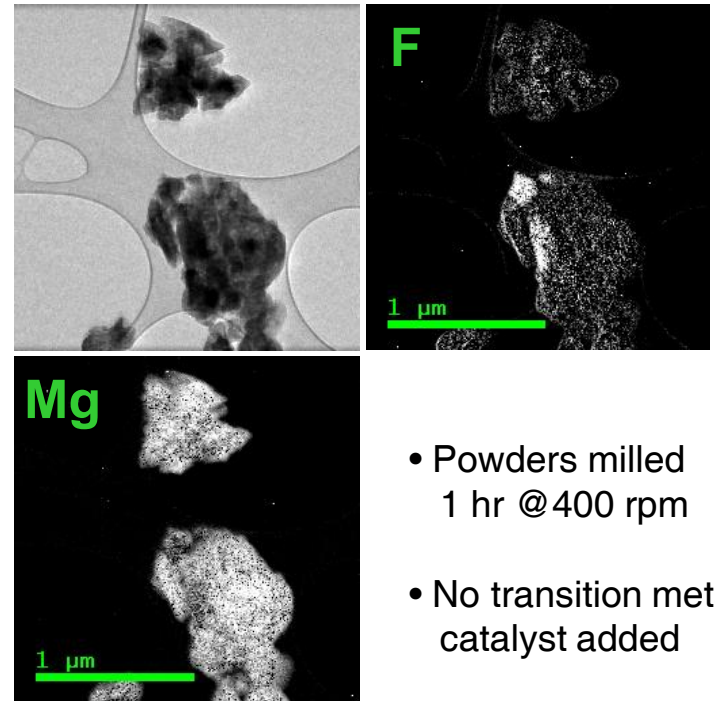


- Powders milled 1 hr @ 400 rpm
- No transition metal catalyst added

- $\text{MgF}_2$  slows desorption, but increases amount desorbed despite added weight
- Fluoride is distributed over particle surface; no evidence for bulk substitution (XRD)

# Fluoride Effect Persists through Repeated Cycling

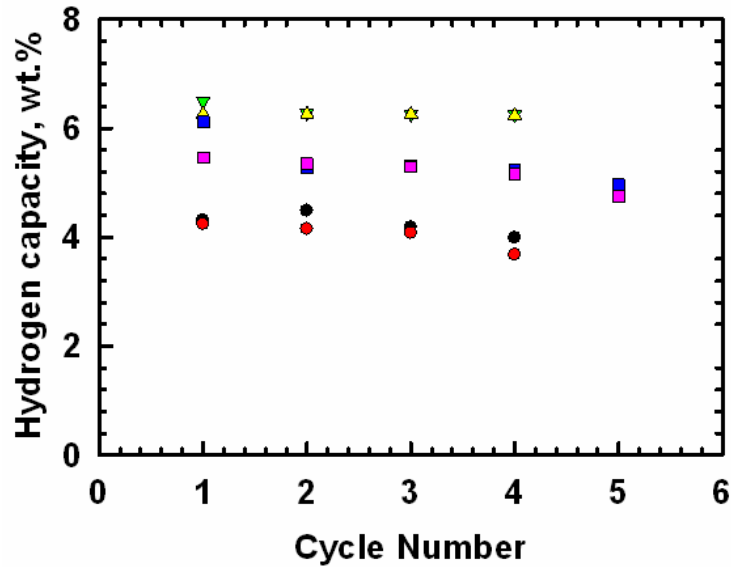


- 1 mol % MgF<sub>2</sub> desorption @ 400 °C, 0 bar
- 1 mol % MgF<sub>2</sub> absorption @ 300 °C, 45 bar
- ▼ 3 mol % MgF<sub>2</sub> desorption @ 400 °C, 0 bar
- ▲ 3 mol % MgF<sub>2</sub> absorption @ 300 °C, 45 bar
- 10 mol % MgF<sub>2</sub> desorption @ 400 °C, 0 bar
- 10 mol % MgF<sub>2</sub> absorption @ 300 °C, 45 bar

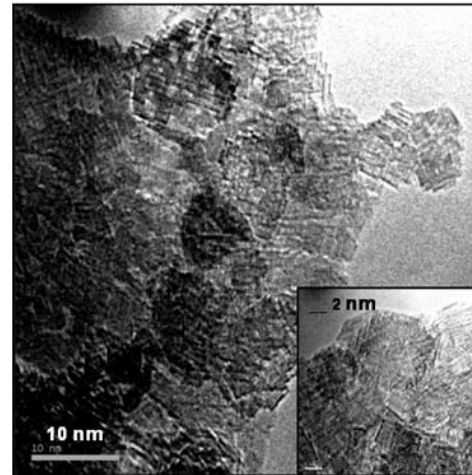

MgH<sub>2</sub> + 3 mol% MgF<sub>2</sub> after 2nd desorption @ 300° C

High-resolution TEM shows sharp faceting and marked inhibition of Mg grain growth in fluoride-containing samples.


Without fluoride, sintering and coarsening reduce surface area and contribute to Mg isolation

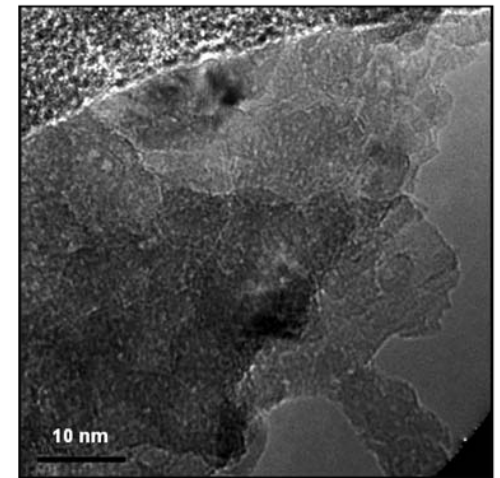

MgH<sub>2</sub> after 2nd desorption @ 300° C

- Best results are for 3 mol% MgF<sub>2</sub> added

# Metal Catalyst Activity not Inhibited by Fluoride

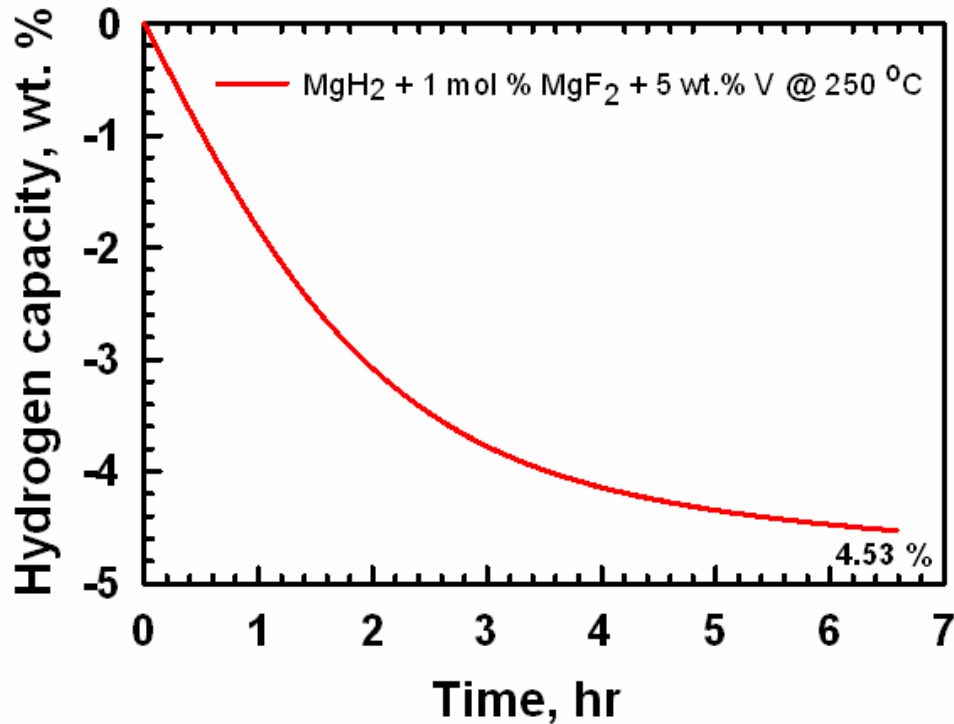

Activity of added vanadium not inhibited by the presence of fluoride

Good utilization at 250 °C

Still below 1 wt % at 200 °C

5wt.% V+ MgH<sub>2</sub> milled for 2hrs(300 rpm)  
1 mol % MgF<sub>2</sub> added (600 rpm for 1hr )

- Future work: higher energy milling and alternative fluoride sources
- In addition, the effect of fluoride addition on ternary hydrides will be studied