

Investigation of reaction networks and active sites in bio-ethanol steam reforming over Co-based catalysts

Acknowledgement
US DOE

Umit S. Ozkan* (P.I.)
I. Ilgaz Soykal
Hua Song
Xiaoguang Bao
Burcu Mirkelamoglu

Heterogeneous Catalysis Research Group
Department of Chemical and Biomolecular Engineering
The Ohio State University
Columbus, OH 43210

<http://www.che.eng.ohio-state.edu/people/ozkan.html>



*Ozkan.1@osu.edu

Project ID#: DE-FC36-05GO15033

June 8, 2010

PD001

Timeline

- ❖ Start Date - May 1, 2005
- ❖ End Date - April 31, 2010
(no-cost extension requested)
- ❖ 90% Complete

Budget

- ❖ Total project funding
 - \$1,145,625 (DOE)
 - \$299,715 (OSU cost share)
- ❖ Funding received in FY05
 - \$100,000(DOE)
 - \$10,458 (OSU Cost share)
- ❖ Funding received in FY06
 - \$185,000 (DOE)
 - \$147,987 (OSU cost share)
- ❖ Funding received in FY07
 - \$290,473 (DOE)
 - \$67,316 (OSU)
- ❖ Funding received in FY08
 - \$140,703 (DOE)
 - \$9,780 (OSU)
- ❖ Funding received in FY09
 - \$429,449 (DOE)
 - \$54,163 (OSU)
- ❖ Funding received in FY10
 - No funding

Overview

Barriers

- ❖ A. Fuel Processor Capital Costs
- ❖ C. Operation and Maintenance
- ❖ D. Feedstock Issues

Partners

- ❖ Argonne National Laboratory
 - Advanced Photon Source
Synchrotron techniques
- ❖ Chemistry Dept. at OSU (Prof. Hadad)
 - Molecular simulation
- ❖ NexTech Materials, Ltd.
 - Catalyst manufacturing scale-up
- ❖ Directed Technologies Inc.
 - Economic analysis and feasibility considerations
- ❖ PNNL
 - Sharing findings



Relevance

Project overview

- ❖ Catalytic H₂ production from bioethanol
 - Renewable sources;
 - Plant matter (natural CO₂ recycling);
 - Lends itself well to distributed H₂ production strategy;
- ❖ Non-precious metal catalysts, low-temperature operation
- ❖ A university program addressing many fundamental questions such as:
 - Catalytic active sites;
 - Reaction networks and mechanisms;
 - Surface species and intermediates;
 - Deactivation mechanisms;
 - Regeneration mechanisms.

Objectives-Relevance

- ❖ To acquire a fundamental understanding of the reaction networks and active sites in bioethanol steam reforming over Co-based catalysts that would lead to
 - Development of a precious metal-free catalytic system which would enable
 - ❑ Low operation temperature (350-550°C)
 - ❑ High EtOH conversion
 - ❑ High selectivity and yield of hydrogen
 - ❑ High catalyst stability
 - ❑ Minimal byproducts such as acetaldehyde, methane, ethylene, and acetone
 - ❑ Ease of operation
 - Addressing the barriers
 - ❑ Fuel Processor Capital Costs
 - ❑ Operation and Maintenance
 - ❑ Feedstock Issues


Approach

Milestones and Progress

	Tasks	Progress	% comp
1	Setting up the experimental systems, establishing protocols, training	Built, installed a reactor system and established experimental protocols; Completed a HAZOP review for the ethanol reforming reactor system; Went through a safety inspection conducted by a DOE Safety Panel.	100%
2	Economic analysis	Completed an initial economic analysis based upon a 1,500 kg/day of hydrogen process using H2A model.	95%
3	Catalyst synthesis and optimization	Prepared over 100 batches of catalysts; Investigated the effect of support, promoters, precursors, active metal loading, synthesis techniques and parameters on catalytic performance.	95%
4	In-situ, pre- and post-reaction characterization	Completed characterization studies using CO, N ₂ O and H ₂ chemisorption, X-ray diffraction, temperature programmed reduction, oxidation, desorption, and thermogravimetric analysis, differential scanning calorimetry. Combined characterization studies (XPS, DRIFTS, LRS, TGA) with mechanistic investigations to understand the pre- and post-reaction nature of the catalyst, reaction mechanisms and deactivation characteristics; XANES and EXAFS studies using the Synchrotron Facilities at Argonne National Laboratories Advanced Photon Source.	90%
5	Activity tests, kinetic studies, deactivation, regeneration studies	Established correlations between synthesis parameters, structure and activity; Evaluated synthesized catalysts for ethanol steam reforming in the temperature range 200-500°C and gas hourly space velocities from 5,000-300,000h ⁻¹ ; Conducted transient and steady-state experiments to understand the reaction network and mechanisms; Examined the role of pre-treatment procedures. Initiated studies with dimethyl ether (DME) steam reforming.	90%
6	Information dissemination	Published 12 articles in refereed journals, five articles in conference proceedings, and gave 27 presentations, one key-note lecture and several invited lectures.	90%
7	Data analysis, reproducibility tests, literature awareness	Built a literature data base; Data analysis and reproducibility tests are performed in conjunction with the experiments.	90%

Technical Approach

An integrative approach - Iterative with feed-back

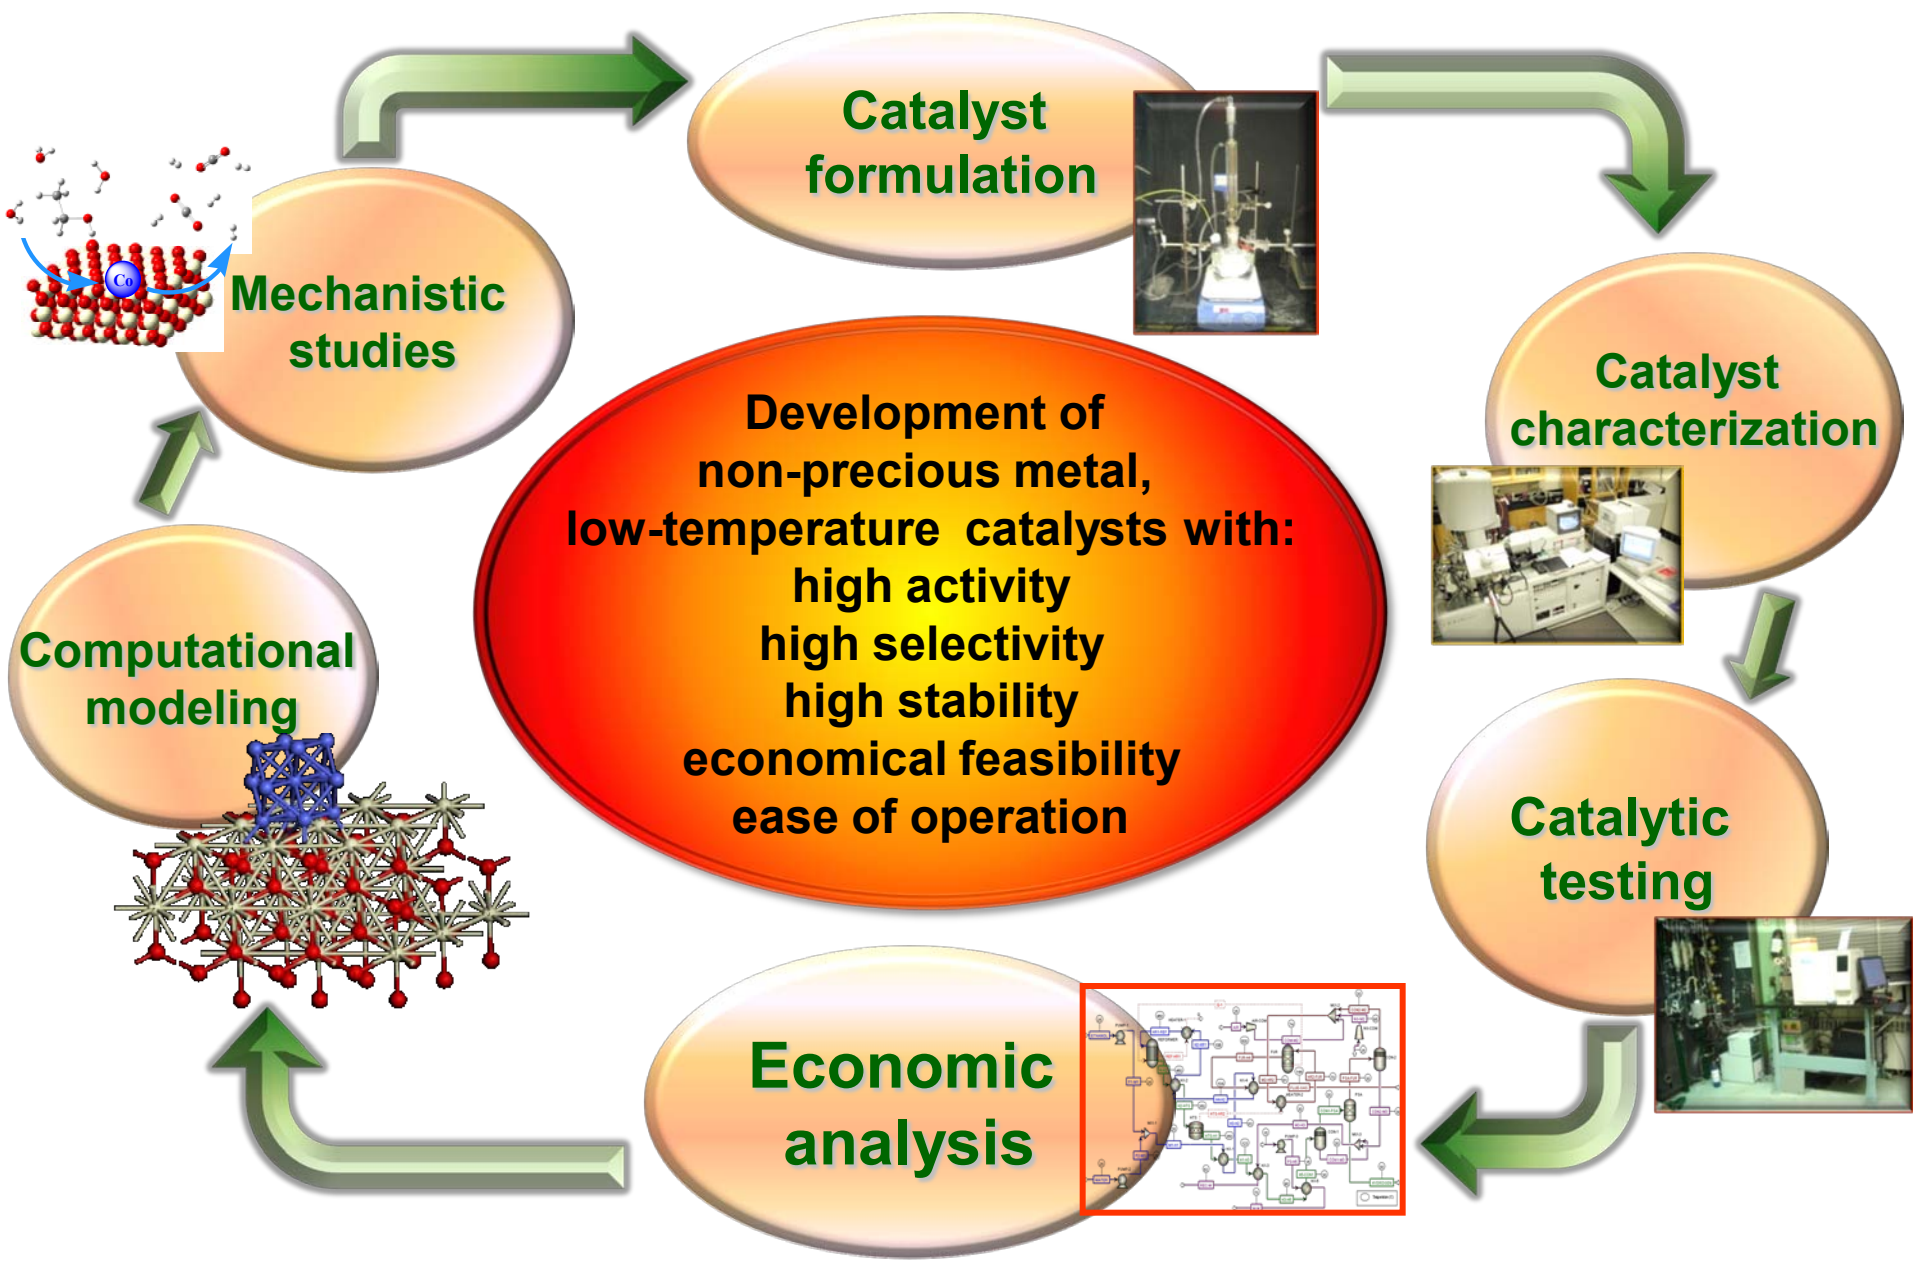

Technical Accomplishments and Progress

Understanding how to control the most important catalytic properties

Synthesis method

IWI, SG, CCT
solvothermal, hydrothermal

Support effect

ZrO₂, SiO₂, Al₂O₃
CeO₂

Formulation

Loading, dopants
promoters

Precursor effect

Co(NO₃)₂, CoCl₂, CoSO₄, CoCO₃
Co(AcAc)₂, CoAc, Co₂(CO)₈, CoC₂O₄

Impregnation medium





water, ethanol
ethylene glycol

Support Morphology

3-D ordered macroporous
cubic, cuboid, belt
rod, plate, polyhedron


Pre-treatment/ activation parameters

calcination temp., calcination time
reduction temp., reduction time



Different CeO₂
nano-structures

Metal Dispersion
Reducibility
Oxygen mobility
Surface acidity
Metal-Support Interaction
Support nano-structure

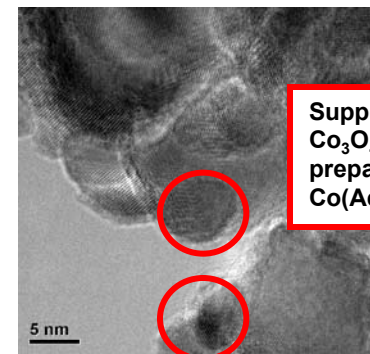

Supported
Co₃O₄ crystalline size
prepared by
Co(AcAc)₂: 3-6 nm

**Activity, Selectivity,
Stability**

Results published in

- *Catalysis Letters*, **132**, 422-429 (2009).
- *J. Molecular Catalysis*, **318**, 21-29 (2010).
- *Applied Catalysis A*
doi:10.1016/j.apcata.2010.04.01
- *Green Chemistry*, **9**, 686-694 (2007).
- *Journal of Physical Chemistry A*. **114**, 3796-3801 (2010).


Catalytic performance

Technical Accomplishments and Progress

Understanding the structural and molecular nature of the catalyst and the surface sites



N₂ Physisorption



X-Ray Diffraction



Laser Raman Spectroscopy



DRIFTS



Mass Spectrometry



X-ray photoelectron Spectroscopy



Thermogravimetry Scanning calorimetry



Adsorption desorption



Electron microscopy EDX



X-ray Absorption Spectroscopy

Technical Accomplishments and Progress

Understanding the Reaction Network



Steady-state reaction experiments



Transient response experiments




Isotopic labeling experiments

Results published in



Song, H., Zhang, L., Ozkan, U.S.,
"Reaction Networks in Ethanol Steam Reforming over Supported Co Catalysts,"
Industrial and Engineering Chemistry Research, accepted

A complex network of reactions catalyzed by different sites

Ethanol steam reforming
Temperature programmed reaction

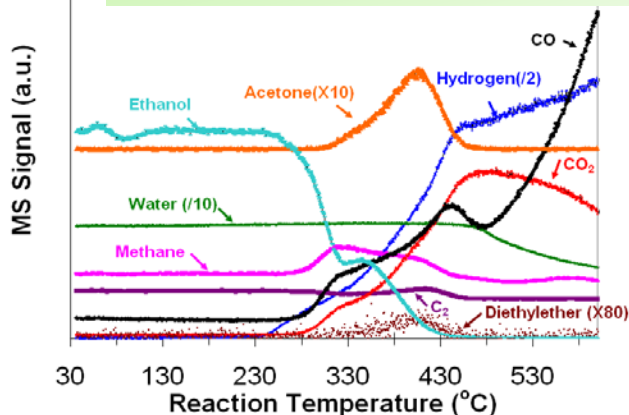


EtOH+D₂O TPD

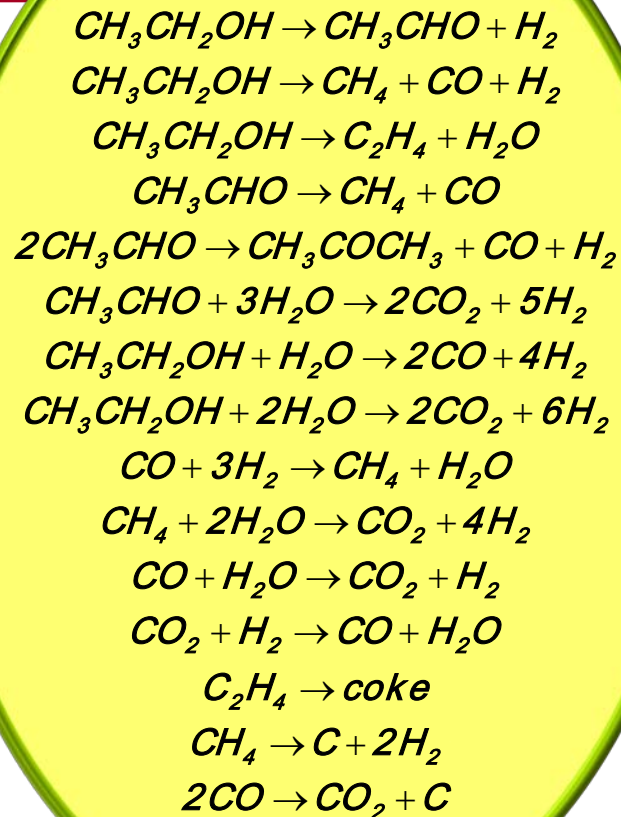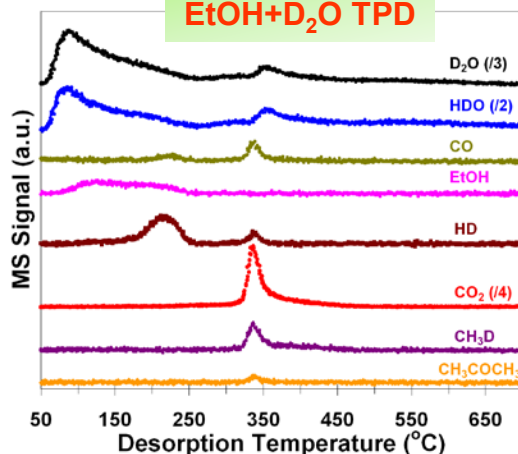

Technical Accomplishments and Progress


Identifying the surface species and elucidating the surface mechanisms

Molecular modeling

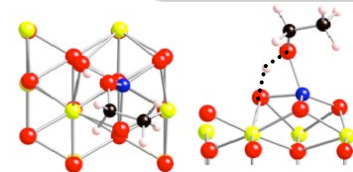

Multiple pathways that directly impact the yield, selectivity and stability

Proposed mechanism

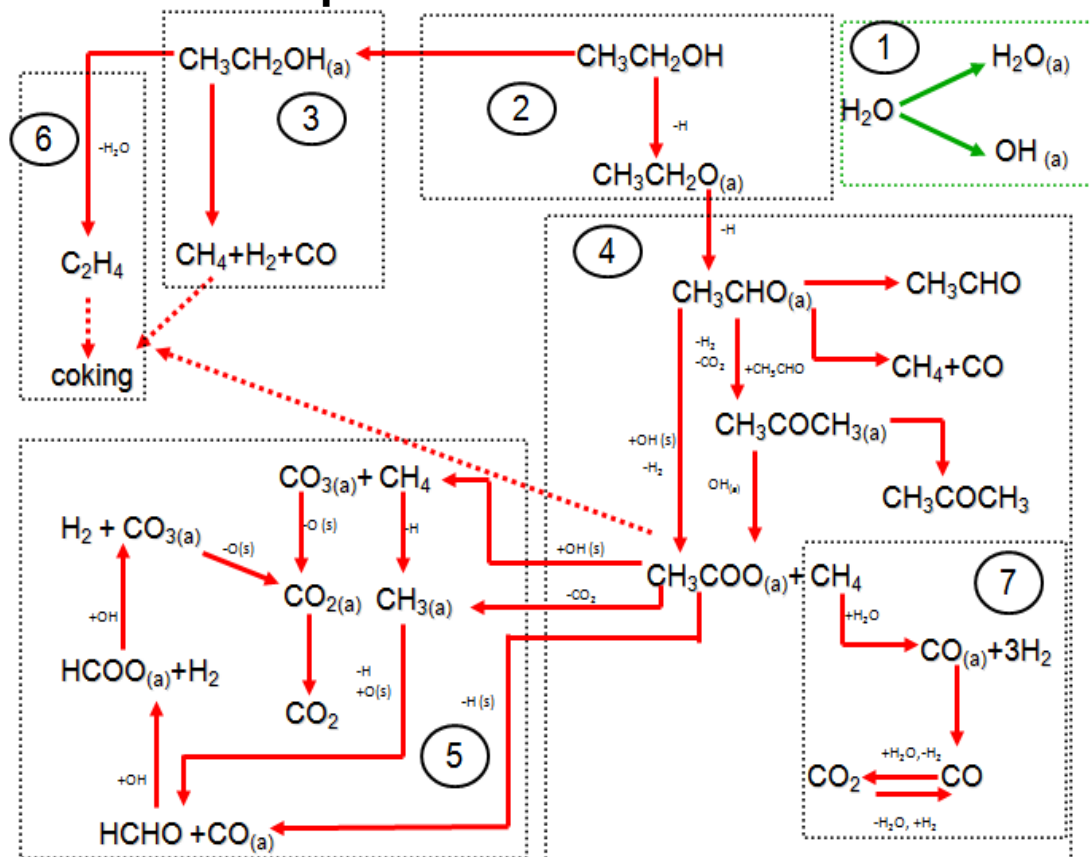

Isotopic labeling
Mass spectrometry

Temperature-programmed
desorption

Calorimetry

Thermogravimetry

In-situ vibrational
spectroscopy

Results published in

- Song, H. Zhang, L. Watson, R.B., Braden, D., Ozkan, U.S., "Investigation of Bio-ethanol Steam Reforming over Cobalt-based Catalysts," *Catalysis Today*, **129**, 346-354 (2007).
- Song, H. and Ozkan, U.S., "Adsorption/desorption Behavior Ethanol Steam Reforming Reactants and Intermediates over Supported Cobalt Catalysts," *J Phys. Chem.* Accepted

Technical Accomplishments and Progress

Understanding the major deactivation mechanisms

Primary modes of deactivation

Coking



Factors that lead to coking

- High surface acidity
- Low oxygen mobility
- Low metal-support interface


Sintering

Factors that lead to sintering

- Low dispersion
- Low oxygen mobility
- High operating temperatures
- Need for pre-reduction with H₂

Findings from this project that allow us to prevent deactivation

- Increasing oxygen mobility by creating anion vacancies in the support
- Neutralizing acidic sites
- Improving dispersion by using organic ligands in the synthesis
- Improving activity to reduce the operating temperature
- Eliminating the need for pre-reduction with H₂





Results published in

Song, H., Ozkan, U.S., "Ethanol Steam Reforming over Co-based Catalysts: Role of Oxygen Mobility," *J. Catalysis*, **261** 66-74 (2009).
 Song, H., Ozkan, U.S., "Changing the Oxygen Mobility in Co/Ceria Catalysts by Ca Incorporation: Implications for Ethanol Steam Reforming," Invited paper. *Journal of Physical Chemistry A*, **114**, 3796-3801 (2010).

A catalyst formulation with high activity, selectivity and stability

EtOH:H₂O=1:10 (molar ratio);
C_{EtOH}=7.5vol.%;
WHSV~1.08gEtOH/gCat/h;
GHSV~10,000h⁻¹

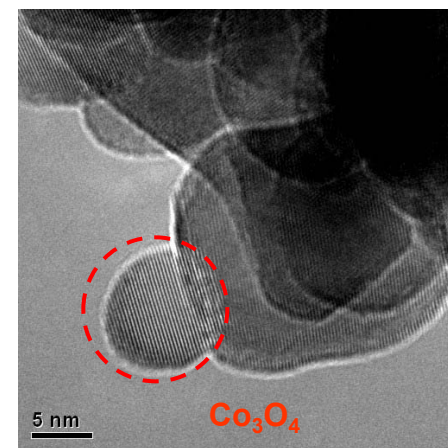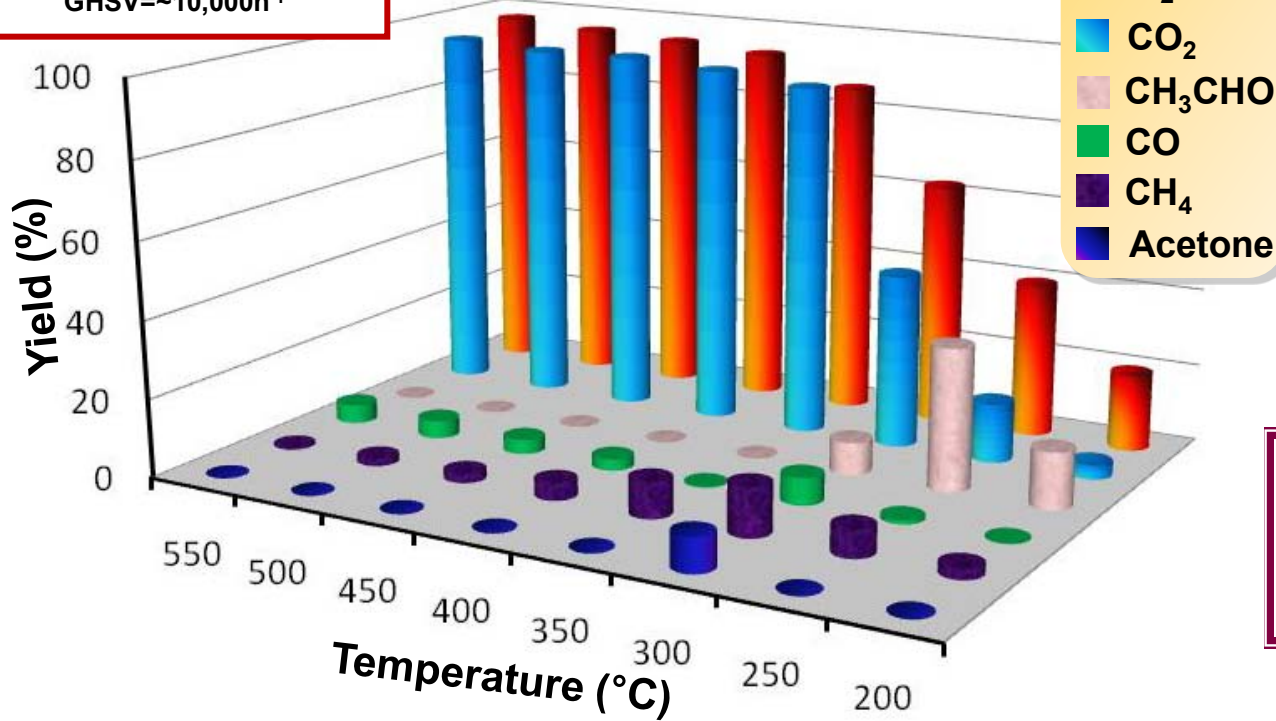

Co/CeO₂ catalyst prepared by a reverse microemulsion technique




- ❖ Over 95% H₂ yield
- ❖ No liquid by-products above 300°C
- ❖ Stable activity in accelerated aging study

Results published in

Song, H., Tan, B. and Ozkan, U.S., "Novel Synthesis Techniques for Preparation of Co/CeO₂ as Ethanol Steam Reforming Catalysts," *Catalysis Letters*, **132**, 422-429 (2009)

Technical Accomplishments and Progress

Economic analysis

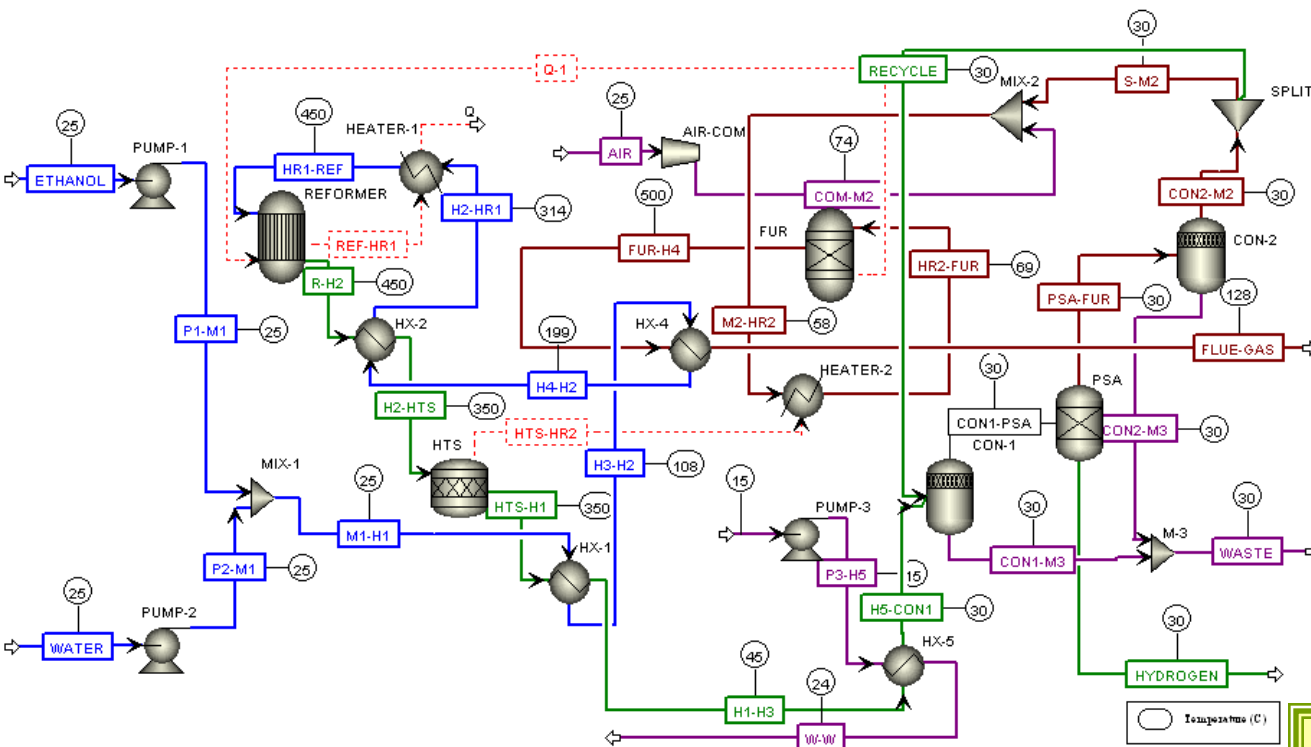

Forecourt Production Scale - (1,500 kg H ₂ /day)	
Production Cost \$/kg	Total Cost (Production/Storage/Disp.) \$/kg
2.75	4.63

Results published in
 Song, H. and Ozkan, U.S., "Economic Analysis of Hydrogen Production through a Bio-ethanol Steam Reforming Process: Sensitivity Analyses and Cost Estimations," *International Journal of Hydrogen Energy*, 35, 127-134 (2010).


- ❖ Economic analysis based on Aspen Plus and DOE-H2A model.
- ❖ Agreement with Directed Technologies independent analysis.
- ❖ Based on conservative estimates for catalyst life-time and GHSV.

Technical Accomplishments and Progress

Understanding the effect of catalyst pre-treatment



New capability
New collaboration
New insight

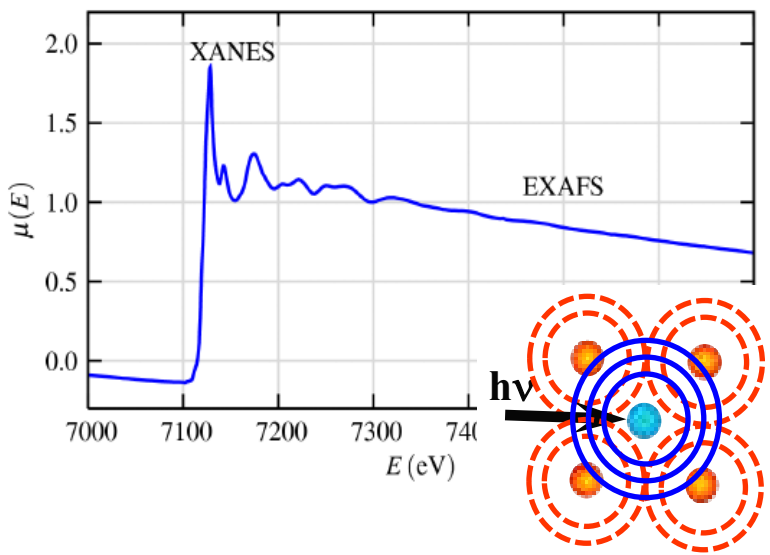

XAFS spectroscopy was utilized to provide insight on the oxidation state and the local coordination environment of Co during ethanol steam reforming with Co/CeO₂


X-ray absorption spectroscopy capability was recently added

XAFS (X-ray Absorption Fine Structure) spectroscopy provides information on the local atomic structure of a selected element, including:

- formal oxidation state
- coordination
- bond distances
- nature of immediate neighbors

Advanced Photon Source (APS) at the Argonne National Laboratories was utilized

The APS is a third generation synchrotron facility with the nation's most brilliant X-ray beams

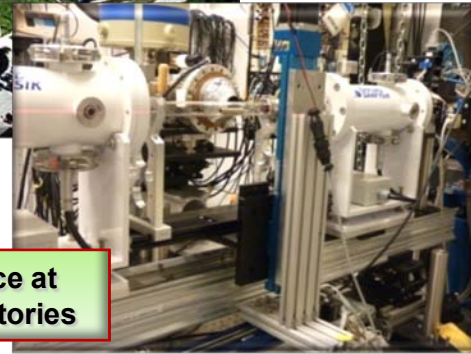


Advanced Photon Source at Argonne National Laboratories

Technical Accomplishments and Progress


Understanding the effect of catalyst pre-treatment



Reduction pretreatment
with H₂

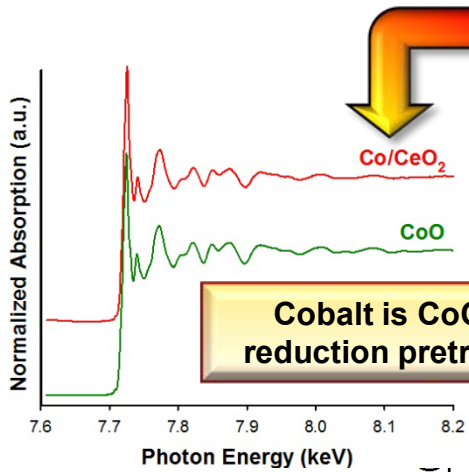

Cobalt is CoO after reduction pretreatment

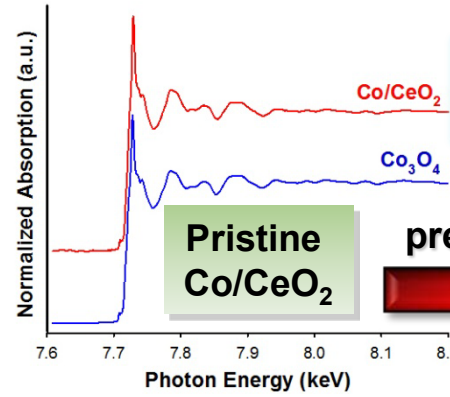


Co₃O₄ over pristine catalyst

No pretreatment


Pristine Co/CeO₂

Co₃O₄ is reduced to CoO during reaction at 350°C

Reaction after reduction pretreatment

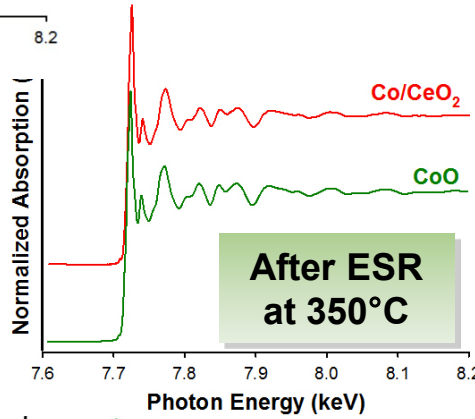


After ESR at 350°C

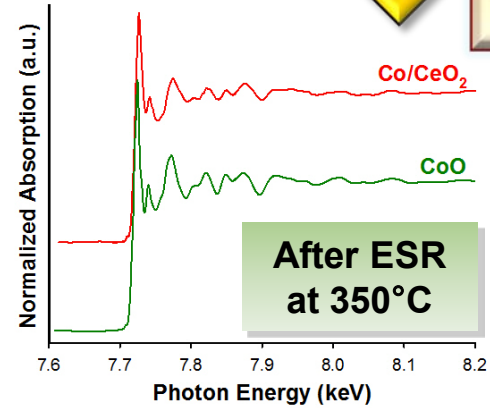


After ESR at 350°C

CoO is further reduced to metallic Co during reaction

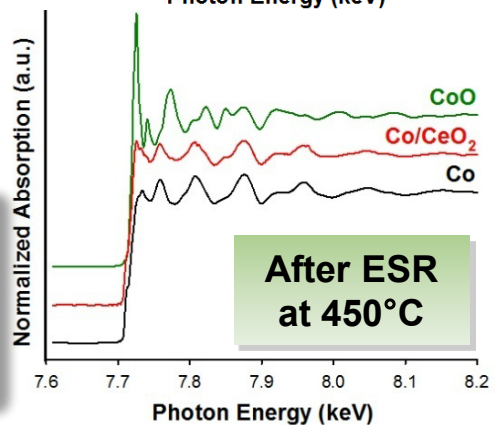

After ESR at 450°C

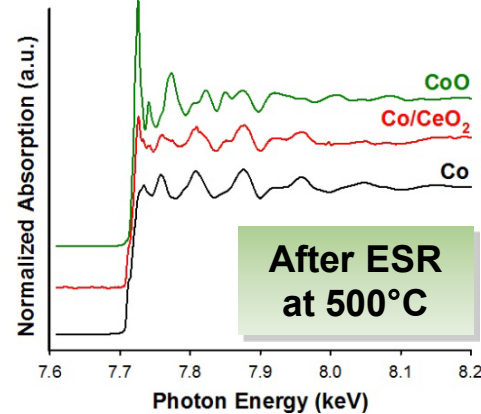

CoO is further reduced to metallic Co during reaction


Co reduction takes place under reaction conditions

Technical Accomplishments and Progress



Understanding the effect of catalyst pre-treatment



XANES Spectroscopy (X-ray Absorption Near Edge)

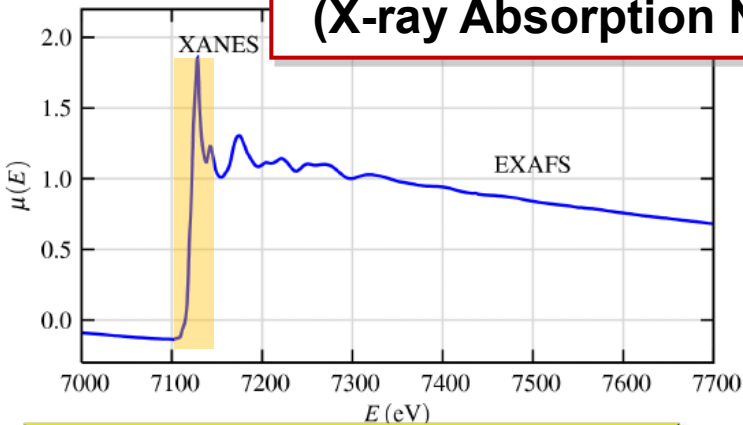

- Catalyst reduction takes place under reaction conditions
- Both samples converged to the same oxidation state for cobalt regardless of pretreatment
- XPS over post ESR samples further supported the conclusion

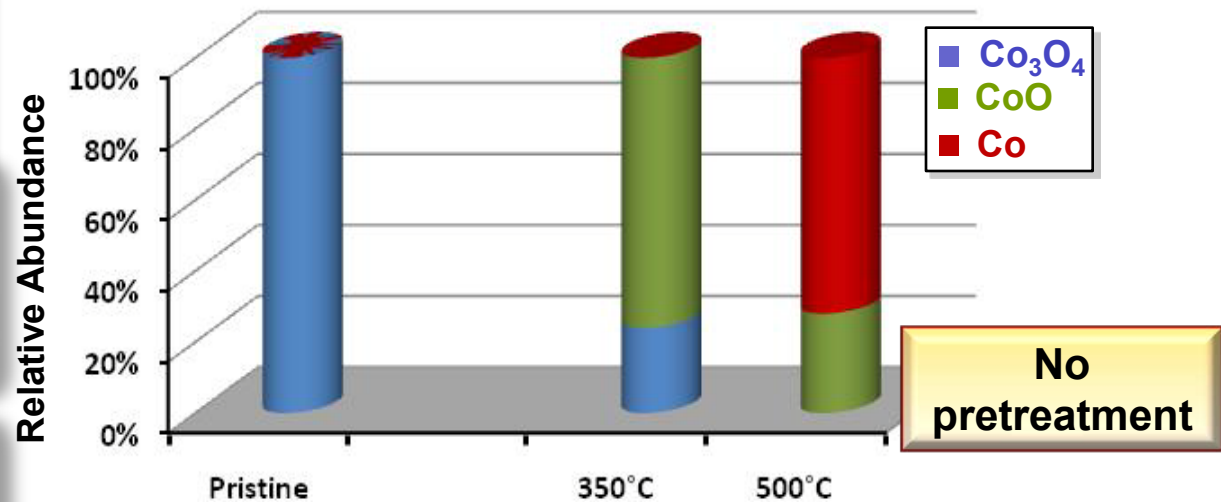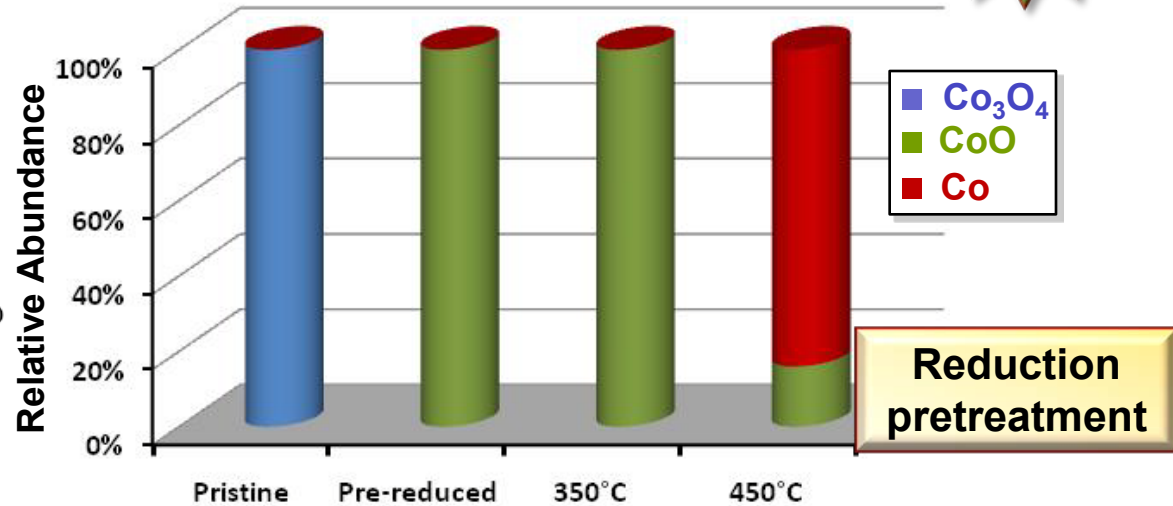

Reduction pretreatment is not necessary for catalytic activity

Ease of Operation



Technical Accomplishments and Progress



Vibrational spectroscopy under actual reaction conditions (operando)

DRIFTS during Temperature-programmed desorption

- Thermal transformation of adsorbed species
- Provides limited information on the surface species during ethanol steam reforming

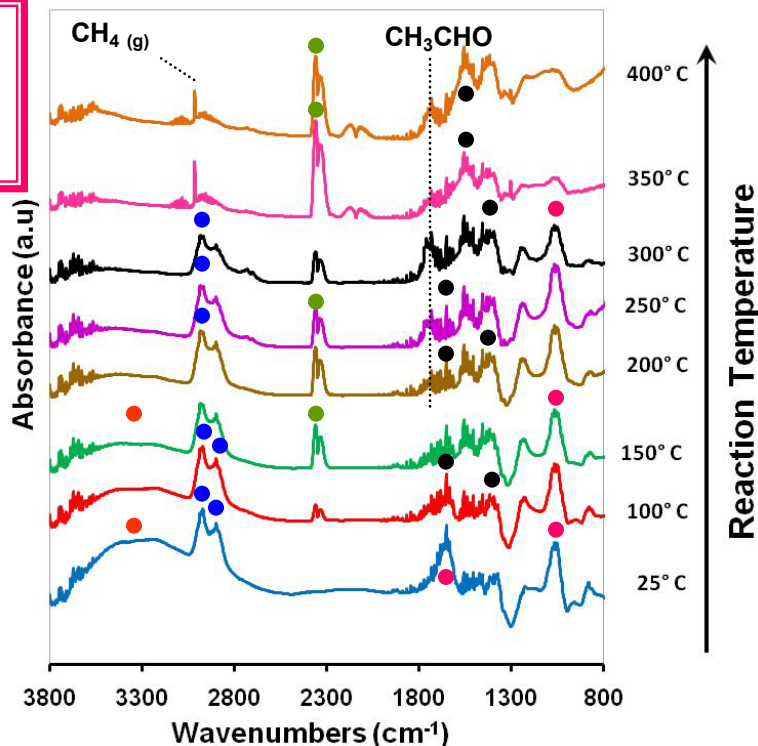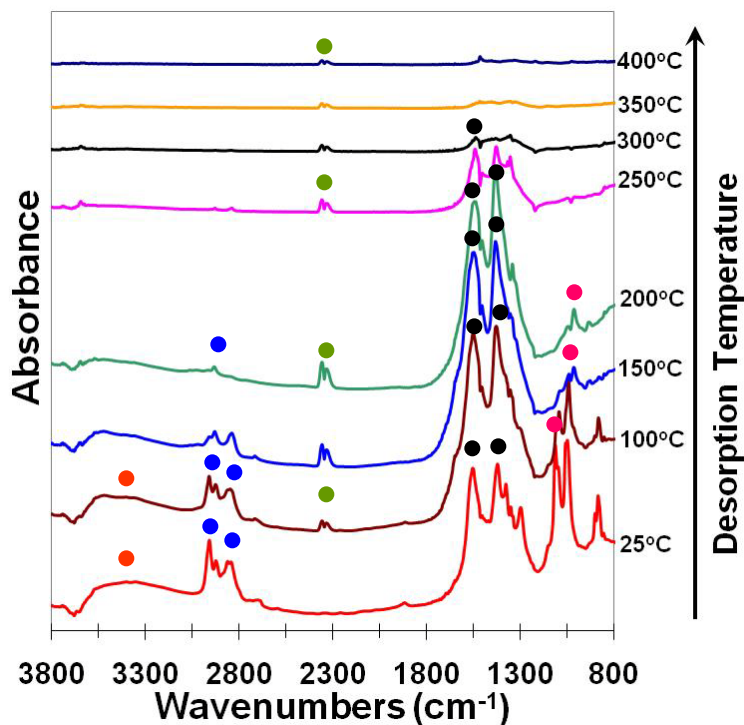

Acetaldehyde formation and decomposition to CH₄ and CO₂ can be directly observed.

DRIFTS during ESR Reaction



- Spectra collected while reaction is progressing
- Provides information on the surface species and mechanistic steps under **true** reaction conditions

<p>● M-OH 3650~3150cm⁻¹, O-H stretching</p> <p>● CH₃- or CH₃CH₂- 2962, 2927, 2865 cm⁻¹: C-H stretching 1385cm⁻¹: CH₃- bending</p> <p>● Monodentate and bidentate ethoxide 1169, 1106, 1063cm⁻¹ CCO stretching</p>	<p>● Acetates CH₃COO 1569, 1429, 1348cm⁻¹</p> <p>● CO₂ 2361, 2336cm⁻¹: O=C=O stretching</p> <p>● Molecularly adsorbed H₂O 1654cm⁻¹</p>
--	---

Monodentate ethoxide

Bidentate ethoxide

Molecularly adsorbed H₂O

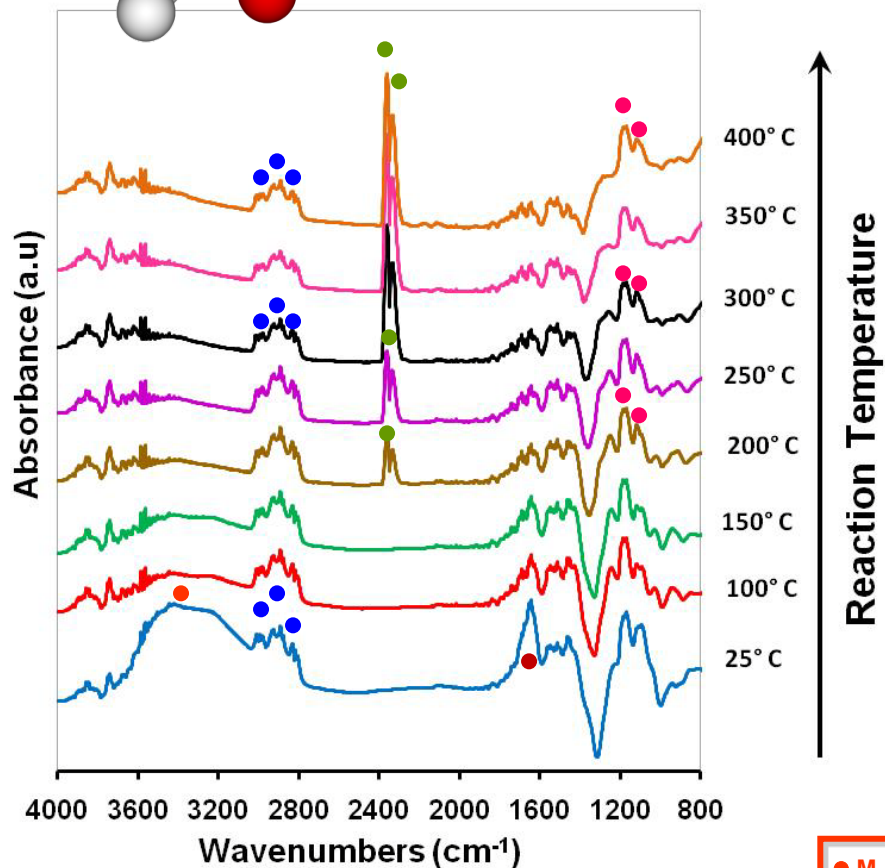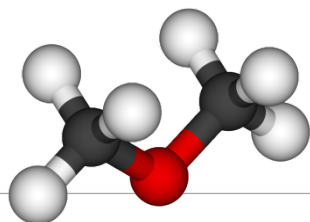


- Multi-source clean fuel which can be produced from a wide spectrum of feeds including lignocellulosic biomass
- Inert, non-carcinogenic, nonmutagenic, non-corrosive, and virtually non-toxic
- Hydrogen content is equal to that of ethanol

In-situ DRIFTS data show that Co/CeO₂ catalysts can be used in steam reforming of DME

Formation of various adsorption and oxidation products observed on the surface



- **M-OH**
3650~3150cm⁻¹, O-H stretching
- **CH₃-**
2962, 2927, 2865 cm⁻¹: C-H stretching
1385cm⁻¹: CH₃- bending
- **Surface Carbonates and methoxy region**
1176, 1166, 1101, 1079cm⁻¹ v(OC)
- **CO₂**
2361, 2336cm⁻¹: O=C=O stretching
- **Molecularly adsorbed H₂O**
1654cm⁻¹




Technical Accomplishments and Progress



Active and selective catalysts for PROX



- **Co/CeO₂ nanoparticles** were found to have high activity as Preferential Oxidation (PROX) catalysts for removing CO from H₂ streams.
- In the 150-180°C, high CO conversion (~100%) and high O₂ selectivity to CO₂ (>90%).
- Examined the effect of O₂ concentration, H₂ concentration, space velocity, temperature on conversion and selectivity
- Examined possible side reactions (WGS, r-WGS, methanation)
- Examined time-on-stream activity
- Measured activation energies for CO oxidation and H₂ oxidation

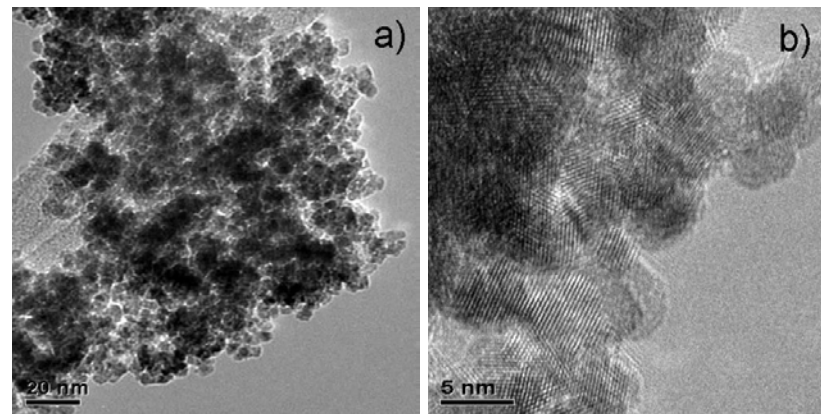

Nano-particles of CeO₂

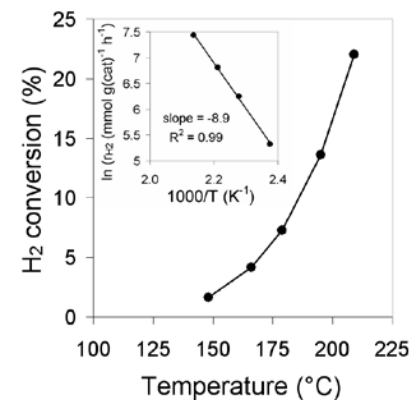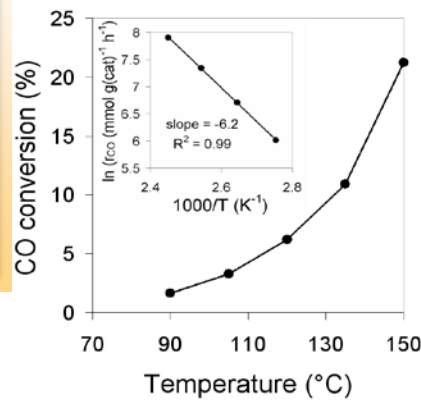

Results published in

Woods, M. P. Gawade, P., Tan, B. Ozkan, U.S., "Preferential Oxidation of Carbon Monoxide on Co/CeO₂ Nano-particles," *Applied Catalysis B*: in press. doi:10.1016/j.apcatb.2010.03.015

Collaborations

- ❖ [A new collaboration with Argonne National Lab](#) (Dr. Jeffrey Miller and Dr. Christopher Marshall) has been initiated to incorporate XAFS studies in the project. Three consecutive proposals for “In-situ XAFS Characterization of cobalt-based catalysts for steam reforming of bio-derived liquids” have been submitted to Argonne National Laboratory to request beam time at the synchrotron facilities and they all have been accepted. Seven members of the P.I.’s team have registered as facility users at Advanced Photon Source of Argonne National Laboratory. Dr. Miller has been working closely with the team members in in-situ experimentation and data analysis.
- ❖ [Collaboration with Chemistry Department \(Prof. Hadad\) on combining experimental work with molecular simulation](#) has progressed. A paper, that resulted from this collaboration “Computational Study of the Ethanol Steam Reforming Reaction over Co/CeO₂(111): from Ethanol to Acetate” has already been presented at the ACS National Meeting in August 2009. A refereed journal article written jointly has been accepted for publication in *Journal of Physical Chemistry*. A second collaborative article is in preparation. A post-doctoral researcher and a graduate student are being jointly advised by the P.I. and Dr. Hadad.
- ❖ [Collaboration with Nextech Materials, Inc.](#) for scale-up of the catalyst manufacturing process is in place. A joint proposal (OSU and NexTech) to NSF has been accepted.
- ❖ [Collaboration with PNNL.](#) Sharing findings
- ❖ [Directed Technologies, Inc.](#) Economic analysis and feasibility considerations

Summary



Relevance:

A fundamental study aimed at developing precious-metal free catalysts for hydrogen production from bio-ethanol and other bio-derived liquids

Approach:

An integrative approach that combines catalyst synthesis, characterization, kinetic studies and molecular simulation in an iterative manner to develop a fundamental understanding of the nature of active sites, reaction networks and reaction mechanisms involved in ethanol steam reforming over Co-based catalysts

Technical accomplishments and progress:

Developed an understanding of the reaction networks and surface mechanisms that allow correlating specific sites with specific reaction steps and deactivation mechanisms

Developed techniques for tailoring the catalytic properties to meet the needs of the reaction

Developed promising catalyst formulations that can achieve high H₂ yields, high selectivities and high stability at low temperatures

Collaborations:

New partnership with Argonne National Lab for XAFS studies

Active partnership with Chemistry Department on molecular simulation

Partnership with NexTech for catalyst manufacturing

Partnership with PNNL and Directed Technologies, Inc. for sharing findings

Proposed Future work:

Long term stability tests, accelerated deactivation tests, kinetic measurements to obtain kinetic parameters and allow kinetic modeling, *in-situ* XAFS studies



Future Work

- ❖ Kinetic and mechanistic studies will be continued in conjunction with catalyst characterization under reaction conditions to obtain kinetic parameters. Rate expressions will be developed for kinetic modeling.
- ❖ Long term time-on-stream experiments will be continued.
- ❖ Accelerated deactivation and regeneration studies (e.g., higher C/S ratio and GHSV) will be continued.
- ❖ Economic analysis will be fine-tuned based on process modification with no pre-reduction.
- ❖ Molecular simulation work using DFT calculations will be continued and used to guide rational catalyst design. This is a collaborative activity.
- ❖ *In-situ* XAFS experiments will be performed at Argonne National Lab to elucidate the oxidation state and coordination environment of cobalt sites during reaction. Accelerated deactivation studies will be coupled with in-situ XAFS studies. This will be a collaborative activity.
- ❖ Catalyst synthesis for best performing catalysts will be scaled-up through industrial partnership. This is a collaborative activity.
- ❖ Several more publications are in preparation and will be submitted within the next 6 months.