



Hydrogen Storage by Novel CBN Heterocycle Materials

Shih-Yuan Liu (lsy@uoregon.edu)

Department of Chemistry, University of Oregon

2010 Annual Merit Review

Washington DC, June 10, 2010

In partnership with the Chemical Hydrogen Storage Center of Excellence

Project ID: ST038

This presentation does not contain any confidential or otherwise restricted information

Overview

Timeline

start date: September 2008

end date: March 2012

percent complete: 40%

Budget

total project funding: \$1,440,614

DOE share: \$1,149,085

UO share: \$291,529

funding received: \$403,432

funding for FY10: \$200,000

Barriers

A. system weight and volume

C. efficiency

E. charging/discharging rates

R. regeneration process

Project Collaborators



Prof. David Dixon



Dr. Tom Autrey




Prof. Karen Goldberg

Prof. Mike Heinekey

Key Summary

- A relatively new project as part of the CHSCoE.
- Focus on cyclic H₂ storage materials containing C, B, and N.
- New approach to H₂ storage that complements the materials currently under investigation.
- Couple *exothermic* H₂ desorption from *BN* with *endothermic* H₂ desorption from *CC* in a *cyclic* system to address reversibility.
- Strong collaborative effort with feedback loops between theory, synthesis, catalysis, and charge/discharge characteristics measurements.
- Progress: synthesized CBN heterocycle materials, demonstrated a pathway for regeneration of the spent fuel that includes using molecular H₂, developed a First-Fill synthesis, measured thermodynamic parameters that corroborate computational predictions, performed preliminary desorption studies.

Research in the Liu Group - Relevance

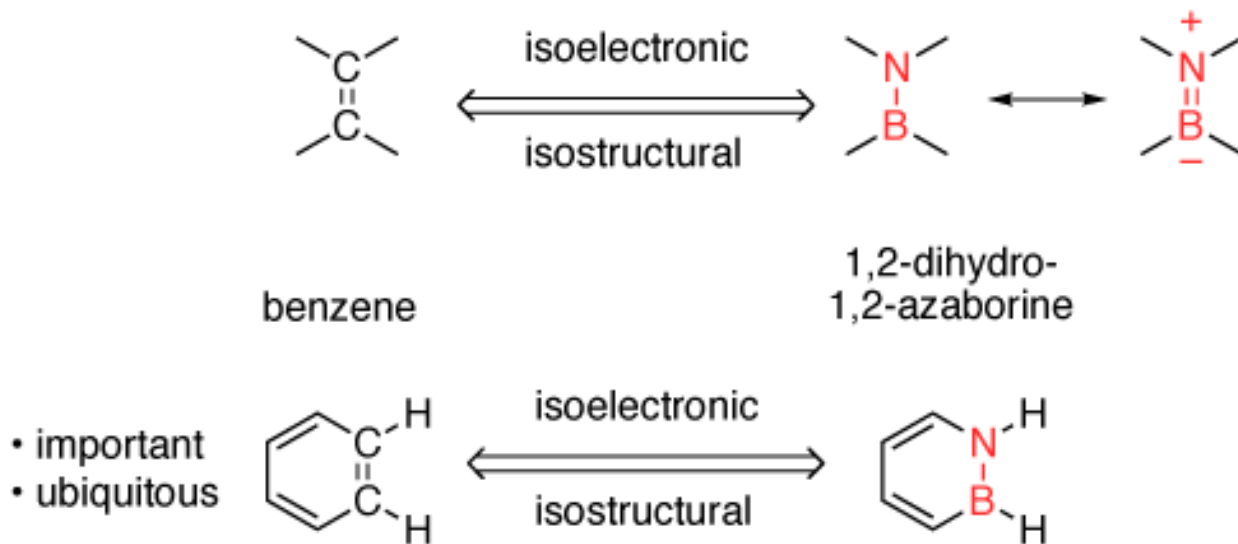

Scientific Research:

synthesis

structure, bonding

aromaticity

catalysis, mechanism



Applications:

new synthetic methods

biomedical applications

optoelectronic materials

H₂ storage materials



Project Objectives - Relevance

Develop CBN heterocycles as novel hydrogen storage materials:

- liquid-phase storage system
- gravimetric density
- volumetric density
- thermodynamics (H_2 absorption and desorption)
- cost effective and energy efficient regeneration (reversibility)

Specific objectives – Phase I (9/1/2008 – 3/31/2010):



- calculate thermodynamic properties of CBN heterocycle materials
 - synthesize novel CBN heterocycle materials
 - determine thermodynamic properties for CBN heterocycles via experiment
-

Phase II objectives (4/1/2010 – 3/31/2012)


- optimize the gravimetric density of materials
- develop a First-Fill synthesis
- develop/identify/optimize conditions for H_2 absorption (regeneration)
- develop/identify/optimize conditions for H_2 desorption (release)

The CBN Heterocycle Approach

calculated at CCSD(T) level (298K):

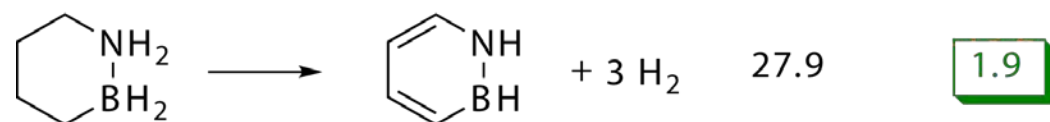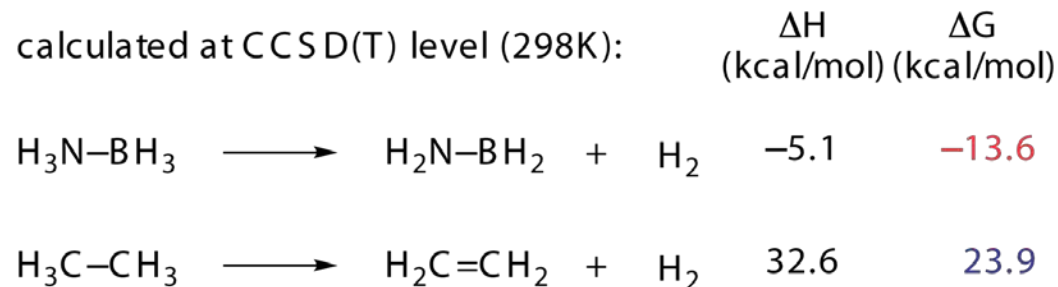

couple *exothermic* H₂ desorption from *BN* with *endothermic* H₂ desorption from *CC* in a *cyclic* system to achieve optimal thermodynamics for the overall H₂ absorption/desorption process.

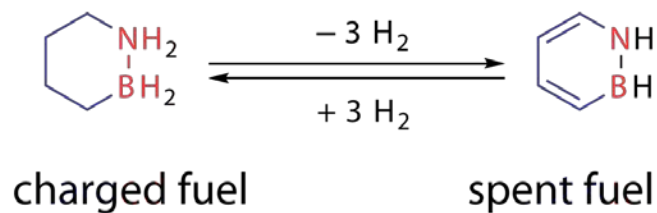

• Spent fuel can potentially be directly regenerated with H₂.

A Collaborative Approach

(calculate, synthesize, measure, optimize)_n



$$\Delta G = \Delta H - T\Delta S$$


reversible H₂ storage: $\Delta G \sim 0!$

- use theory to help select synthetic candidates




Myrna Matus

J. Phys. Chem. A **2010**, *114*, 2644-54.

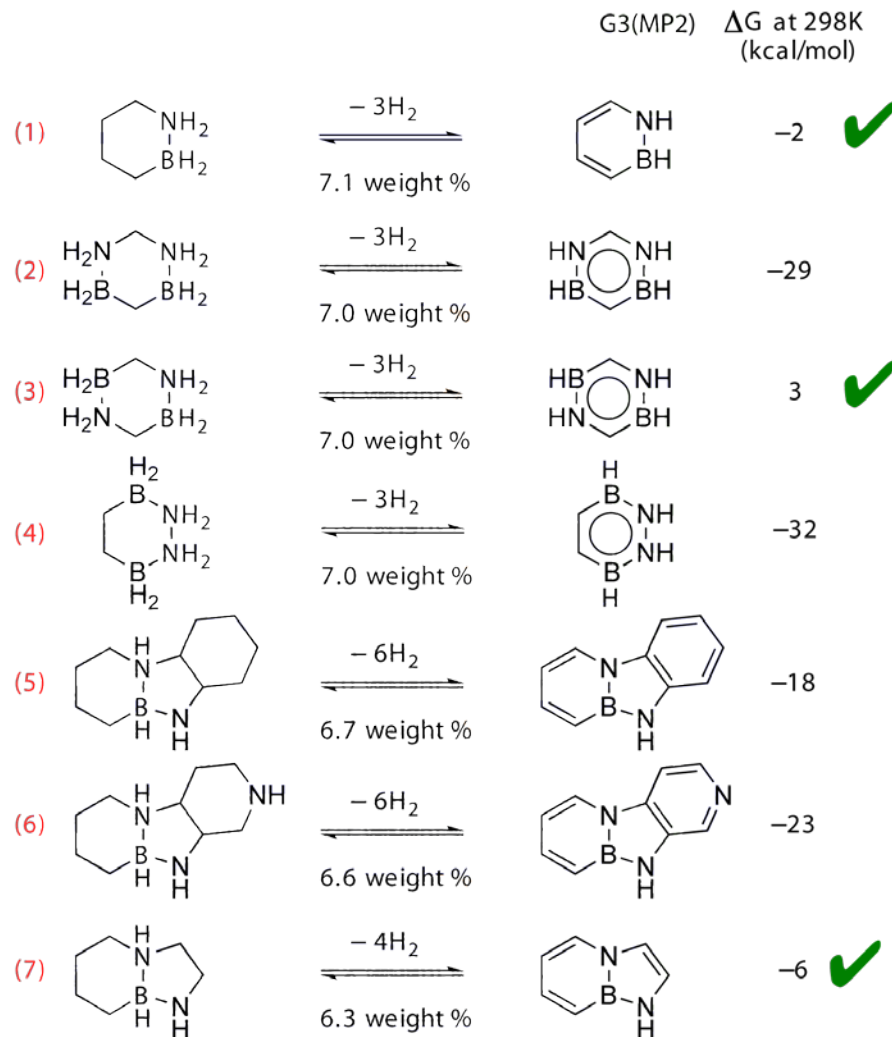

Progress - Developing Synthetic Tools


organic



benzene


Faraday
(1825)

hybrid
organic/inorganic



1,2-dihydro-
1,2-azaborine
(2008)

inorganic



borazine


Stock
(1926)


 Adam Marwitz



Myrna Matus










Angew. Chem. Int. Ed.
2009, 48, 973-7.




 Adam Marwitz

Org. Lett. **2007**, 9, 4905-8.

- The proposed CBN heterocycle materials are new and not commercially available. New synthetic tools have been developed to address the synthetic challenge.**

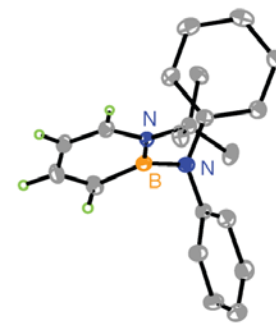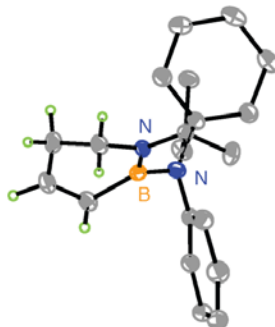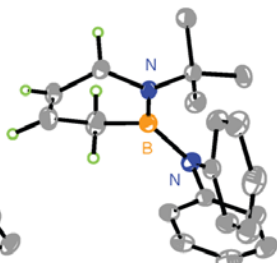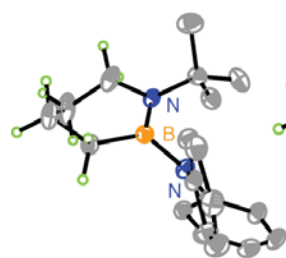


J. Am. Chem. Soc.
2008, 130, 7250-2.


 Eric Abbey

Progress – Model for C₄BNH_x System

- Model and parent materials have similar thermodynamic properties.

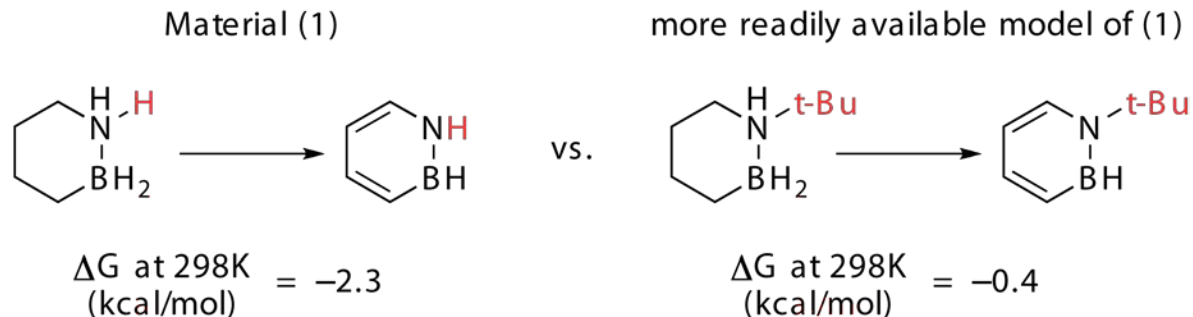


- successfully prepared several compounds related to the model material

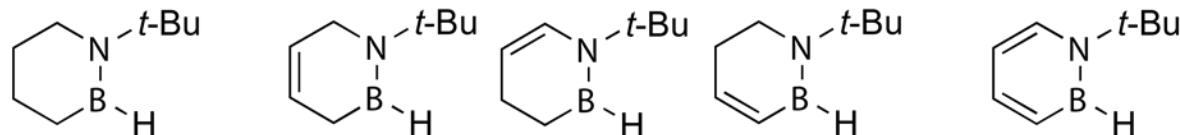



- low-melting liquids
mp < -30 °C

- determined density of select model material



d = 0.849 kg/L

Progress – Hydrogenation Enthalpies: Theory vs. Experiment

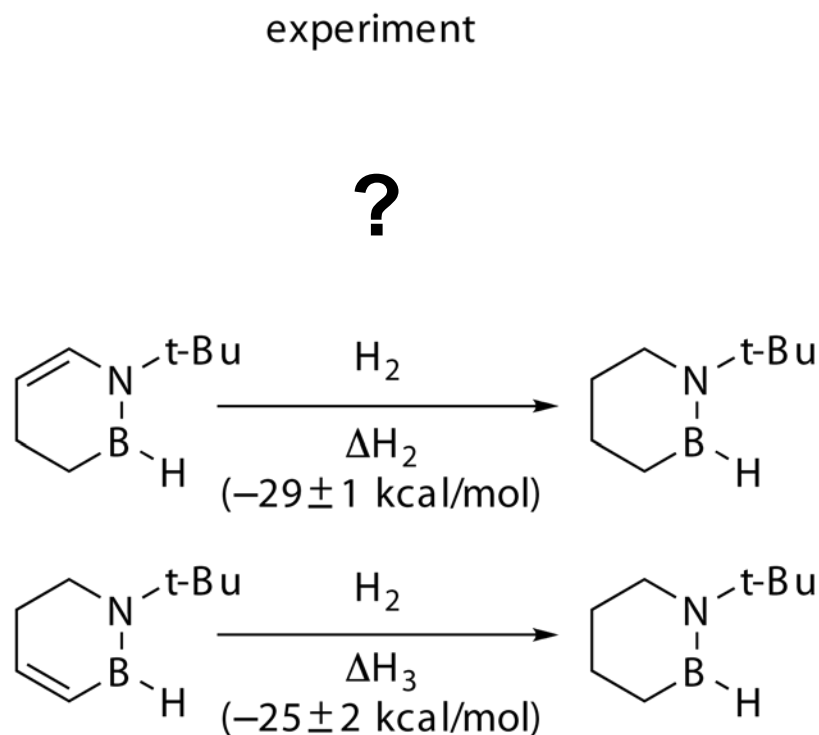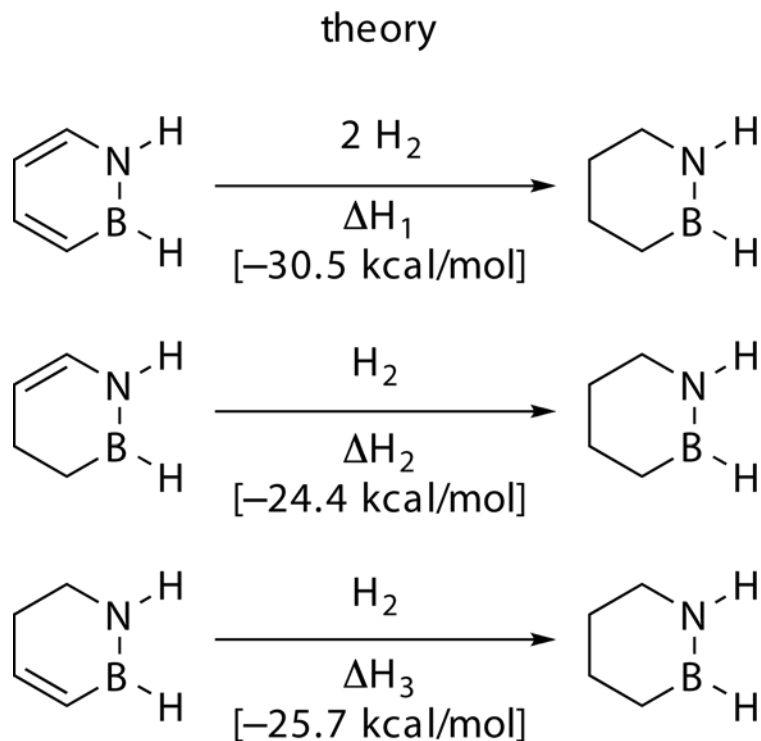


RuCl₂(PPh₃)₃ catalyst (homogeneous)


• Experimental data are consistent with theory.

Progress – Relevance of Aromaticity

benzene
highly aromatic








vs.



1,2-azaborine
less aromatic

more difficult to
hydrogenate

easier to hydrogenate
= regenerate

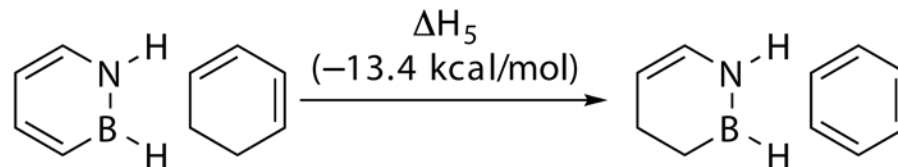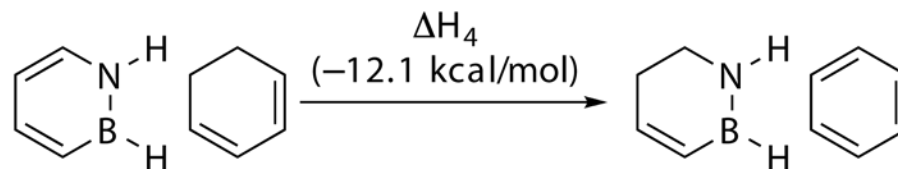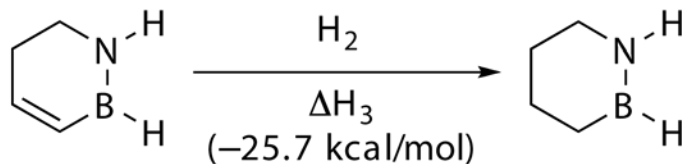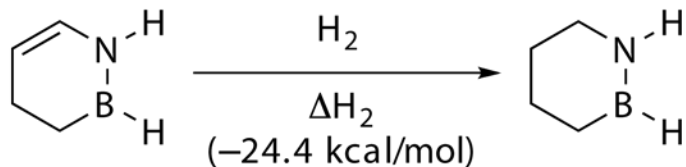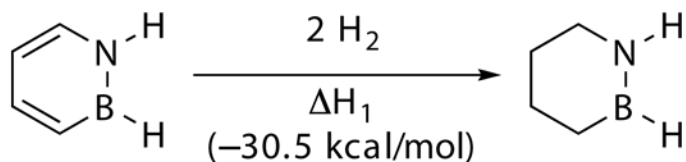


$$\text{ASE} = \Delta H_1 - (\Delta H_2 + \Delta H_3) = 19.6 \text{ kcal/mol}$$


$$\text{ASE} = 32.2 - |(\Delta H_4 + \Delta H_5)/2| = 19.5 \text{ kcal/mol}$$

- **Regeneration of CBN heterocycle materials with H₂ should be facile due to reduced aromaticity compared to the all-carbon system.**


Progress – Facile Hydrogen Uptake

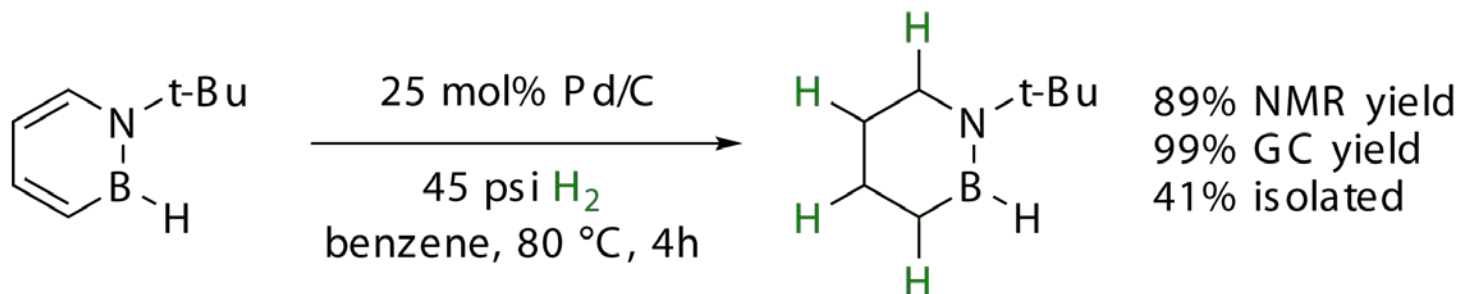

vs.


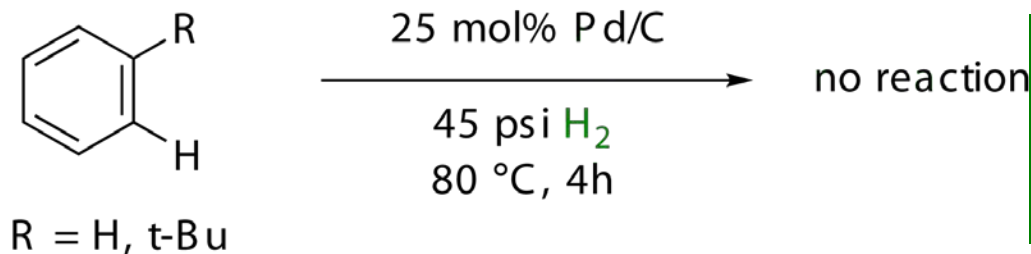


• CBN heterocycle materials ARE easier to regenerate with H₂ compared to the all-carbon system.

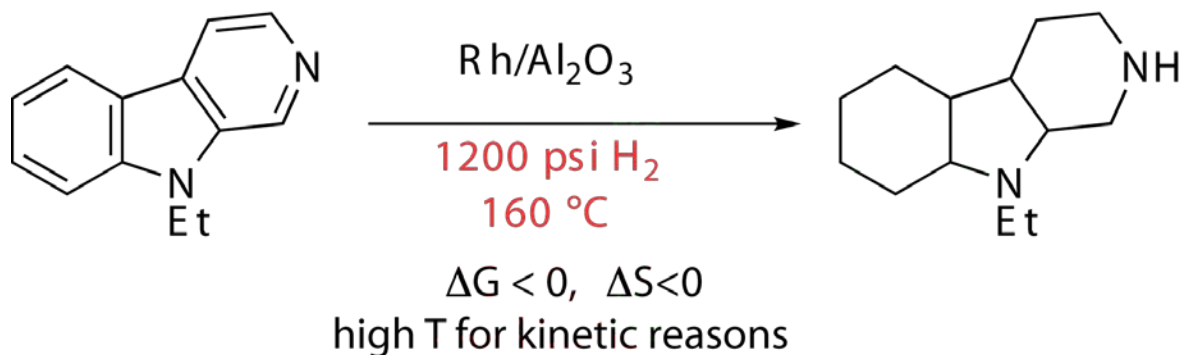


Progress – Regeneration Completed


^{11}B NMR: δ 39.1 (d)

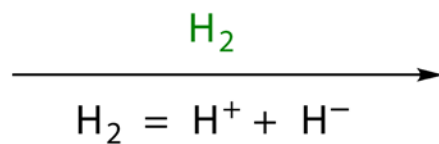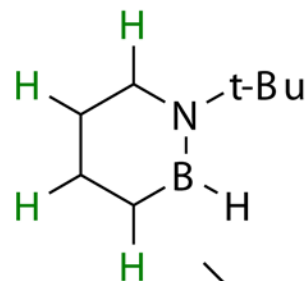

^{11}B NMR: δ -11.0 (t)

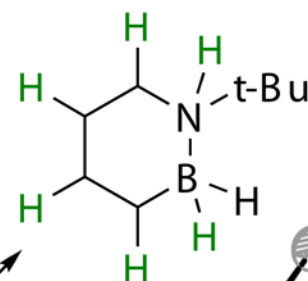


charged fuel

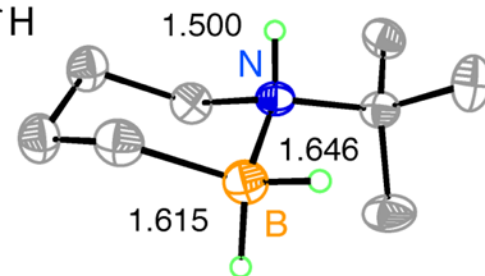

KH , 18-crown-6



not necessary

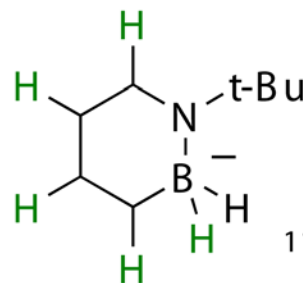

$\text{HCl} \cdot \text{Et}_2\text{O}$


$\text{K}^+ \cdot 18\text{-crown-6}$

^{11}B NMR: δ -13.1 (t)

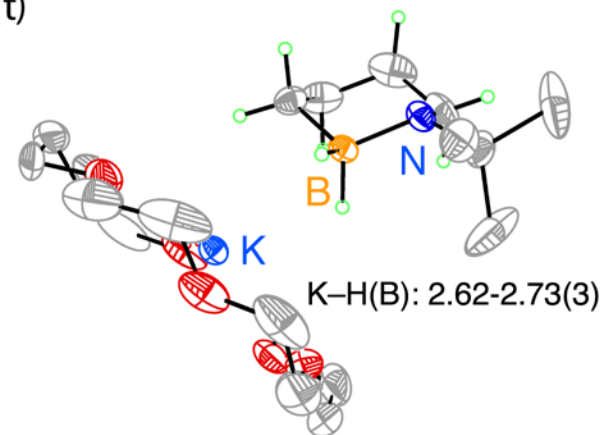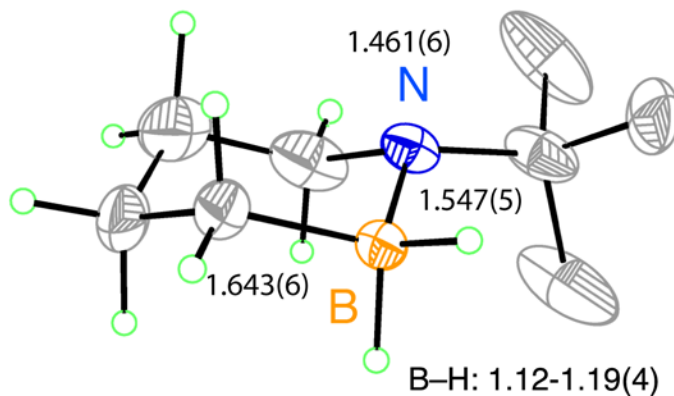


Progress – Simple Regeneration using H_2 , H^- , H^+

- developed a simple three-step procedure for regeneration of spent fuel
- first synthetic access to the charged CBN fuel (Material (1))

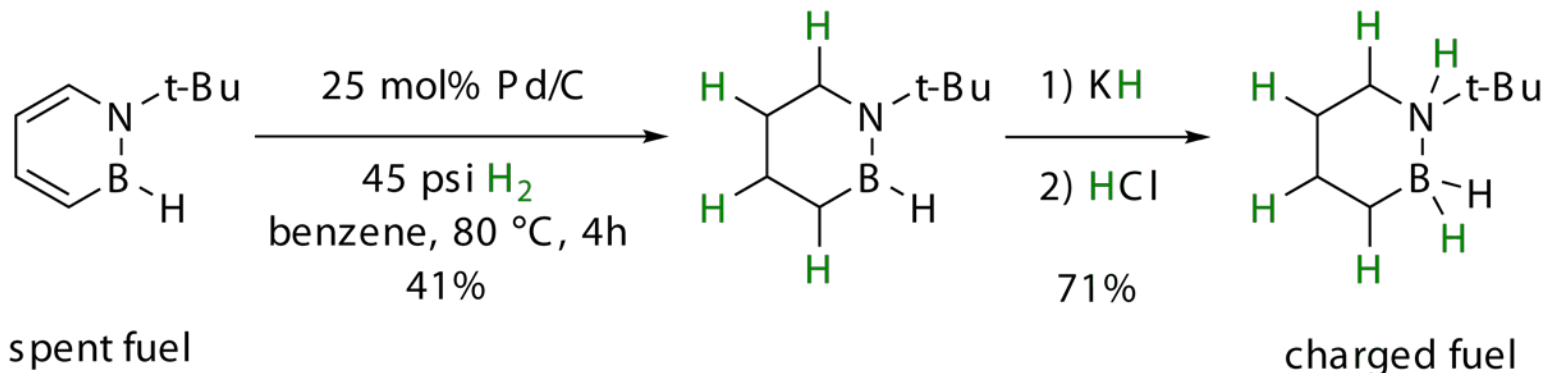


- need to screen for milder reductants, e.g., transition metal hydrides, formic acid

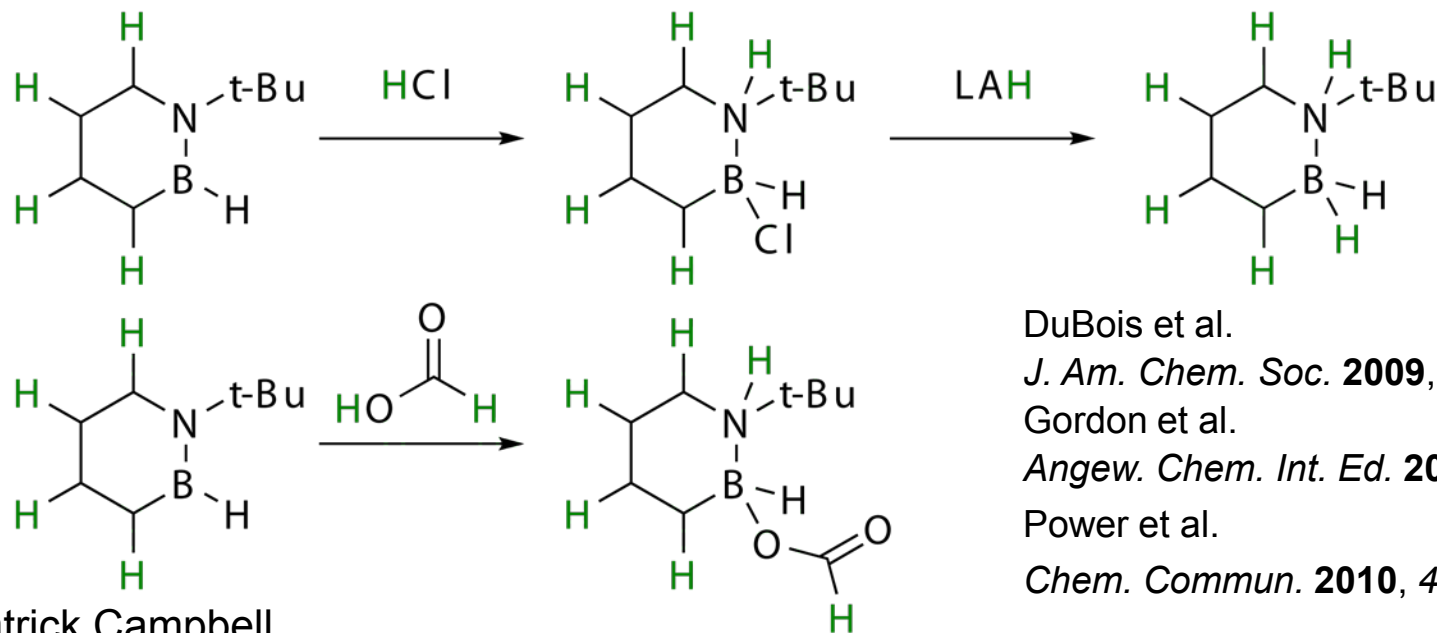

DuBois et al.
J. Am. Chem. Soc. **2009**, *131*, 14454-65.
 Gordon et al.
Angew. Chem. Int. Ed. **2009**, *48*, 6812-6.
 Power et al.
Chem. Commun. **2010**, *46*, 148-9.


Progress – First Fill Synthesis

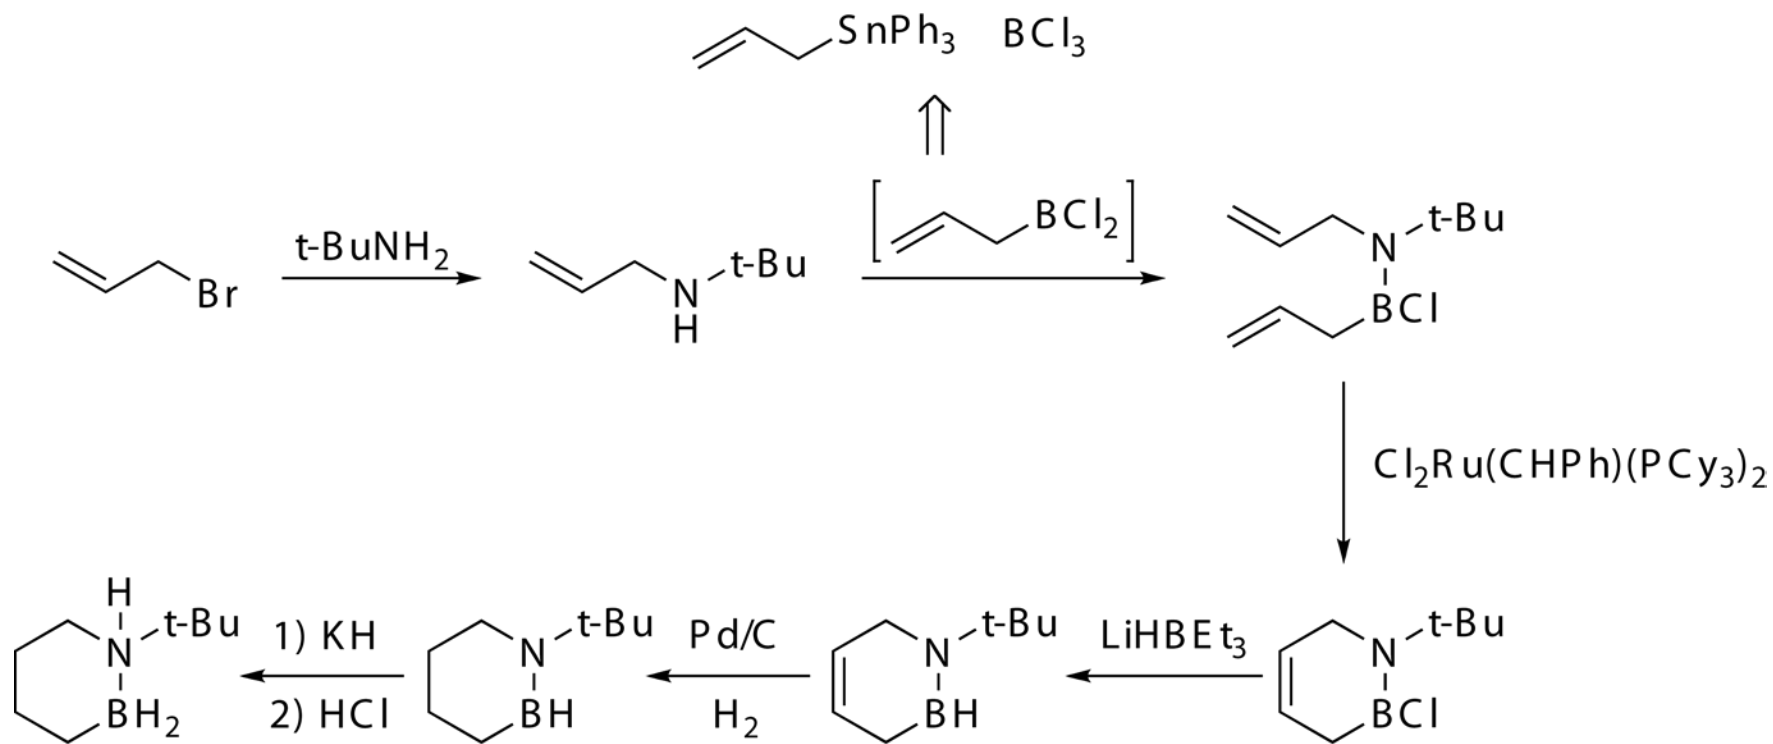

7 steps, 9% overall yield


There is a need for a simple First-Fill synthesis!

Progress – First Fill Synthesis

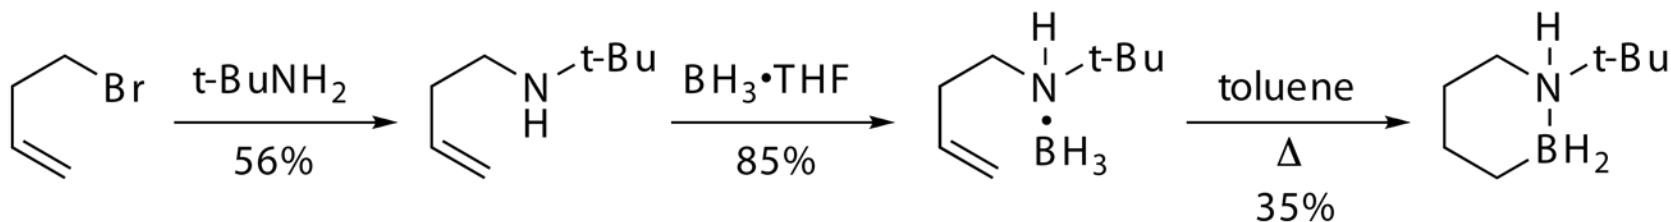



3 steps, 17% overall yield

- ^{11}B NMR is a suitable diagnostic tool

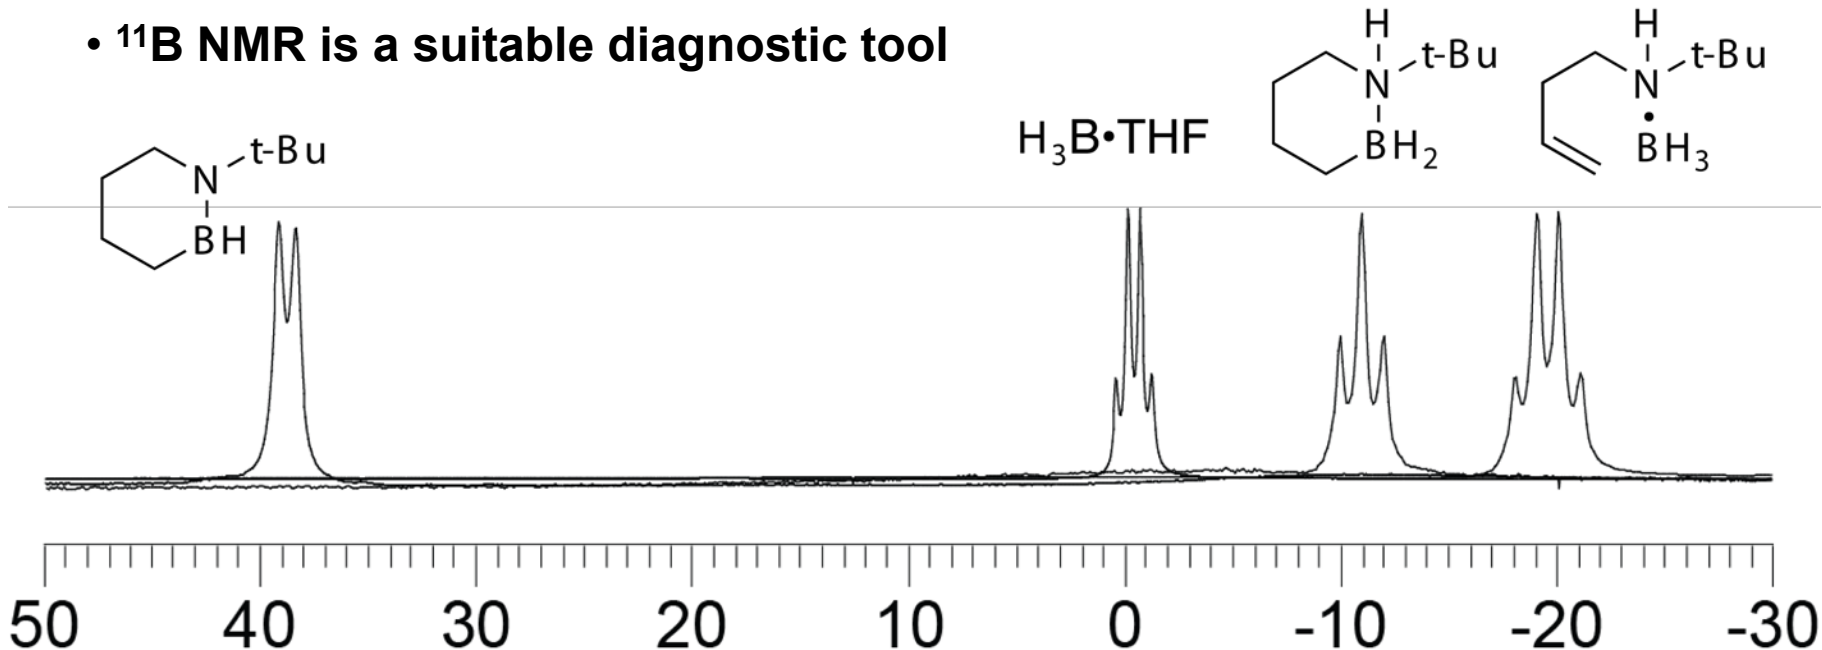


- accomplished a simplified First-Fill synthesis
- need to improve each individual steps
- need to improve gravimetric density

Progress – Improving the Gravimetric Density of CBN Materials

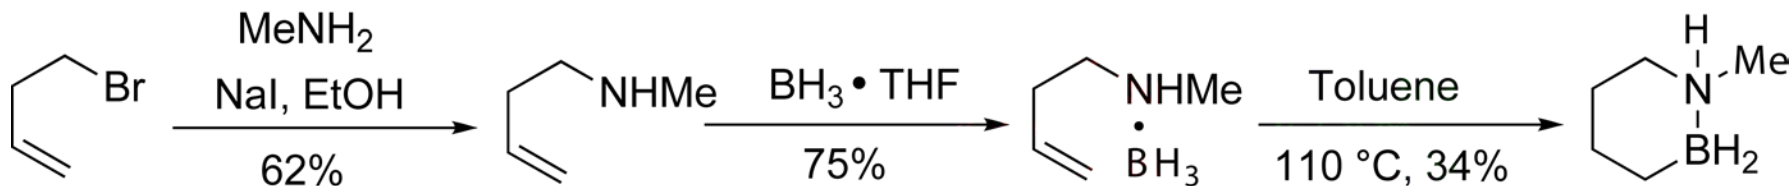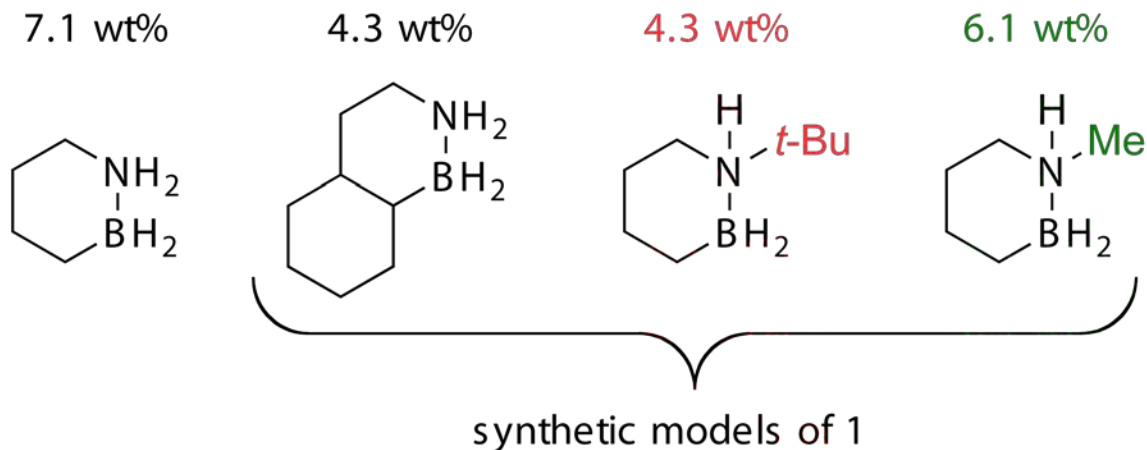


• synthesized a material with significantly improved storage capacity

UW - Progress

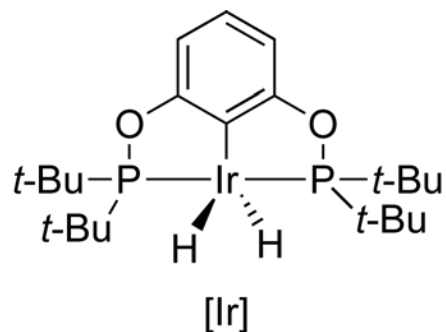

**Highly active
catalyst**

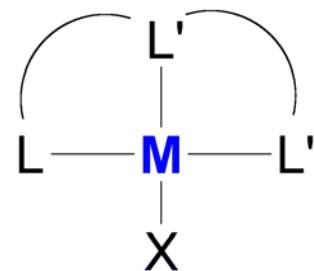

**Basic Tridentate
Ligand Motif**

synthesis of new metal catalysts based on the tridentate ligand motif

- Replace Ir with inexpensive metal
- Tune L, L', L'' and X to achieve high activity and catalyst stability

Heinekey and Goldberg et al.



J. Am. Chem. Soc. **2006**, 128, 12048-9.

J. Am. Chem. Soc. **2008**, 130, 10812-20.

Inorg. Chem. **2010**, 49, 1733-42.


UW - Progress

Dehydrogenation of CBN Heterocycles

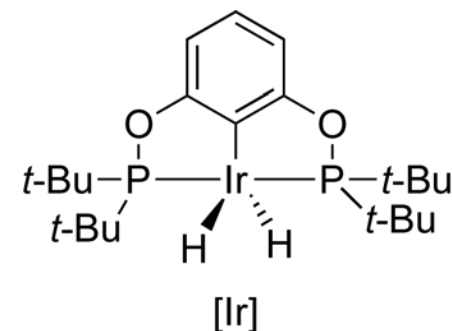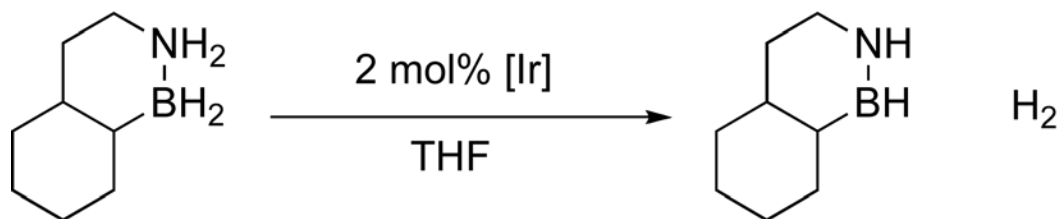

- At RT release of 1 eq. H_2 is observed.
- ^{11}B NMR is consistent with formation of BHNH product.
- Product characterization is in progress.

40.7735
40.0317

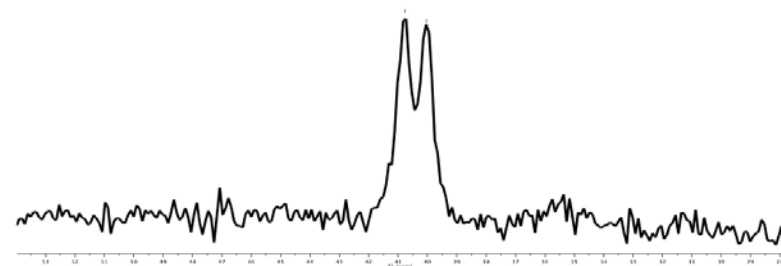

Collaborations

Project Collaborators



computational studies of H₂ desorption pathways of cyclic CBN materials, evaluation of thermodynamics and energetics



experimental mechanistic studies of H₂ absorption/desorption to/from cyclic CBN materials, thermodynamic measurements using reaction calorimetry, H₂ charge/discharge characteristics



development/discovery of efficient catalysts for H₂ desorption from CBN materials

Technology Transfer



obtained computed thermodynamic data and H₂ desorption reaction pathways for CBN heterocycle materials, will continue provide feedback with experimental data



obtained thermodynamic data via reaction calorimetry



prepared CBN heterocycle materials and delivered to UW for further investigation
obtained preliminary H₂ desorption data

Proposed Future Work

- focus on developing CBN Materials (1) and (7)
- complete experimental thermodynamic data for CBN heterocycle materials for comparison with theory
- develop/identify/optimize conditions for H₂ desorption from these CBN materials
- determine charge/discharge characteristics
- develop more efficient regeneration of spent fuel
- formulate the charged fuel as liquids

Project Summary

Relevance: development of novel hydrogen storage materials with desirable storage parameters and thermodynamics for reversible H₂ absorption and desorption

Approach: coupling of exothermic H₂ desorption from BN with endothermic H₂ desorption from CC in a cyclic system to achieve optimal thermodynamics for H₂ absorption/desorption; distinct from amine-borane and cyclic materials currently under investigation

Progress:

- **developed synthetic tools for CBN heterocycle materials**
- **measured experimental thermodynamic data that corroborate the values predicted by theory**
- **demonstrated regeneration of spent fuel material using H₂, H⁻, and H⁺ sources**
- **developed a First-Fill synthesis of charged fuel**
- **performed preliminary H₂ release studies**

Collaborations: active partnership with CHSCoE members (UA, PNNL, UW)

Future Work:

- further develop the synthesis of CBN Heterocycle Materials (1) and (7)
- complete experimental thermodynamic data for CBN materials
- determine/optimize H₂ charge/discharge characteristics
- develop more efficient regeneration of spent fuel