

2014 DOE Hydrogen and Fuel Cells Program Review

Hydrogen Storage in Metal-Organic Frameworks

P. I. Jeffrey Long

Lawrence Berkeley Nat. Lab., Univ. of California Berkeley
Nat. Inst. of Standards and Technology, General Motors Co.

June 17, 2014

Project ID #: ST103

This presentation does not contain any proprietary, confidential, or otherwise restricted information



NIST



U.S. DEPARTMENT OF
ENERGY

Energy Efficiency &
Renewable Energy

Overview

Timeline

- Start: April 2012
- Finish: March 2015

Budget

- FY13 DOE Funding:
 - \$600k
- Planned FY14 DOE Funding:
 - \$700k
- Total project funding
 - Total Project Value: \$2,625k
 - Cost Share: \$525K
 - DOE Share: \$2,100K
 - DOE Funding Spent*: \$1,533K

*as of 3/31/14

Barriers

- Barrier addressed
 - A. System Weight and Volume

Partners

- LBNL: synthesis and modeling
- NIST: neutron diffraction
(start Oct. 2012)
- GM: high-pressure adsorption
(start July 2012)
- Project lead: Jeffrey Long (LBNL)



NIST



2



U.S. DEPARTMENT OF
ENERGY

Energy Efficiency &
Renewable Energy

Relevance

Project objectives

- Research and development of on-board systems that allow for a driving range greater than 300 miles.
- Materials sought with the potential for meeting the DOE targets of reversible uptake:
 - 2017 targets: 5.5 % H₂ by mass, volumetric capacity of 40 g/L
 - “ultimate full fleet” targets: 7.5 % H₂ by mass, 70 g/L.
- Synthesize new metal-organic frameworks capable of achieving the –15 to –20 kJ/mol adsorption enthalpy required for use as hydrogen storage materials operating under 100 bar at ambient temperatures



NLST



3



U.S. DEPARTMENT OF
ENERGY

Energy Efficiency &
Renewable Energy

Approach

Task 1: Synthesis of Metal-Organic Frameworks
(Jeffrey Long-LBNL)

Task 2: Characterization of Framework-H₂ Interactions
(Craig Brown-NIST)

Task 3: First-Principles Calculations of Hydrogen Binding Enthalpies
(Martin Head-Gordon-LBNL)

Task 4: High-Pressure H₂ Adsorption Measurements
(Anne Dailly-GM)



NIST



4





U.S. DEPARTMENT OF
ENERGY

Energy Efficiency &
Renewable Energy

Approach

Multiple H₂ Binding Sites per Metal

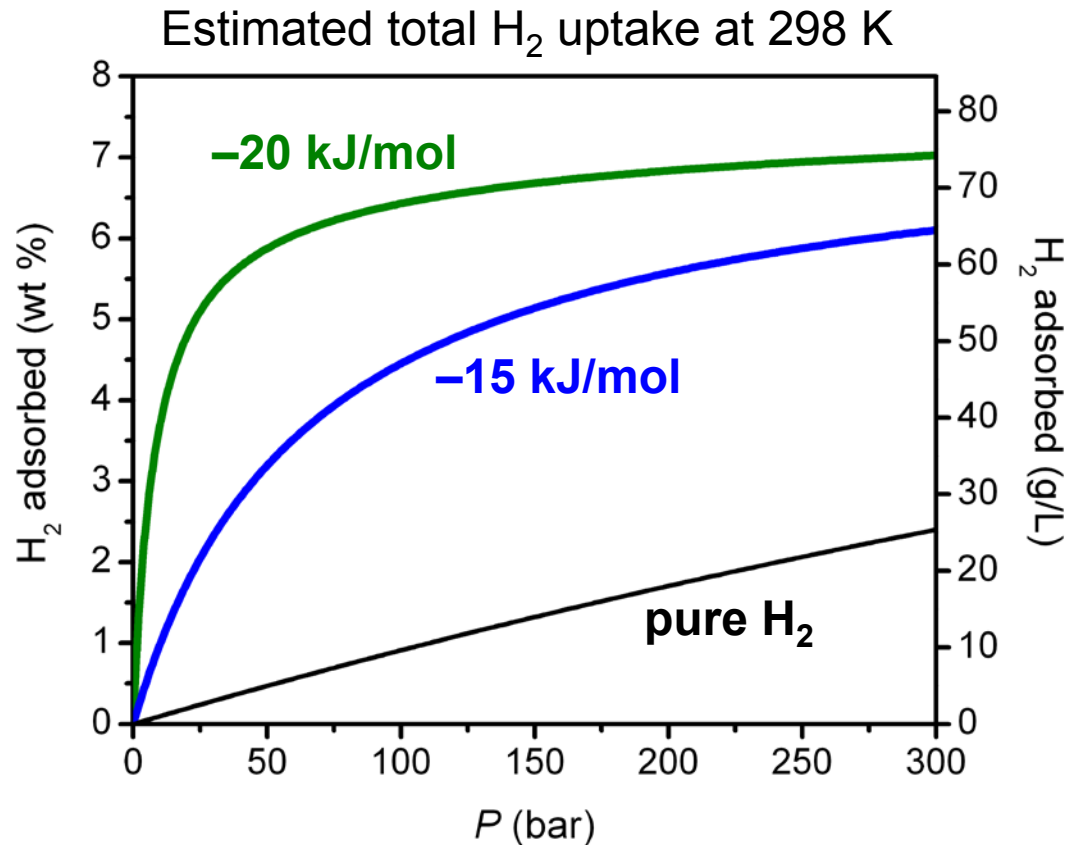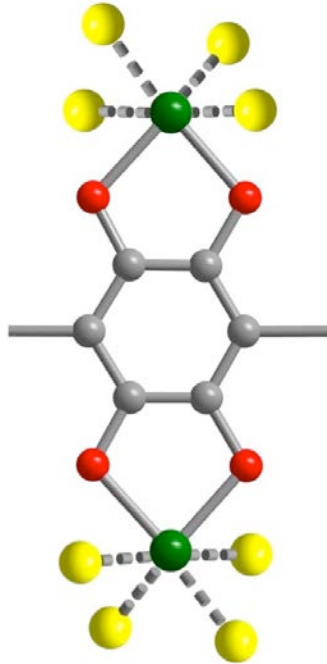

- Create MOFs with exposed M²⁺ or M³⁺ cations, each binding 4 or 5 H₂ molecules
- Hypothetical MOF can meet capacity targets, depending on Mg²⁺ binding enthalpy

Approach: Milestones Tasks 1&2

Due date	Description	% Comp	Status April 2014
03/14	Task 1 (G/N): Synthesis of MOFs with reversible excess H₂ uptake > 2.5 wt %	100%	MOF-74 analogues synthesized which may surpass 2.5 wt %
03/14	Task 1: Preparation of a high-valent MOF with an initial H ₂ adsorption enthalpy greater than 12 kJ/mol	100%	Ni ₂ (<i>m</i> -dobdc) displays H ₂ binding enthalpy of -12.3 kJ/mol
03/14	Task 1: Synthesis of MOFs with the ligands prepared in year 1	100%	3 bipyridine-MOFs synthesized
03/14	Task 1: Demonstration of the post-synthetic insertion of metals into the open chelate sites of these new materials	100%	Single crystal diffractions shows binding of M ²⁺ to the bipy sites
03/14	Task 1: Preparation of at least 2 MOFs with the optimal 7 Å between opposing pore surfaces as predicted with <i>in silico</i> screening	100%	3 dicarboxylate MOFs synthesized with optimal pore size
03/15	Task 1: Demonstration of a MOF with an initial H ₂ adsorption enthalpy greater than the current record of 15.1 kJ/mol	40%	On-track
03/15	Task 1 (G/N): Synthesis of a metal-organic framework with reversible hydrogen uptake greater than 4.5 wt % at 298 K	30%	On-track
03/14	Task 2: Demonstrate that understanding of MOF-H ₂ interactions through inelastic neutron scattering experiments provide new insight	90%	INS meas. on H ₂ in MOF-74 variants; waiting for new materials
03/15	Task 2: Demonstrate the use of quasielastic neutron scattering to help understand the roles of diffusion and entropy in H ₂ binding to MOFs	50%	Experiments underway; analysis underway



NLST



6



U.S. DEPARTMENT OF
ENERGY

Energy Efficiency &
Renewable Energy

Approach: Milestones Tasks 3&4

Due date	Description	% Comp	Status April 2014
12/14	Task 3: Demonstrate the ability to determine H ₂ -metal interactions in realistic systems containing low-coordinate metal cations	25%	Calculation performed for catechol and bipyridine systems
03/15	Task 3: Pre-screen optimal MOF targets by identification of systems that produce an H ₂ binding enthalpy > 20 kJ/mol	12%	Preliminary results indicate a number of potential targets
03/14	Task 4: Demonstration of a correlation between high-pressure measurements and theoretical and spectroscopic predictions	100%	Correlation demonstrated for several MOF-74 variants
06/14	Task 4: Demonstrate the ability to measure H ₂ adsorption in a test material up to 10 cycles at 298 K	25%	On-track
09/14	Task 4: Demonstrate the ability to measure H ₂ adsorption in a test material up to 10 cycles at t° relevant to onboard vehicle applications	10%	On-track
12/14	Task 4: Down select 1 or 2 samples for 100 cycles measurement	0%	Not started
03/15	Task 4: Demonstrate the ability to measure high-pressure H ₂ adsorption in MOFs up to 100 cycles at temperatures relevant to use in onboard vehicle applications	0%	Not started



NLST



7





U.S. DEPARTMENT OF
ENERGY


Energy Efficiency &
Renewable Energy

Accomplishments: Task 1


Synthesis of $\text{Zr}_6\text{O}_4(\text{OH})_4(\text{bpydc})_6$ (UiO-67-bipy)

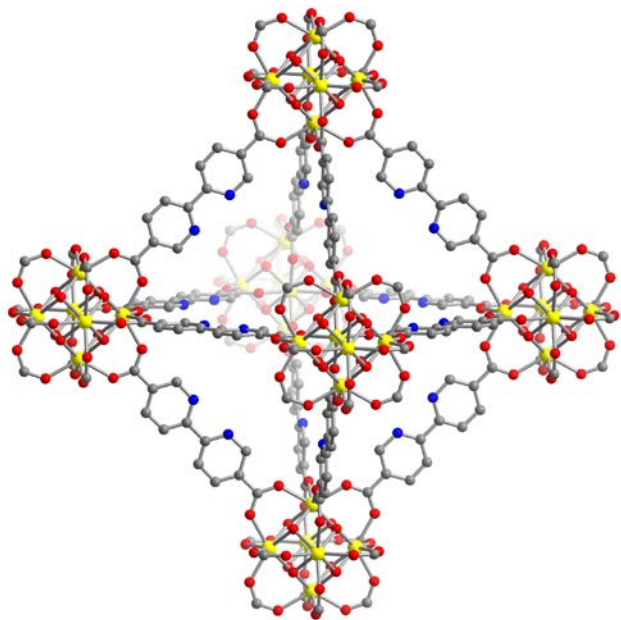

$\text{SA}_{\text{BET}} = 2645 \text{ m}^2/\text{g}$

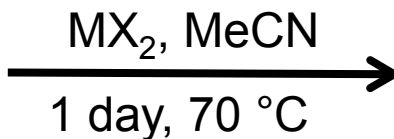

$\text{MX}_2 = \text{CoCl}_2, \text{MnCl}_2, \text{MnBr}_2,$
 $\text{FeCl}_2, \text{FeBr}_2, \text{CuCl}_2, \text{PdCl}_2$


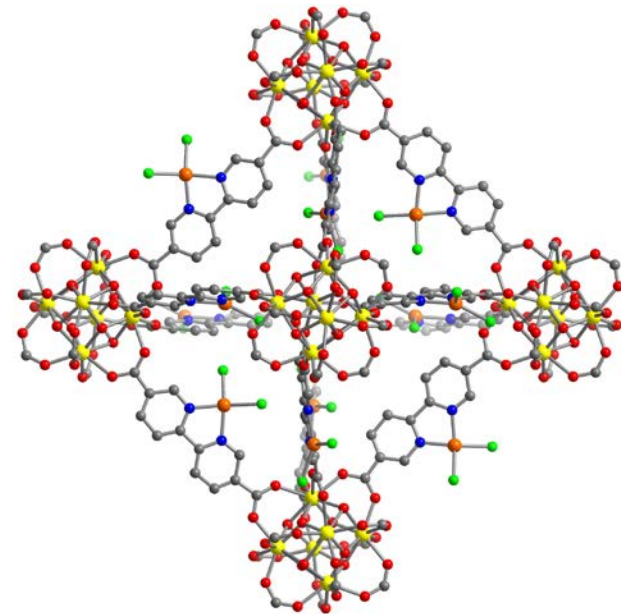


$\text{SA}_{\text{BET}} = 1200\text{-}1800 \text{ m}^2/\text{g}$


- Single crystal X-ray diffraction unambiguously confirms metal insertion
- Gas adsorption experiments are ongoing

Accomplishments: Task 1

Synthesis of Charge Balancing UiO-67-bipy Analog

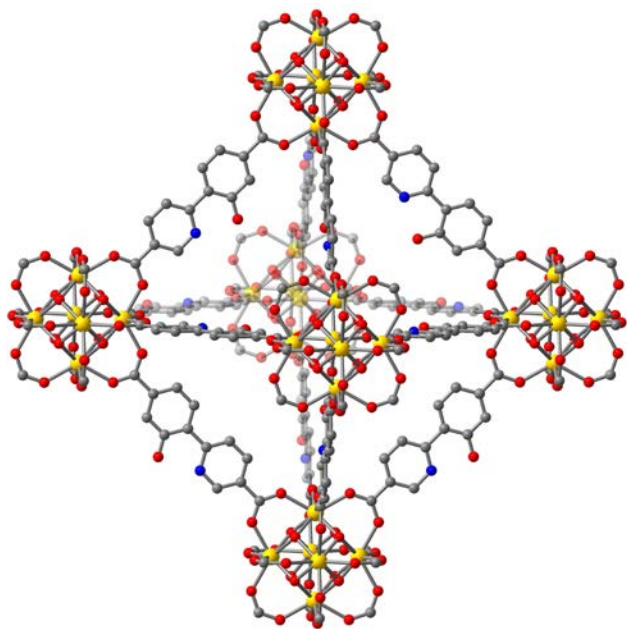

$\text{SA}_{\text{BET}} = 2715 \text{ m}^2/\text{g}$

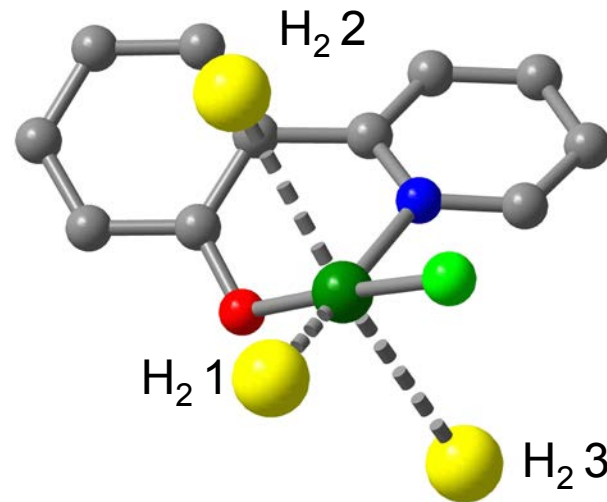

Predicted binding enthalpies:

$\text{H}_2 \text{ 1} = -16.8 \text{ kJ/mol}$


$\text{H}_2 \text{ 2} = -11.8 \text{ kJ/mol}$

$\text{H}_2 \text{ 3} = -9.6 \text{ kJ/mol}$

- Phenol group provides charge balance and access to multiple H_2/M^{2+}
- Robust framework is expected to accommodate high activation temperatures required for full desolvation of Ni^{2+} sites

Accomplishments: Task 1


Synthesis and Characterization of $M_2(m\text{-dobdc})$

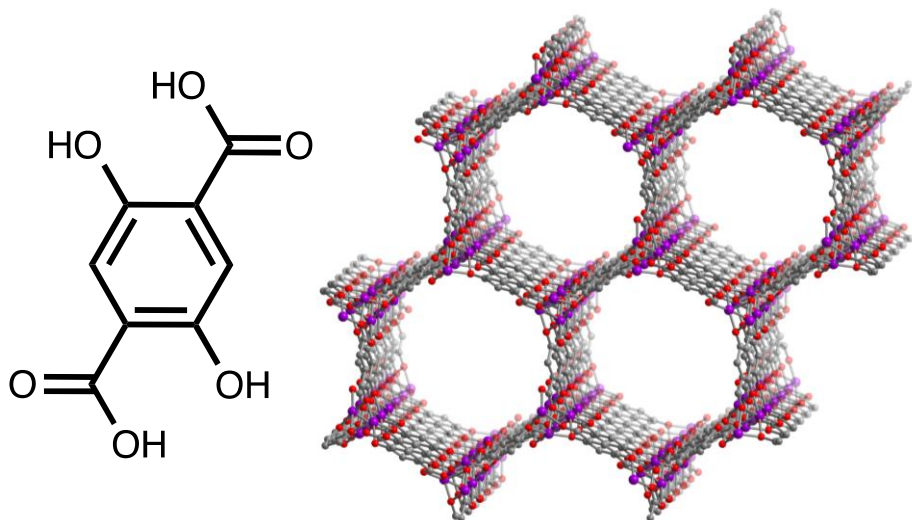

$M_2(\text{dobdc})$

(M = Mg, Mn, Fe, Co, Ni, Cu, Zn)

$SA_{\text{BET}} = 800\text{-}1750 \text{ m}^2/\text{g}$

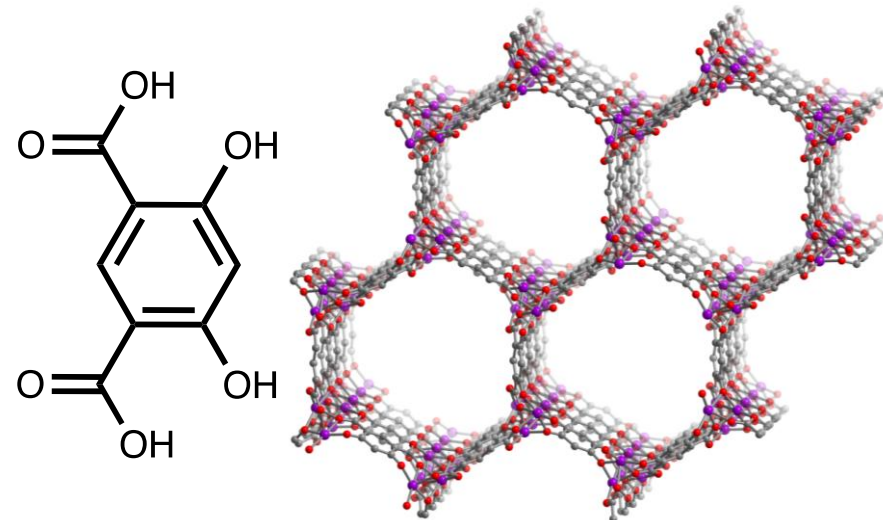

$M_2(m\text{-dobdc})$





(M = Mn, Fe, Co, Ni)

$SA_{\text{BET}} = 1100\text{-}1600 \text{ m}^2/\text{g}$

- Cheaper ligand via direct carboxylation of resorcinol
- Symmetry change of ligand is expected to impact H_2 adsorption properties

Accomplishments: Task 1










Synthesis and Characterization of $M_2(m\text{-dobdc})$

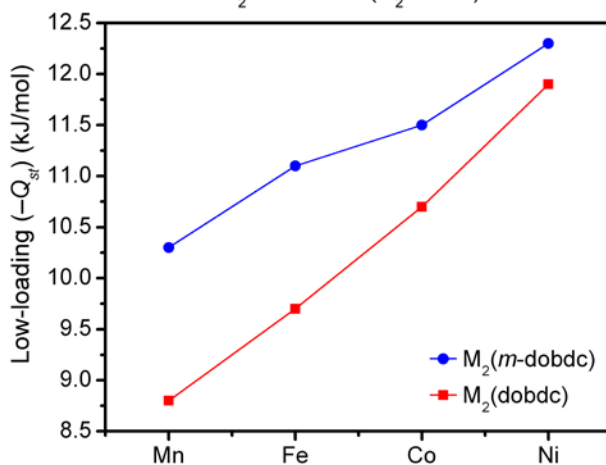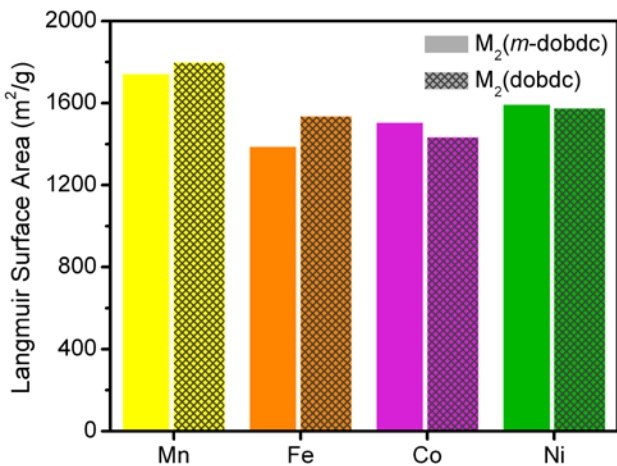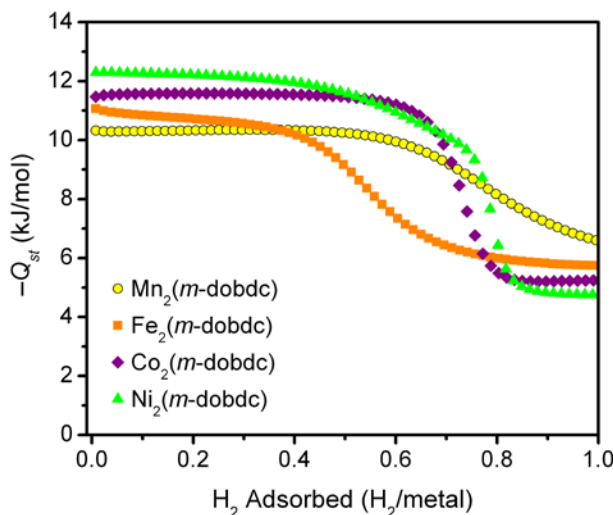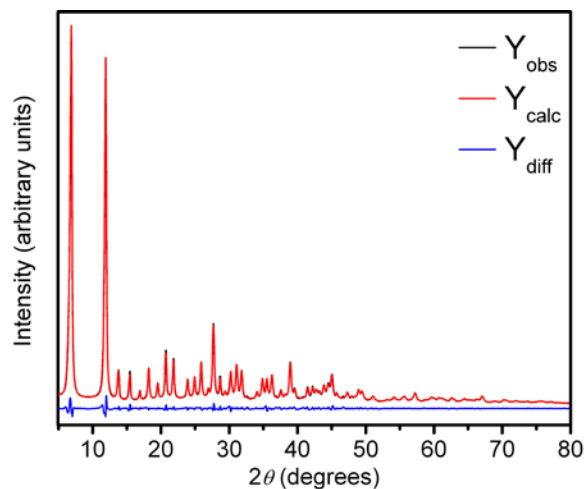

- High crystallinity enabled structure determination via powder x-ray diffraction
- $M_2(m\text{-dobdc})$ features comparable surface area to $M_2(\text{dobdc})$
- $M_2(m\text{-dobdc})$ displays increased isosteric heat of H_2 adsorption

Accomplishments: Task 1


Synthesis of New Charge Balancing Ligands

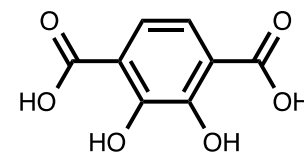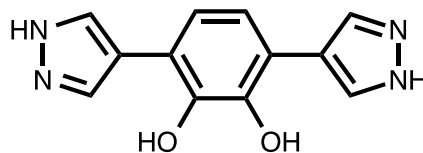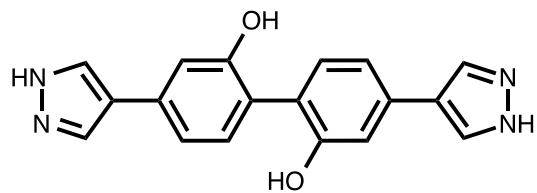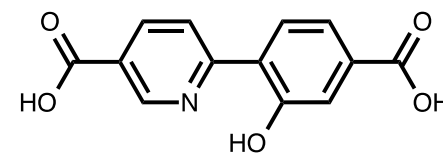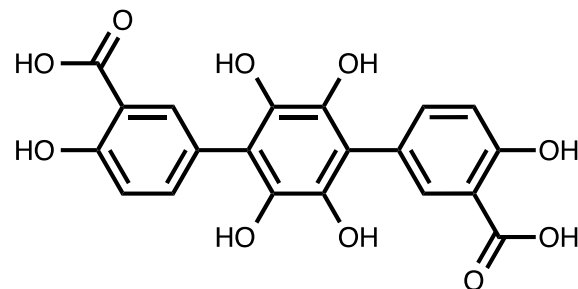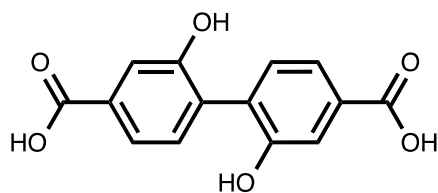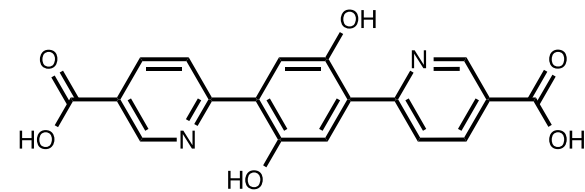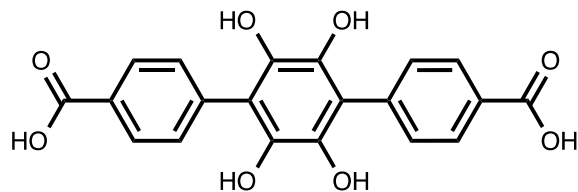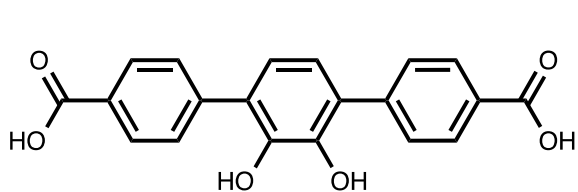


- These new ligands have all been synthesized and applied in MOF formation
- The resulting MOFs will be metallated to give M^{2+} cations with 4 open sites

Accomplishments: Task 1

Protecting Group Strategy

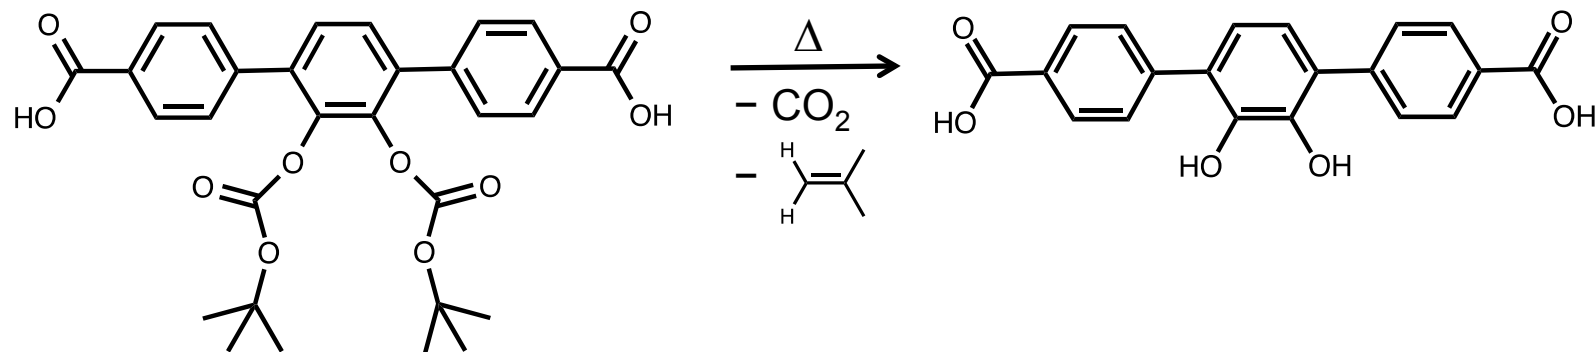


Zn(NO₃)₂·6H₂O
DEF, 2.5 M NaOH
90 °C

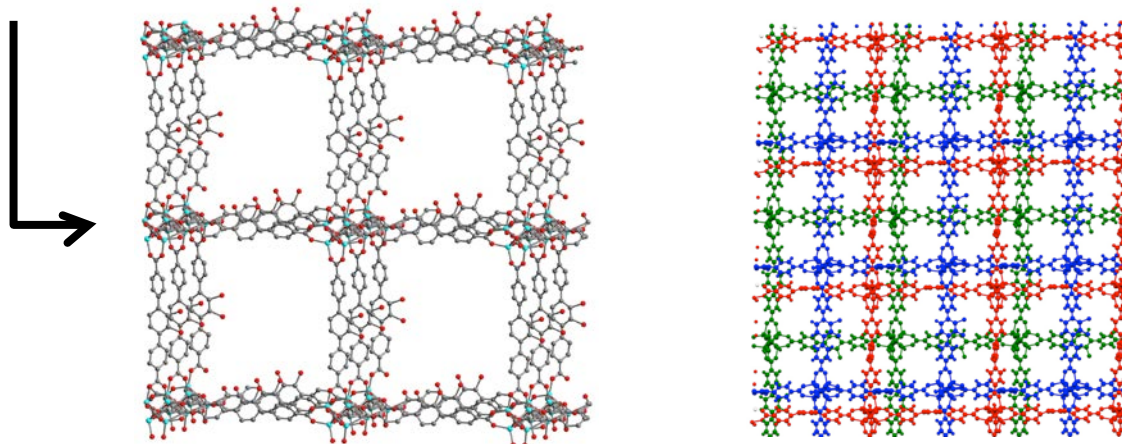

- Protecting groups needed to block chelate sites during synthesis
- Bulky protecting groups may be used to control interpenetration

Accomplishments: Task 1


High-Pressure Adsorption in MOF-74 Analogues

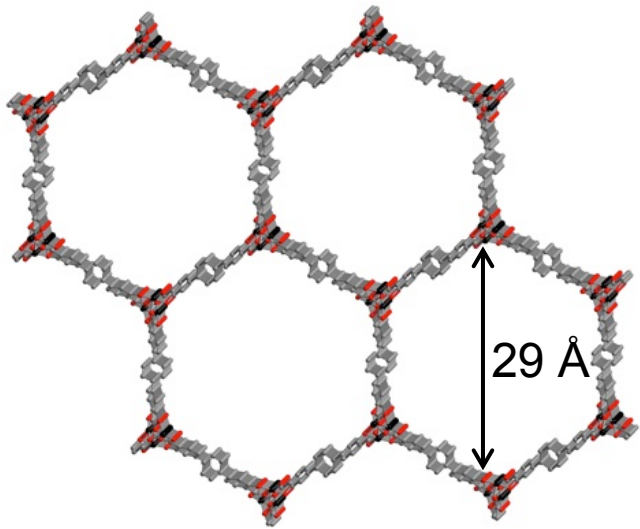

$M_2(\text{dotpdc})$

(M = Mg, Mn, Fe, Co, Ni)


$SA_{\text{BET}} = 2700\text{-}3600 \text{ m}^2/\text{g}$

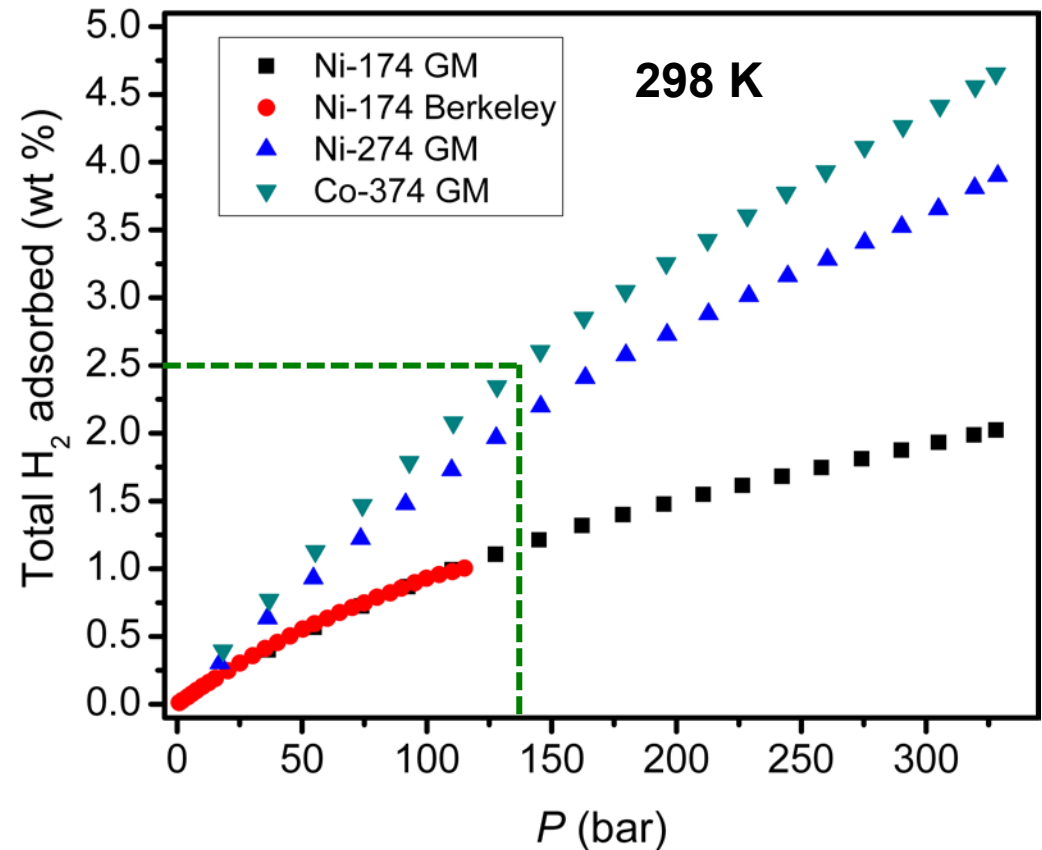


- $\text{Co}_2(\text{dotpdc})$ reaches 2.5 wt % at 298 K and 140 bar
- $\text{Mg}_2(\text{dotpdc})$ is expected to reach 2.5 wt % by 100 bar

Accomplishments: Task 2

Neutron Powder Diffraction: D₂ in Co(*m*-dobdc)

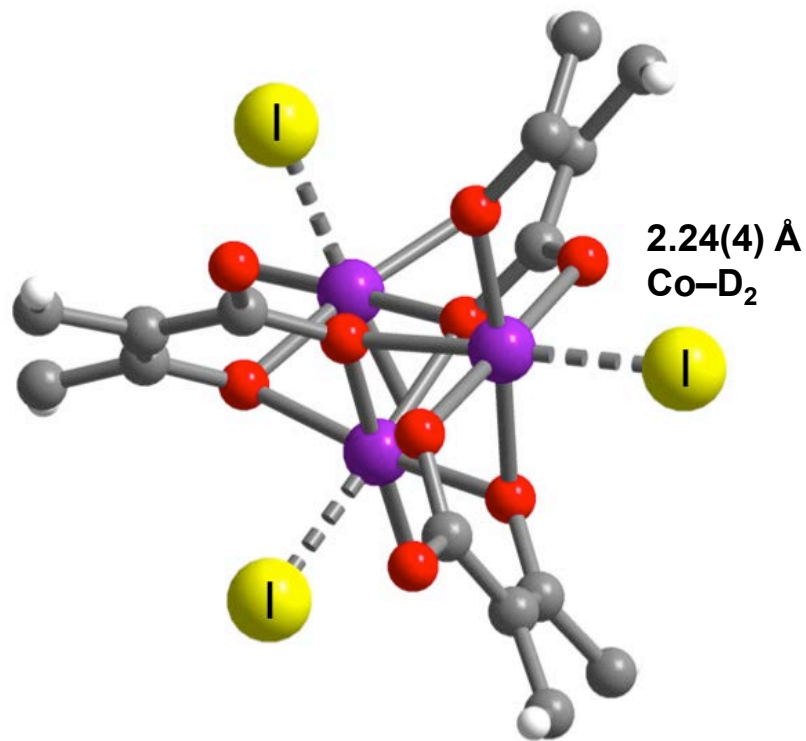



Co(*m*-dobdc) loaded with 0.75 D₂:Co
Initial adsorption at metal sites with Co...D₂
distance 2.24(4) Å

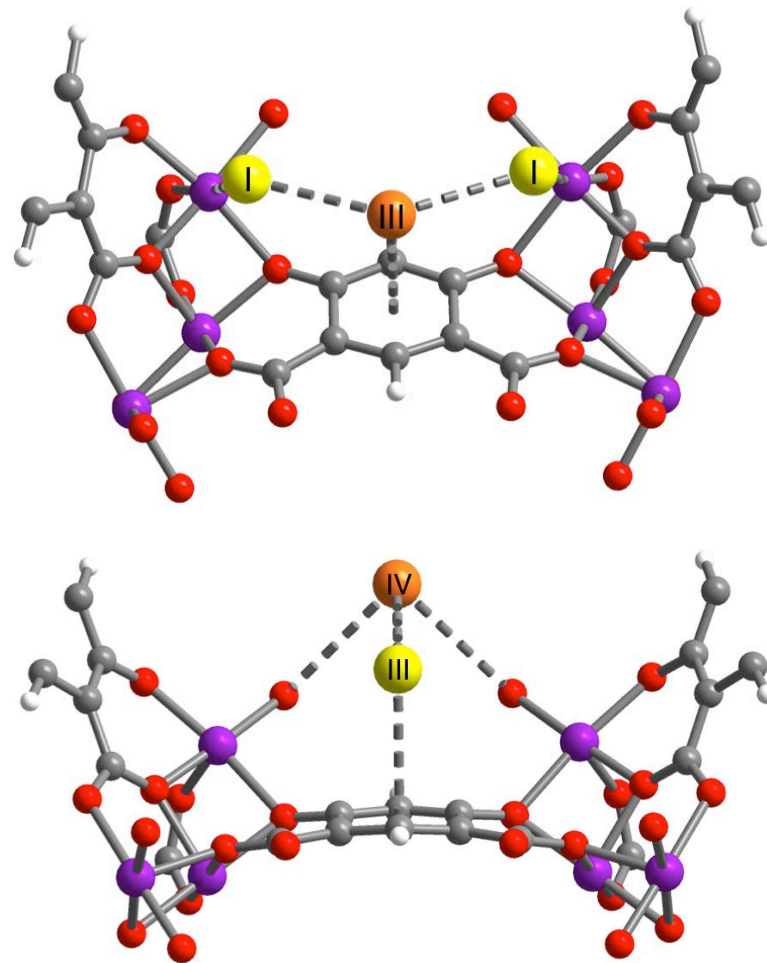

Accomplishments: Task 2

Neutron Powder Diffraction: D₂ vs H₂

First structure for H₂ adsorbed in a MOF
Typically D₂ is used due to much lower inelastic scattering cross section

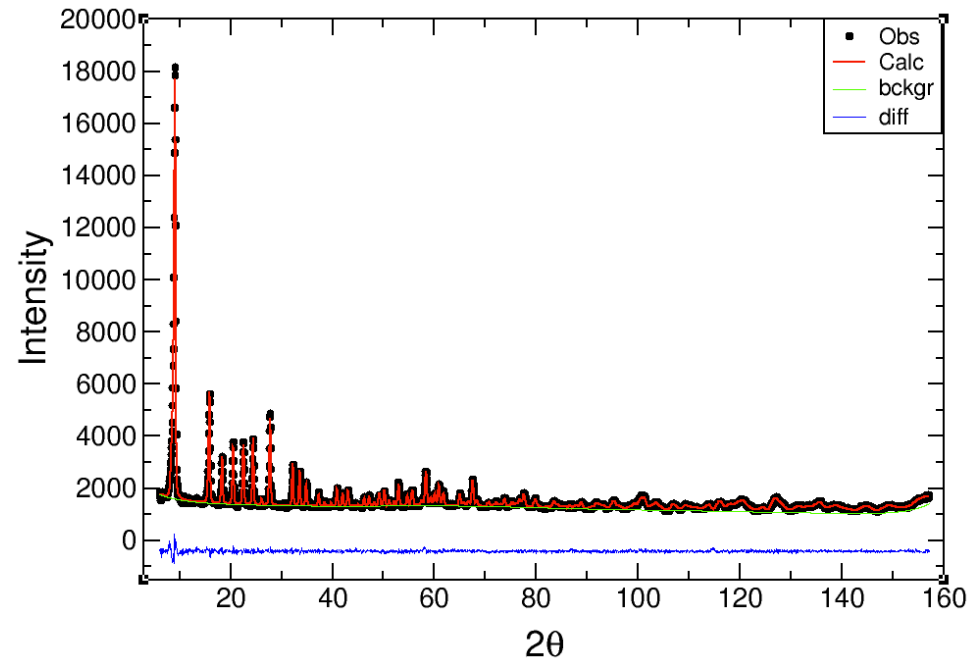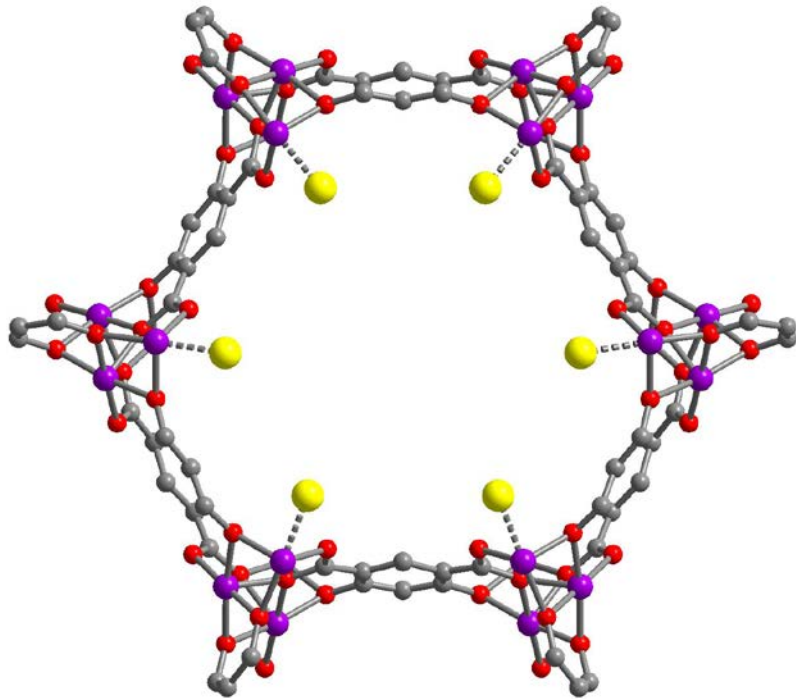


Low loading (0.5 per metal) binding sites
are the same with slight distance difference

$$\text{Co—D}_2 = 2.23(5) \text{ \AA}$$

$$\text{Co—H}_2 = 2.27(3) \text{ \AA}$$

Accomplishments: Task 2


Neutron Powder Diffraction: High Pressure D₂ Adsorption

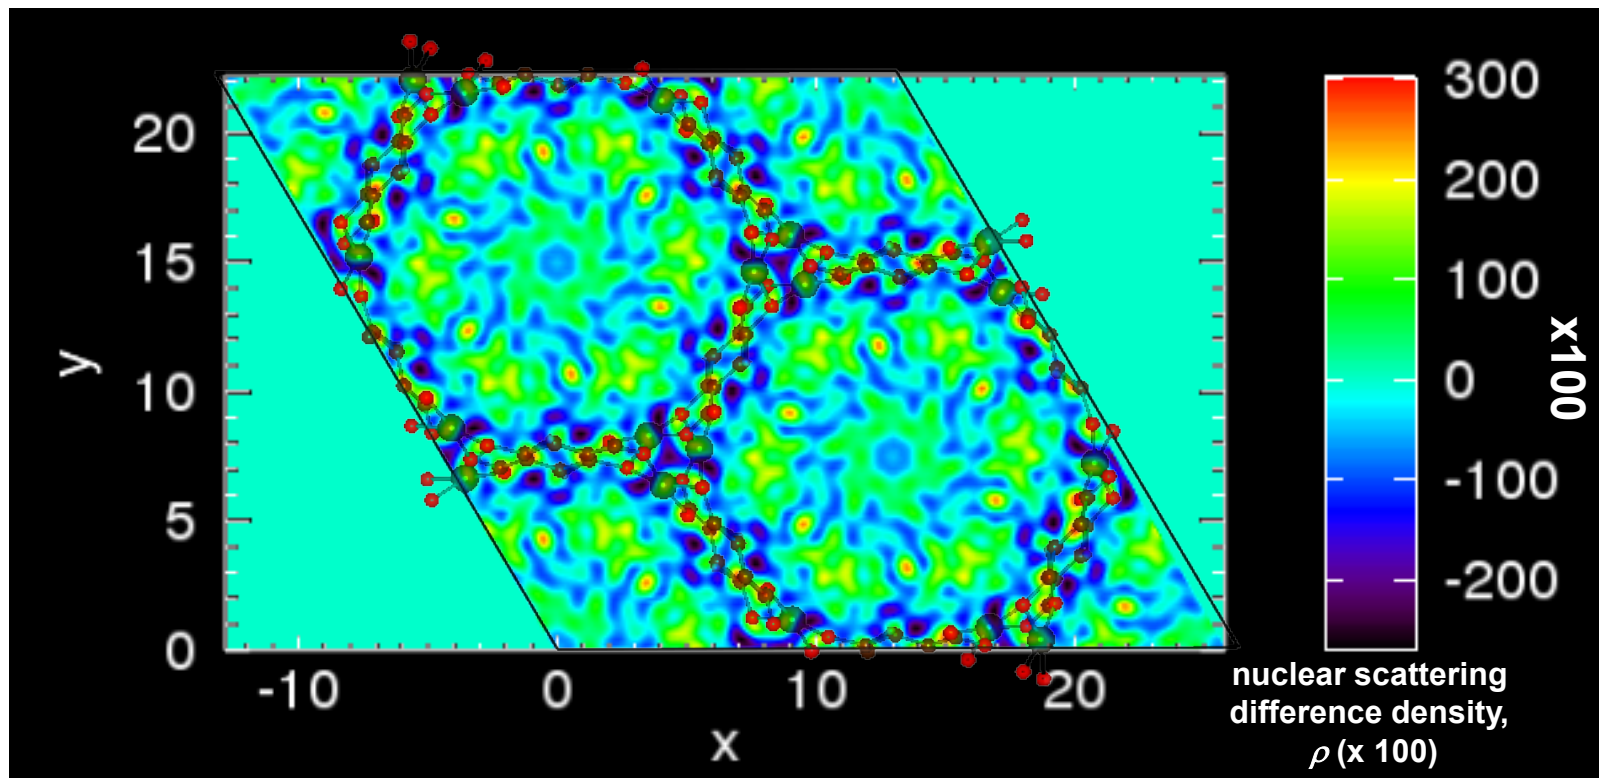


- Difference Fourier map obtained from pattern of 90 bar D₂ in Zn(dobdc) at 77 K
- Attempting to image hydrogen density in pore at relevant pressures and temps
- Maximum-Entropy data interpretation and measurements are ongoing

Accomplishments: Task 2


Inelastic Neutron Scattering Data for $M_2(m\text{-dobdc})$

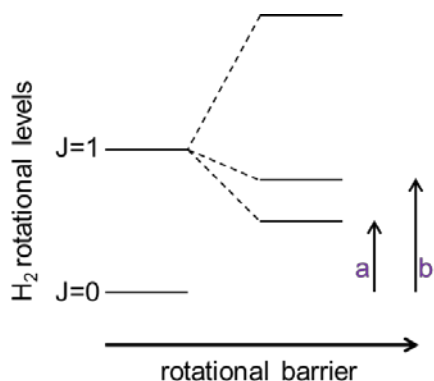

Data from BT-4 and DCS, NIST
Measured at 10 K

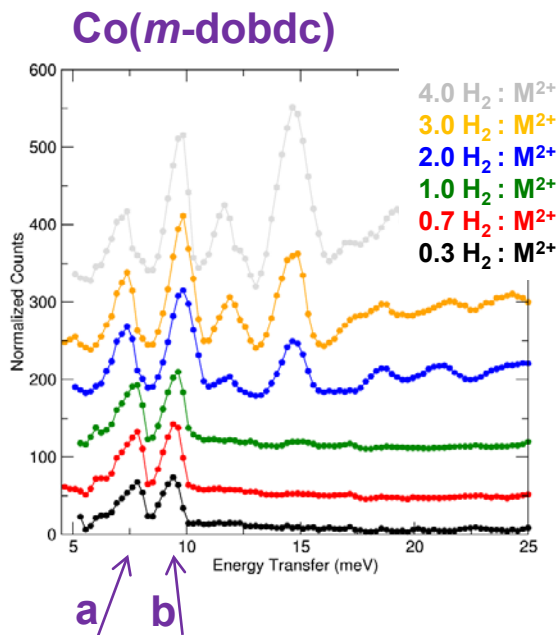

Measured vs. Theoretical momentum transfer dependence of H_2 rotations

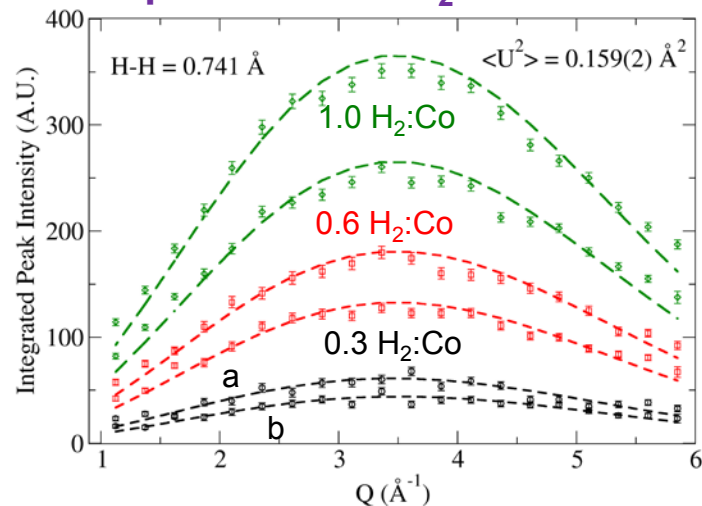


$$I(Q) \propto e^{(-Q^2 \langle u^2 \rangle / 3)} j_1(d_{HH} Q / 2)^2$$


- Rotational barrier at first adsorption site indicates that the $m\text{-dobdc}$ materials have similar characteristics compared to dobdc materials
- Local adsorption potential is weaker with further filling
- Correlates with diffraction and isotherm data
- Q -dependence indicates an almost ideal H_2 molecule adsorbed at the metal

Accomplishments: Task 3


Calculation of Ligand-H₂ Interactions

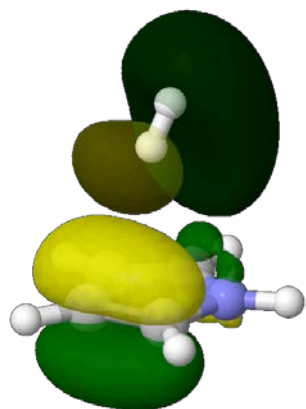


Pyrrole
-2.07 kJ/mol

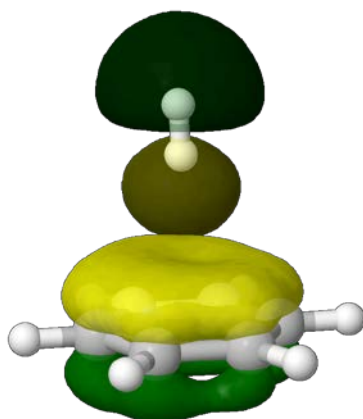

Benzene
-1.42 kJ/mol

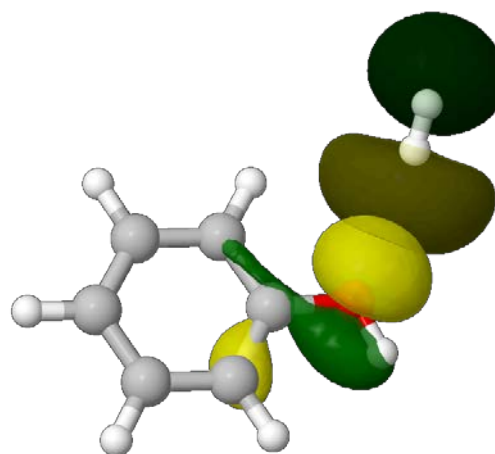

Phenol
-0.93 kJ/mol

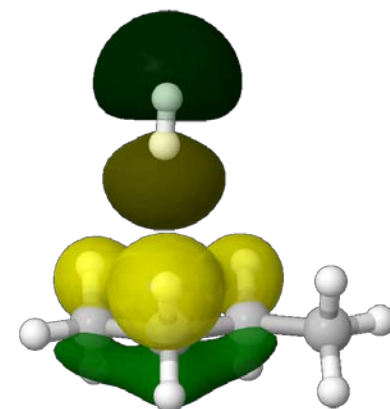


Butene
-1.35 kJ/mol

- Nonnegligible charge transfer between bare ligand/H₂
- To maximize H₂ adsorption enthalpy both metal-H₂ and ligand-H₂ interactions must be considered


Accomplishments: Task 3

Calculation of H₂ Binding Enthalpies



Mg-catechol
-19.2 kJ/mol

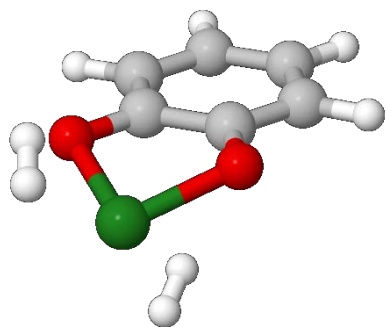

Ca-catechol
-15.5 kJ/mol

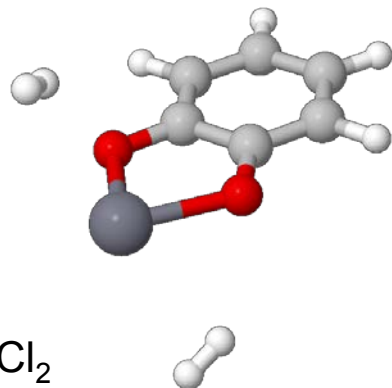

bipy-CuCl₂
-6.6 kJ/mol

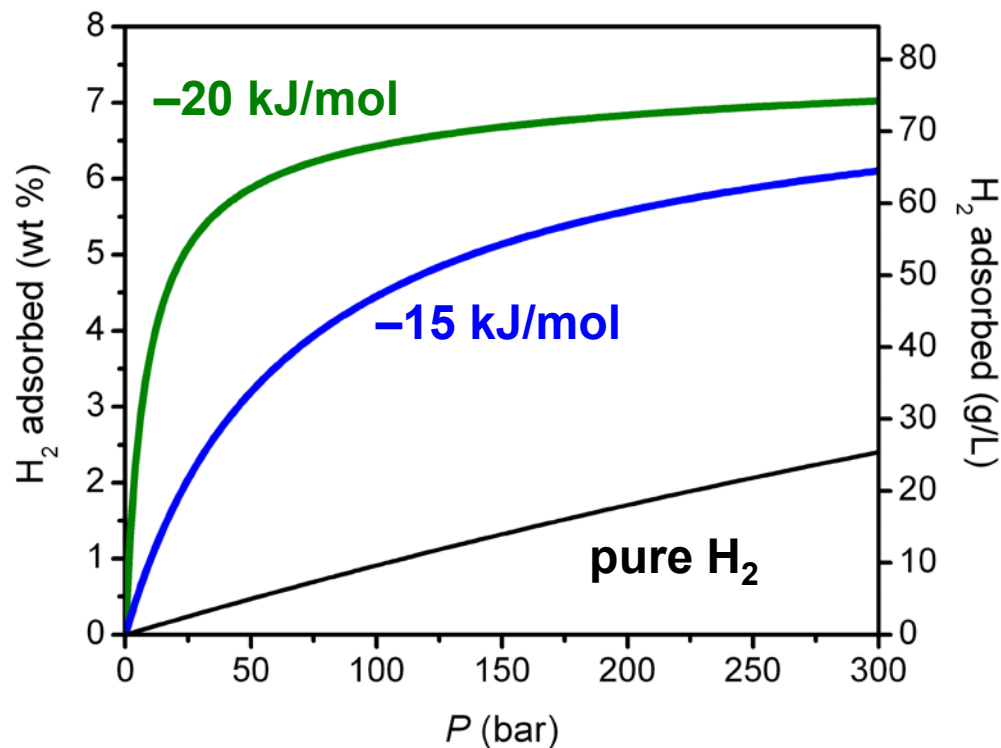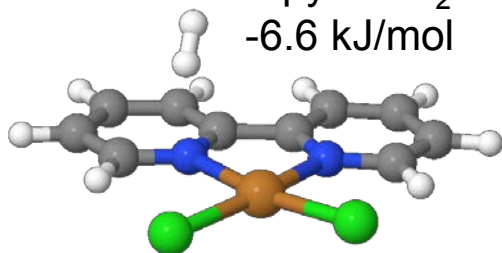


- Calculated average H₂ binding enthalpies for free Mg- and Ca-catechols indicate 15-20 kJ/mol are attainable
- Although metals coordinated to bipyridine have two open coordination sites the predicted H₂ binding enthalpy is low

Accomplishments: Task 4

High Pressure H₂ Adsorption System


System Specifications

- Max operating pressure: 344 bar
- Thermoelectric temperature control
- Large sample capacity (~500 mg)

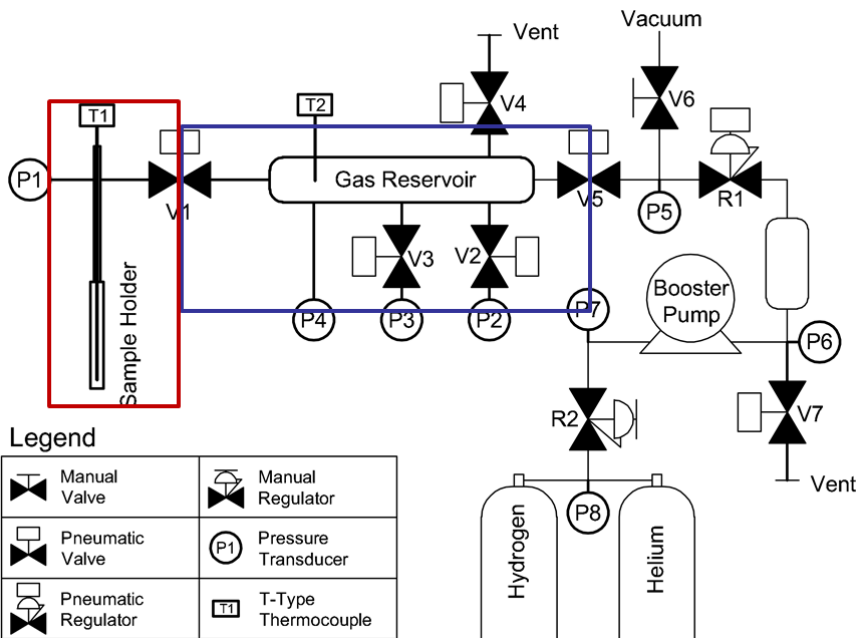

Challenges of 350 bar H₂ measurements

- Careful system calibration
- 0.05 cm³ reference volume error results in 0.5 mmol deviation at 350 bar
- 0.5 g of MSC-30 adsorbs ~3 mmol H₂ at 350 bar and 298 K

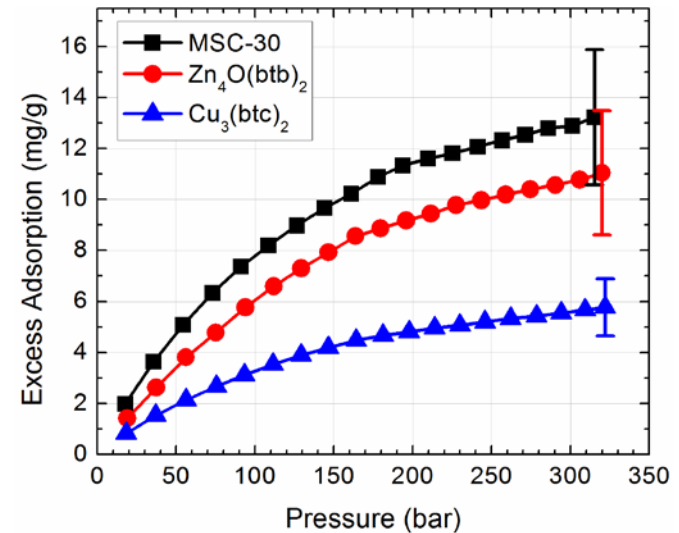


Accomplishments: Task 4

Evaluation of Materials

Adsorption Enthalpy from One Isotherm



- Apply van't Hoff formula directly to the Dubinin-Astakhov model
- Empirical temperature independent constants are used
- Results for benchmark materials are consistent with expectations

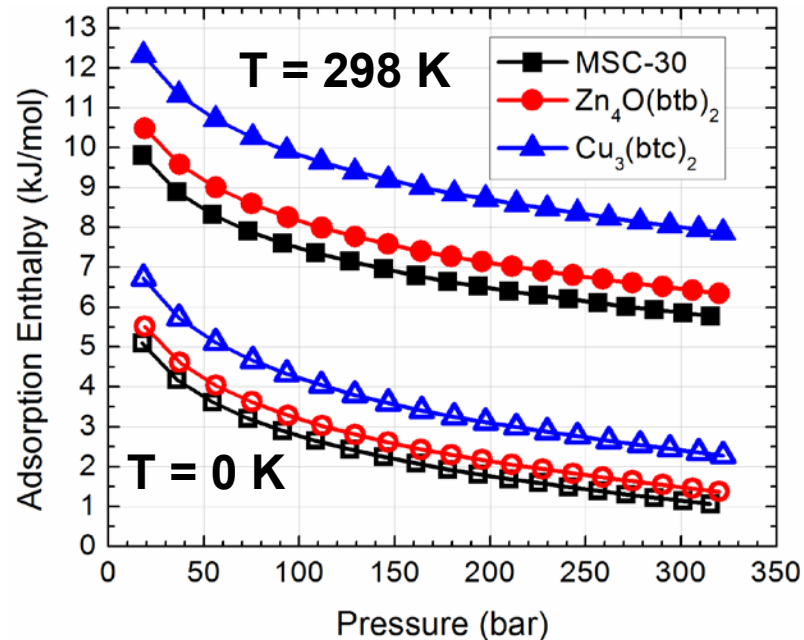

Am. J. Analytical Chem. **2013**, 4, 8-16.

Accomplishments: Task 4

Evaluation of New Materials

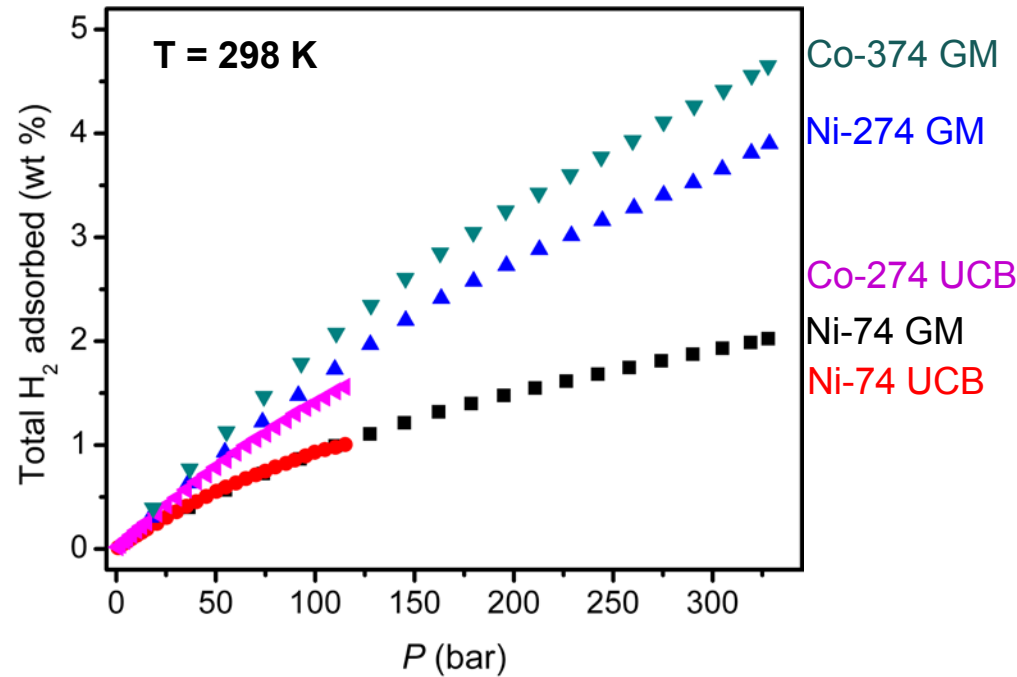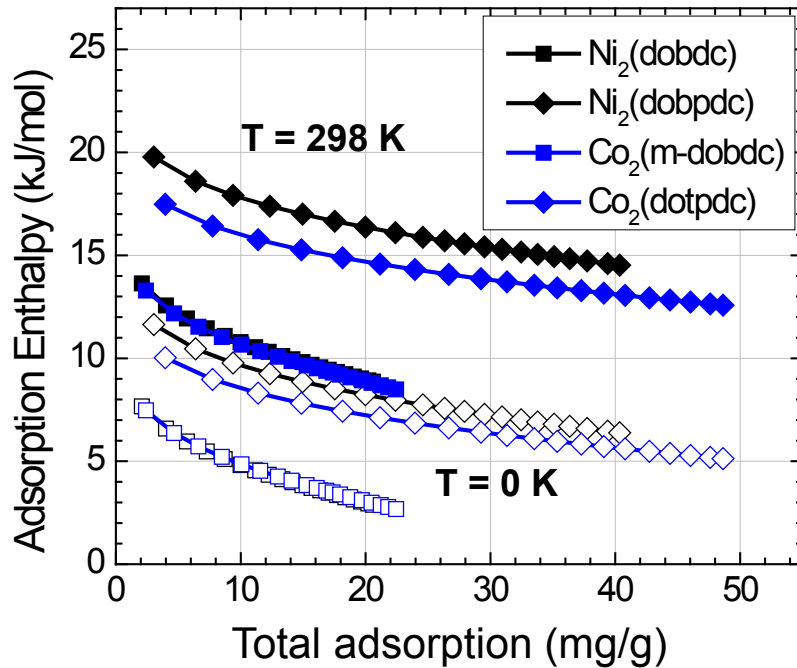

- Expanded MOF-74 analogues feature increased gravimetric H₂ uptake
- M₂(dotpdc) frameworks reach 2.5 wt. % total at 298 K, 140 bar

Accomplishments and Progress: Responses to Previous Year Reviewers' Comments

- As specified on Slide 3, our focus is on the creation of materials that can help meet the 2017 system capacity targets of 5.5% H₂ by mass, volumetric capacity of 40 g/L
- We have in fact collected H₂ uptake at both low and high pressures and various temperatures for dozens of new MOFs, but these results were summarized rather showing the isotherms owing to presentation time restrictions. A few selected data sets are now depicted Technical Back-Up Slides 31-34.
- Our overall strategy, as summarized on Slide 5, is to create materials with a high-density of open M²⁺ or M³⁺ cation sites, each capable of binding 4 or 5 H₂ molecules. This is the only viable route we see to meeting the volumetric capacity target of 40 g/L in a MOF.
- Our roadmap to accomplishing this involves the synthesis of thermally robust MOFs containing anionic chelating sites that can then be metallated and fully activated.
- We agree that the very high-pressure measurement system at GM is unnecessary if we achieve our goals. However, the instrument has already been installed and it enables validation and extension of the high-pressure data collected at Berkeley.



NLST



24



U.S. DEPARTMENT OF
ENERGY

Energy Efficiency &
Renewable Energy

Collaborations

Project team within DOE Fuel Cell Technologies Office:

- Lawrence Berkeley National Laboratory (prime, National Lab.)/UC Berkeley:
 - Jeffrey Long: Synthesis and basic characterization of MOFs
 - Martin Head-Gordon: Calculation and prediction of H₂ binding energies
- National Institute of Standards and Technology (sub, National Lab.):
 - Craig Brown: Neutron diffraction and neutron spectroscopy
- General Motors Company (sub, Industry):
 - Anne Dailly: Measurement of high-pressure H₂ uptake capacity

Additional collaborations:

- Variable-temperature infrared spectroscopy with *in situ* H₂ dosing
 - Silvia Bordiga (University of Turin), Stephen FitzGerald (Oberlin College)
- Synthesis and metallation of porphyrin-containing MOFs
 - T. David Harris (Northwestern University)



NIST



25



U.S. DEPARTMENT OF
ENERGY

Energy Efficiency &
Renewable Energy

Remaining Challenges and Barriers

- Charge balancing ligands have been realized, however, optimal metallation and activation procedures need to be discovered.
- Correlation between OSAD program selected materials and experimentally promising frameworks needs to be realized.
- Gravimetric storage capacity targets have been achieved at pressures higher than 100 bar and/or temperatures below 298 K. New Mg^{2+} based materials should address these issues.
- While theoretical predictions have suggested optimal metallation targets, experimental realization must be achieved to confirm theoretical results.

Proposed Future Work

Task 1: Synthesis of Metal-Organic Frameworks

- Determine optimal metal-insertion and activation conditions for pyridine/phenol ligand
- Scale up synthesis of catechol containing MOFs and insert metal cations
- Complete synthesis of expanded MOF-74 analogues with Mg^{2+}
- Continue synthesis of catechol based ligands for metal insertion.

Task 2: Characterization of Framework- H_2 Interactions

- Solve structure of $Zr_6O_4(OH)_4(bpydc)_6(PdCl_2)_6$
- Complete neutron powder diffraction experiments on this material as 2 H_2 molecules per Pd^{2+} should be possible
- Continue inelastic neutron scattering experiments
- Perform quasielastic neutron diffraction experiments to study diffusion and entropy effects on H_2 adsorption

Proposed Future Work

Task 3: First-Principles Calculations of Hydrogen Binding Enthalpies

- Explore H₂-Metal interactions in real systems that have been realized experimentally
- Determine optimal metallation conditions for charge balancing ligands, investigating solvation effects solvent binding enthalpies.
- Pre-screen optimal targets to identify potential H₂ binding sites greater than 20 kJ/mol.

Task 4: High-Pressure H₂ Adsorption Measurements

- Measure high-pressure H₂ adsorption on samples up to 10 cycles.
- Down select 1-2 materials for 100 adsorption/desorption cycles.
- Test high performing MOFs for 100 cycles up to 350 bar



NLST



28



U.S. DEPARTMENT OF
ENERGY

Energy Efficiency &
Renewable Energy


Summary

- Expanded MOF-74 analogues have achieved 2.5 wt.% total adsorption at 140 bar
- A new mixed pyridine/phenol ligand has been incorporated into a zirconium based framework and has been shown to bind divalent metals.
- Four MOF-74 isomers have been synthesized and characterized and show increased H₂ binding enthalpies.
- Neutron diffraction experiments have been performed using H₂.
- Theoretical calculations have been used to predict metallation targets.
- High-pressure isotherms have been used to calculate H₂ binding enthalpies up to 320 bar.

Capacity	2012	2013	2014	2017*	Ultimate*
Gravimetric	0.016 kg H ₂ /kg adsorbent	0.016 kg H ₂ /kg adsorbent	0.022 kg H ₂ /kg adsorbent	0.055 kg H ₂ /kg system	0.075 kg H ₂ /kg system
Volumetric	0.011 kg H ₂ /L adsorbent	0.011 kg H ₂ /L adsorbent	0.011 kg H ₂ /L adsorbent	0.040 kg H ₂ /L system	0.070 kg H ₂ /L system



*DOE targets

Technical Back-Up Slides

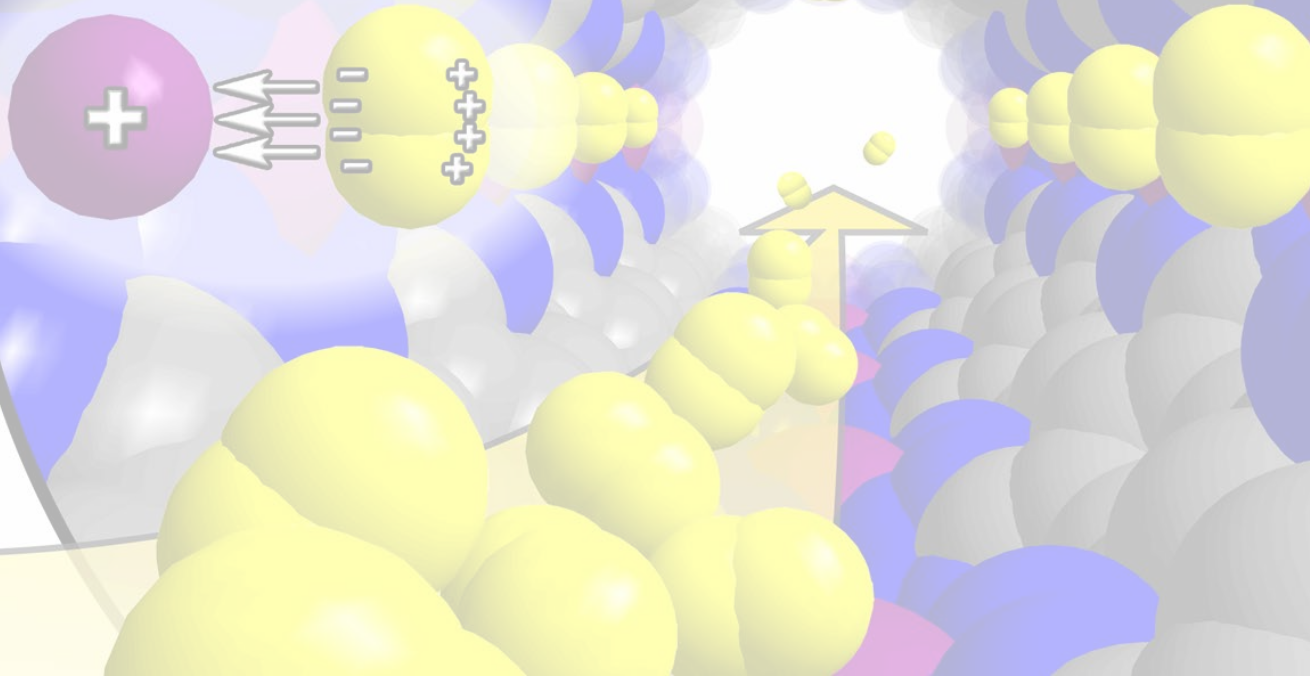


Adsorption Isotherms

$M_2(m\text{-dobdc})$

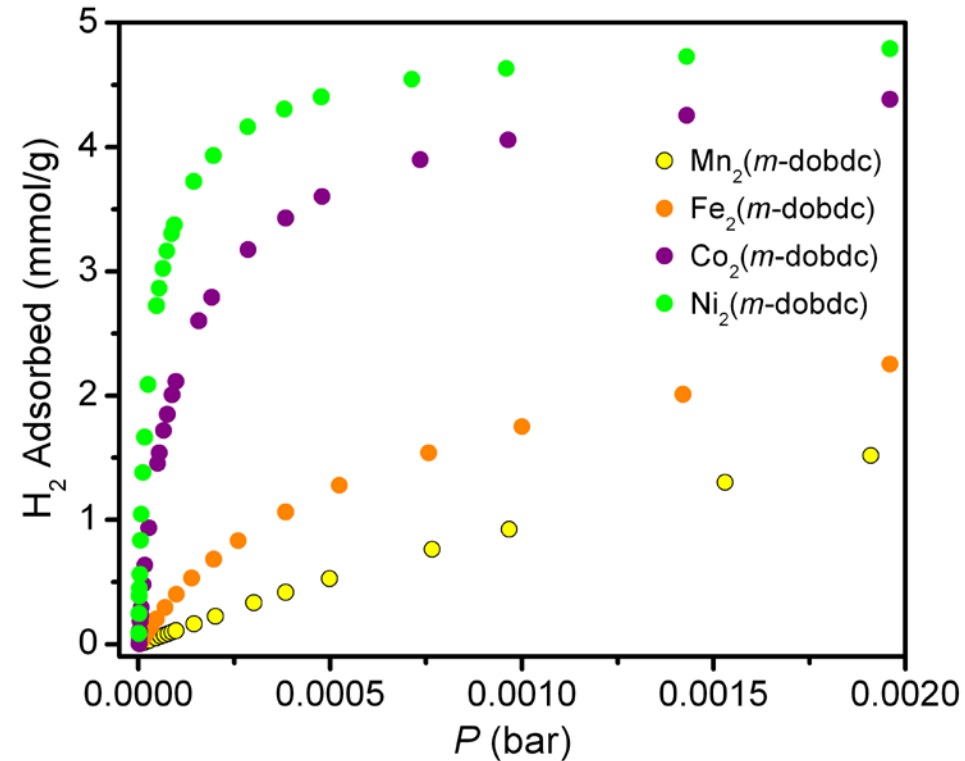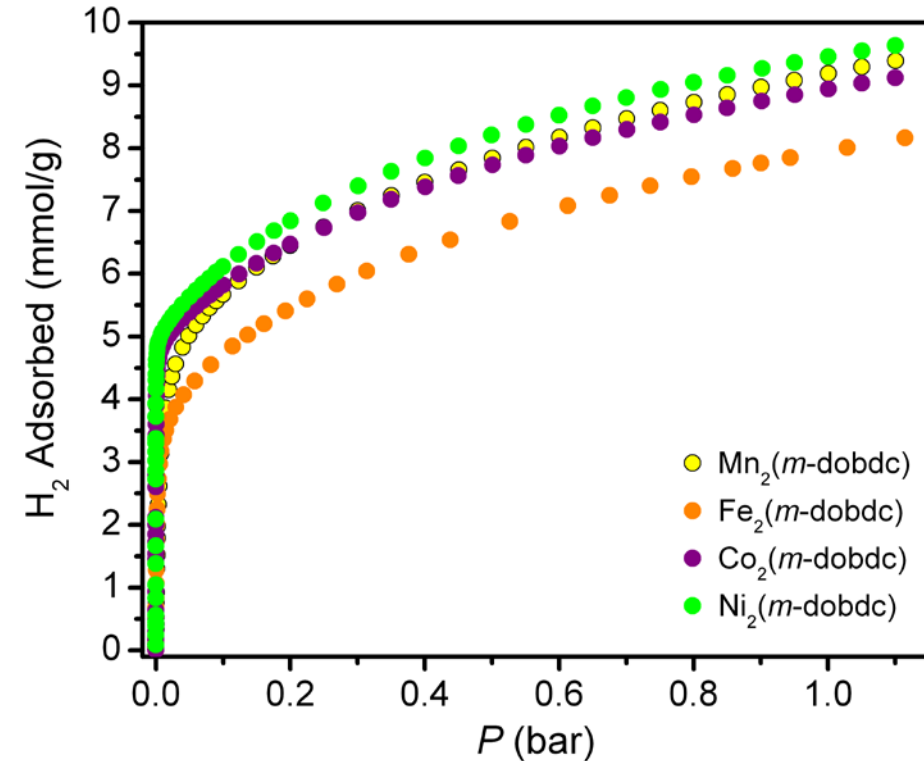

- Although $-Q_{st}$ follows $Ni > Co > Fe > Mn$, saturation capacity at 77 K and 1.2 bar doesn't follow the trend as surface area factors into total uptake


Adsorption Isotherms

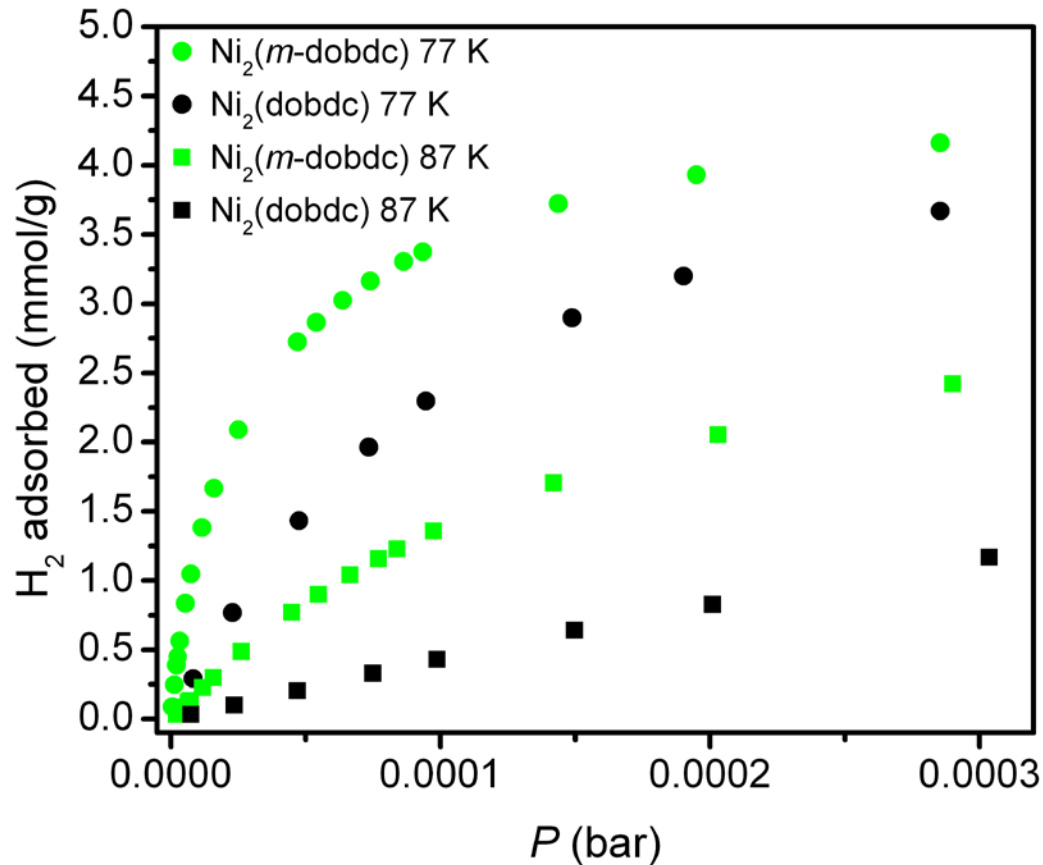

- Adsorption isotherms for Ni₂(*m*-dobdc) are steeper than the *para* isomer, indicating a stronger M-H₂ interaction.

Adsorption Isotherms


$M_2(\text{dobdc})$ vs. $M_2(\text{dobpdc})$

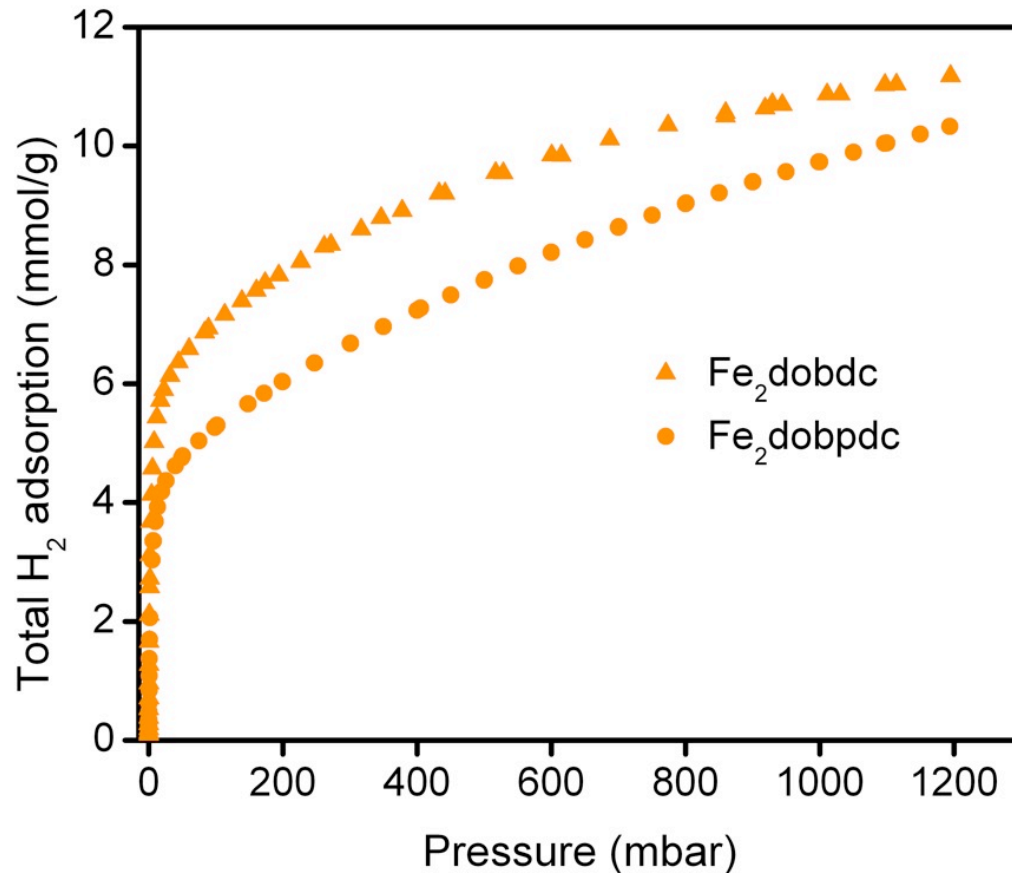

- Given the larger density of coordinatively-unsaturated metal sites, $M_2(\text{dobdc})$ displays higher H_2 capacity at 1.2 bar and 77 K.

Adsorption Isotherms


$M_2(\text{dobdc})$ vs. $M_2(\text{dobpdc})$

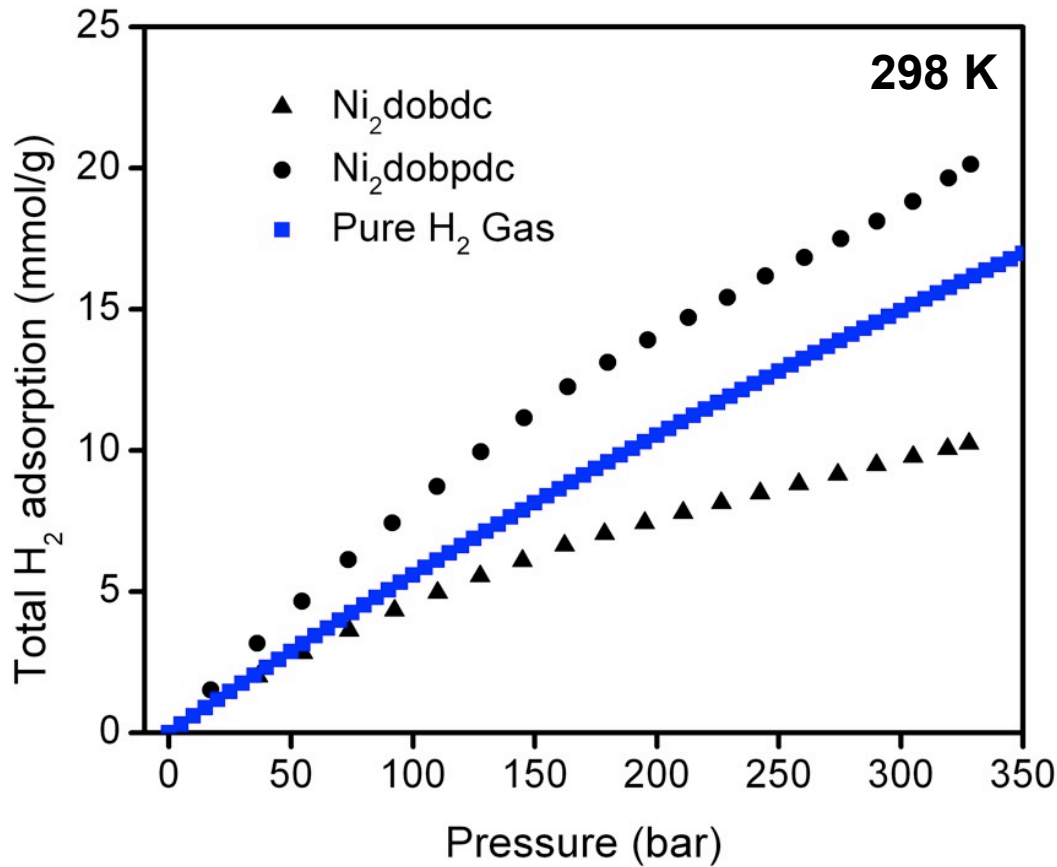


- At high pressure, $M_2(\text{dobpdc})$ significantly outperforms $M_2(\text{dobdc})$ and offers a significant improvement over compressed H_2 .

Optimum Pore Sizes for Hydrogen Storage

77 K

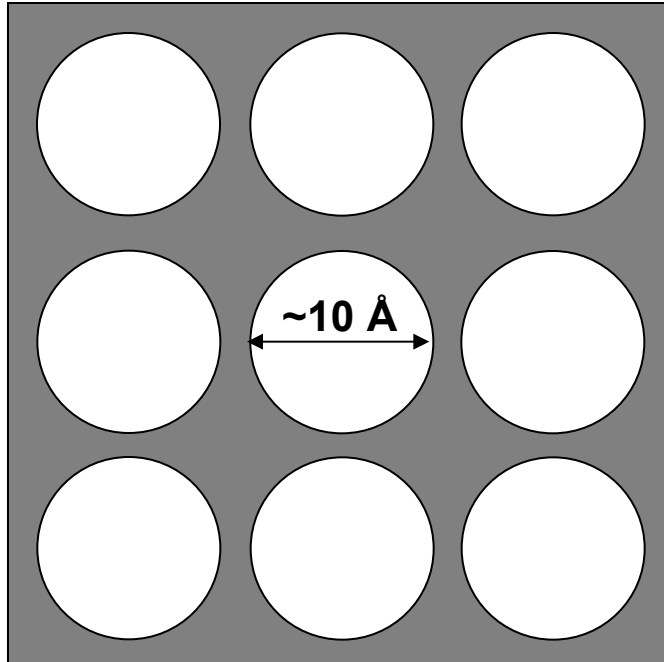


298 K

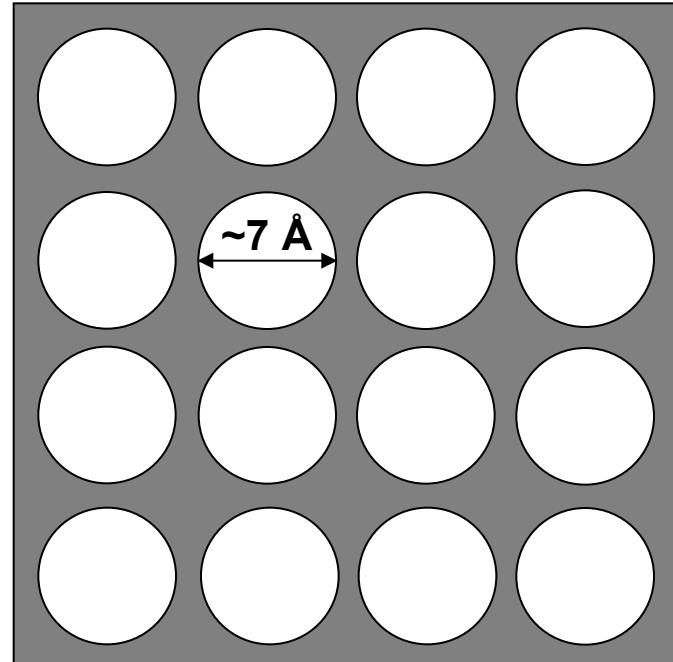

□ Calculated using Monte Carlo simulations with both cylindrical and slit pores




Rzepka, Lamp, de la Casa-Lillo J. *Phys. Chem. B* **1998**, 102, 10894

Geometric Calculation of Opposing Wall Distances

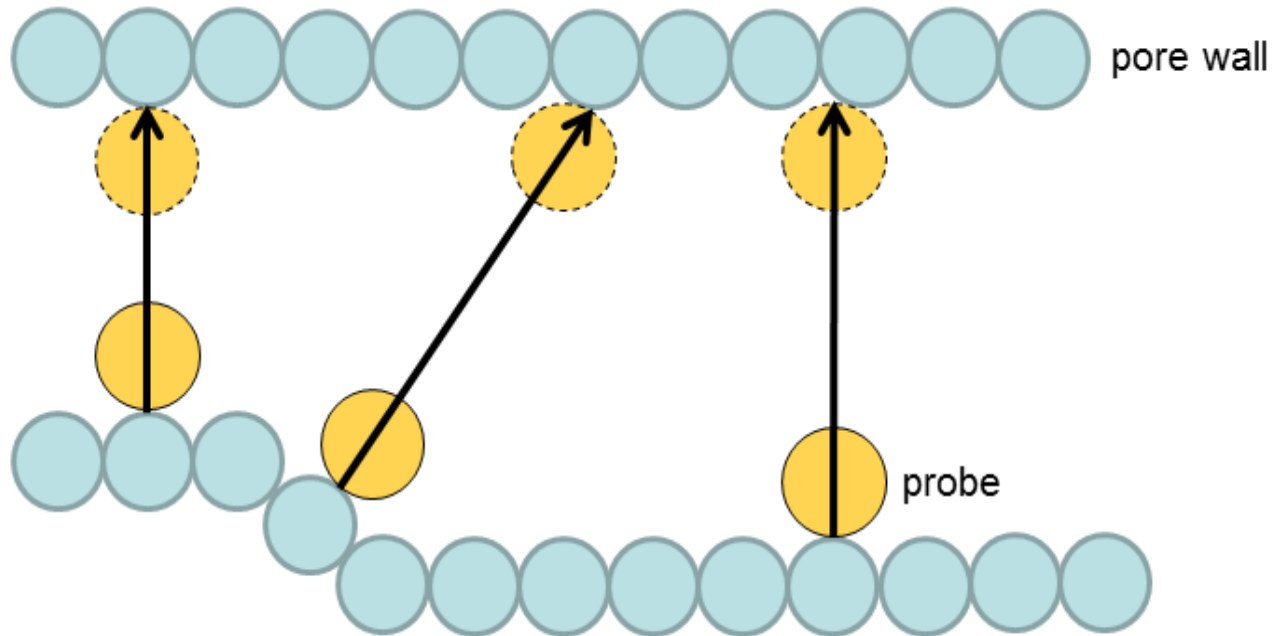


- Probe is inserted on the pore surface, and moved away in a direction normal to the surface until it collides with the opposing wall
- This is repeated until the entire pore surface has been traversed by the algorithm to create a distribution of opposing wall distances

Opposing Surface Area Distribution (OSAD)

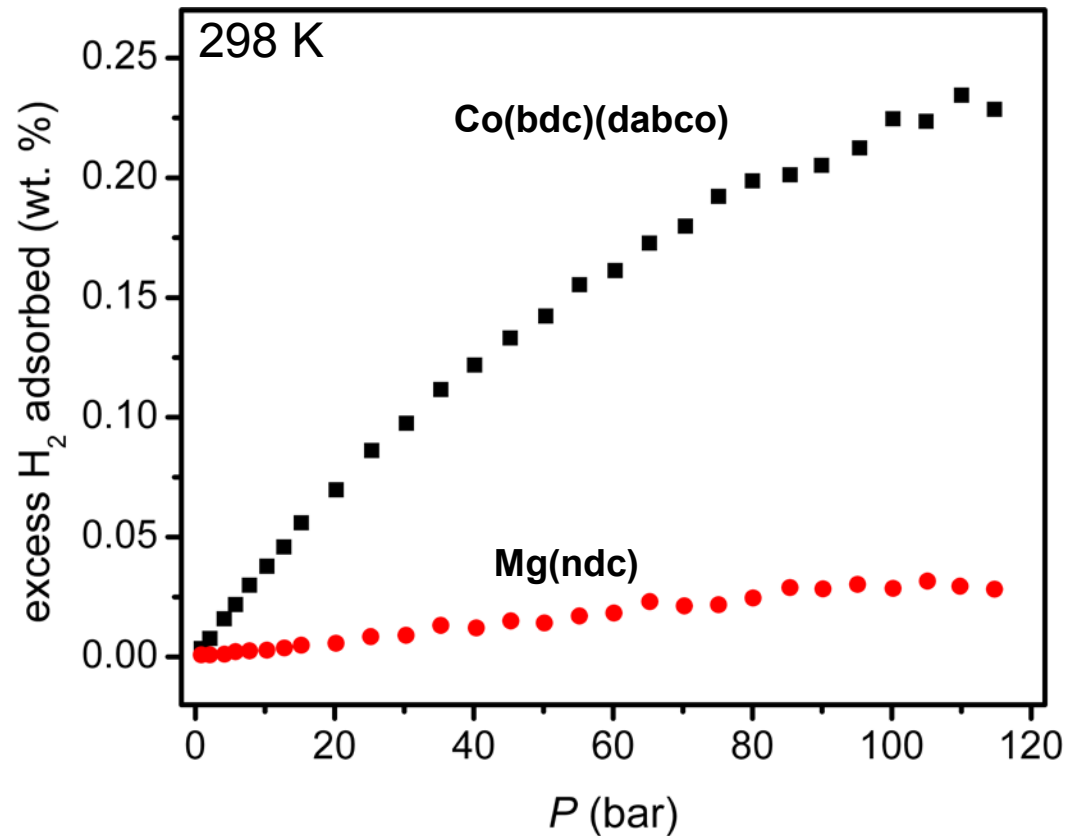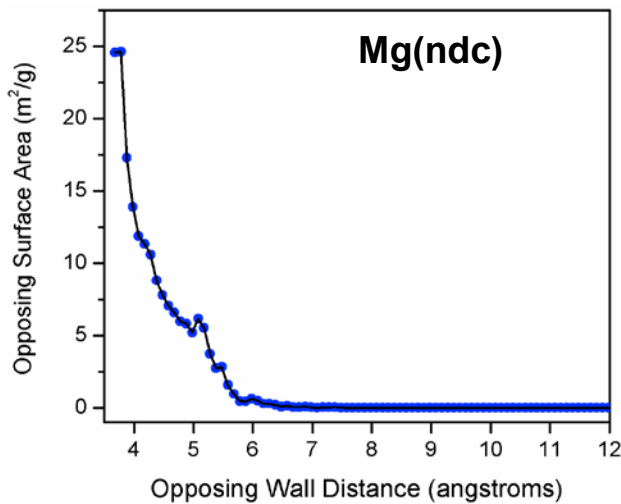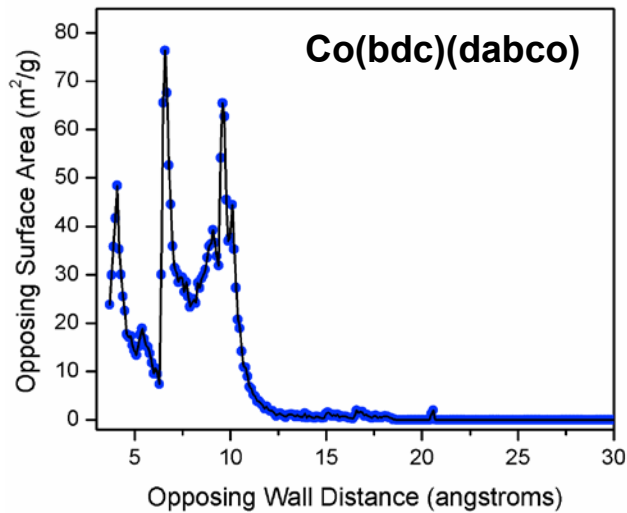

High-Pressure H₂ Adsorption

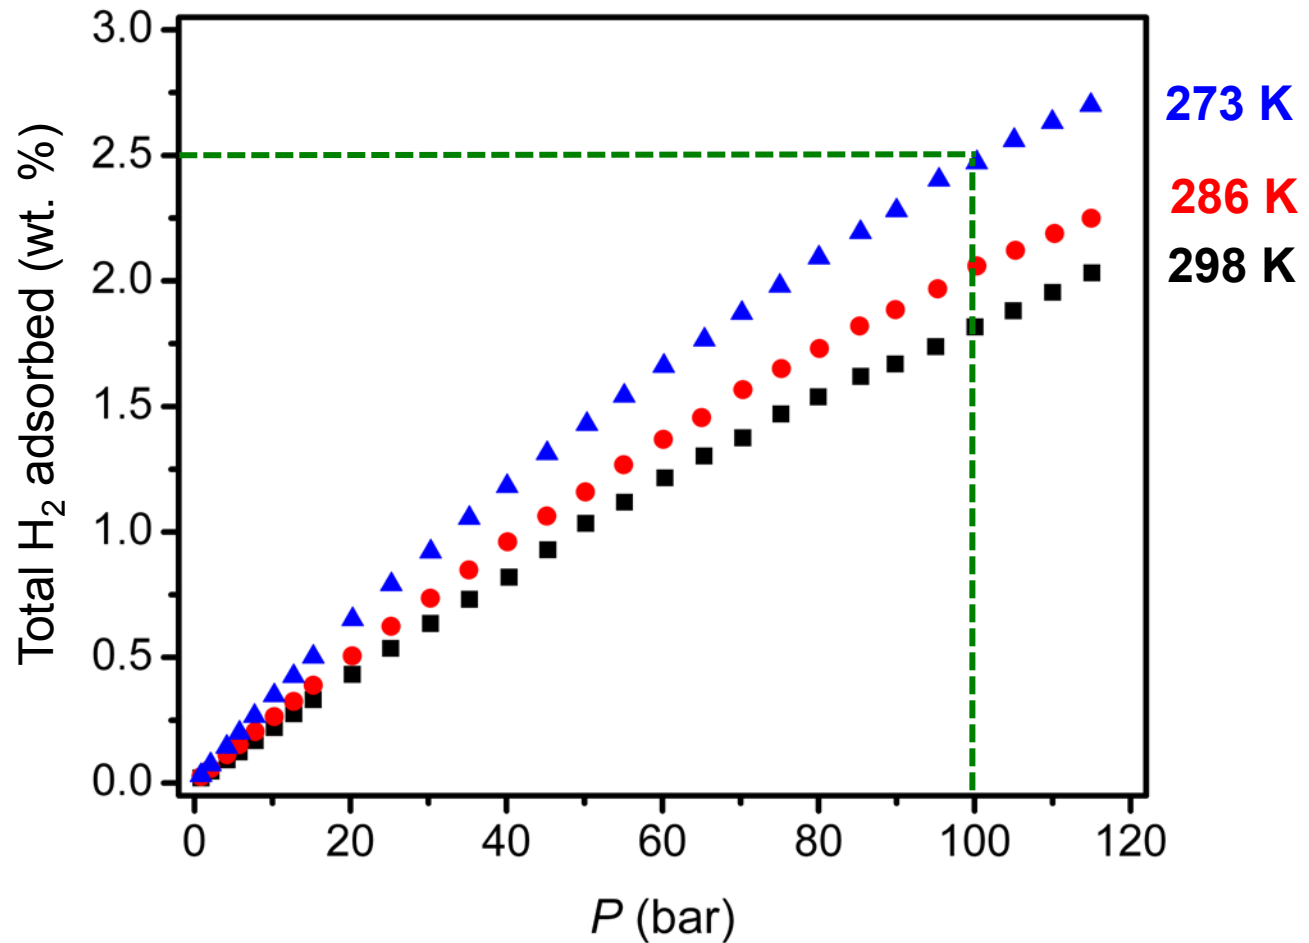

□ Mg₂(dobpdc) achieves 2.5 wt. % target at 273 K, 100 bar.