

## II.F.2 Fundamentals of a Solar-Thermal Hydrogen Production Process Using a Metal-Oxide Based Thermochemical Water Splitting Cycle

Alan W. Weimer

University of Colorado-Boulder  
1111 Engineering Drive  
Boulder, CO 80309

Phone: (303) 492-3759; Fax: (303) 492-4341  
E-mail: Alan.Weimer@Colorado.edu

DOE Technology Development Manager:  
Mark Paster

Phone: (202) 586-2821; Fax: (202) 586-9811  
E-mail: Mark.Paster@ee.doe.gov

DOE Project Officer: Paul Bakke

Phone: (303) 275-4916; Fax: (303) 275-4753  
E-mail: Paul.Bakke@go.doe.gov

Contract Number: DE-FG36-03GO13062

Project Start Date: June 1, 2005

Project End Date: May 31, 2009

### Objectives

- Research and develop a cost effective  $Mn_2O_3/MnO$  solar-thermal thermochemical cycle through theoretical and experimental investigations.
- Based on the above, develop a process flow diagram and carry out an economic analysis of the best process option.

### Technical Barriers

This project addresses the following technical barriers from the High-Temperature Thermochemical, Solar-Driven Production of Hydrogen section (3.1.4) of the Hydrogen, Fuel Cells and Infrastructure Technologies Program Multi-Year Research, Development and Demonstration Plan:

- (U) High-Temperature Thermochemical Technology
- (V) High-Temperature Robust Materials
- (W) Concentrated Solar Energy Capital Cost
- (X) Coupling Concentrated Solar Energy and Thermochemical cycles

### Technical Targets

#### Solar-Driven High-Temperature Thermochemical Hydrogen Production

This project is conducting fundamental studies of the manganese oxide-based thermochemical cycle. Insights gained from these studies will be applied toward solar-driven high-temperature hydrogen production that meets the following DOE 2012 targets:

**TABLE 1.** Solar-Driven High-Temperature Thermochemical Hydrogen Production

Characteristics	Units	2008 Target	2012 Target	2017 Target
Solar-Driven High-Temperature Thermochemical Cycle Hydrogen Cost	\$/gge $H_2$	10.00	6.00	3.00
Heliostat Capital Cost (Installed Cost)	\$/m <sup>2</sup>	180	140	80
Process Energy Efficiency	%	25	30	>35



### Accomplishments

- Demonstrated high conversions of  $Mn_2O_3$  dissociation in an aerosol flow reactor (AFR).
- NaOH removal by vaporization was investigated.
- Explored carrying residual  $NaMnO_2$  through the cycle.
- Testing in progress with mixed manganese oxides for more efficient NaOH recovery.



### Introduction

A three-step metal oxide cycle to produce renewable hydrogen has been proposed. This cycle employs manganese oxide and solar energy to produce hydrogen [1-3]:



The  $\text{Mn}_2\text{O}_3/\text{MnO}$  water splitting cycle is a three-step cycle and has advantages that make it an attractive water splitting cycle. First,  $\text{Mn}_2\text{O}_3$  reduction occurs at low enough temperatures that feasible reactor materials of construction may be found. In addition, the somewhat lower temperatures (compared with other potential cycles) involved in this solar driven cycle allow for lower re-radiation losses, and in turn a higher reactor efficiency [2]. Second, an inert gas flow must be present in the metal oxide reduction of many high-temperature thermochemical cycles to thermodynamically carry out the reactions. However, the  $\text{Mn}_2\text{O}_3$  reduction to  $\text{MnO}$  is thermodynamically favored even in the presence of air. This would eliminate the need to use inert gas to separate oxygen downstream of the reactor, which can significantly increase the overall process efficiency. Third, the phase separation of  $\text{MnO}$  from dissociated  $\text{O}_2$  appears simple because  $\text{MnO}$  is a solid at the reaction temperature. Due to these advantages of the manganese oxide cycle it is suggested to further study the feasibility of this cycle [2,4,5].

## Approach

The  $\text{Mn}_2\text{O}_3$  dissociation and  $\text{NaOH}$  recovery step have been identified as the essential steps that must be investigated to make the cycle realistic. It is essential to understand the  $\text{Mn}_2\text{O}_3$  dissociation step because the entire feasibility of the manganese oxide cycle is based on this reaction having a high overall conversion [2]. Specifically, the viability of the  $\text{MnO}$  and  $\text{O}_2$  phase separation must be investigated to determine how much recombination might occur during the quench step [1,5,6]. For the past year, kinetic studies have been performed in an AFR, as it can handle a high throughput of powder, while allowing reaction conditions to be tightly controlled.

The step described by Reaction 3 has proven to be the most challenging of the three steps. Challenges arise from the reaction not going to completion and a difficult  $\text{Mn}_2\text{O}_3/\text{NaOH}$  separation. There have been many approaches in the past fiscal year to resolve the issues associated with this step and they include: (1) thermal separation of  $\text{NaOH}$ , (2) creation of mixed manganese oxides to improve the separation and (3) processing residual  $\text{NaMnO}_2$  through the cycle.

## Results

Experiments for the  $\text{Mn}_2\text{O}_3$  dissociation were completed in the AFR. An oxygen monitor showed a significant increase when the reaction was initiated, which indicated that the reaction was occurring. Initial results showed conversions ranging between 56-75%. Analyzing the results indicated that the main effects (temperature and residence time) are statistically significant and that the binary effects are not. The

highest conversion was achieved with a combination of a high temperature and short residence time. A high temperature favors the forward reaction and the low residence time possibly stopped the reaction in the quench tube more rapidly, thus preventing oxygen recombination. Further verifying the results, X-ray diffraction (XRD) spectra (Figure 1) illustrated a strong  $\text{MnO}$  spectrum and a weak  $\text{Mn}_3\text{O}_4$  spectrum. A dotted line helps illustrate that all of the peaks can be seen from the  $\text{MnO}$  standard and that only the major peaks from the  $\text{Mn}_3\text{O}_4$  standard. The results from this study may be used in the DOE framework to help evaluate the efficiency of the cycle and for a plant simulation to put the cycle in context in an H2A cost estimate.

It has been proposed to vaporize  $\text{NaOH}$  to separate it from  $\text{Mn}_2\text{O}_3$ . A horizontal tube furnace was utilized to conduct experiments where the sample is pulled into the hot zone at the desired temperature. Results indicated that a significant amount of  $\text{NaOH}$  was not vaporized. In addition, a statistical analysis indicated that there were no significant effects. This indicated that within the ideal operating ranges selected for the factors that it is not possible to achieve a high vaporization rate of  $\text{NaOH}$ . For the vaporization to proceed at an ideal rate, a high temperature would be required. Likely problems with a higher temperature include reverse reaction to  $\text{NaMnO}_2$  and partial reduction of  $\text{Mn}_2\text{O}_3$  to  $\text{Mn}_3\text{O}_4$ . It was thus concluded that vaporization of  $\text{NaOH}$  is not a viable method to separate  $\text{Mn}_2\text{O}_3$  and  $\text{NaOH}$ .

Use of mixed manganese oxides may potentially improve  $\text{Mn}_2\text{O}_3/\text{NaOH}$  separation. The investigation of mixed manganese oxides has been divided into three phases: (1) synthesis of  $\text{Mn}_x\text{Fe}_{1-x}\text{O}$  and  $\text{Mn}_x\text{Zn}_{1-x}\text{O}$ , (2) verification of hydrogen production with the mixed oxides and (3) investigation of the mixed manganese oxide- $\text{NaOH}$  separation efficiency. A sol-gel precipitation reaction in basic solution from metal salts is used to create a precipitate which is then calcined in  $\text{N}_2$  to produce the mixed metal oxide. A successful synthesis


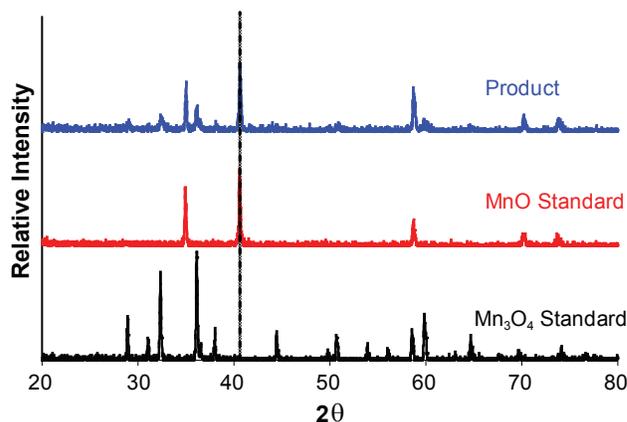


FIGURE 1. XRD Product Spectrum of  $\text{Mn}_2\text{O}_3$  Dissociation Product

of a mixed manganese oxide with 5:1 manganese to zinc ratio has been done. Figure 2 is an XRD spectrum showing mixed manganese/zinc oxide. This mixed manganese oxide was then heated with NaOH and the H<sub>2</sub> generation step was demonstrated (Figure 3). With the hydrogen generation demonstrated, the NaOH separation with the mixed manganese oxide will be investigated in the next fiscal year. This result fits into the DOE framework by potentially improving the efficiency of the Mn<sub>2</sub>O<sub>3</sub>/MnO cycle.

Under reaction conditions, Reaction 3 will have approximately 10% residual NaMnO<sub>2</sub>, thus processing the residual NaMnO<sub>2</sub> with Mn<sub>2</sub>O<sub>3</sub> in the dissociation step is being explored. The reaction sequence is theorized in Equations 5 and 6:



A proof-of-concept of Equation 5 was done in a thermal gravimetric analyzer (TGA) in conditions

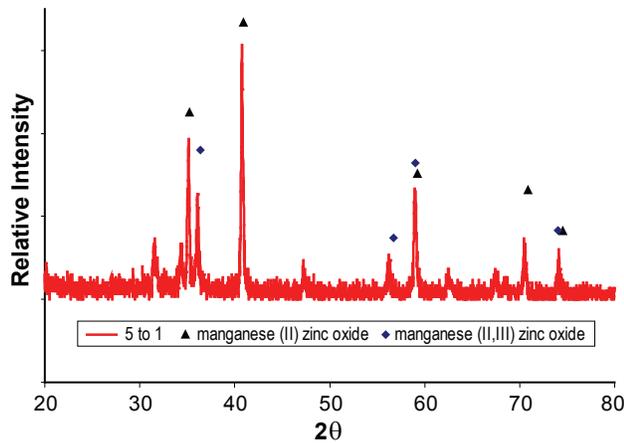


FIGURE 2. XRD Spectrum of Synthesized Mixed Manganese Oxide

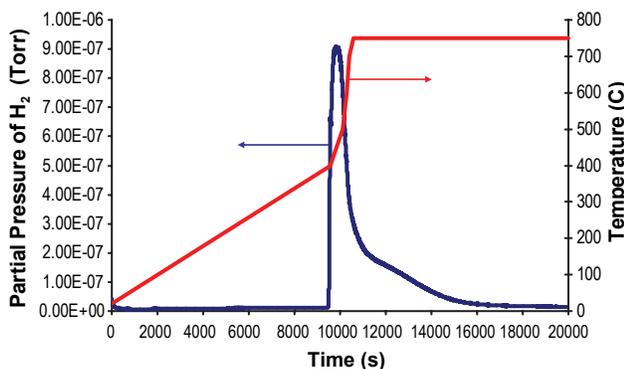


FIGURE 3. H<sub>2</sub> Generation from a Mixed Manganese Oxide and NaOH Reaction

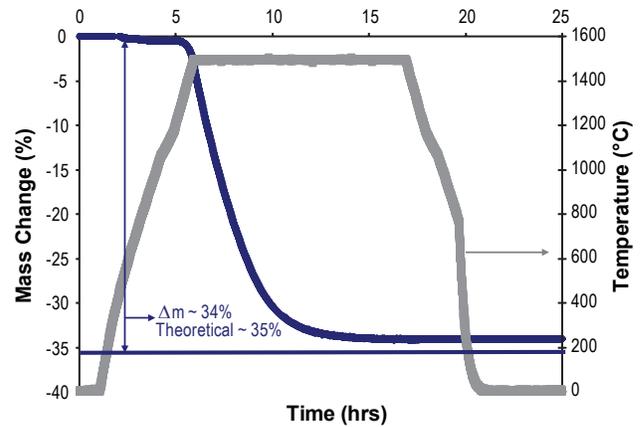


FIGURE 4. TGA Mass Trace Showing Near Theoretical Conversion

that Mn<sub>2</sub>O<sub>3</sub> would dissociate. TGA results (Figure 4) showed that Reaction 5 will proceed to near theoretical conversion at 1,500°C. With Equation 5 proven to work, more research must be done to better understand processing the residual NaMnO<sub>2</sub>. Specifically what form does the sodium take in Equation 5 and will the reaction kinetics become faster when diffusion resistances are negligible in an AFR? If it is demonstrated that residual NaMnO<sub>2</sub> can be processed with Mn<sub>2</sub>O<sub>3</sub>, then the efficiency of the manganese oxide cycle will likely increase.

### Conclusions and Future Directions

Significant experimental progress has been made with the Mn<sub>2</sub>O<sub>3</sub>/MnO cycle:

- High conversions for Mn<sub>2</sub>O<sub>3</sub> dissociation have been demonstrated.
- Potential solutions for NaOH recovery have been identified and investigations have begun.
- Studies on ways in to process non-reacted NaMnO<sub>2</sub> have been shown and more work is ongoing.

### Future Work

- On sun testing of Mn<sub>2</sub>O<sub>3</sub> dissociation.
  - Reactor design and construction.
  - Reactor materials testing.
- Continue work plans for NaOH recovery.
- Perform H<sub>2</sub>A analyses with experimental results.

### FY 2007 Publications/Presentations

1. Francis, T.M., C.J. Gump, and A.W. Weimer, Spinning wheel powder feeding device - fundamentals and applications. Powder Technology, 2006. 170(1): p. 36-44.

## References

1. Sturzenegger, M., J. Ganz, P. Nuesch, and T. Schelling, *Solar hydrogen from a manganese oxide based thermochemical cycle*. Journal De Physique IV, 1999. 9(P3): p. 331-335.
2. Sturzenegger, M. and P. Nuesch, *Efficiency analysis for a manganese-oxide-based thermochemical cycle*. Energy, 1999. 24(11): p. 959-970.
3. Nuesch, P., *Wasserstoff aus Sonnenenergie - Ein neuer Thermochemischer Zyklus auf der Basis von Manganoxiden*. 1998, Universitat Zurich.
4. Perkins, C. and A.W. Weimer, *Likely near-term solar-thermal water splitting technologies*. International Journal of Hydrogen Energy, 2004. 29(15): p. 1587-1599.
5. Abanades, S., P. Charvin, G. Flamant, and P. Neveu, *Screening of water-splitting thermochemical cycles potentially attractive for hydrogen production by concentrated solar energy*. Energy, 2006. 31(14): p. 2805-2822.
6. Ganz, J., E. Steiner, and M. Sturzenegger. *Powder cloud reactors. An attractive concept to run solar high-temperature reactions*. in *9th SolarPaces International Symposium on Solar Thermal Concentrating Technologies*. 1998. Font-Romeu, France: EDP Sciences.