

II.G.4 Laboratory-Scale High Temperature Electrolysis System

J. Stephen Herring (Primary Contact),
James E. O'Brien, Carl M. Stoots, Keith
Condie, Kevin DeWall, Michael G. McKellar,
Edwin Harvego, Manohar Sohal, G.L. Hawkes
Idaho National Laboratory (INL)
2525 N. Fremont Ave.
Idaho Falls, ID 83415-3860
Phone: (208) 526-9497; Fax: (208) 526-2930
E-mail: j.herring@inl.gov

DOE Technology Development Manager:
Carl Sink

Phone: (301) 903-5131; Fax: (301) 903-0180
E-mail: carl.sink@nuclear.energy.gov

DOE High Temperature Electrolysis Manager:
Melissa C. Bates

Phone: (208) 526-4652; Fax: (208) 526-6249
E-mail: batesmc@id.doe.gov

Subcontractors:

- Ceramatec, Inc.
Joseph J. Hartvigsen, S. Elangovan, Dennis Larsen
2425 South 900 West, Salt Lake City, UT
- Materials and Systems Research, Inc. (MSRI)
Anil Virkar, Gregory Tao
5395 West 700 South, Salt Lake City, UT

Collaborating National Laboratories:

- Argonne National Laboratory (ANL)
Theodore Krause, J. David Carter, Jennifer Mawdsley
- National Aeronautics and Space Administration
Glenn Research Center, Cleveland, OH
Thomas Cable, Andrew Eckel and John Setlock

Collaborating Universities:

- Massachusetts Institute of Technology (MIT)
Bilge Yildiz, Harry Tuller, Vivek Sharma
- Virginia Polytechnic Institute and State University
Kathy Lu
- Georgia Institute of Technology
Hamid Garmestani

Start Date: January 23, 2003

Projected End Date: Engineering Demo, 1 MW,
2018

- Develop energy-efficient, high-temperature, solid-oxide electrolysis cells (SOECs) for hydrogen production from steam.
- Develop and test integrated SOEC stacks operating in the electrolysis mode.
- Develop optimized plant configuration for coupling to Generation IV Reactor.
- Combine components in an Integrated Laboratory-Scale (ILS) experiment.
- Scale up to a 200 kW pilot plant and a 1 MW engineering demonstration facility.

** Since there are no objectives specific to the nuclear production of hydrogen, we have adopted those cited from wind water electrolysis.*

Technical Barriers

This project addresses the following technical barriers of the Multi-Year Program Plan p. 3.1-24 and the Nuclear Hydrogen Initiative:

- **G. Capital Cost** – Development of larger systems is also needed to take advantage of economies of scale.
- **H. System Efficiency** – New membrane, electrode and system designs are needed to improve system efficiency.
- **I. Grid Electricity Emissions** – Low-cost, carbon-free electricity generation is needed. Electrolysis systems that can produce both hydrogen and electricity need to be evaluated.

Technical Targets

- No greenhouse gas releases from industrial scale H₂ production.
- Energy efficiency: 50% (lower heating value of H₂ produced/total thermal output of reactor).
- Cost of hydrogen: \$3.10/kg – centralized production only, 2012.
- Life of cells: 20,000 hours of continuous operation.

Contribution to Achievement of DOE Systems Analysis Milestones

This project contributed/will contribute to achievement of the following DOE systems analysis milestones from the Systems Analysis section of the Hydrogen, Fuel Cells and Infrastructure Technologies Program Multi-Year Research, Development and Demonstration Plan:

Objectives

- By 2012, reduce the cost of central production of hydrogen from high temperature electrolysis to \$3.10/gasoline gallon equivalent (gge) at plant gate, by 2017, reduce the cost of central production of hydrogen from high temperature electrolysis to <\$2.00/gge at plant gate.*

- **Milestone 2:** Complete baseline economic, energy efficiency and environmental targets for fossil, nuclear and renewable hydrogen production and delivery technologies. (4Q, 2005)
- **Milestone 8:** Complete analysis and studies of resource/feedstock, production/delivery and existing infrastructure for technology readiness. (4Q, 2014)
- **Milestone 10:** Complete an analysis of the hydrogen infrastructure and technical target progress for technology readiness. (2Q, 2015)
- **Milestone 11:** Complete environmental analysis of the technology environmental impacts for the hydrogen scenarios and technology readiness. (2Q, 2015)

Accomplishments (Fiscal Year 2009)

- Demonstrated improved performance of oxygen and steam hydrogen electrodes through the deposition of electrocatalytic materials by atomic layer deposition or other infiltration processes. (Argonne National Laboratory) 9/30/2008
- Completed analysis of hot oxygen handling and cooling options based on collaboration with Atomic Energy Canada, Limited. 7/2/2008
- Tested the three-module (each module 4 x 60 cells) for the ILS experiment for 1,080 hours in Idaho Falls with a maximum output of 5.65 N m³ H₂/hour (0.504 kg H₂/hour). 9/5/2008-10/20/2008
- Completed analysis report on corrosion testing of the second series of balance of plant materials on 9/30/2008.
- Completed report on experimental data from the operation of the High Temperature Electrolysis (HTE) ILS experiment on 2/17/2009.
- Completed report on critical causes of stack degradation in ILS cells on 5/27/2009.
- Demonstrated low-degradation performance of a 10-cell stack using improved oxygen electrodes, 5/27/2009-9/8/2009.



Introduction

A research program is under way at the Idaho National Laboratory and collaborating laboratories to assess the performance of solid oxide cells operating in the steam electrolysis mode for hydrogen production over a temperature range of 800 to 900°C. The research program includes both experimental and modeling activities. The electrolysis cells are electrolyte-supported, with scandia-stabilized zirconia electrolytes (~140 μm thick), nickel-cermet steam/hydrogen

electrodes, and manganite oxygen electrodes. The metallic interconnect plates are fabricated from ferritic stainless steel. In the last year we have begun testing various electrode-supported configurations as well.

During FY 2009, experimental results were obtained from three modules of four 60-cell stacks each, fabricated by Ceramtec, Inc. Additional experiments at ANL, MIT, and INL investigated the characteristics of cells used in previous tests and the performance of a variety of materials being considered for use in the balance of plant for HTE hydrogen production plants. We also organized a workshop on the long-term degradation of solid oxide cells used in high temperature electrolysis in conjunction with the Fuel Cell Seminar in Phoenix, October 27, 2008.

Approach

High-temperature electrolysis testing of single button cells and stacks has been in progress at the INL and the subcontractor Ceramtec Inc. (Salt Lake City, UT) since 2003. The scales of testing accomplished to date at the INL are pictured in Figure 1. The ILS facility operated at a maximum hydrogen production rate of 5,650 normal (273°K, 1 atm) L/hr (0.504 kg H₂/hr) with an input of 18 kWe. The ILS operated continuously for 1,080 hours from September 5 through October 20, 2008. Because of degradation of the oxygen electrodes, the hydrogen output decreased to 800 NL/hr in the course of the test.

After each of the tests, the stacks have been disassembled and the cells have been destructively examined to determine elemental migration during the test and to detect changes in the morphology of the electrolyte and electrodes. These examinations have also been conducted on cells in the test of the three-module ILS.



FIGURE 1. General View of the HTE ILS Experiment

Results

The full, three-module ILS experiment operated in Bay 9 of the Bonneville County Technology Center, Idaho Falls, from September 5 through October 20, 2008, a total of 1,080 hours [1]. A 420-hour test of the ILS with a single module was conducted in September and October 2007 [2]. The general layout of the experiment is shown in Figure 1, with the numbered components listed in Table 1.

TABLE 1. Identifiers for Figure 1

ID	Component
1	Hot zone enclosure lid
2	Power supply and instrument racks
3	Electrical distribution cabinet
4	Data acquisition and control monitors
5	Deionized water system
6	Steam generator
7	Steam and H ₂ superheaters
8	Air compressor
9	Patch panel
10	Product finned cooler
11	Steam condenser
12	Mass flow controllers
13	H ₂ vent
14	Air and O ₂ vent

As can be seen in Figure 1, the ILS contains most of the components needed in a full-scale high temperature electrolysis plant, with exception of the nuclear reactor and facilities for using the hydrogen produced. The three modules, with the associated voltage taps and thermocouples are shown in Figure 2a, immediately before the closure of the hot zone lid.

Two capabilities were added to ILS between the single module and the three-module tests. In order to more closely simulate the operation of a commercial hydrogen plant, we added a system for recycle of 10-30% of the product hydrogen back into the input steam to maintain reducing conditions on the steam/hydrogen electrodes of the cells within the modules. Secondly, we installed heat recuperators under the modules to allow the use of steam at 350° to 450°C, rather than the 800°C required at the input to the modules. As shown in Figure 2b, the heat in the hydrogen and oxygen product streams at ~820°C is used to heat the input streams to ~790°C. The inherent ohmic heating in the cells provides the required 20°-40°C temperature difference between the countercurrent streams.

Heat up of the INL three-module ILS system began at approximately 5 PM on September 4, 2008. Peak

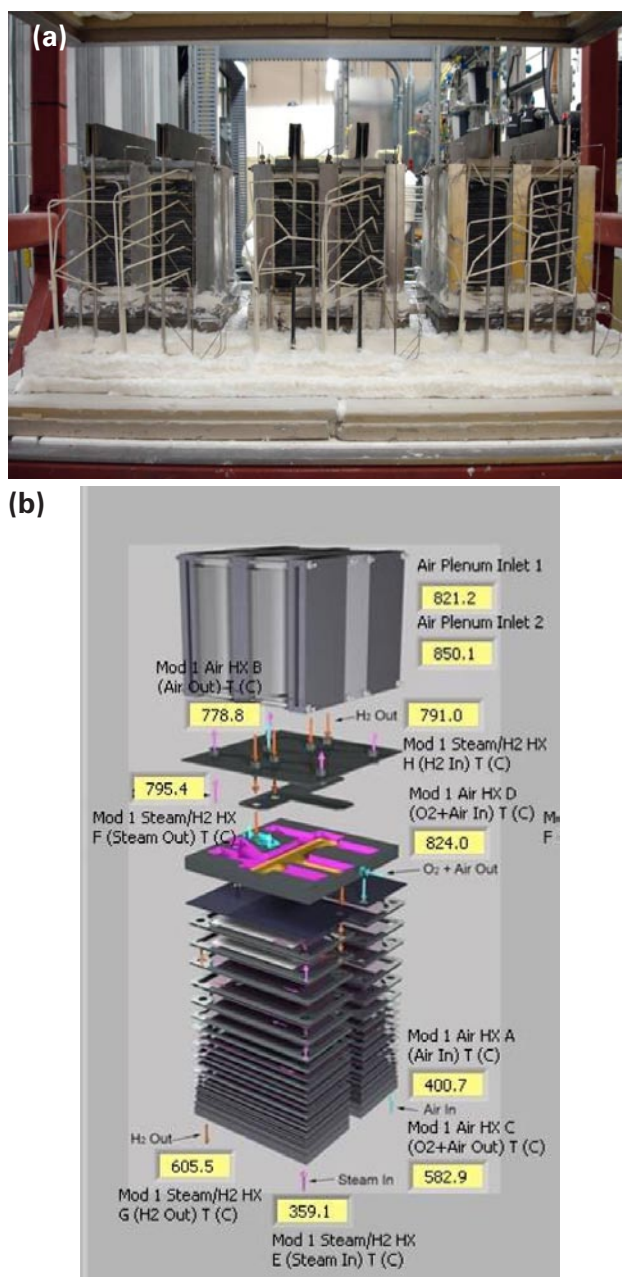


FIGURE 2. (a) Three modules each containing four stacks of 60 cells. The six recuperators are partially covered in insulation below the modules. (b) A screen print from our LabView® control software, showing the temperatures of the various streams entering and leaving the two recuperators under module 1.

hydrogen production as well as peak electrolysis power input was achieved at approximately 10 AM on September 5, 2008 (~17 hours elapsed test time). At this time, the electrolysis modules were consuming 18 kW of electrical power and producing over 5.7 Nm³/hr H₂. Early test module area-specific resistance (ASR) values ranged from 1.25 Ω-cm² to just over 2 Ω-cm². Testing continued for 1,080 hours. Significant module performance degradation

was observed over the first 480 hours, after which no further degradation was noted for the remainder of the test for modules 1 and 2, while module 3 continued to degrade. The total H_2 production rate decreased from $5.7 \text{ Nm}^3/\text{hr}$ to a steady-state value of $0.7 \text{ Nm}^3/\text{hr}$, primarily due to cell degradation. Most of the test was conducted at a constant electrolyzer power supply voltage of 76 V.

Once all test objectives had been successfully met, the test was terminated in a controlled fashion. Two relatively minor problems were encountered during testing. First, one N_2 mass flow controller failed and was replaced with a rotameter without any disruption of the experiment. Second, water condensation occurred in the H_2 recycle system. This was due to the elevated pressure required in the H_2 recycle loop. The condensate would sometimes collect in and interfere with the inlet H_2 mass flow controllers, leading to periodic interruptions in the hydrogen recycle flow. This may have caused accelerated degradation of the ILS modules. In particular, the flow interruptions could have caused electrode oxidation to occur in the modules. Once H_2 flow resumed, reduction would occur on the electrode surfaces. This cycling of oxidation and reduction may have contributed to the high rate of performance degradation observed. Around 480 hours elapsed test time, the condensate problem was finally fixed by installing a water trap just upstream of the H_2 mass flow controllers. Subsequent to this, the ASR values for modules 1 and 2 improved and finally leveled out with no further degradation. The reason for the continued performance degradation of module 3 after the condensation problem was solved while modules 1 and 2 improved is not understood.

The effectiveness of the heat recuperation system was estimated. A comparison was made between heater loads, steam generator loads, and hot zone heat losses between the earlier single module test (no heat recuperation) and the present three module test (with heat recuperation). The total per-module electric heater power was reduced by 50% in the case of heat recuperation.

Once the condensation problem was solved, the hydrogen recycle system worked flawlessly and made unnecessary the use of any external hydrogen source for maintaining reducing conditions in the cells.

The facility instrumentation and data acquisition/control system performed as designed except for condensation interfering with the inlet hydrogen mass flow controllers and failure of one nitrogen mass flow controller. Both problems were circumvented/solved without any disruption of the experiment.

Overall, the facility successfully demonstrated the largest scale high temperature solid oxide-based production of hydrogen to date.

Post-test examination of the representative cells from the three-module ILS test indicated that the oxygen electrode had delaminated from the electrolyte over part of the electrolyte area [3]. After a series of short-term tests of various diffusion-barrier layers in the cells, a long-duration test of a 10-cell stack was started May 27. As of this writing, that stack has operated ~1,000 hours and has shown only about 5% degradation. It is expected that this test will run until the end of FY 2009.

References

1. Stoots, C.M., Condie, K.G., Moore-McAteer, L., O'Brien, J.E., Housley, G.K., and Herring, J.S., "Integrated Laboratory Scale Test Report", INL/EXT-09-15283, February 2009.
2. Condie, K.G., Stoots, C.M., O'Brien, J.E., and Herring, J.S., "Characterization of the Transient Response of the ILS with One Module Installed to Heatup Changes in Power Level and Cooldown," INL/EXT-07-13626, December 2007.
3. Sohal, M.S., O'Brien, J.E., Stoots, C.M., Herring, J.S., Hartvigsen, J.J., Larsen, D., Elangovan, S., Carter, J.D., Sharma, V.I., and Yildiz, B., "Critical Causes of Degradation in Integrated Laboratory Scale Cells during High-Temperature Electrolysis," INL/EXT-09-16004, May 27, 2009.

FY 2009 Journal Articles

1. Stoots, C.M., O'Brien, J.E., Herring, J.S., Hartvigsen, J.J., "High Temperature Electrolysis of Steam and CO_2 for Syngas Production," in *Syngas: Production Methods, Post Treatment, and Economics*, edited by Dr. Frank Columbus, in press, Nova Science Publishers, New York, 2009.
2. Stoots, C.M., O'Brien, J.E., Condie, K., Moore-McAteer, L., Housley, G.K., Hartvigsen, J.J., and Herring, J.S., "The High-Temperature Electrolysis Integrated Laboratory Experiment," *Nuclear Technology*, April, 2009.
3. Harvego, E.A., McKellar, M.G., and O'Brien, J.E., "System Analysis of Nuclear-Assisted Syngas Production from Coal," in press, *Journal of Engineering for Gas Turbines and Power*, Vol. 131, July, 2009.
4. O'Brien, J.E., McKellar, M.G., Stoots, C.M., Herring, J.S., and Hawkes, G.L., "Parametric Study of Large-Scale Production of Syngas via High Temperature Electrolysis," in press, *International Journal of Hydrogen Energy*, 2009.
5. Stoots, C.M., O'Brien, J.E., "Results of Recent High-Temperature Co-electrolysis Studies at the Idaho National Laboratory," in press, *International Journal of Hydrogen Energy*, 2009.
6. Hawkes, G.L., O'Brien, J.E., and Stoots, C.M., "3D CFD Model of a Multi-Cell High Temperature Electrolysis Stack," in press, *International Journal of Hydrogen Energy*, 2009.
7. Stoots, C.M., O'Brien, J.E., Herring, J.S., and Hartvigsen, J.J., "Syngas Production via High-Temperature Coelectrolysis of Steam and Carbon Dioxide," *Journal of*

Fuel Cell Science and Technology, Vol. 6, part 1, paper no. 011014, pp. 1–12, February, 2009.

FY 2009 Conference Papers and Presentations

1. Harvego, E.A., O'Brien, J.E., McKellar, M.G., "System Analysis of High and Low Temperature Interface Designs for a Nuclear-Driven High Temperature Electrolysis Hydrogen Production Plant," International Conference on Nuclear Energy, paper no. ICONE17-75473, Brussels, Belgium, July 12–16, 2009.
2. Stoots, C.M., Condie, K.G., O'Brien, J.E., Herring, J.S., and Hartvigsen, J.J., "Test Results from the Idaho National Laboratory 15 kW High Temperature Electrolysis Test Facility," International Conference on Nuclear Energy, paper no. ICONE17-75417, Brussels, Belgium, July 12–16, 2009.
3. O'Brien, J.E., Stoots, C.M., Herring, J.S., Condie, K.G., and Housley, G.K., "The High-Temperature Electrolysis Program at the Idaho National Laboratory: Observations on Performance Degradation," High Temperature Water Electrolysis Limiting Factors, Eifer, Karlsruhe, Germany, June 9–10, 2009.
4. Stoots, C.M., O'Brien, J.E., Herring, J.S., Hartvigsen, J.J., "High Temperature Electrolysis Experimental Activities at the Idaho National Laboratory," High Temperature Water Electrolysis Limiting Factors, Eifer, Karlsruhe, Germany, June 9–10, 2009.
5. O'Brien, J.E., McKellar, M.G., Harvego, E.A., and Stoots, C.M., "High-Temperature Electrolysis for Large-Scale Hydrogen and Syngas Production from Nuclear Energy – system Simulation and Economics," International Conference on Hydrogen Production, ICH2P-09, Oshawa, Canada, May 3–6, 2009.
6. Stoots, C.M., O'Brien, J.E., Condie, K.G., and Hartvigsen, J.J., "High-Temperature Electrolysis for Large-Scale Hydrogen Production from Nuclear Energy – Experimental Investigations," International Conference on Hydrogen Production, ICH2P-09, Oshawa, Canada, May 3–6, 2009.
7. O'Brien, J.E., Stoots, C.M., McKellar, M.G., Harvego, E.A., Condie, K.G., Housley, G.K., Herring, J.S., and Hartvigsen, J.J., "Status of the INL High Temperature Electrolysis Research Progra – Experimental and Modeling," Fourth Information Exchange Meeting on Nuclear Hydrogen, NEA, Oakbrook, IL, April 14–16, 2009.
8. O'Brien, J.E., "Thermodynamic Considerations for Thermal Water Splitting Processes and High-Temperature Electrolysis," 2008 ASME International Congress and Exposition, paper# IMECE2008-68880, Boston, Nov., 2008.
9. Housley, G.K., O'Brien, J.E., and Hawkes, G.L., "Design of a Compact Heat Exchanger for Heat Recuperation from a High Temperature Electrolysis System," 2008 ASME International Congress and Exposition, paper# IMECE2008-68917, Boston, Nov., 2008.
10. Hawkes, G.L., O'Brien, "3D CFD Electrochemical and Heat Transfer Model of an Integrated-Planar Solid Oxide Electrolysis Cell," 2008 ASME International Congress and Exposition, paper# IMECE2008-68866, Boston, Nov., 2008.
11. Stoots, C.M., O'Brien, J.E., Herring, J.S., and Hartvigsen, J.J., "Recent Progress at the Idaho National Laboratory in High Temperature Electrolysis for Hydrogen and Syngas Production," Proceedings of the 2008 ASME International Mechanical Engineering Congress and Exposition, paper# IMECE2008-68440, Boston, MA, Nov., 2008.
12. McKellar, M.G., Hawkes, G.L., and O'Brien, J.E., "The Production of Syngas via High-Temperature Electrolysis and Bio-Mass Gasification, Proceedings of the 2008 ASME International Mechanical Engineering Congress and Exposition, paper# IMECE2008-68900, Boston, MA, Nov., 2008.
13. Harvego, E.A., McKellar, M.G., and O'Brien, J.E., "System Analysis of Nuclear-Assisted Syngas Production from Coal," Proceedings, 4th International Topical Meeting on High Temperature Reactor Technology, paper# HTR2008-58085, Washington, DC, Sept. 2008.
14. Stoots, C.M., O'Brien, J.E., Herring, J.S., Condie, K.G., and Hartvigsen, J.J., "Idaho National Laboratory Experimental Research in High Temperature Electrolysis for Hydrogen and Syngas Production, Proceedings, 4th International Topical Meeting on High Temperature Reactor Technology, paper# HTR2008-58086, Washington, D.C., Sept. 2008.

DOE Milestone Reports

1. Sohal, M.S., O'Brien, J.E., Stoots, C.M., Herring, J.S., Hartvigsen, J.J., Larsen, D., Elangovan, S., Carter, J.D., Sharma, V.I., and Yildiz, B., "Critical Causes of Degradation in Integrated Laboratory Scale Cells during High-Temperature Electrolysis," INL/EXT-09-16004, May 27, 2009.
2. Stoots, C.M., Condie, K.G., Moore-McAteer, L., O'Brien, J.E., Housley, G.K., and Herring, J. S., "Integrated Laboratory Scale Test Report," INL/EXT-09-15283, February 27, 2009.
3. Hawkes, G.L., and O'Brien, J. E., "Alternate Geometry CFD Predictions," INL/EXT-08-14587, August 1, 2008.
4. Sohal, M.S., and Herring, J.S., "Oxygen Handling and Cooling Options in High Temperature Electrolysis Plants," INL/EXT-08-14483, July 2, 2008.