Plate Based Fuel Processing System

Ralph Dalla Betta, Carlos Faz, Armando Jimenez,
Helen Liu, Yafeng Liu, Jacques Nicole & David Yee
Catalytica Energy Systems, Inc.

May 23 – 26, 2005

This presentation does not contain any proprietary or confidential information

Project ID#
FCP15

CLEAN AIR STARTS HERE™

Overview

Timeline

- Project start: October 2001
- Project end: September 2005
- Percent complete: 85%

Barriers

- Barriers addressed
  - A. Durability
  - B. Cost
  - I. Hydrogen Purification/Carbon Monoxide Clean-up
  - J. Start-up Time/Transient Operation

Budget

- Total project funding
  - DOE share: $7M
  - Contractor share: $3M
- Funding received in FY04: $1.9M
- Funding for FY05: $1.1M

Partners

- Argonne National Laboratory
- Pacific Northwest National Laboratory

CLEAN AIR STARTS HERE™

Objectives

- Design and fabricate steam reforming prototype plate reactors at the 2 to 10kW(e) scale
  - Demonstrate steady state and transient performance
  - Evaluate rapid start up performance
- Develop highly active and durable low cost steam reforming, water-gas-shift and preferential oxidation catalyst materials compatible with the plate reactor system targeted at the DOE's $10 per kW(e) target
- Identify alternative applications and potential commercial outlets for the technology developed under this contract

Approach

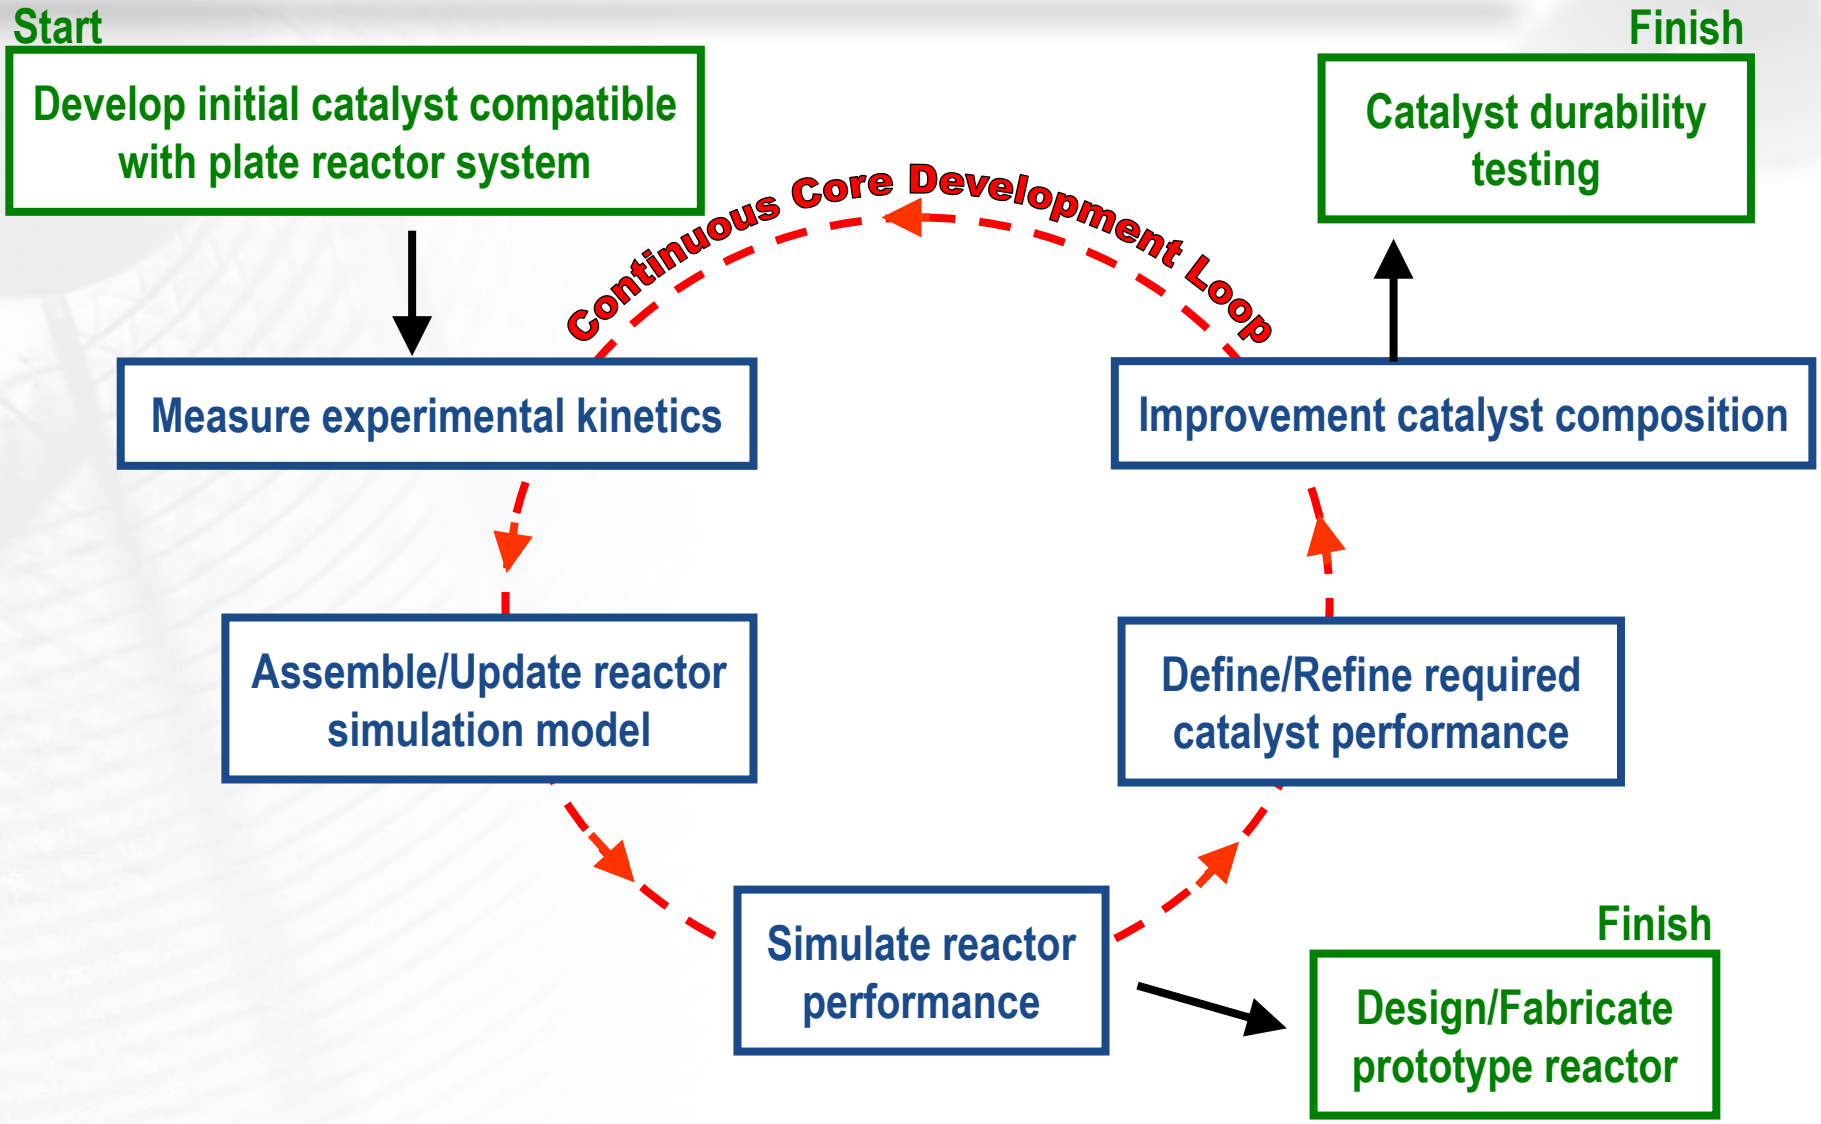

CLEAN AIR STARTS HERE™

CESI Steam Reforming Plate Reactor Approach

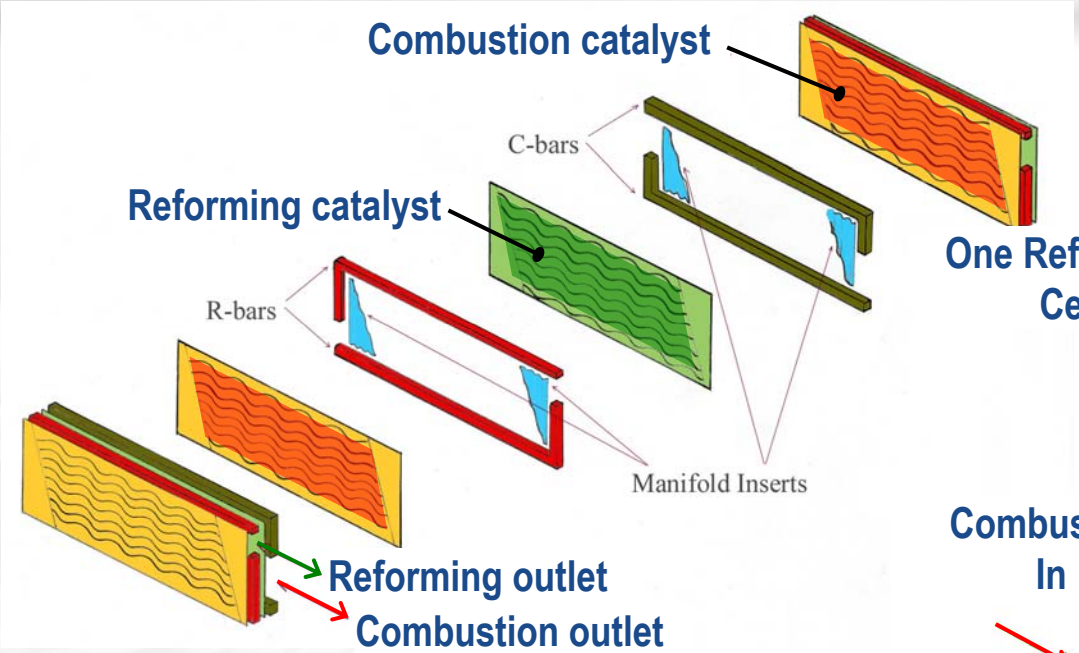

One Reforming Cell

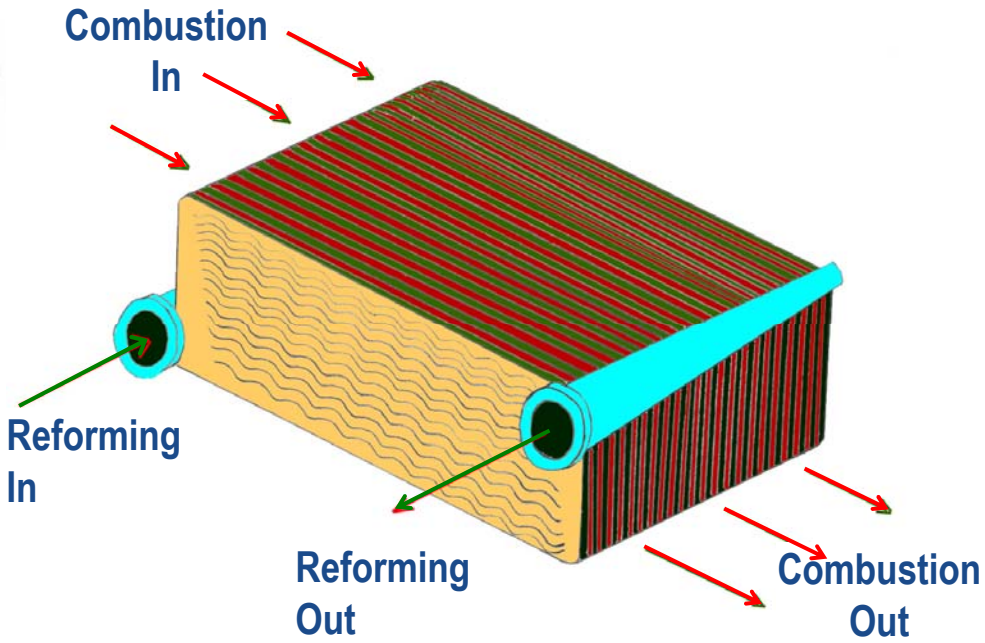

- Design based on plate-type heat exchanger
- Plates are coated with catalysts and paired together to form single cells
- Multiple cells are welded together to form the plate stack

CLEAN AIR STARTS HERE™

First Steam Reformer Prototype Fabrication

- To reduce fabrication time, CESI utilized 0.0075” (0.2 mm) thick plates from an existing heat exchanger of a gas turbine recuperator
- Cut one-tenth sector (shaded region) to fabricate a simple prototype
- Utilized CESI coating knowledge to successfully develop a coating process
- Developed a welding process for the plate stack assembly

CLEAN AIR STARTS HERE™

Details of First Prototype Plate

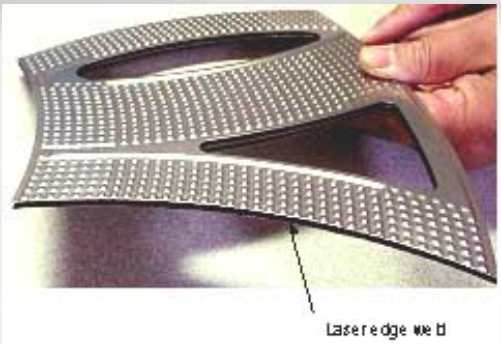

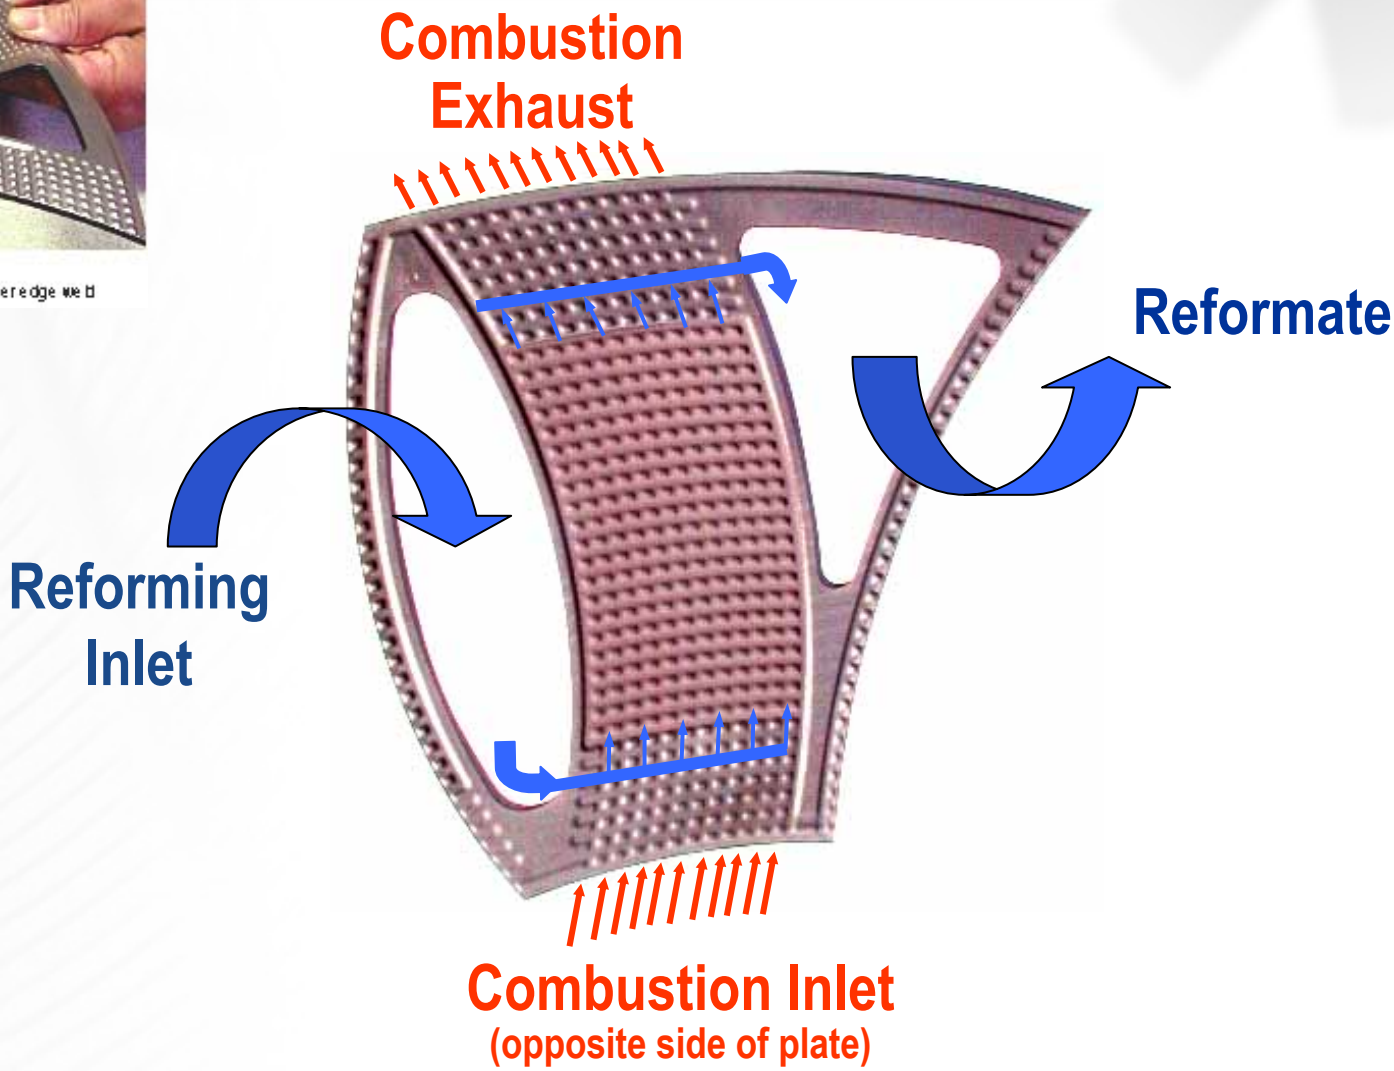

CLEAN AIR STARTS HERE™

First Prototype Assembly

AGT-2 Plate Stack

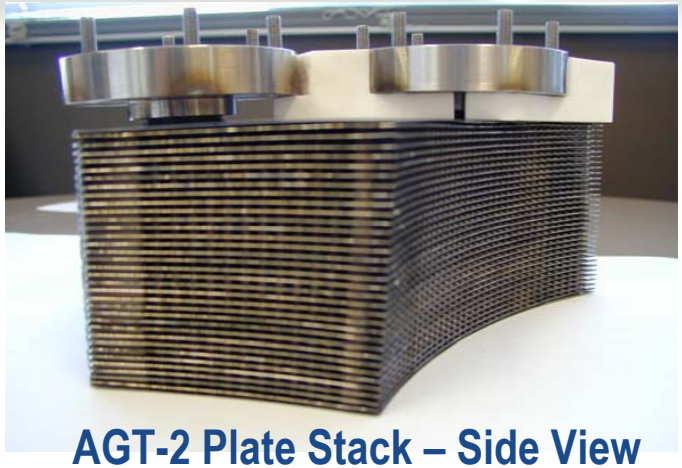

AGT-2 Plate Stack – Side View

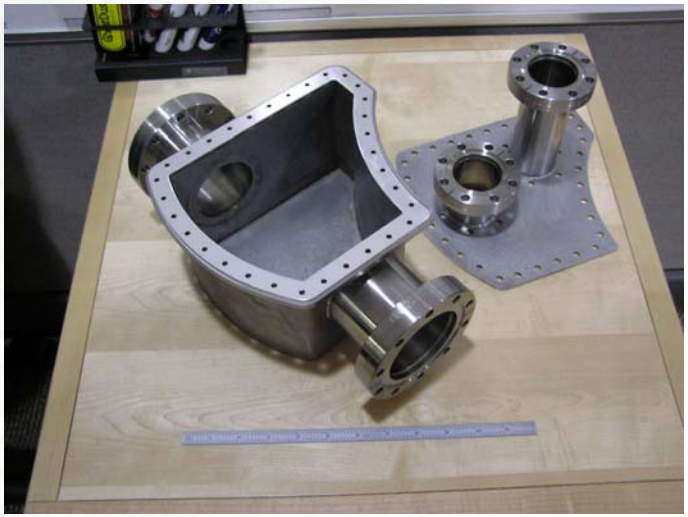

AGT-2 Manifold-Box

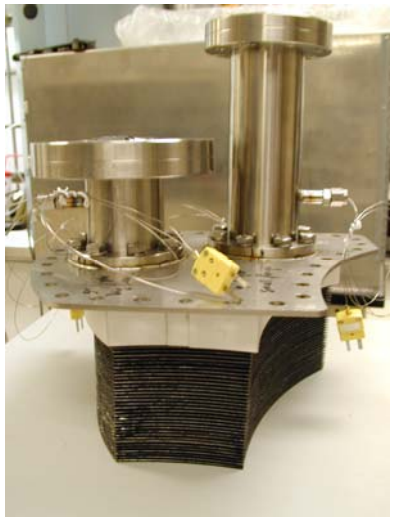

Plate Stack attached to Reforming side Manifold

First Prototype Assembly

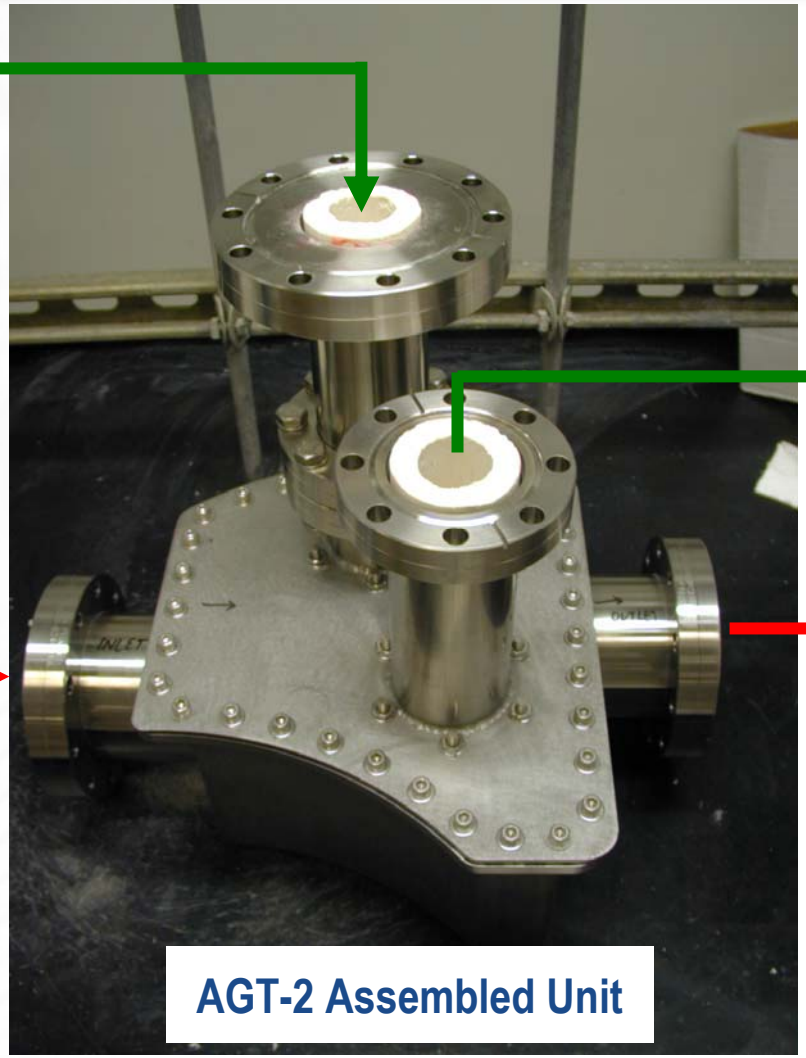

Prototype Test Cell

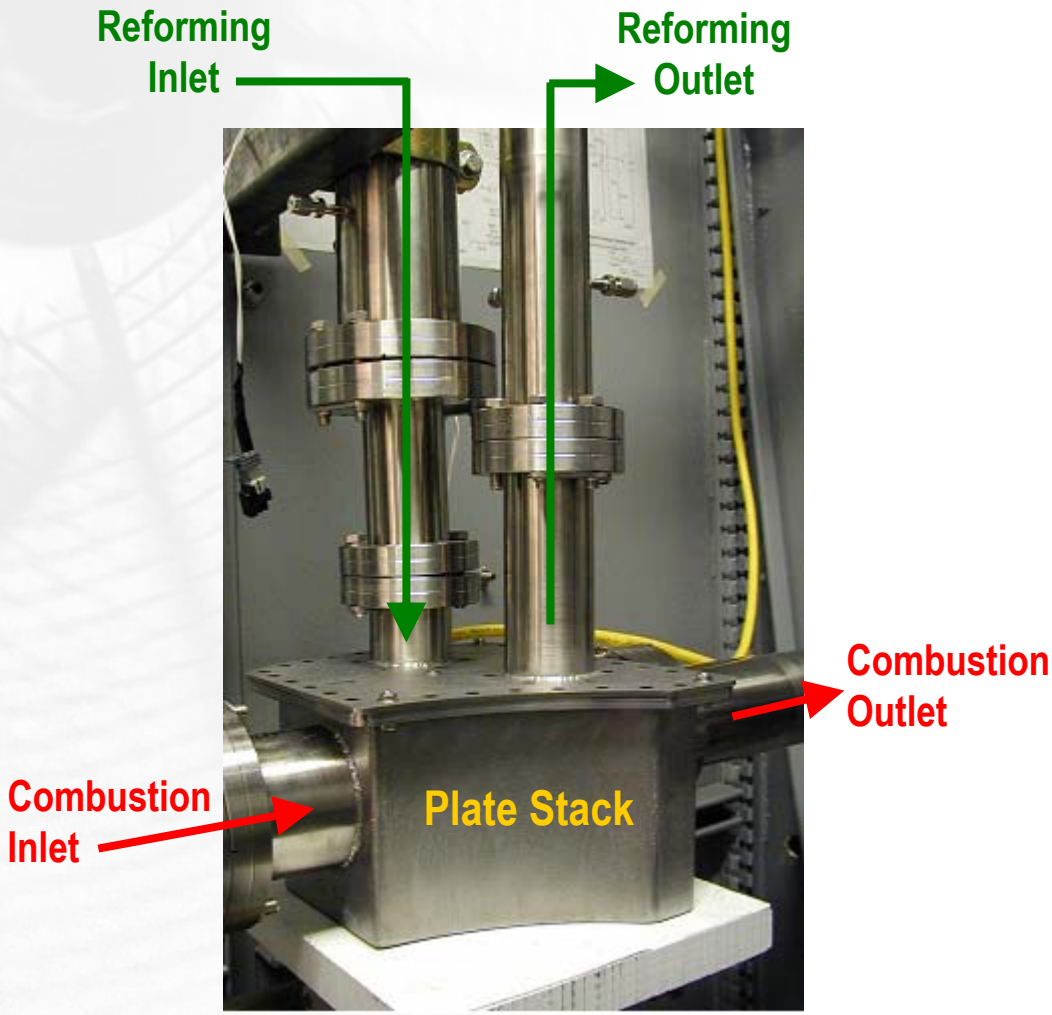

CLEAN AIR STARTS HERE™

Steam Generator

- Combustor – provides high temperature air to vaporizer

Xonon ® Catalyst to complete combustion

- PNNL's Micro-channel vaporizer – vaporizes water and preheats the steam

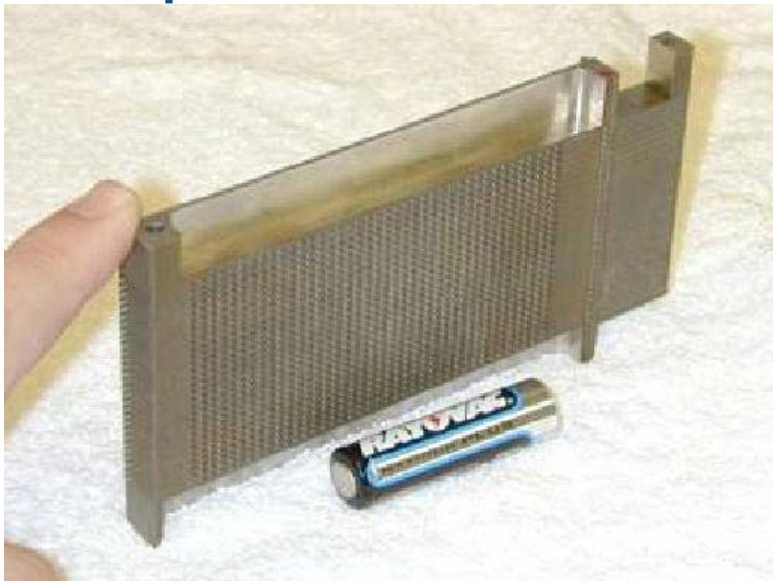

The combination of these two components results in an efficient and flexible steam generator for testing purposes

CLEAN AIR STARTS HERE™

Steam Generator and Secondary Heater Performance

- Steam generator is operated with constant thermal input
- As the steam flow changes, a secondary heater provides supplemental heat to maintain the steam at the desired operating temperature

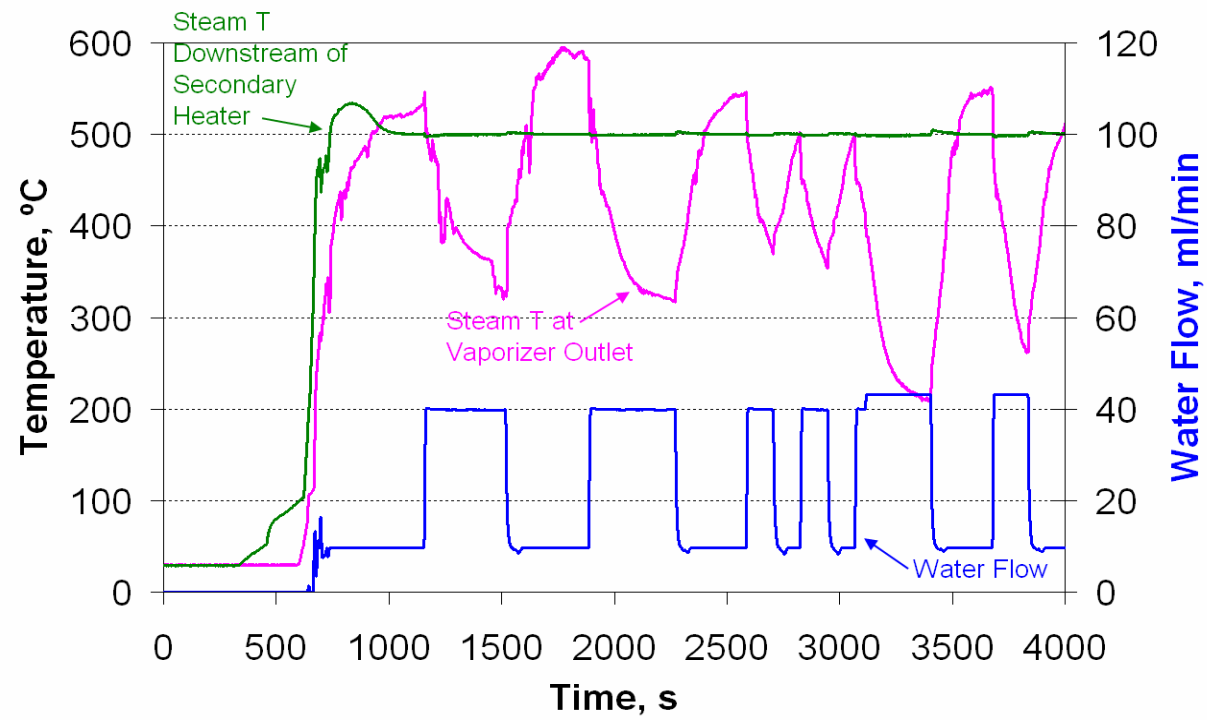

Steam generator and secondary heater combined can maintain constant steam reformer inlet temperature at different loads

CLEAN AIR STARTS HERE™

3 kW(e) Prototype Steady State Performance

- Previous equipment and controls resulted in significant perturbations during steady state
- Upgraded equipment and controls to achieve stable operating conditions during steady state

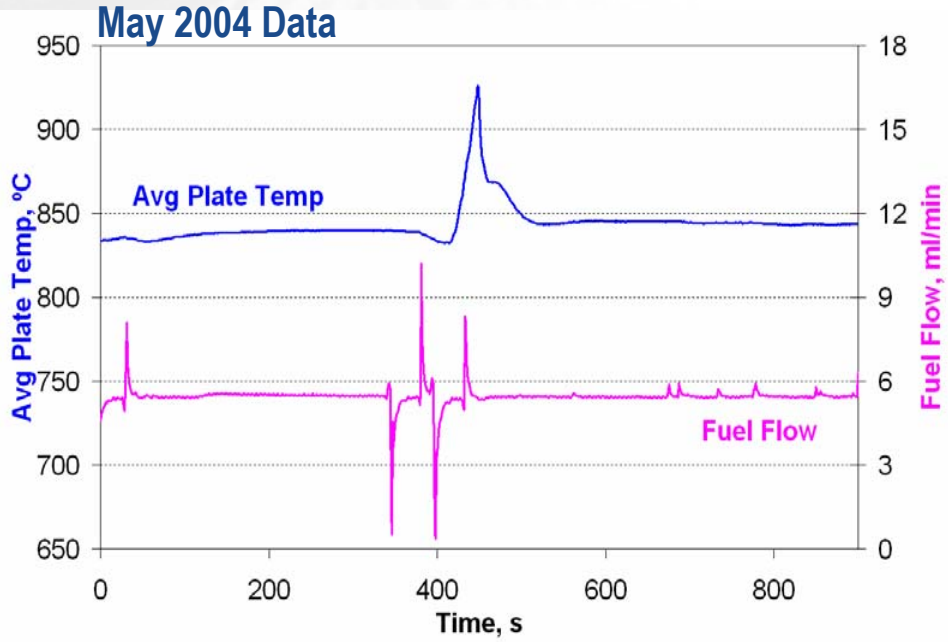

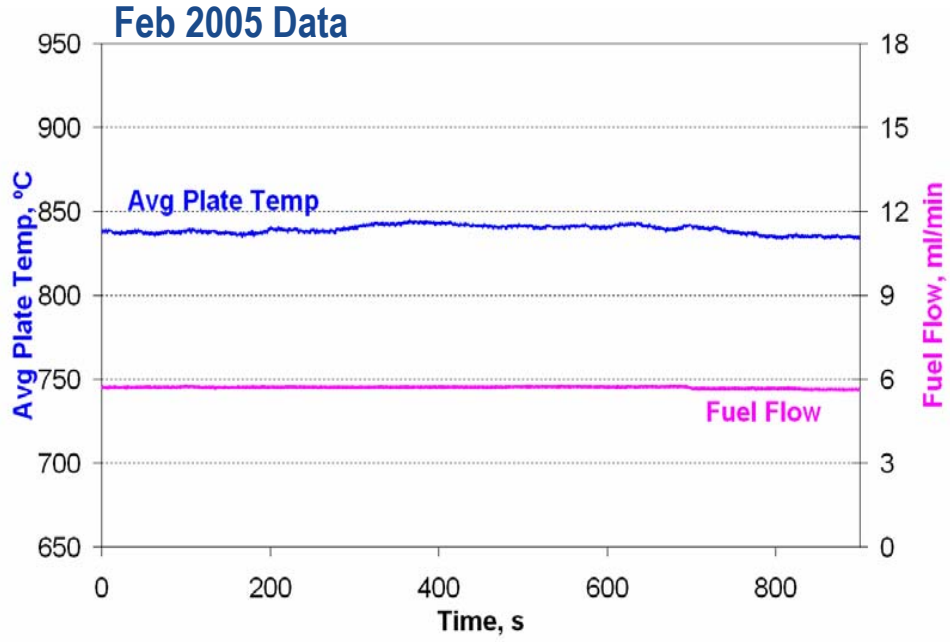

Improved fuel delivery system and PID control scheme resulted in less perturbations during steady state operation

CLEAN AIR STARTS HERE™

3 kW(e) Prototype Transient Performance

- Previous equipment and controls were limited to a 20% load change for a 1 second transient
- Upgraded equipment and controls permit 90% load change for a 1 second transient

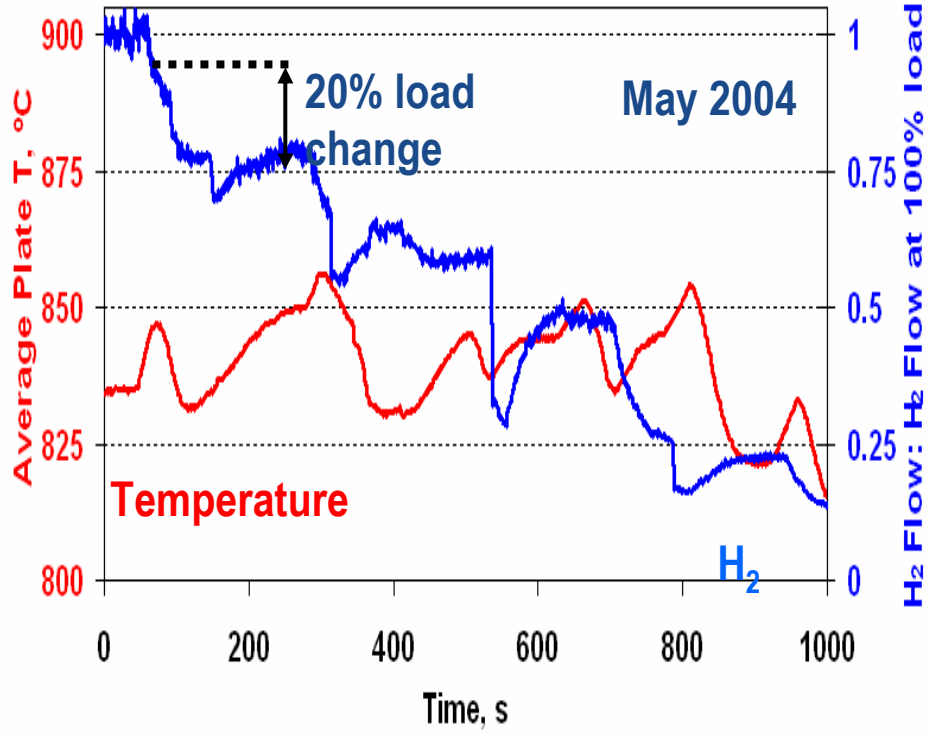

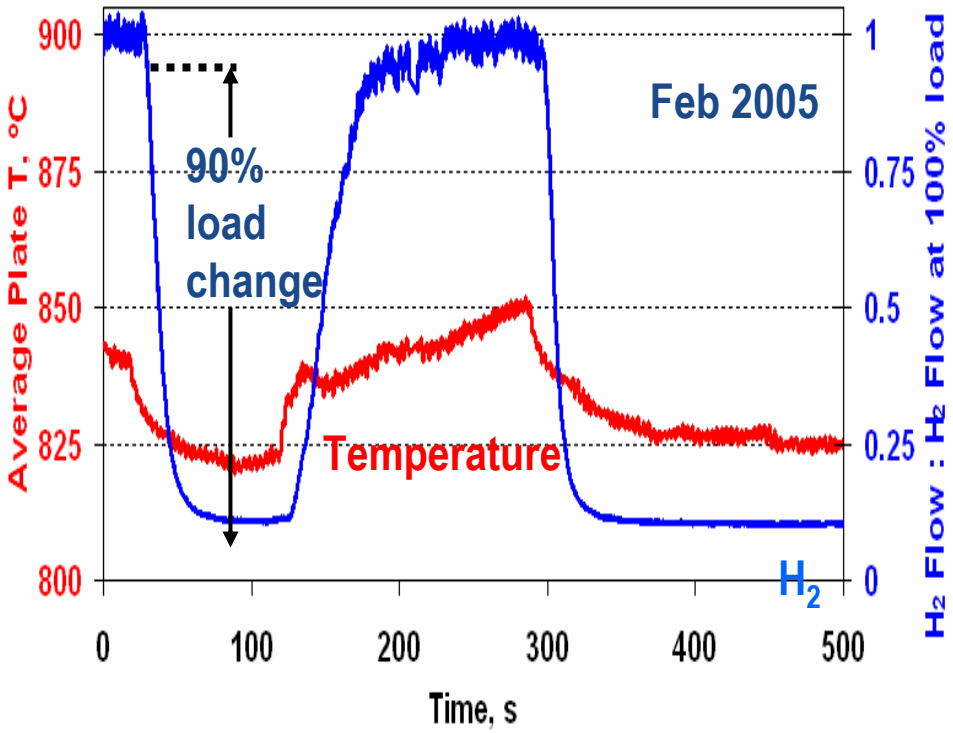

Implemented improvements allow for faster and smoother transients

CLEAN AIR STARTS HERE™

Modification of 3 kW(e) Prototype System

- Major performance improvements are due to:
  - Integration of automated control features
  - New low-flow fuel pumps for liquid delivery
  - Introduction and refinement of PID control loops
  - New quicker response steam generator
  - Use of secondary steam heater to more precisely control the temperature of steam entering the reformer

CLEAN AIR STARTS HERE™

Gasoline Steam Reforming Catalyst Improvements

- Steam Reforming (SR) catalyst improvements focused on lowering steam to carbon ratio, lowering operating temperature requirement, increasing catalyst activity and reducing catalyst cost
- Gasoline = ANL Benchmark I Fuel containing 10 ppm Sulfur

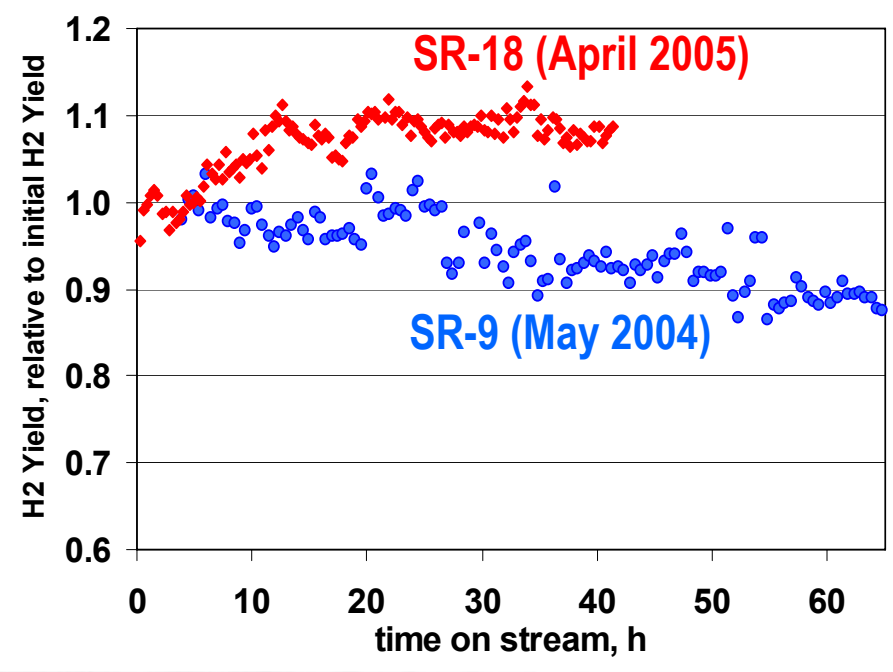

Catalyst performance summary

		SR-9 (May 2004)	SR-18 (April 2005)
Steam to carbon ratio	mol/mol	3.8	3.0
Lowest T of operation	°C	825	785
Initial catalyst activity	a.u.	1.00	1.57
Catalyst cost	$/kW(e)	20.15	2.56

Significant improvements in catalyst durability, operability and cost

CLEAN AIR STARTS HERE™

Water Gas Shift Catalyst Durability

- Water Gas Shift (WGS) catalyst durability test performed to measure rate of deactivation
- WGS catalyst will be sized for 2x operating margin (assuming regeneration every 1000 hours)
- Durability testing will continue

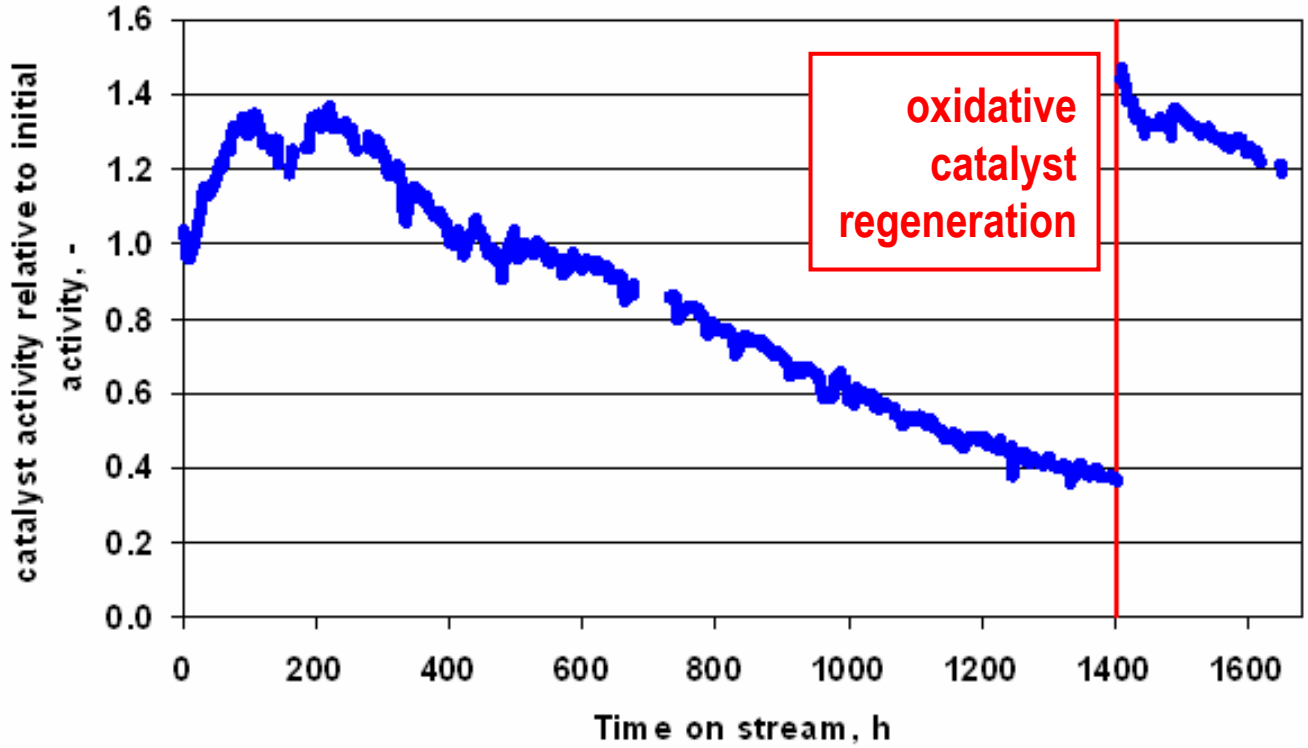

WGS catalyst activity can be fully recovered with regeneration cycle

CLEAN AIR STARTS HERE™

Preferential Oxidation Catalyst Improvements

- Preferential Oxidation (PrOx) catalyst improvements focused on achieving the < 10 ppm CO target over a wide temperature range

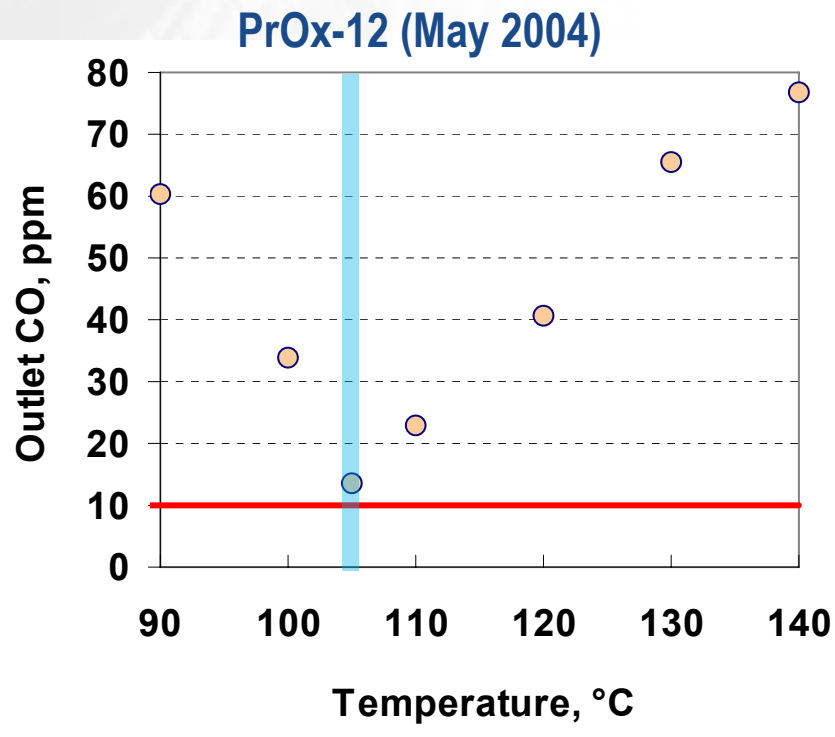

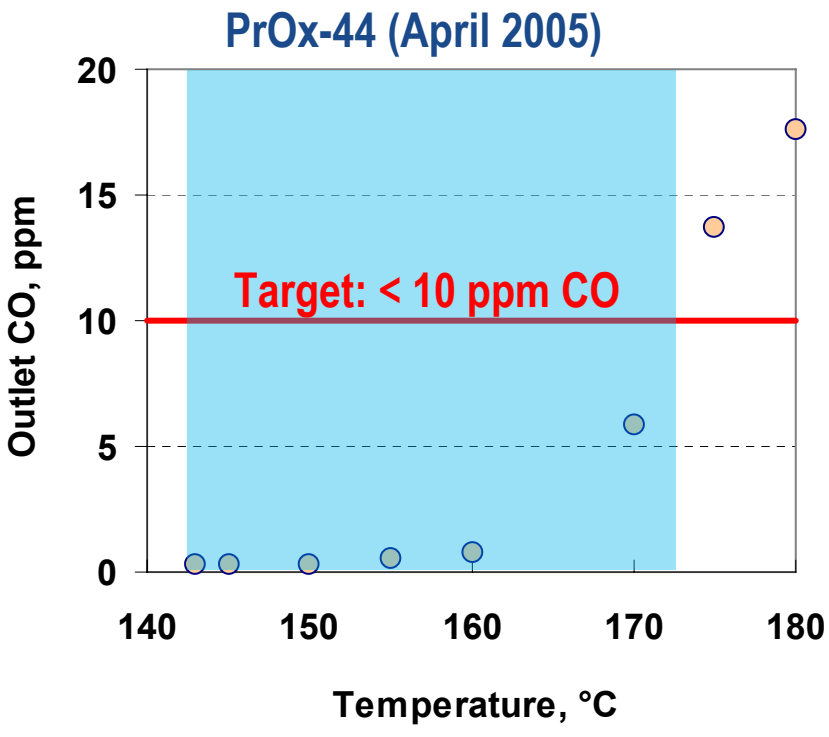

Significant improvement in the < 10 ppm CO operating temperature range

CLEAN AIR STARTS HERE™

Next Steam Reforming Prototypes

- Advantages of New Prototypes:
  - Custom stamped plates for more efficient use of plate surface area
    - Increased active surface area per plate
    - Higher power density
  - Features that reduce thermal mass for more rapid start-up and transient response
    - Thinner plates
    - Improved structural design to support new plate stack
  - More commercial fabrication and assembly process
- Developing 2 different prototypes in parallel

CLEAN AIR STARTS HERE™

Next 3kW(e) Steam Reforming Plate Stack

Solid model of low thermal mass plate stack prototype

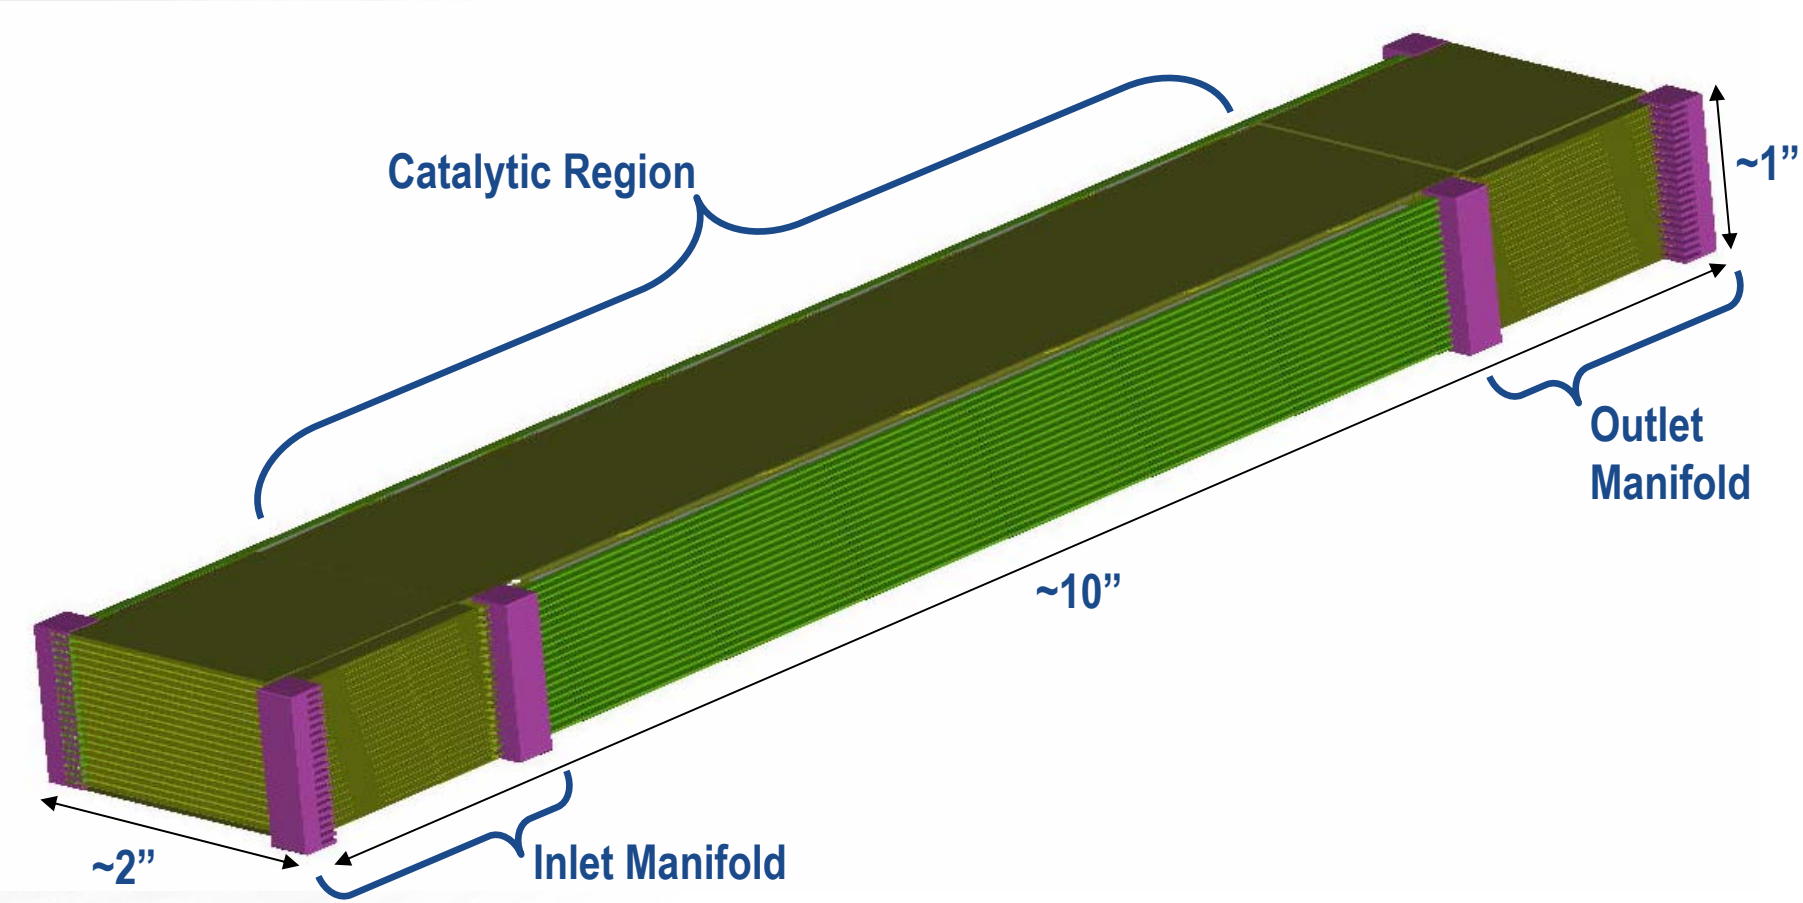

CLEAN AIR STARTS HERE™

Custom Stamped Plate

- A series of custom stamped plates will be used for the next steam reforming plate stacks
- Custom stamped plates are 0.002” (0.05 mm) thick, significantly thinner than the first prototype plates
- Plate design maximizes catalyst active surface area per plate

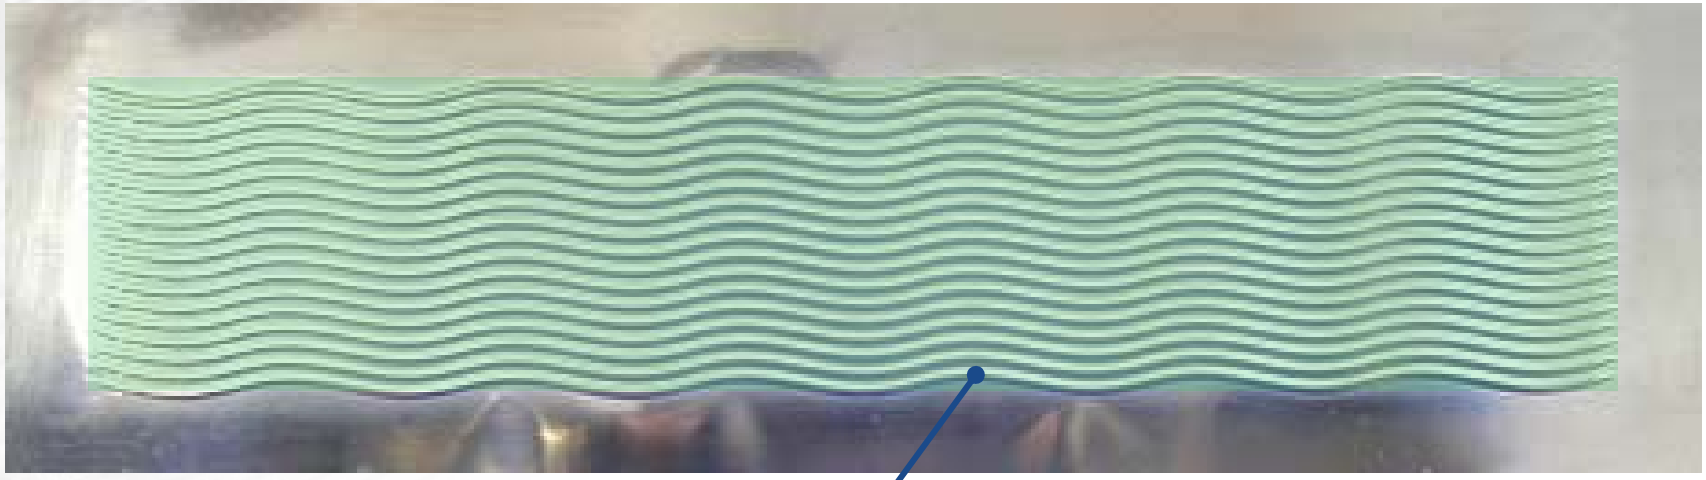

Corrugated region will be coated with catalyst
(shaded for illustration purposes)

CLEAN AIR STARTS HERE™

Alternative Applications for Plate Base Fuel Processing System

- Office of Naval Research (ONR) has a need for a compact, high-power density, man-portable 1 kW(e) fuel cell power generating system fueled by JP-8
- US Army Tank Automotive Research Development and Engineering Center (TARDEC) has a need for 5 – 20 kW(e) ground vehicle fuel cell auxiliary power units (APUs) fueled by JP-8

Alternative applications exist for plate base fuel processing technology developed under this contract

Future Work

- Demonstrate improved start-up and transient performance with new reactor prototypes
- Demonstrate steam reforming and preferential oxidation catalyst durability (1000 hours)
- Explore alternative applications for the technology developed under this contract
- Complete final report to document results and close-out the program

CLEAN AIR STARTS HERE™

Publications and Presentations

Publications:

- J. M. Zalc, D. G. Löffler, Fuel processing for PEM fuel cells: transport and kinetic issues of system design, *J. Power Sources* 111 (2002) 58-64.
- J. M. Zalc, V. Sokolovskii, D. G. Löffler, Are Noble Metal-Based Water–Gas Shift Catalysts Practical for Automotive Fuel Processing?, *J. Catal.,* 206 (2002) 169–171.

Presentations:

- System Integration Issues for a Plate Reactor-Based Automotive Fuel Processor – Am. Institute of Chemical Engineers Annual Meeting, 8 November 2002, Indianapolis, IN.
- Plate Based Fuel Processing System – FreedomCAR Technical Team Review, 19 March 2003, Detroit, MI.
- Non-noble Metal Water-Gas Shift Catalysts for Automotive Fuel Cell Application – American Chemical Society Meeting, April 2003.
- Plate Based Fuel Processing System – 2003 DOE Hydrogen, Fuel Cells and Infrastructure Technologies Program Review Meeting, 19-22 May 2003, Berkeley, CA.
- System Integration of a Plate Reactor for Gasoline Steam Reforming for Automotive Applications – 2003 Grove Fuel Cell Symposium, October 2003, London, UK.
- System Integration of a Plate Reactor for Gasoline Steam Reforming for Automotive Applications – 2003 Fuel Cell Seminar, November 2003, Miami Beach, FL.
- Plate Based Fuel Processing System – FreedomCAR Technical Team Review, 18 February 2004, Washington, DC.
- Plate Based Fuel Processing System – 2004 DOE Hydrogen, Fuel Cells and Infrastructure Technologies Program Review Meeting, 24-27 May 2004, Philadelphia, PA.
- Modeling and Test Results of Plate Reactors for a Gasoline Fuel Processor System – 2004 Fuel Cell Seminar, November 2004, San Antonio, TX.
- Modeling and Test Results of Plate Reactors for a Gasoline Fuel Processor System – 2005 Meeting of the Pacific Coast Catalysis Society, March 2004, Berkeley, CA.

Hydrogen Safety

- The most significant hydrogen hazard associated with this project is with undesired combustion of the hydrogen within the steam reforming prototype plate reactor.
  - Hydrogen is flammable and therefore, fire is the most significant hydrogen hazard if it results in injury to personnel and/or destruction or loss of equipment. A fire can result when hydrogen (from a leak in the 3 atm reformer side of the prototype) and an oxidizer (air on the 1 atm combustion side of the prototype) forms a combustible mixture, the combustible mixture contacts an ignition source (combustion catalyst on the combustion side of the prototype), and ignition occurs.
  - A burn can result from direct contact to a hydrogen fire, thermal radiation from a hydrogen fire, or contact with a surface that has been exposed to a hydrogen fire.

Hydrogen Safety

- Our approach to deal with the fire hazards associated with the steam reforming prototype plate reactor is:
  - Ensure a leak free plate reactor by pressure testing all welds during plate stack assembly, after final assembly of the plate stack and before installing the plate stack for steam reforming testing
  - Pressure testing the plate stack on a daily basis prior to the day's steam reforming testing
  - Prohibiting access into the prototype test cell while the plate reactor is fueled
- The test cell is continuously monitored by a lower explosive limit (LEL) detector. When the hydrogen concentration in the test cell is > 20% of the LEL, the monitoring system will automatically:
  - Shut-down power and fuel flow to the prototype system
  - Initiate a nitrogen purge through the prototype hardware
  - Trigger a laboratory evacuation alarm
- In the event a fire develops during a steam reforming experiment, thermocouples monitoring temperature of the prototype will initiate an automatic power and fuel shut-down sequence when the plate temperature exceeds 900°C (well below the hydrogen flame temperature).