2008
DOE Hydrogen Program
Merit Review Presentation

Advanced Materials for Proton Exchange Membranes

James E. McGrath	Donald G. Baird
University Distinguished Prof. of Chemistry	Harry C. Wyatt Prof. of Engineering
Macromolecules and Interfaces Institute	Dept. of Chemical Engineering (0211)
and Department of Chemistry	Virginia Tech
Virginia Tech	128 Randolph Hall
Blacksburg, VA 24061	Blacksburg, VA 2406
Jmcgrath@vt.edu	dbaird@vt.edu

Project ID # FC16

This presentation does not contain any proprietary, confidential, or otherwise restricted information

McGrath Group 2008

Front Row: Rachael VanHouten, Natalie Arnett, Jim McGrath
Back Row: Dr. Gwangsu Byun, Mou Paul, Ozma Lane, Hae Seung Lee, Yu Chen, Dr. Abhishek Roy, Dr. Daniel Brandell (*now at Upsala Univ., Sweden*); missing, Dr. Chang Hyun Lee

Outline

- *Overview*
- *Acknowledgements*
- *Objectives*
- *Results*
- *Conclusions*
- *Current and Future Research*

OVERVIEW

Timeline

- Project State Date: May 2006
- Project End Date: May 2011
- Percent Complete: 40%

Barriers

- Conductivity at 120°C and low RH
- Swelling Deswelling

Budget

Total Project Funding: $1.5MM

Funding received in FY07: $300K

Funding for FY08: $350K

Partners

- Los Alamos National Labs
- Giner Electrochemical Systems
- Hydrosize, Inc.
- Nissan Motors Co
- Arkema

Acknowledgements

- McGrath Research Group: past and present
- May 2006" DOE Contract on "*High Temperature, Low Relative Humidity, Polymeric Membranes Based on Hydrophilic-Hydrophobic Disulfonated Poly(arylene ether) Block Copolymers*
- *Los Alamos National Laboratory (LANL)*
- *Nissan Motor Co*

Objectives and Approach

- Design, identify, and develop the knowledge base to enable proton exchange membrane films and related materials to be utilized in fuel cell applications, particularly for H2/Air Systems at 100-120°C/low RH
- Nano-phase Separated Hydrophilic-Hydrophobic Thermally Stable Multi-Block Copolymers
- Correlate Water Diffusion Coefficients with Proton Conductivity Under Partially Hydrated Conditions
- Relate Thermodynamics of Nano-phase Formation to Ordered Morphology and to Conductivity, Diffusivity and Novel Membrane Self Assembly

Material Design Options

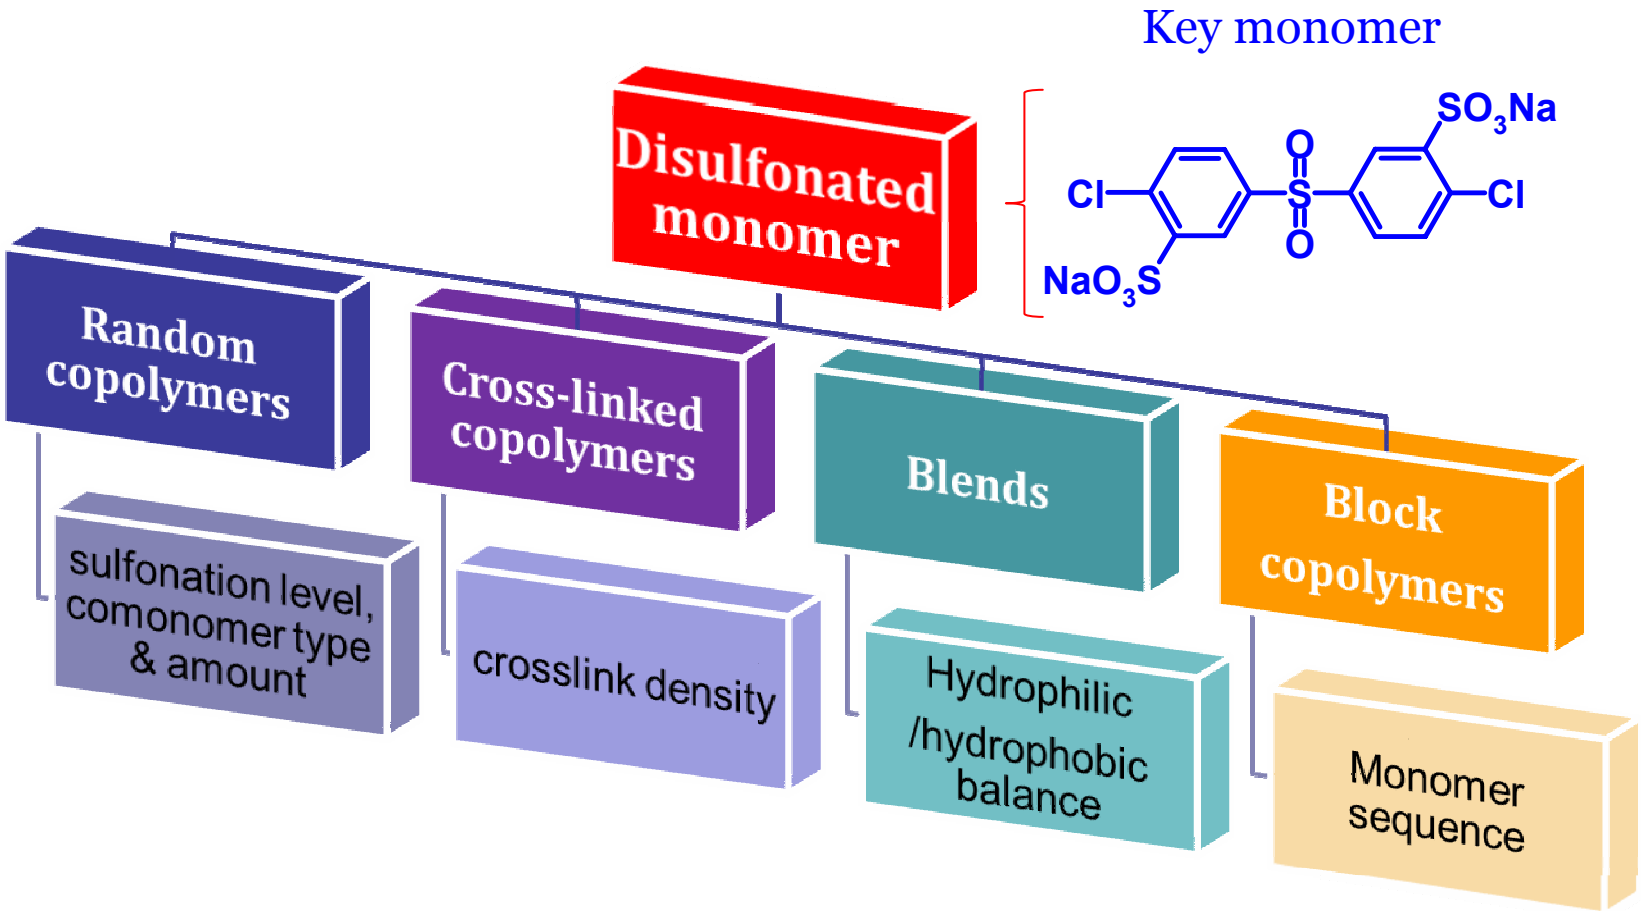

Highly Hydrophobic-Hydrophilic Multiblock Copolymers

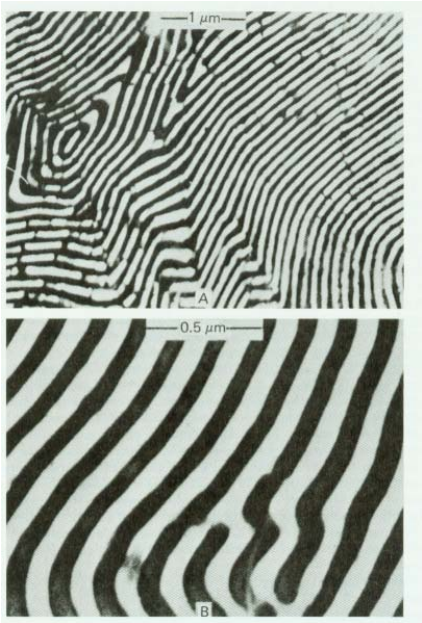

A. Noshay and J. E. McGrath, "Block Copolymers: Overview and Critical Survey," Academic Press, New York, January 1977, p.91.an S-B diblock copolymer

- Nanophase-separated morphology may be precisely controlled through synthesis.
- Enhanced proton conductivity, water diffusion coefficient and mechanical strength are expected.

Our Initial work:

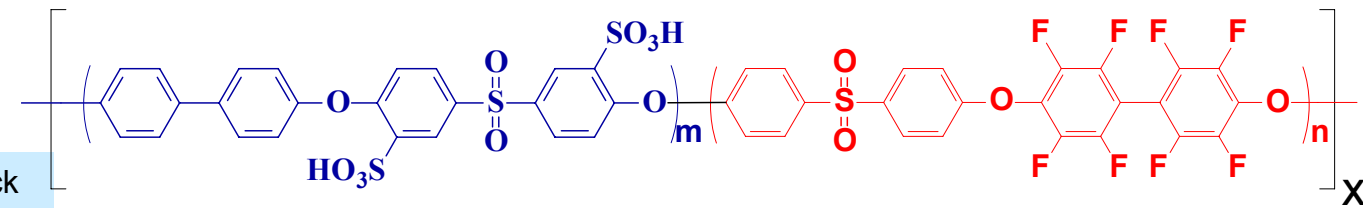

Hydrophilic segments, provides Proton conductance

Hydrophobic segments, imparts mechanical integrity

Yu, Xiang; Roy, Abhishek; Dunn, Stuart; Yang, Juan; McGrath, James E. Synthesis and characterization of sulfonated-fluorinated, hydrophilic-hydrophobic multiblock copolymers for proton exchange membranes. Macromolecular Symposia (2006), 245/246(World Polymer Congress--MACRO 2006), 439-449.

Hydrophilic-Hydrophobic Multi-Block and Random(control) Copolymers

1

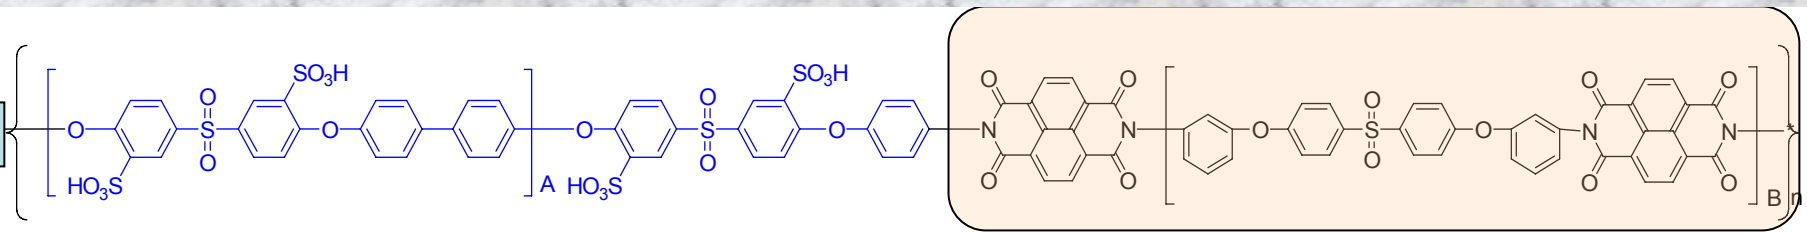

BPSH-PI (A:B)

A~ Hydrophilic block length in kg/mole, B~ Hydrophobic block lengths in kg/mole

2

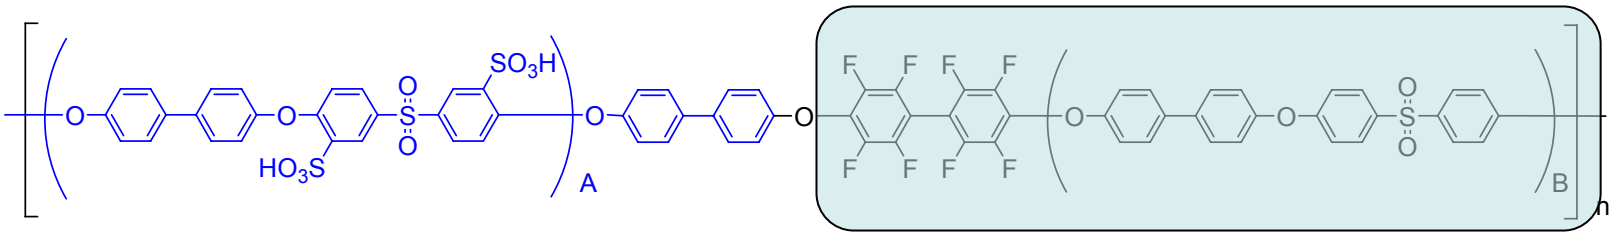

BPSH-BPS (A:B)

3

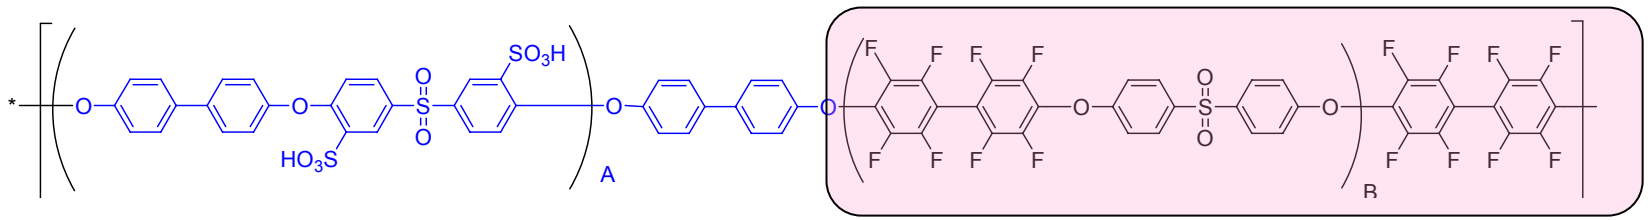

BPSH-BisSF (A: B)

4

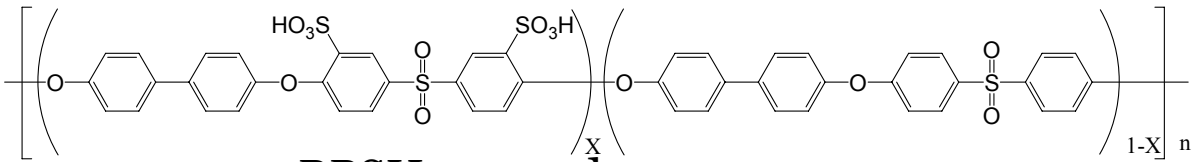

BPSH-xx random

Modulus-Temperature Behavior of a 10K-10K BPSH100-BPS-0 Multi-Block Copolymer

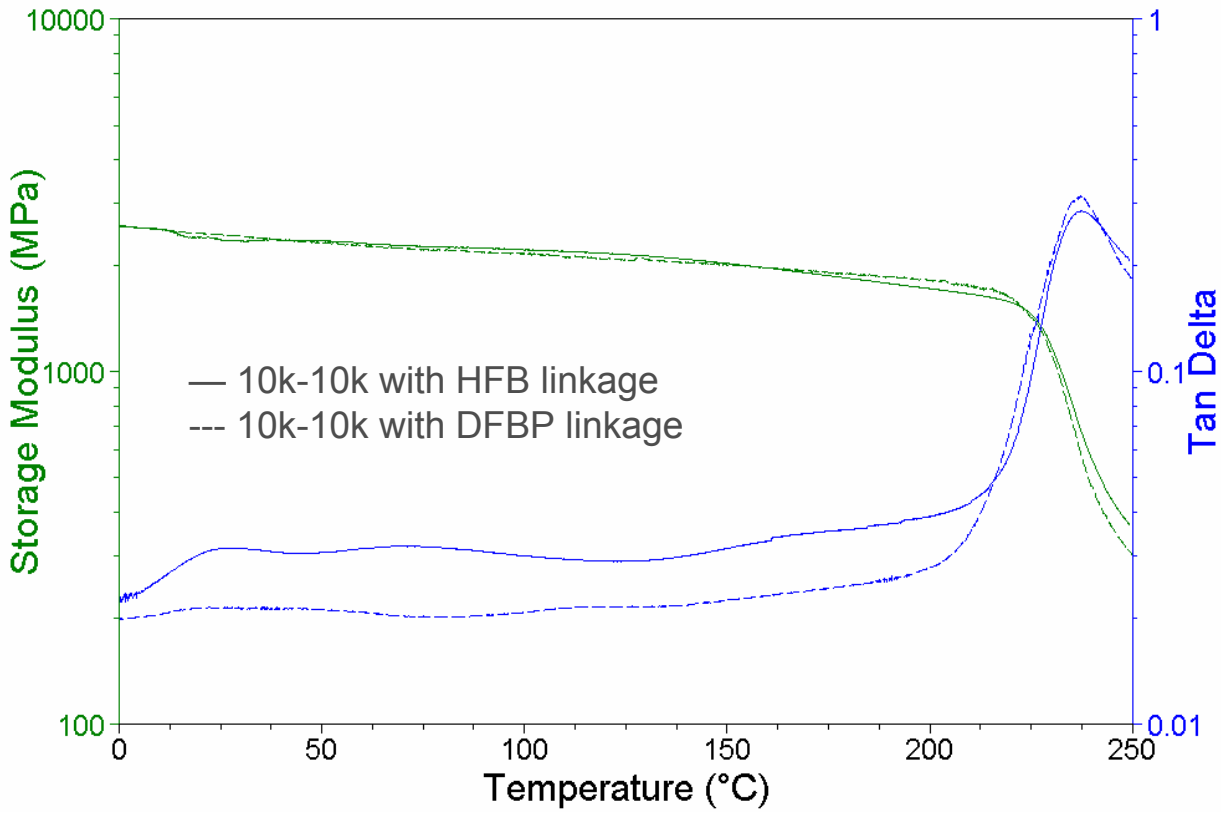

- T_g virtually identical for both linkage types

Analysis performed with TA Instruments DMA 2980 at 1 Hz. An initial drying run to 200 °C for 10 min followed by cooling with liquid N_2 to 0 °C for 10 min preceded each temperature sweep. Samples heated at 5 °C/min to 250 °C. Displacement set at approx. 0.1% of sample length.

Toward Improved Conductivity of Sulfonated Aromatic Proton Exchange Membranes at Low Relative Humidity

Melinda L. Einsla[1], Yu Seung Kim*[1], Marilyn Hawley[1], Hae Seung Lee[2], James E. McGrath[2], and Bryan S. Pivovar[1]

[1]Sensors and Electrochemical Devices Group, Los Alamos National Laboratory, Los Alamos, NM 87545

[2]Macromolecules and Interfaces Institute, Virginia Tech Blacksburg, VA 24061

***Submitted to Chemistry of Materials*

Diffusion coefficients of hydrocarbon copolymers and Nafion as a function of relative humidity (Nafion is shown for comparison)

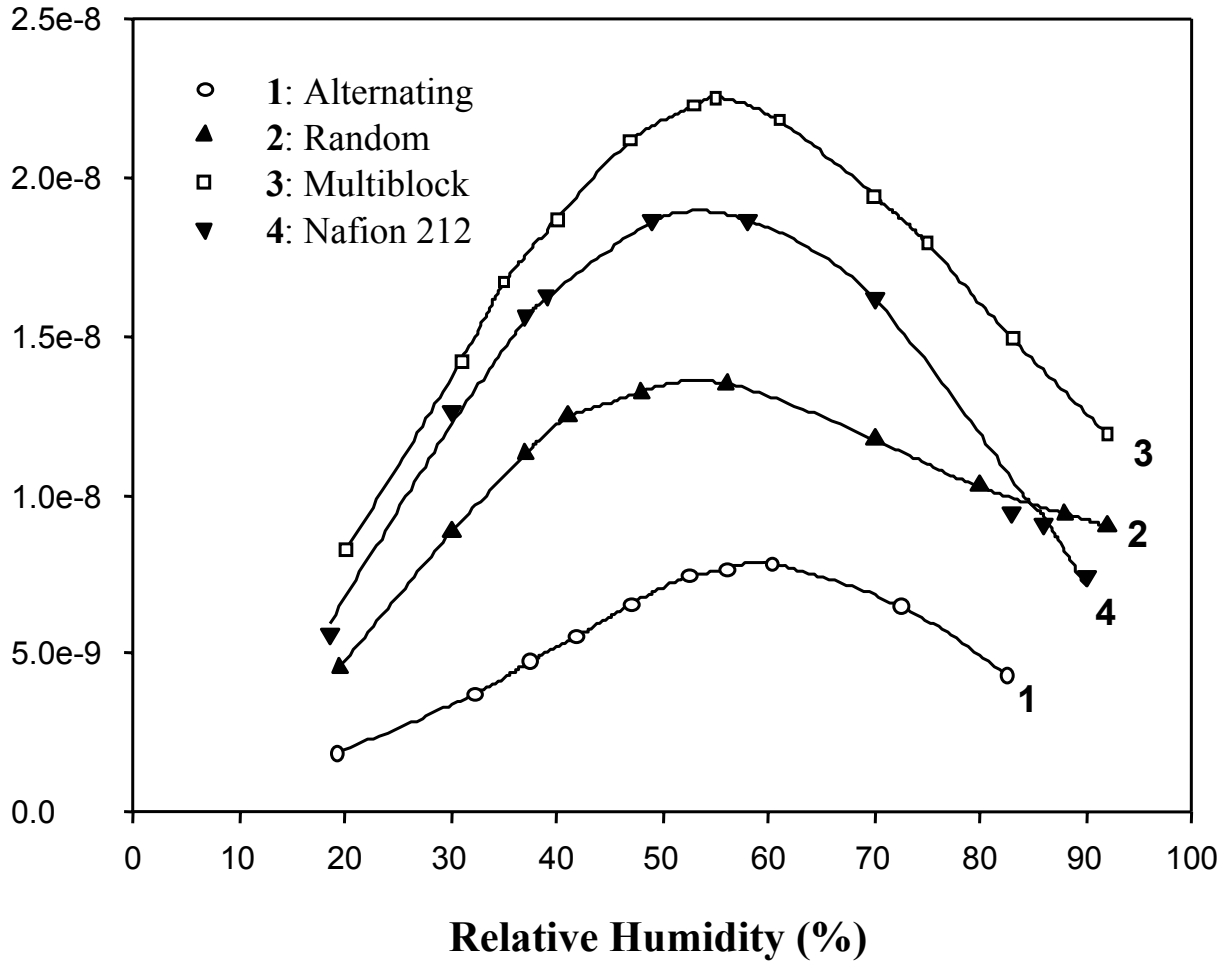

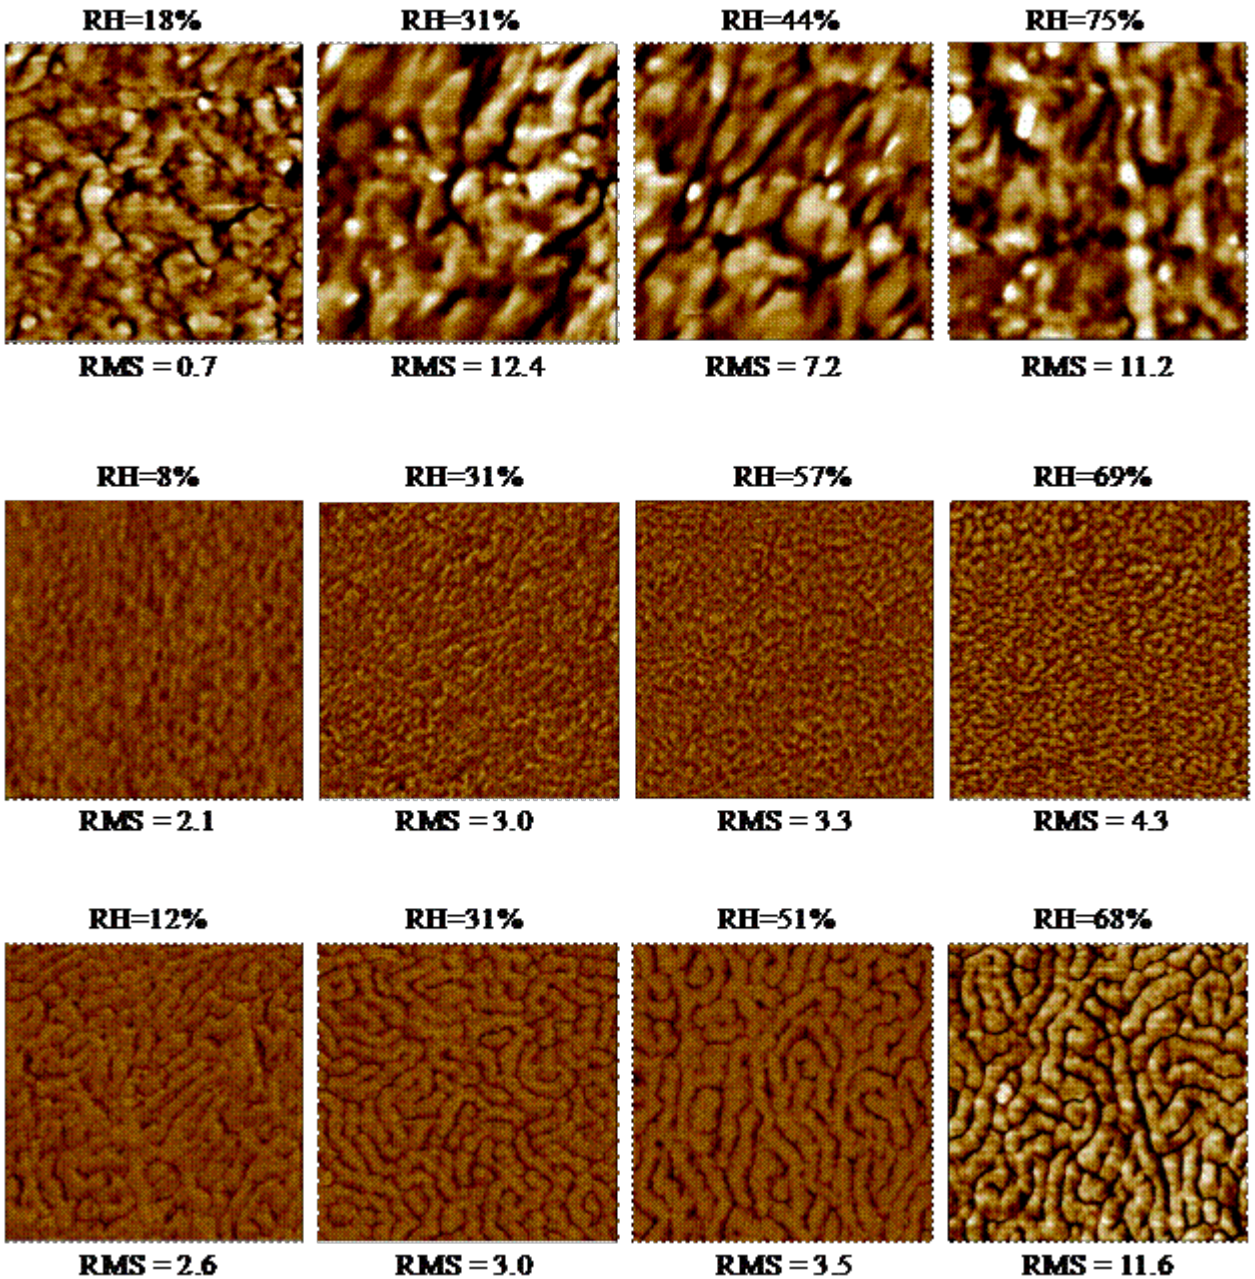

SFM images of alternating (top), random (center), and multi-block (bottom) copolymers at low and high humidity. Image size is 1 mm and phase range is 40° for all images.

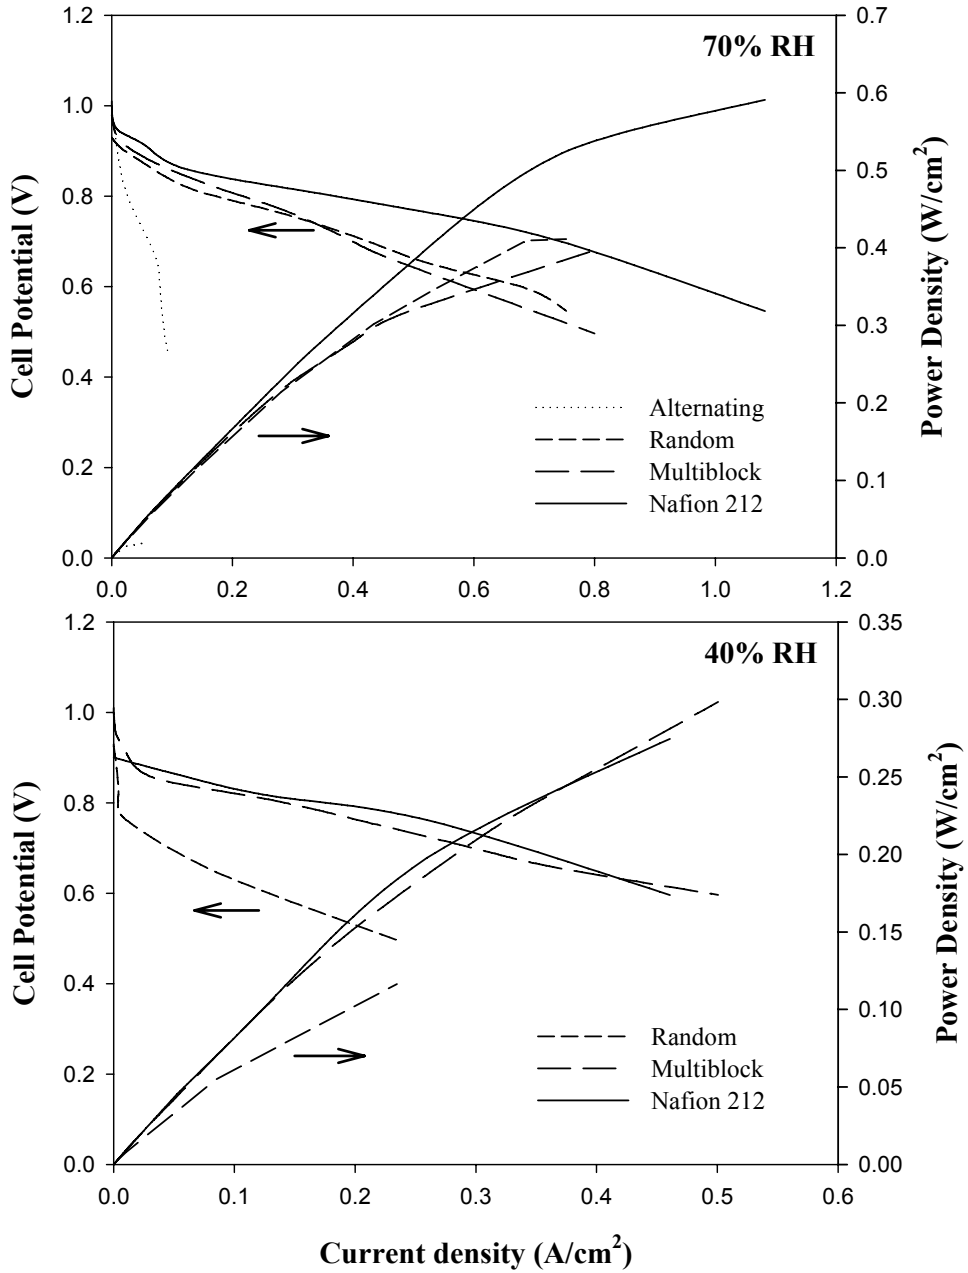

Hydrogen-air fuel cell performance of alternating, random and multiblock aromatic copolymers at 100 °C with Humidification at 70% (top) and 40% (bottom). Nafion 212 is shown for comparison.

Effect of water uptake on proton concentration

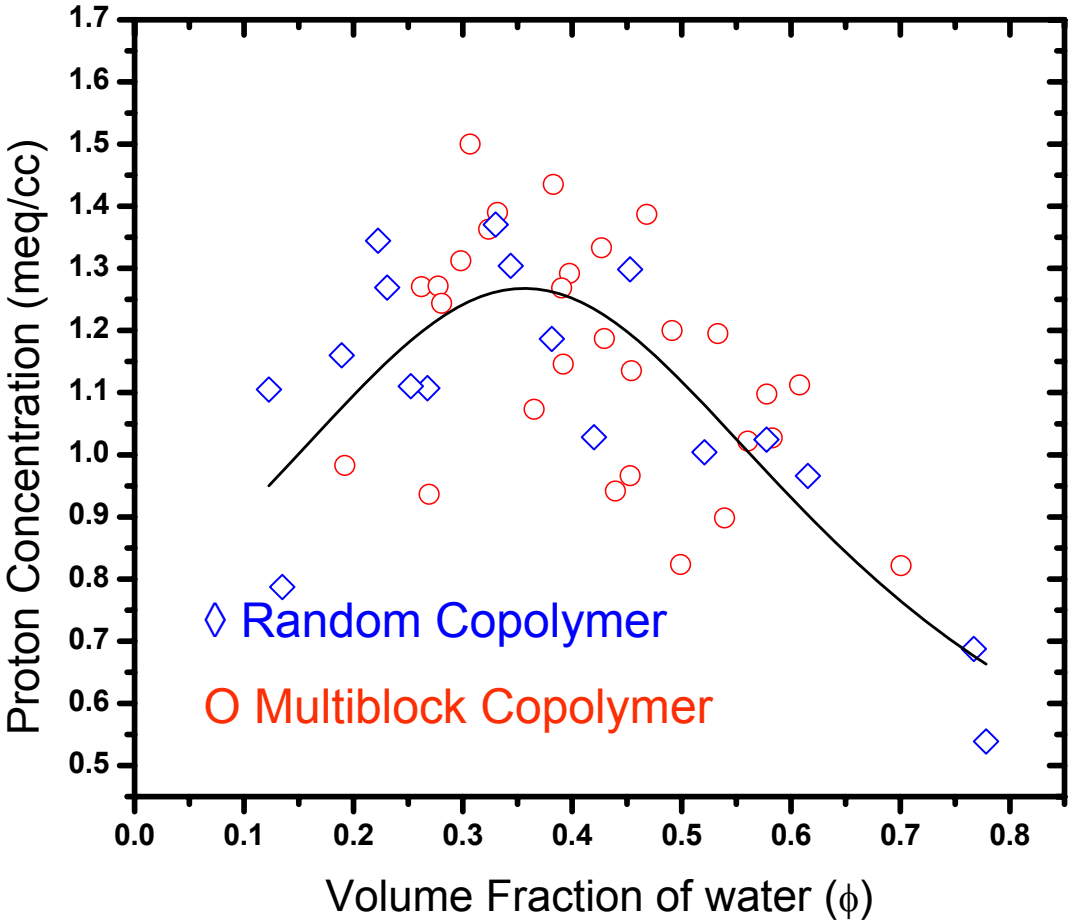

- Effective C_H^+ theoretically increases with IEC. However water uptake also increases
- Increasing water uptake decreases effective proton concentration
- Hence, C_H^+ goes through a maxima when plotted against water volume fraction .

Multiblock copolymers have higher water and proton diffusion coefficients than random copolymers

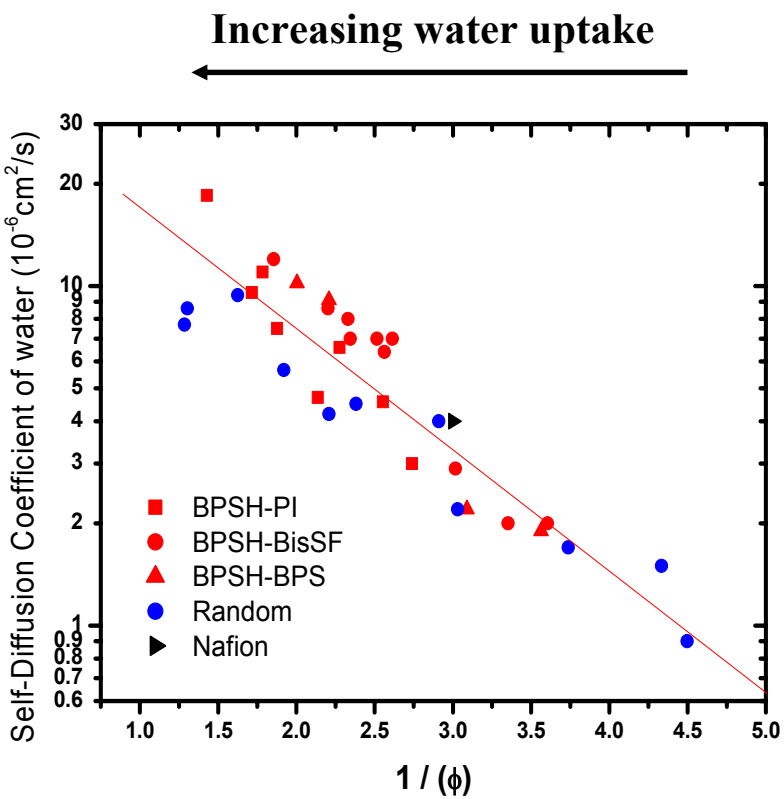

Measured from PGSE NMR, 25 ° C

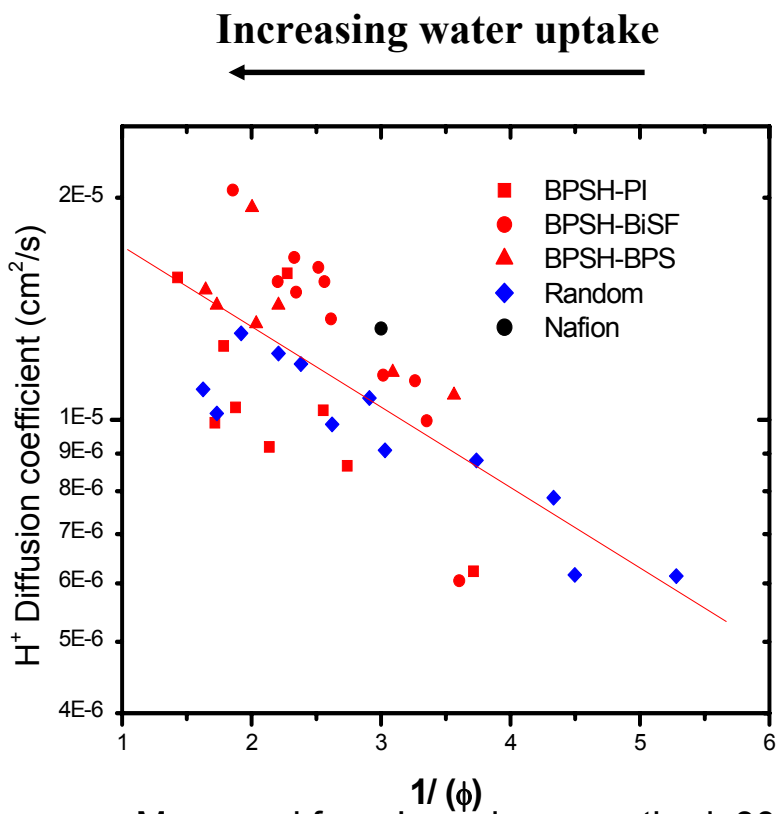

Measured form Impedance method, 30°C

- Both water and proton diffusion coefficient increases with water volume fraction
- Well connected phase separated morphology of block copolymers results in higher diffusion coefficients than the random copolymers at a given water content

Characterization of the BPSH-BPS Multiblock Copolymers

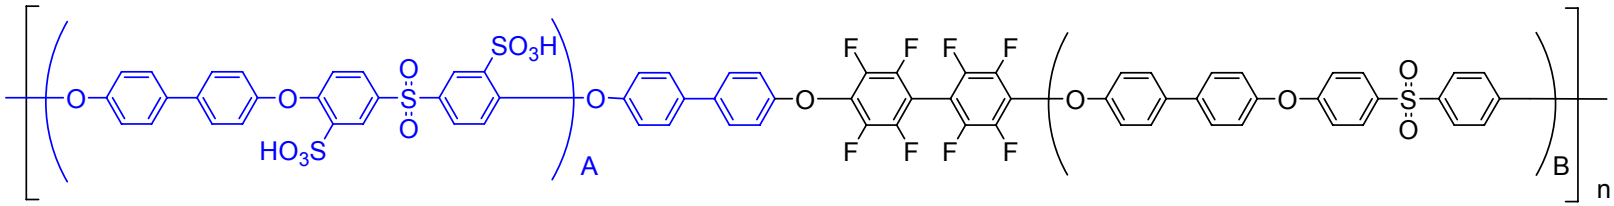

Block Copolymer[a]	Ion Exchange Capacity (IEC) (meq/g)	Water Uptake (%)	Hydration Number (λ)	Proton Conductivity[b] (S/cm)	E_a Proton transport[c] (kJ/mole)
BPSH35	1.50	36	13.3	0.070	13.3
BPSH3-BPS3	1.33	30	12.5	0.065	14.4
BPSH5-BPS5	1.39	33	13.2	0.088	13.4
BPSH10-BPS10	1.28	60	25.6	0.095	8.12
BPSH-10-BPS-5	**1.83**	**100**	**30.3**	**0.160**	**9.8**
BPSH-15-BPS-10	1.71	90	29.2	0.140	8.9
BPSH-20-BPS-15	1.71	70	22.7	0.120	8.8

a. Acronym : BPSH-x-BPS-y **x = Molecular Weight of Sulfonated Poly(arylene ether) in kg/mol**
y = Molecular Weight of Poly(arylene ether) in kg/mol

b. Measurements were conducted in water at 30ºC c. Measured in liq water over temp range of 30 to 80 degree C

DFBP series with unequal block lengths

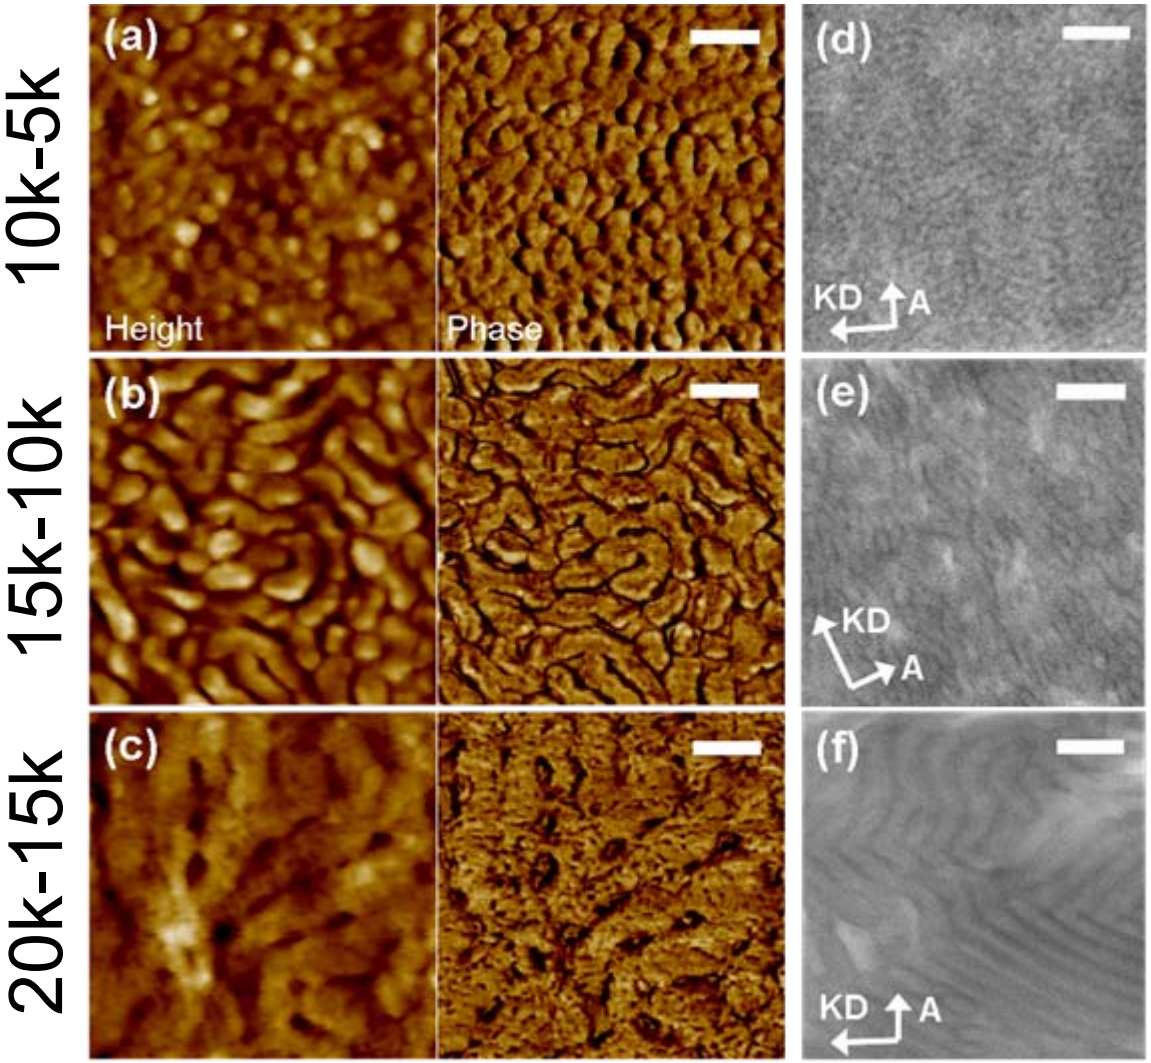

Proton Conductivity (S/cm)[a]	Water Uptake (%)	I.V. (dL/g)[b]	IEC (meq/g)[c]
0.160	100	0.94	1.83
0.140	90	0.97	1.71
0.120	70	1.12	1.71

[a]At 30 ºC in DI water
[b]In NMP at 25 ºC w/ 0.05 M LiBr
[c]Determined by titration

AFM setpoint ratios: 0.91, 0.95, 0.89; Z ranges: 12, 12, 25 nm and 30°. TEM micrographs: “A” denotes direction of air side. “KD” denotes the knife direction during microtoming. Scale bars = 100 nm.

Reverse Roll Film Casting

- Ratio of speeds of coating and transporting rolls

  α =1.5 to 2.0

- Gap between coating and metering rolls

  $$\text{Gap} = (T_w/\alpha)\,/(\lambda/2) = (1+\rho/c)\,T_d\,/(\alpha\,\lambda/2) \qquad \text{(Lubrication model)}$$

  where

T_w: Thickness of wet films

T_d: Thickness of dry films

α: Ratio of speeds of coating and transporting roll (wipe ratio)

λ: Dimensionless flow rate between 1.23~1.33

ρ: Density of the polymer

c: Concentration of casting solution in w/v

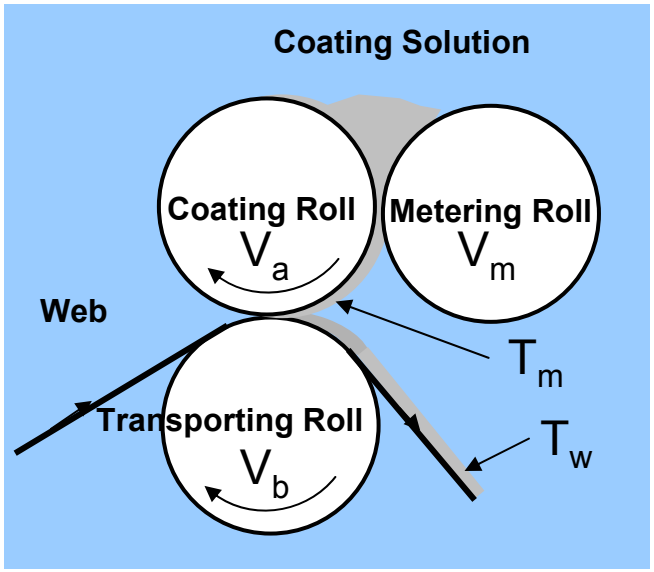

Polymer Processing Influences Performance of Continuous Cast Films

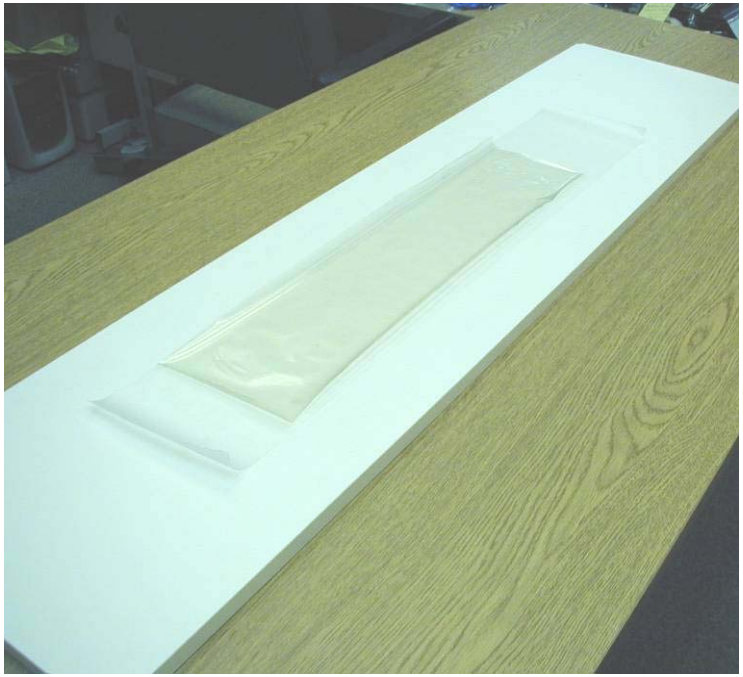

BisSF 17k/12k Block Copolymer Films

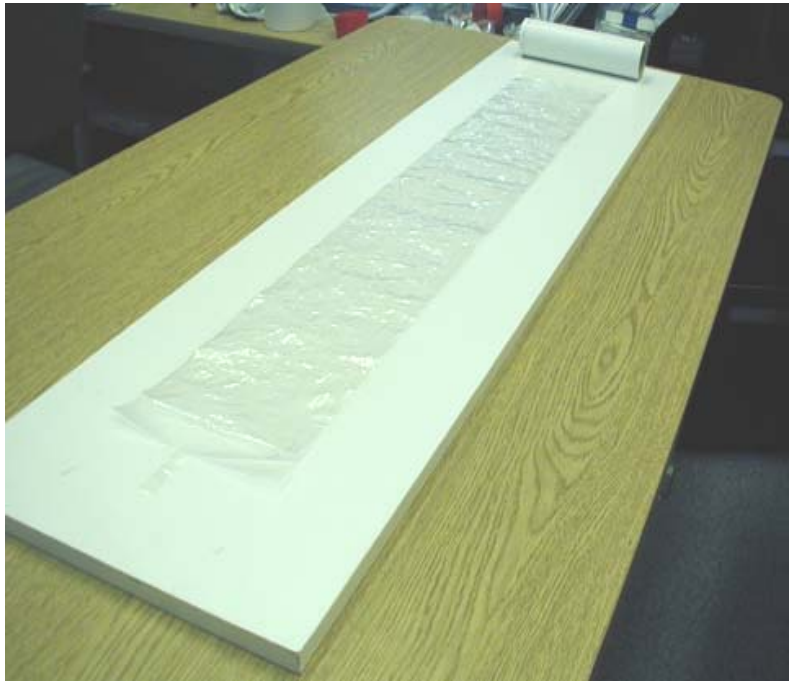

6F40 Random Copolymer Films

Proton conductivity as a function of RH @ 30°C for VT(BPSH-BPS-10-5) sample and NRE212 measured by BekkTech

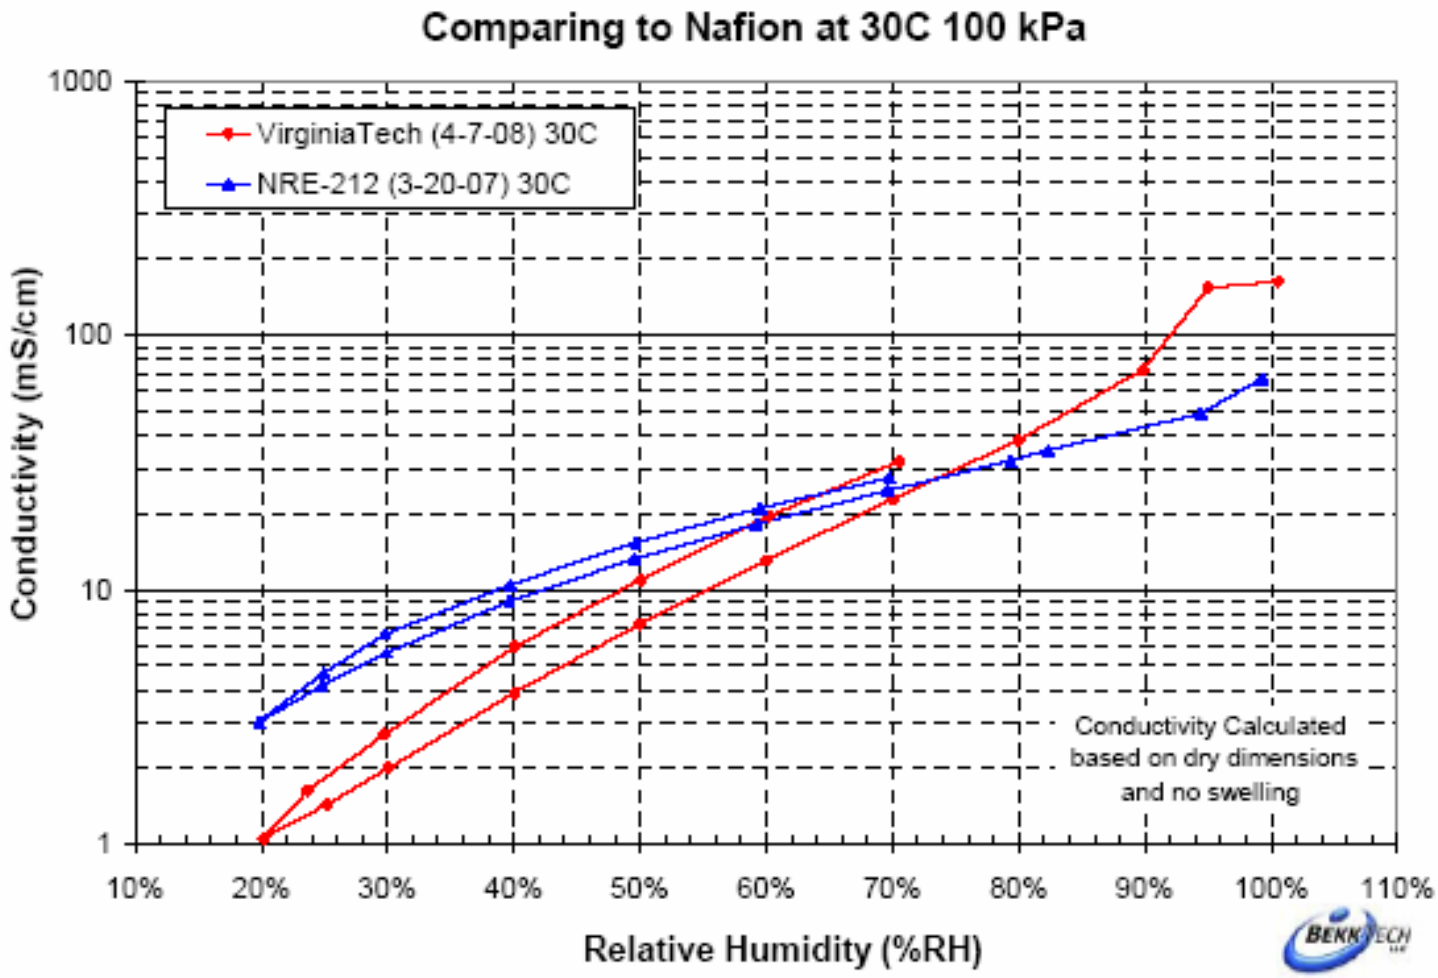

Proton conductivity at VT as a Function of RH using a ESPEC Humidity Oven and Solartron Impedance Analyzer

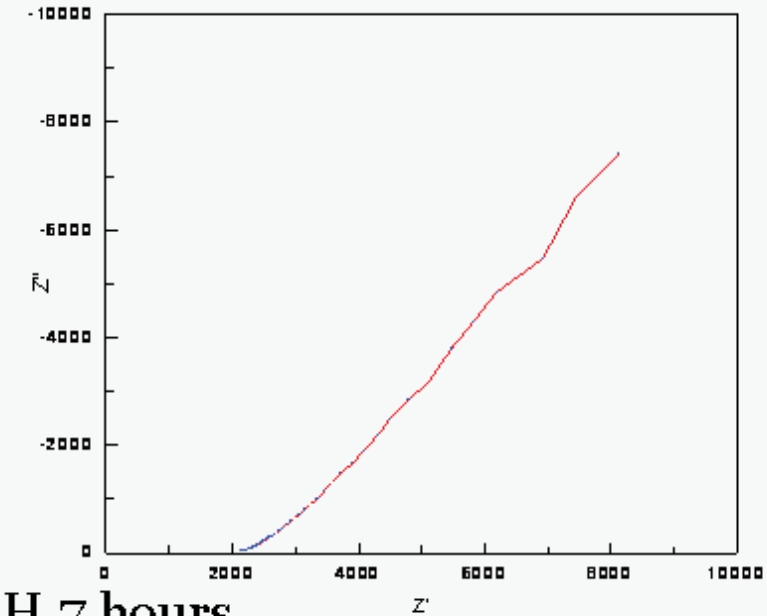

- Membrane conditioned at 30C,70%RH,7 hours

- Conventional RH oven (ESPEC SH240 was used)~ larger equilibration window

BPSH100-BPS-0, 10K-5K

- Step down, from either 95 or 80%RH to 30 % RH

- 4h for each RH(80mS/cm. 80%RH,RT

- Changes in thickness with RH considered

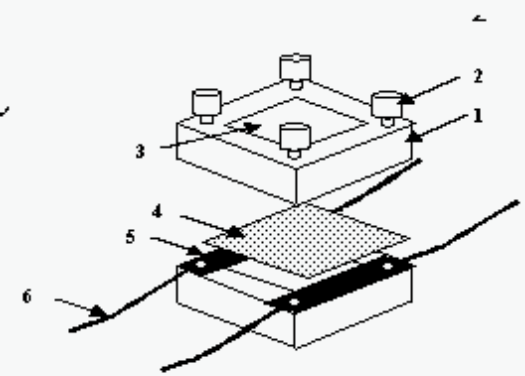

Resistance (ohms)

$$|Z| = \sqrt{R^2 + (X_L - X_C)^2}$$

Two Point, in-plane electrode method

Comparison of VT Sample (BPSH-BPS-10-5) performance at 80° C between BekkTech, VT and Giner

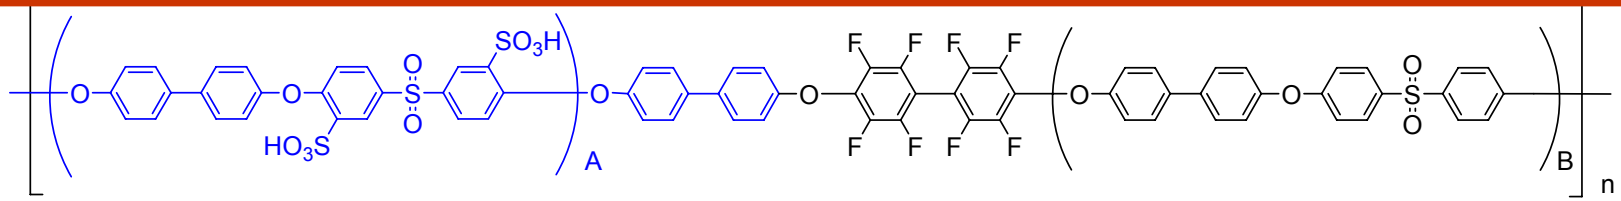

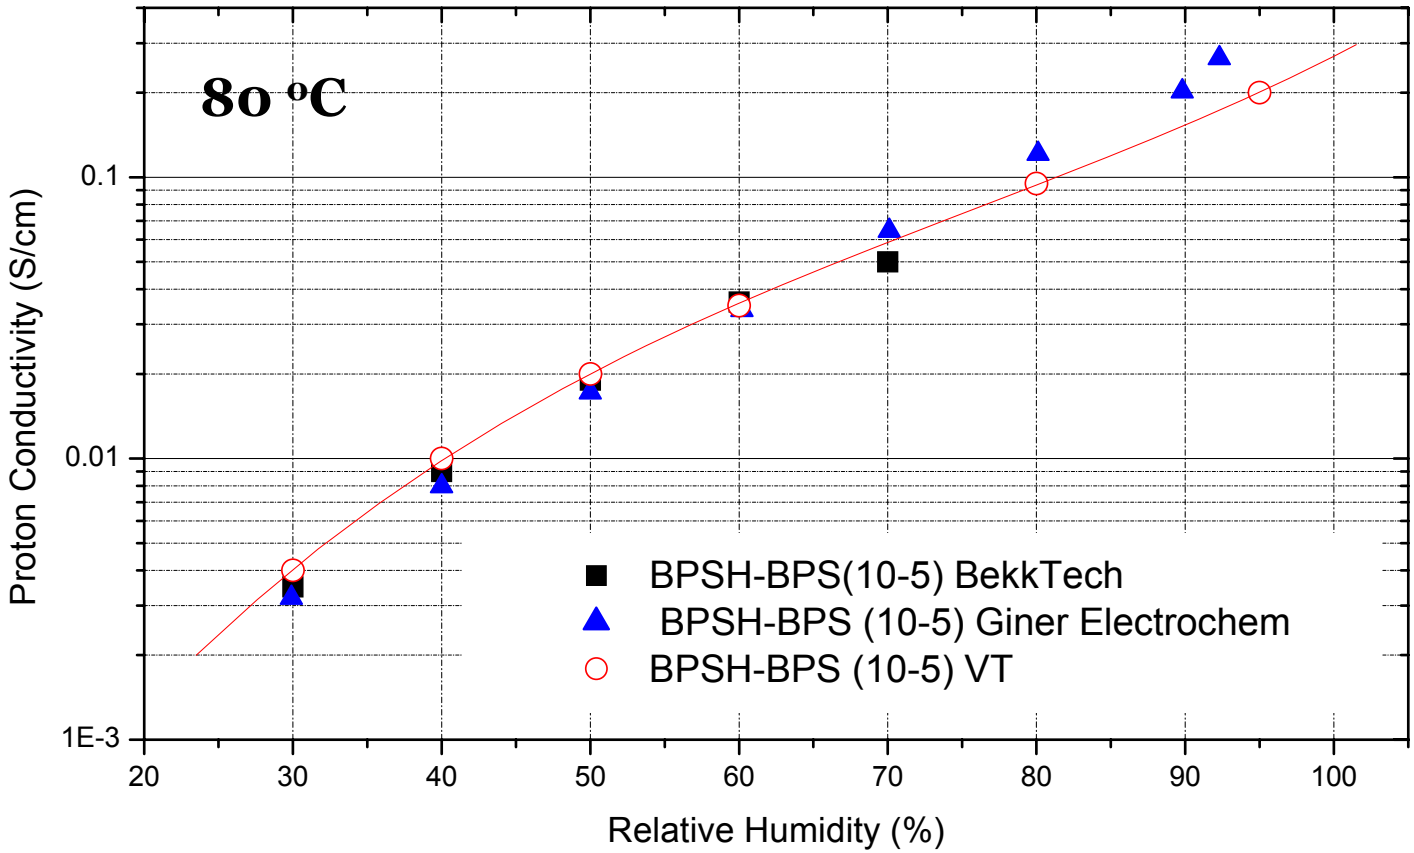

Only step down process is considered.

In case of BekkTech, step down was from 70 % RH , for VT, from 80 %RH

VT perspective on the sample performance

- BekkTech results ~ 38 mS/cm (VT Sample) @ 80 %RH, 30°C, higher than NRE212(~30 mS/cm)
- The value for **VT sample** at 80% RH is expected to be **much higher,** if it was taken during **step-down process**
- "Step-down" gave higher proton conductivity than "step-Up" process for the VT sample ~ differences in vapor phase water absorption and desorption in the sample
- The conductivity value for the BPSH-BPS(10-5) sample is similar to NRE212 up-to 50% RH (considering the step down process) @ 30° C and then drops
- Performance at low RH (~40-20%) may be due to the higher through plane swelling-deswelling nature of the sample.
- Can be definitely improved with longer block length materials and with reasonable swelling-deswelling characteristics

BPSH-BPS Multiblock Copolymers with Higher Block Lengths show Anisotropic Swelling

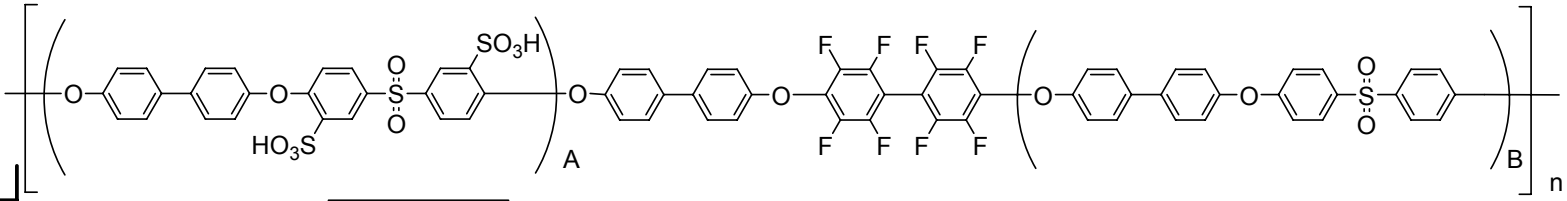

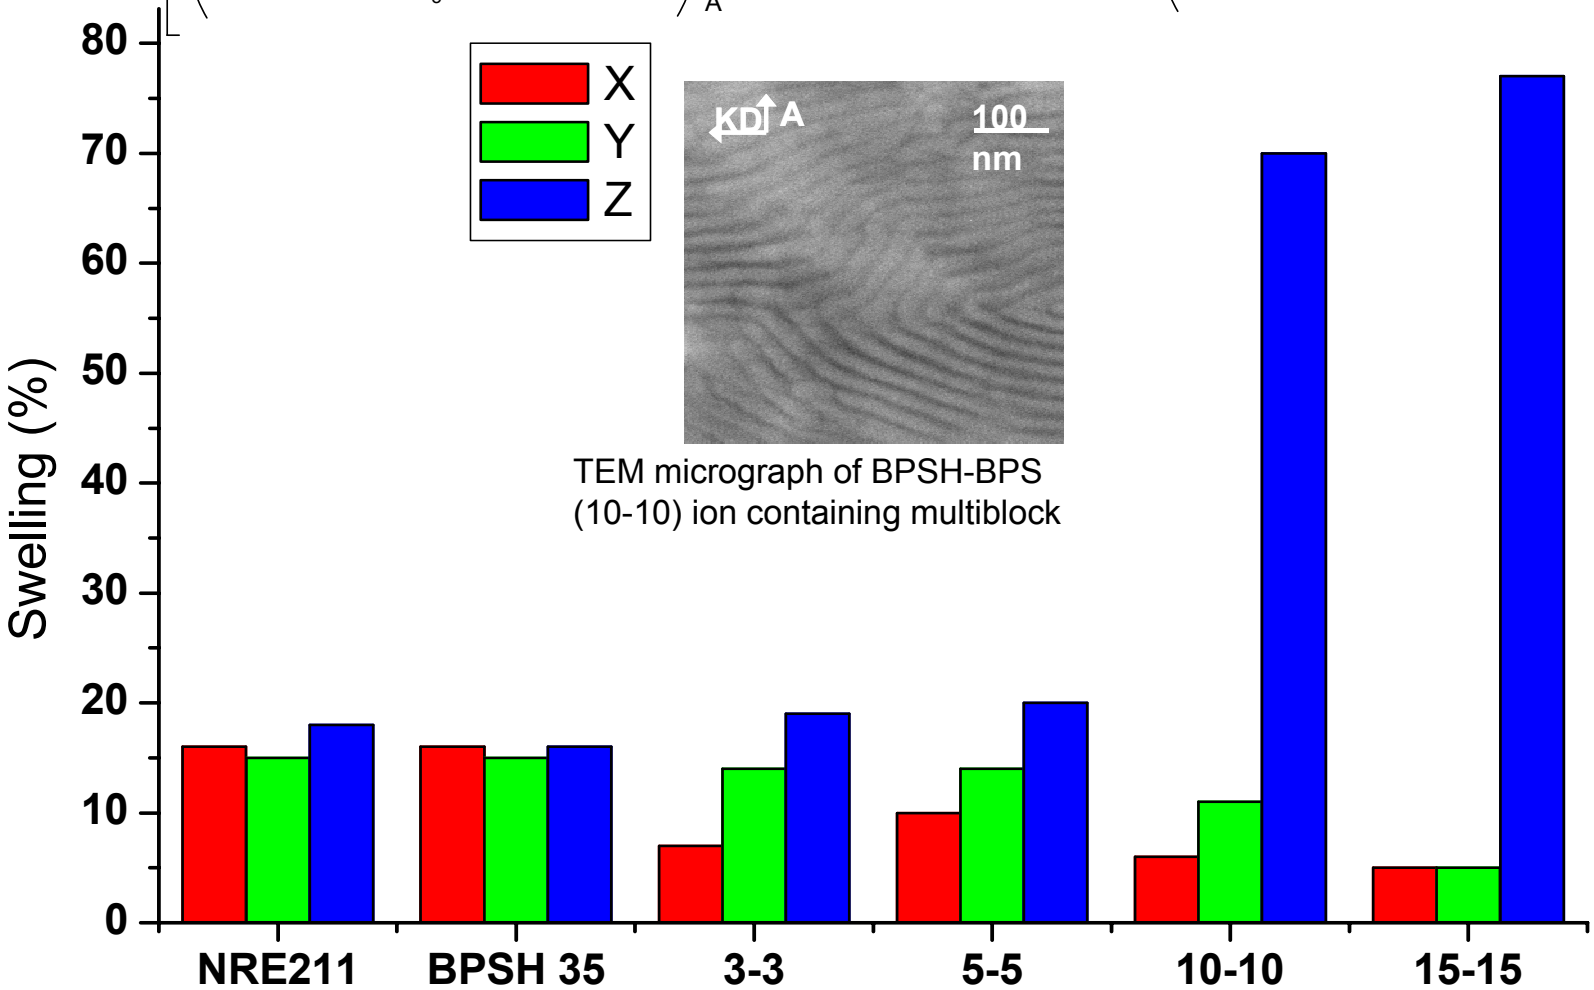

TEM micrograph of BPSH-BPS (10-10) ion containing multiblock

Multi-block Copolymers from BPSH-100 and Amorphous Poly(arylene ether ketone) (6FK)

(larger thermodynamic Xi parameter differential)

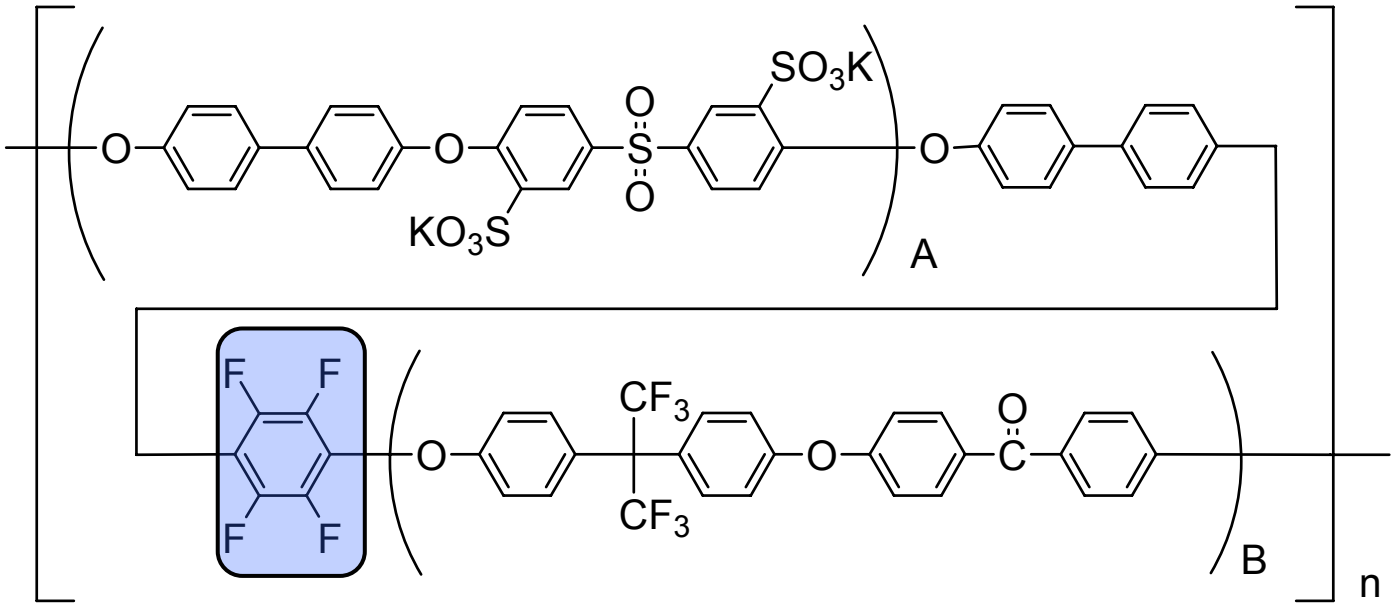

BPSH-6FK Multiblock Copolymer with Hexafluorobenzene Linkage Group

Synthesis of BPSH – 6FK Hydrophilic-Hydrophobic Multiblock Copolymers at 100C

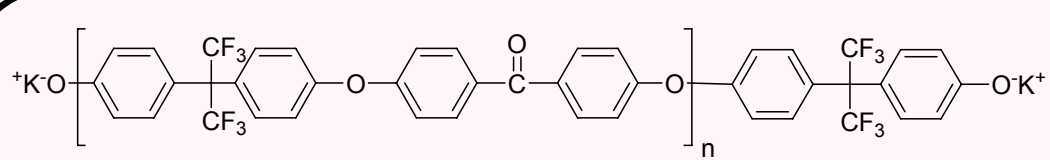

phenoxide terminated 6FK (Hydrophobic Block)

+



Hexafluorobenzene

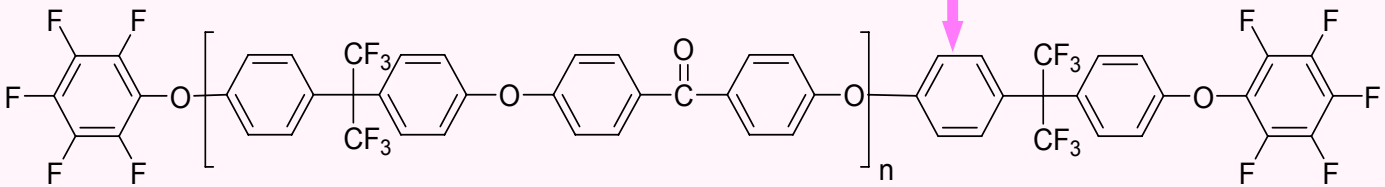

Hexafluorobenzene terminated 6FK (Hydrophobic Block)

+

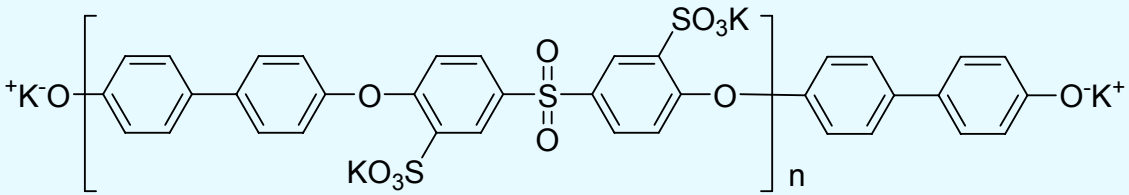

phenoxide terminated BPSH (Hydrophilic Block)

~~(Sulfonated Poly(arylene ether sulfone)$_m$)~~ (Partially Fluorinated Poly (ether ketone)$_n$~~

Influence of Unequal Block Lengths on Properties

Copolymer [a]	*Ion Exchange Capacity (IEC) (meq/g)*	*Water Uptake (%)*	*Hydration Number (λ)*	*Proton Conductivity* [b] *(S/cm)*
BPSH20-6FK15	1.70	178	58	0.09
BPSH10-6FK15	1.32	20	8.3	0.07
BPSH15-6FK20	1.33	45	19	0.10
Nafion112	0.9	25	15	0.09

a. Acronym : BPSH-x-6FK-y, x and y block lengths in kg/mole of hydrophilic and hydrophobic respectively

b. Measurements were conducted in water at 30ºC

Significant Reduction in in-Plane Swelling can be Achieved by Increasing the Fraction of the Hydrophobic Block

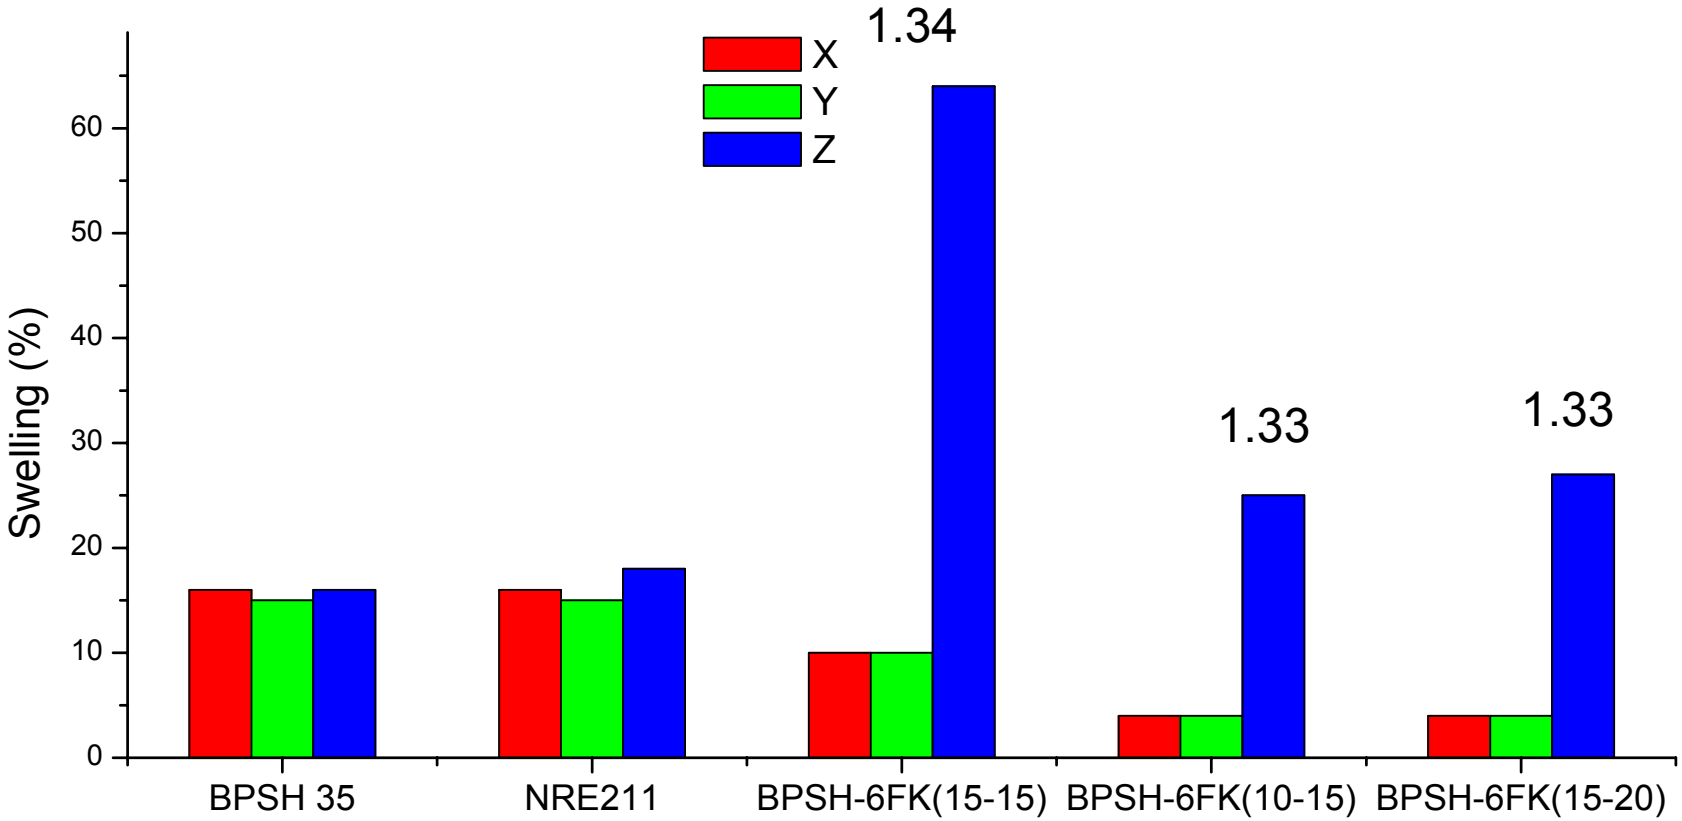

The numbers represent IECs in meq/g

Current and Future Research: Hydroquinone-Based Hydrophilic Oligomers

BPSH 100

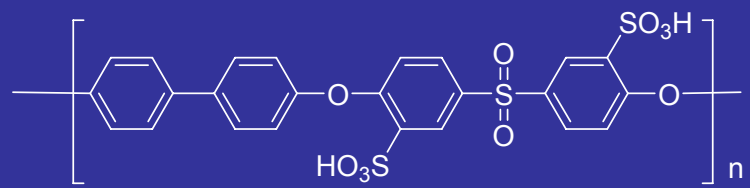

IEC = 3.31 meq/g

HQSH100

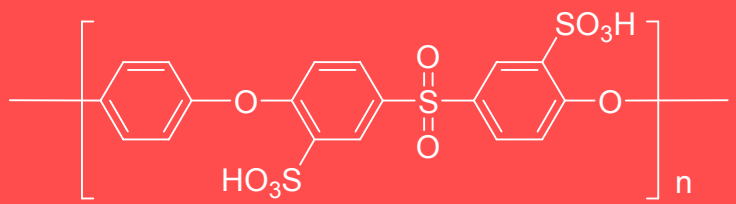

IEC = 3.78 meq/g

- **HQSH100 is more hydrophilic than BPSH100**
  (Higher χ parameter → Sharper Phase Separation)
- **At the same IEC value, the HQSH100 system uses more hydrophobic segments →lower water uptake**
- **Hydroquinone is cheaper than biphenol**

Synthesis of Multiblock Copolymer HQSH-BPS Via Activated Hexafluorobenzene Coupling and Mild Reaction Conditions

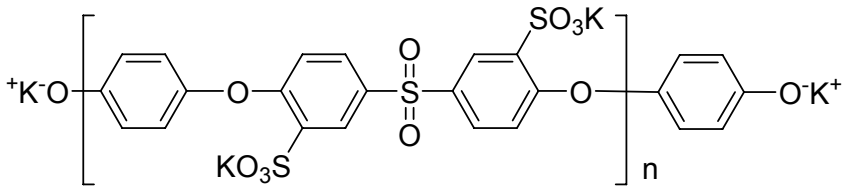

HQS100 Hydrophilic Block (3k)

+

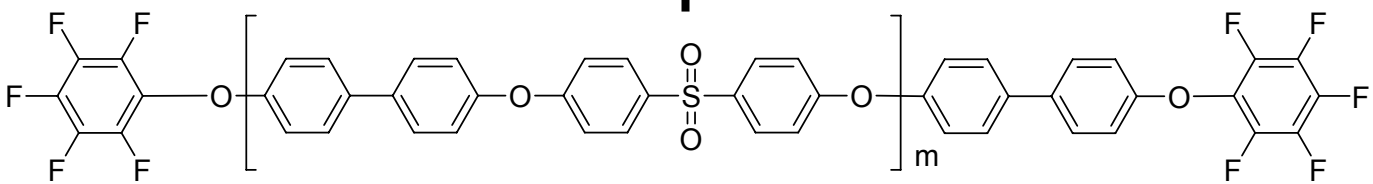

Hexafluorobenzene End-Capped BPS0 Hydrophobic Block (5k)

DMSO
110 ° C
24 h

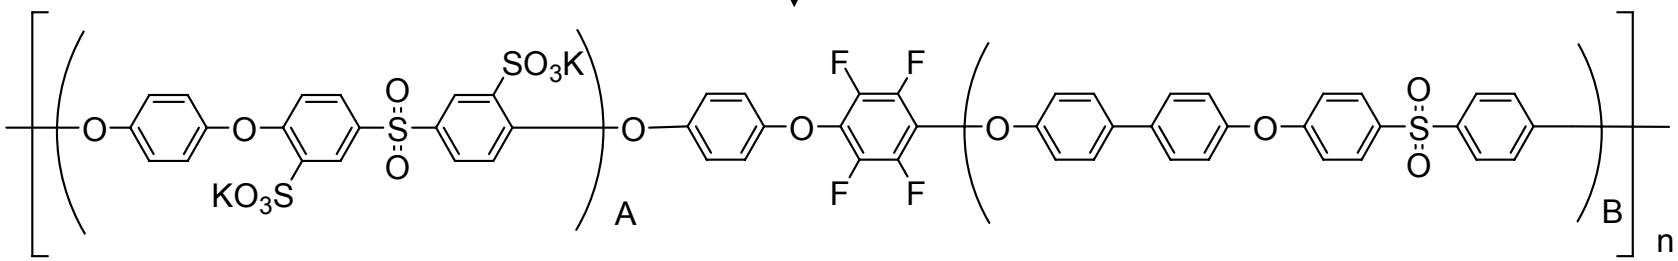

HQSH-BPS multiblock copolymer (3k - 5k)

Conclusions

- Multiblock copolymers based on polyimides or hydrocarbon, partially or highly fluorinated hydrophobic blocks were prepared by coupling activated aryl fluoride ends with very hydrophilic BPSH-100 under mild reaction conditions to produce mechanically tough films and highly ordered morphologies by AFM and TEM.
- Proton conductivity and water self diffusion coefficients increased with block lengths and with the "sharpness: of the nanophase separation
- Cooperation with LANL produced MEA's with conductivity comparable to Nafion 212 at 100C and 40%RH
- Unequal block length materials with higher hydrophobic block lengths also show anisotropic swelling which correlates with the ease of self assembly, affording higher conductivity at lower RH values
- 80mS/cm on one block copolymer was demonstrated at 80%RH and 30C at VT; lower behavior at Becktech could be rationalized by comparing conditioning procedures and extending the data range using independent VT, Giner and Becktech Data

Future Research

- Continue ongoing efforts with LANL and others for understanding chemical structure-processing property relationships in PEM block copolymers and what controls conductivity at low RH
- Investigate new 6FK-0-HQ100 multiblock copolymers utilizing hexafluorobenzene mediated endlinking and mild reaction temperatures
- Swelling-deswelling features of the block copolymers and its possible connection to the most desirable modulus and water swelling values to maximize fuel cell durability
- Scale up Selected Block Copolymer PEM's, Continuously Cast into films via Reverse Roll Coating
- Further Develop Film Casting Expertise for the Multi-Block Copolymers (modeling, time, temperature, substrate, concentrations, dispersion casting, morphology development relationships with conductivity)