

Ionomer Dispersion Impact on PEM Fuel Cell and Electrolyzer Durability

Hui Xu, Ph.D. (PI)
Giner, Inc.
Newton, MA

June 8, 2016

**Project #
FC 117**

Project Overview

Timeline

- Project Start Date: 7/28/2015
- Project End Date: 7/27/2017

Budget

- Total Project Value
 - Phase II: \$1 million
 - Spent: \$353,362

Barriers Addressed

- PEM fuel cell and electrolyzer durability

Giner Researchers

Brian Rasimick, Zach Green and Tom McCallum

Partners

- LANL: Dr. Yu-Seung Kim

Technical Targets

- Integrate Giner dimension-stabilized membrane (DSM) with non-aqueous ionomer dispersions
- Create fuel cell MEAs that are mechanically and chemically stable (DOE 5000 hrs target)
- Develop processible and scalable membranes and MEAs fabrication platforms using non-aqueous ionomer dispersion for water electrolyzers


Project Nature

- First DOE Technology Transfer Opportunity Project (SBIR-TTO)

LANL Ionomer Dispersion Technology

Conventional Ionomer Dispersion


Dupont
European Patent 0066369

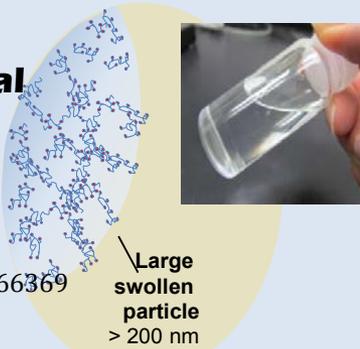

- Water based **multiple** solvent system
- **Expensive** processing: required high temperature ($> 200^{\circ}\text{C}$) & pressure (> 1000 psi)
- **Large** and **non-uniform** particle suspension: particle size (hydrodynamic radius: 200 – 400 nm)
- Produce **brittle** membrane: toughness ~ 0.001 MPa
- Produce **less stable** electrode: cell voltage loss after durability test: 40-90 mV


LANL Ionomer Dispersion

LANL
US Patent 7981319, 8236207,
8394298

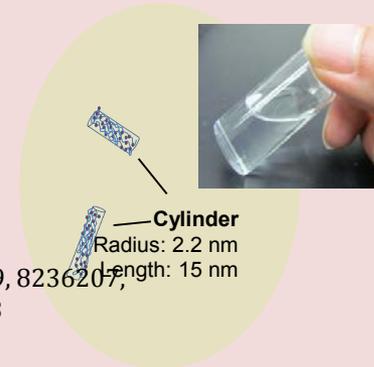

- **Single** solvent system
- **Cost effective** processing: required lower temperature ($< 120^{\circ}\text{C}$) & ambient pressure
- **Small** and uniform particle suspension: particle size (2.2 x 15 nm cylinder)
- Produce **tough** membrane: toughness 10 MPa (> 4 magnitude order difference!!)
- Produce **stable** electrode: cell voltage loss after durability test: 0 mV

Technical Approach

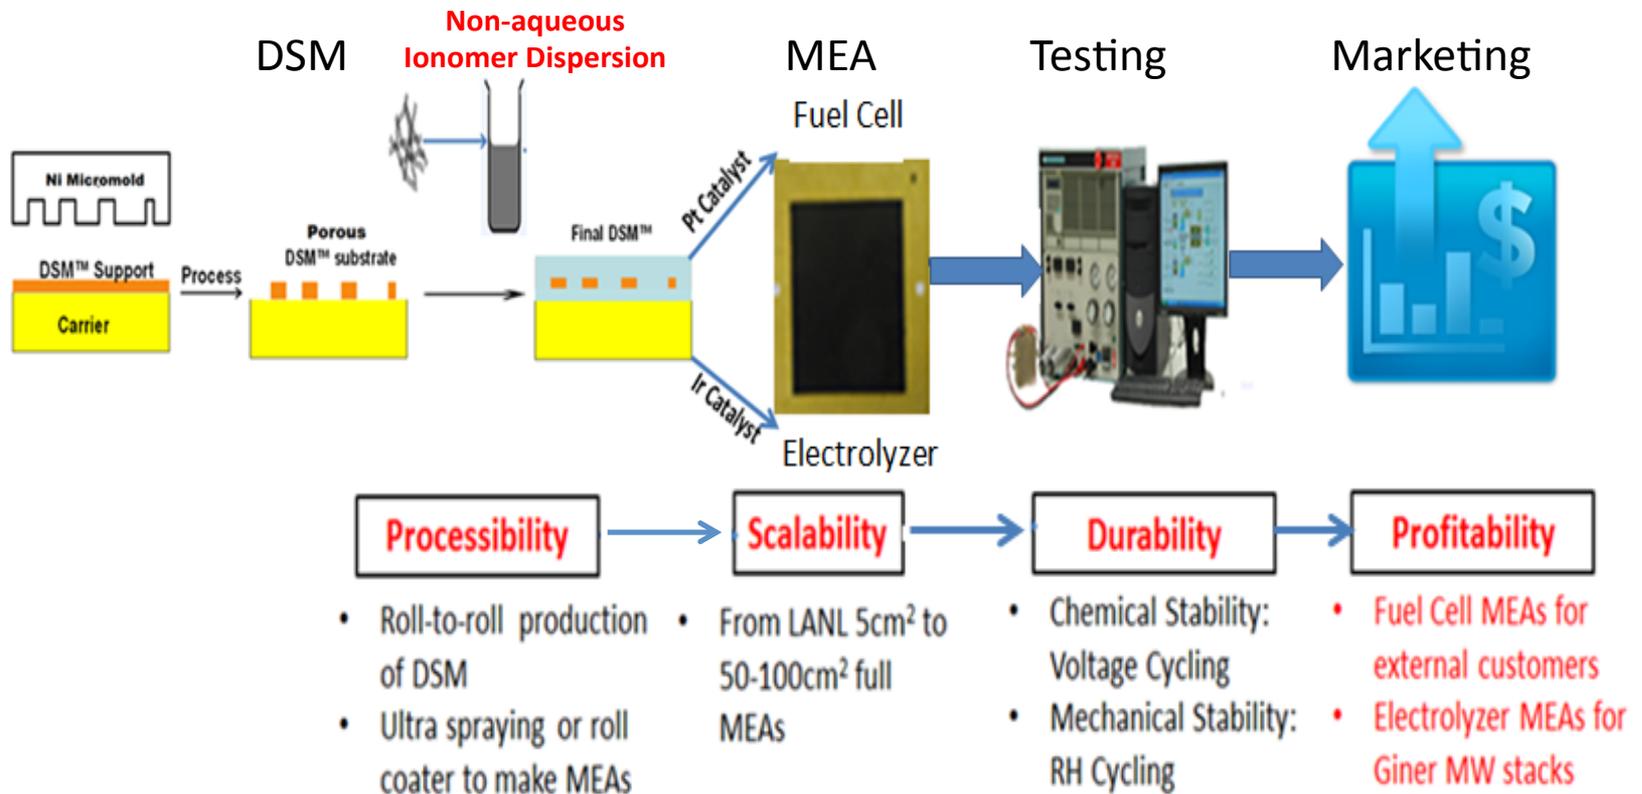

LANL: investigating low Pt loading electrodes using non-aqueous ionomer dispersion for *PEM Fuel cells*

Giner: developing scalable and processible membrane and MEA fabrication platforms for *PEM electrolyzers: membrane cast and electrode fabrication*

Accomplishment 1: Producing Non-aqueous Ionomer Dispersions and Membranes

- **Two Categories of Ionomers**
 - Nafion[®] 1100 EW
 - 3M 825 EW
- **Two Categories of Solvents**
 - Protic: glycerol, n-butanol, 1,2-pentanediol
 - Aprotic: N-Methyl-2-pyrrolidone (NMP)
Dimethylacetamide (DMAc)
- **Processing**
 - Place membrane pieces in individual solvent
 - Heat up to optimized T to obtain ionomer dispersion
- **Ionomer/Solvent Interactions**
- **Membrane: conductivity and mechanical properties**


3M PFSA in Ketone and Ester

• Ketone


10 wt% ionomer in acetone
containing various amounts of
water, aged at 37 °C

Wt (%)	0.2	0.5	1	2	5
λ	0.9	2.3	4.6	9.3	23

6 hrs

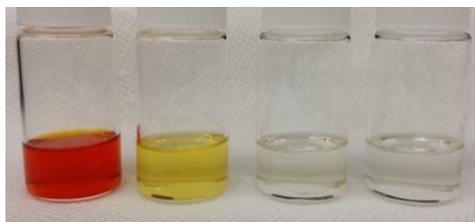

20 hrs

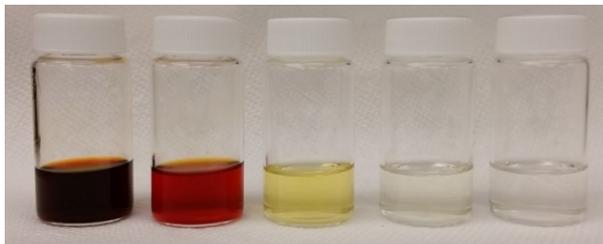

• Ester


20 wt% ionomer in γ -butyrolactone
aged at 37 °C with various water
content

Wt (%)	0.1	1	2	5
λ	0.2	2.3	4.6	12

2 hrs




16 hrs

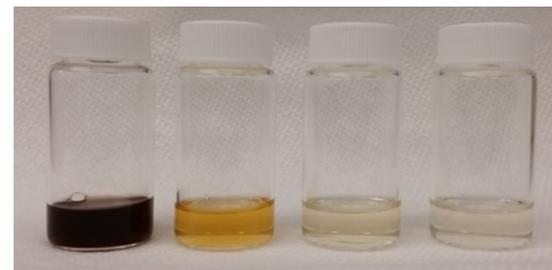

Dispersions containing 1 wt% water or less were unstable as indicated by color

Cast Membranes Using Different Solvents


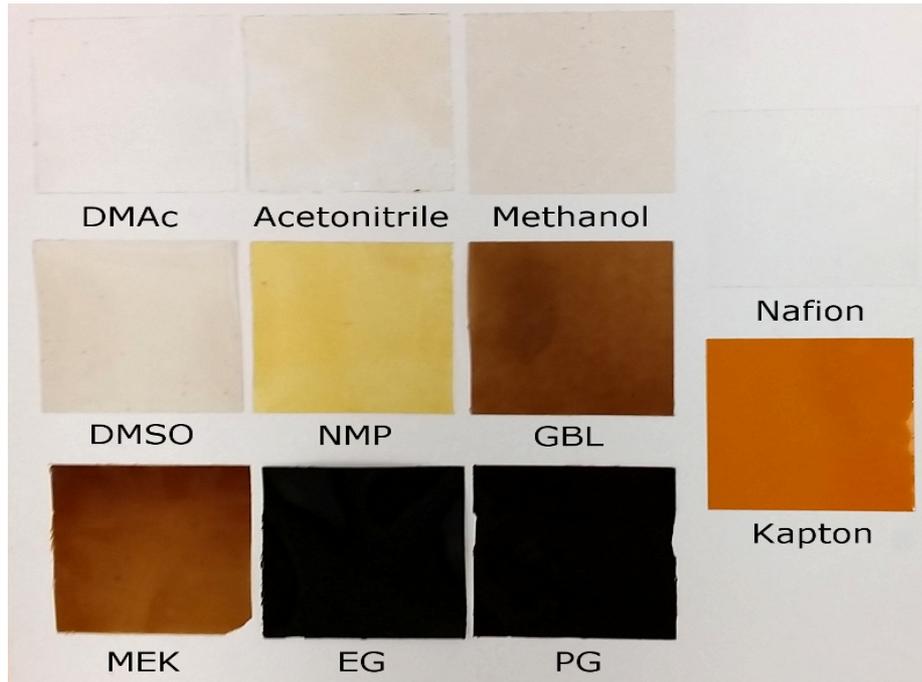


Casting Solvent	Casting Temperature (°C)	Casting Concentration (wt%)
Dimethylacetamide (DMAc)	110	30
N-methylpyrrolidone (NMP)	150	30
Acetonitrile (MeCN)	45	30
Propylene Glycol (PG)	150	30
Ethylene Glycol (EG)	150	30
g-butyrolactone (GBL)	150	20
Methylethylketone (MEK)	45	15
Methanol (MeOH)	45	20
Dimethylsulfoxide (DMSO)	150	20

2 mil Kapton and N115 are shown as a color controls.



- Further chemical reactions occur during the hot-casting and hot-pressing processes
 - Clear ethylene glycol solution turns light brown during hot-casting (150°C for 10 minutes) and darkens to nearly black during hot-pressing (175°C for 15 minutes)
- Despite strong color changes and odors, solvent decomposition does not appear to be a major detriment to the performance of the cast membrane

Membrane Conductivity and Mechanical Property at Various RH

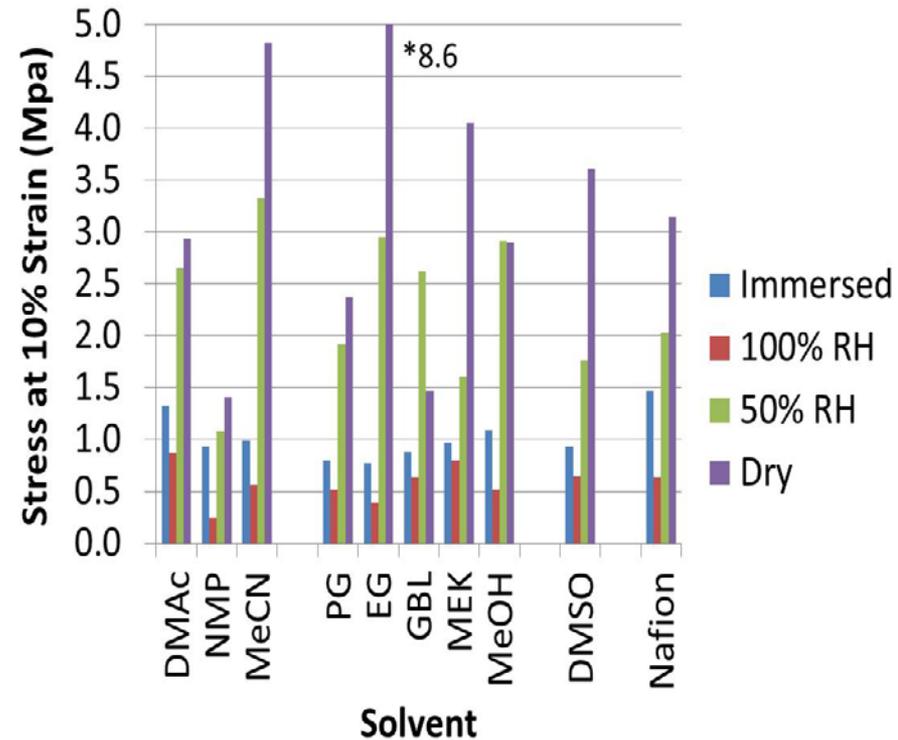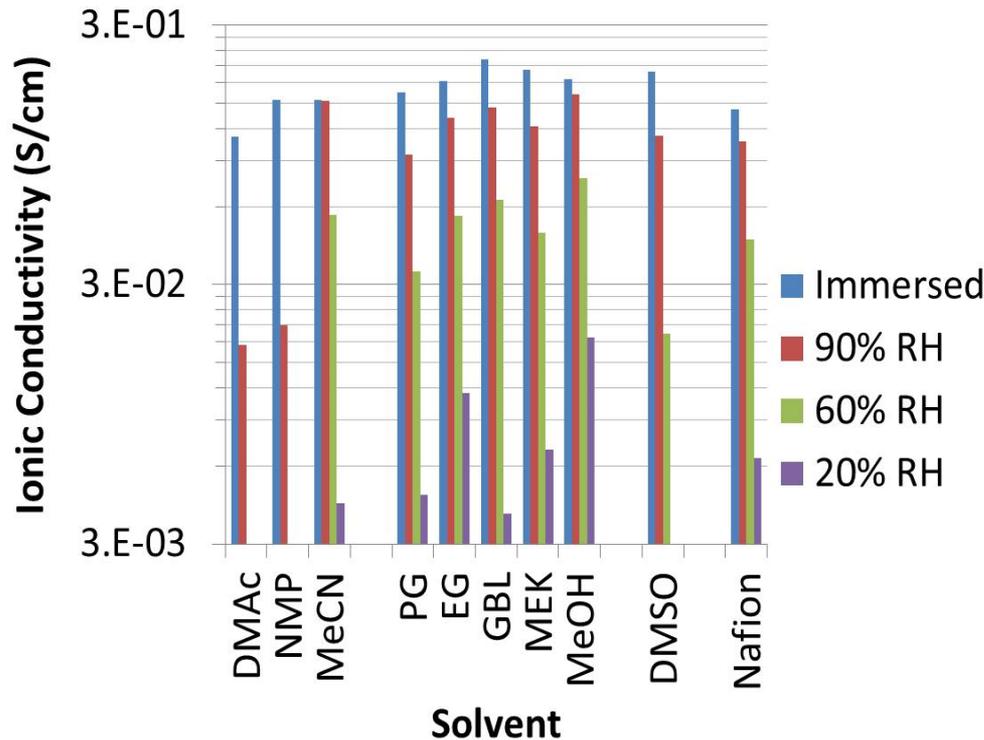


- Solvent impacts conductivity and mechanical properties, particularly at low RH
- MeOH, DMSO and GBL appear to be good solvents for ionomer dispersion based on simultaneously high ionic conductivity and good mechanical property
 - Wet condition typically for electrolyzer application

Conductivity and Mechanical Properties at Immersed Condition

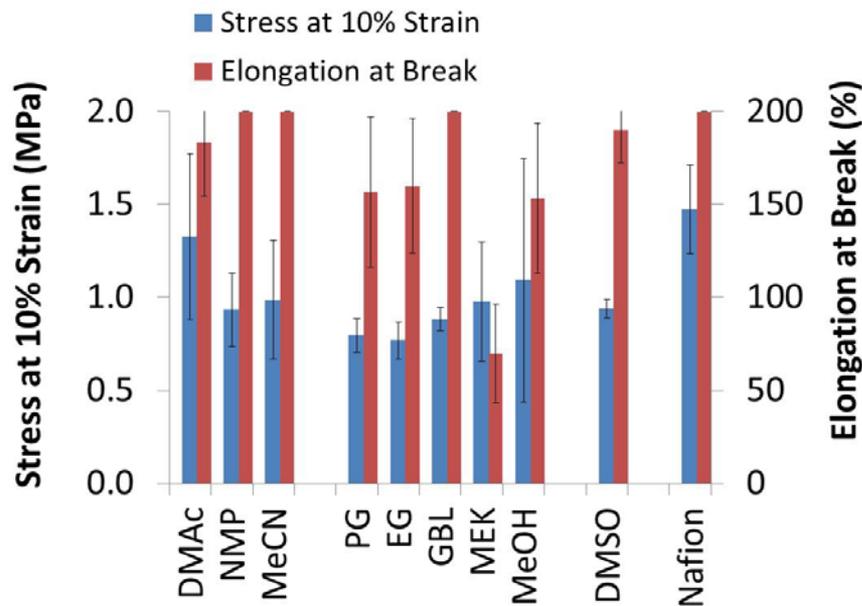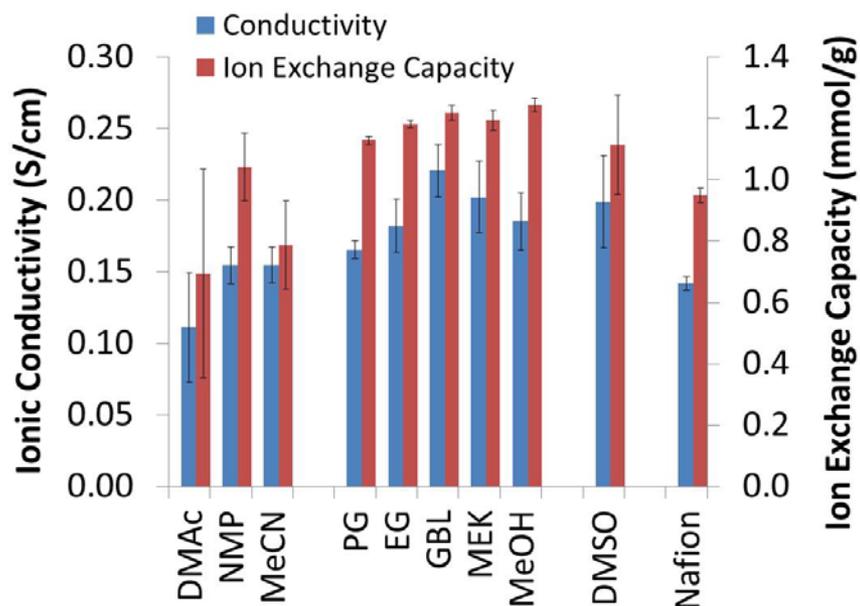



- Immersed condition mimics water electrolyzer operation
- DMSO, MeOH and GBL appear to be good solvents in terms of high membrane conductivity and good mechanical properties at immersed conditions

Membrane Expansion

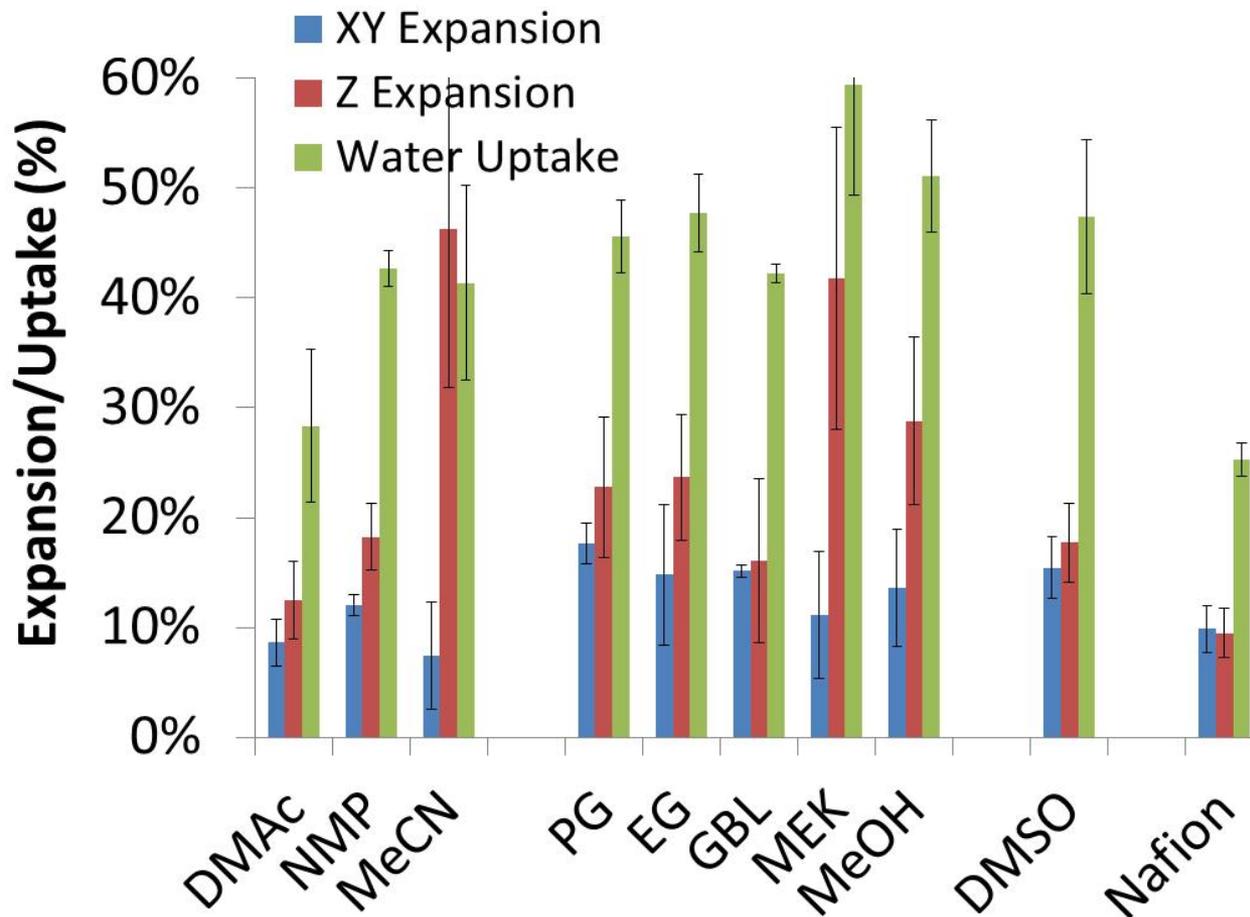

- DMSO, GBL and MeOH solvent-based membranes show less expansion

Hansen Solubility Plot

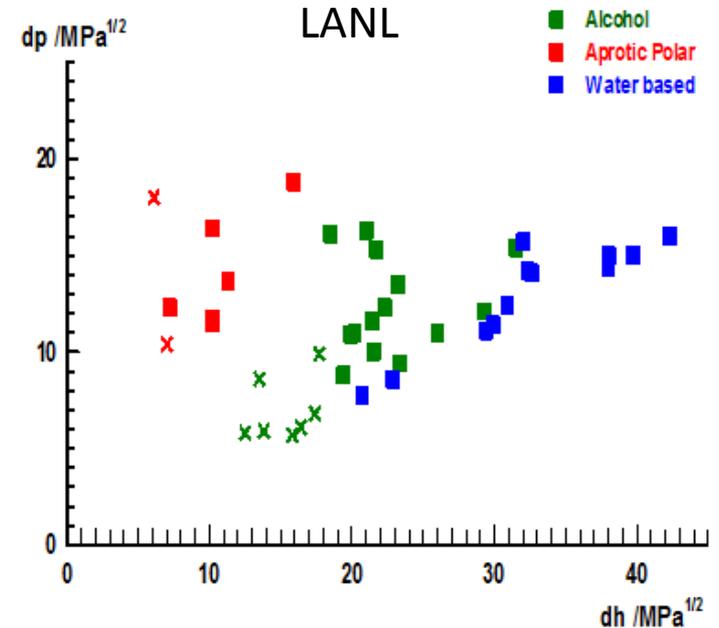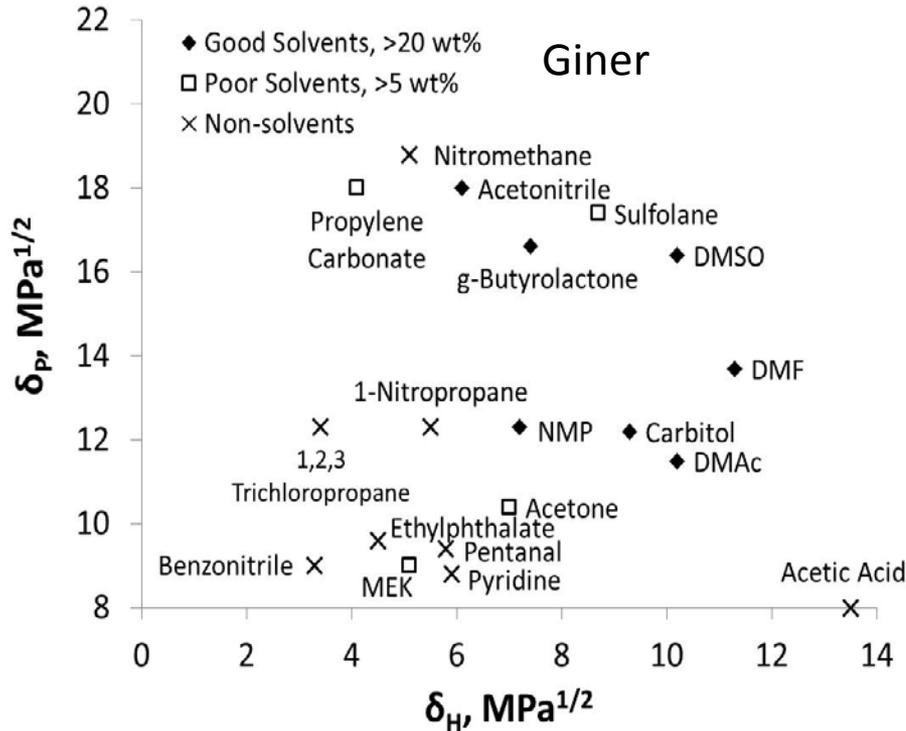


- DMSO, DMF, NMP, GBL tend to disperse ionomer at high concentration (> 20 wt%)
- Unusual wide Hansen solubility parameter range is achieved at LANL

Ionomer Particle Morphology

Particle morphology in dispersion is critical for membrane and electrode properties. LANL performed SANS and dynamic light scattering to investigate the particle morphology. Particle morphology of NMP dispersion is different from what we know.

SANS of Nafion dispersion in NMP

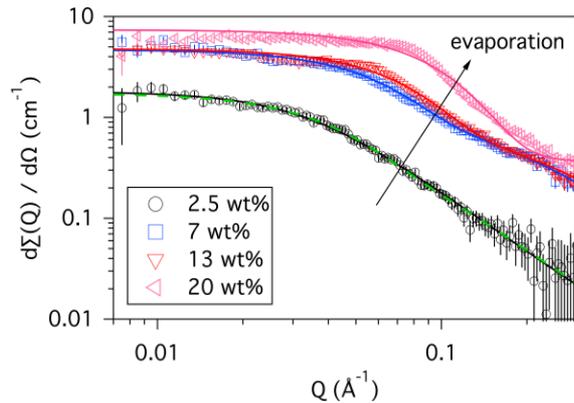

Black line: Random walk modeling




$$I(Q) \propto \Delta\rho \langle P(Q)S(Q) \rangle$$

Green line: Gel particle modeling




$$I(Q) = I_G(0) \exp[-Q^2 \xi^2 / 2] + I_L(0) / (1 + Q^2 \xi^2) + B$$

Particle size from DLS: RH = 8.7 nm

Previous




Current

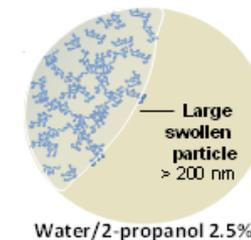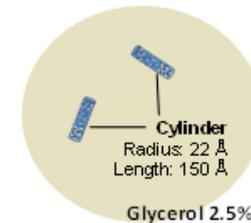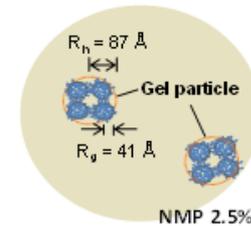


Y.S. Kim et al. *Macromolecules*, 48, 2161-2172 (2015)

Accomplishment 2: Develop DSM Using Non-aqueous Ionomer Dispersions

Batch Process

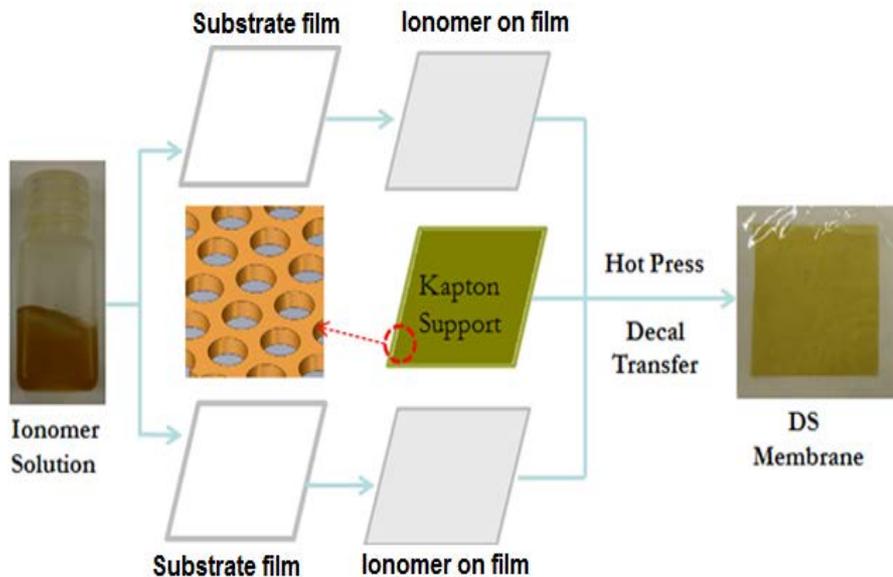

Continuous Process

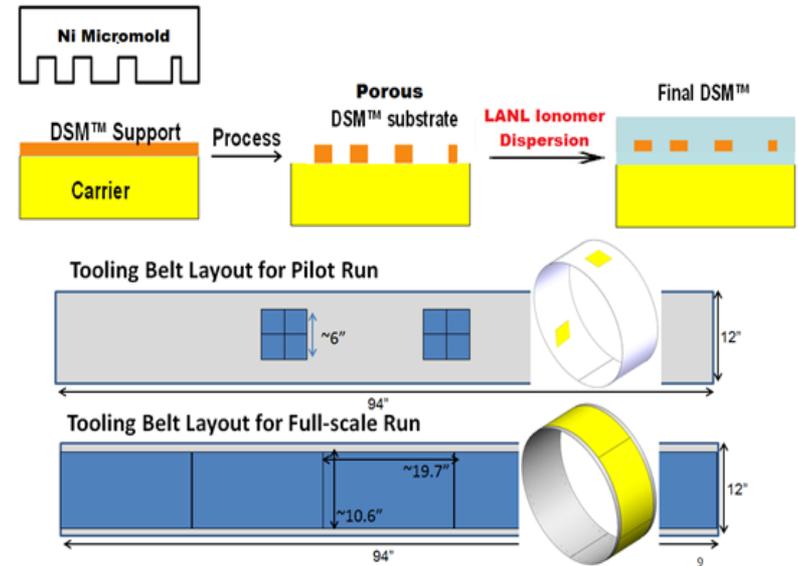

Hybrid membranes obtained using Giner's high throughput continuous DSM fabrication platform

DSM Based Membranes

Phase I Project

Membrane ID	865-15-1	865-18-1 865-29-1 865-30-1	865-17-1	865-32-1
Ionomer	5% N1100EW	5% N1100EW	2.5% 3M 825EW	2.5% 3M 825EW
Solvent	1, 2 Pentanediol	NMP	1, 2 Pentanediol	DMAc
Thickness	35 μm	22 μm	24 μm	41 μm
Color	Dark yellowish	Yellow	Yellow	Yellow

Dark color due to high heating temperature during membrane casting




Phase II Project


#	Ionomer Dispersion	DSM
1	N1100 in NMP	Yes
2	N1100 in NMP	No
3	N1100 in EG	Yes
4	N1100 in EG	No
5	3M 825 in DMAc	Yes
6	3M 825 in DMAc	No
7	3M 825 in PTD	Yes
8	3M 825 in PTD	No

Mechanical Tests and Conductivity

Stress-strain behavior at 90° C: 0% RH

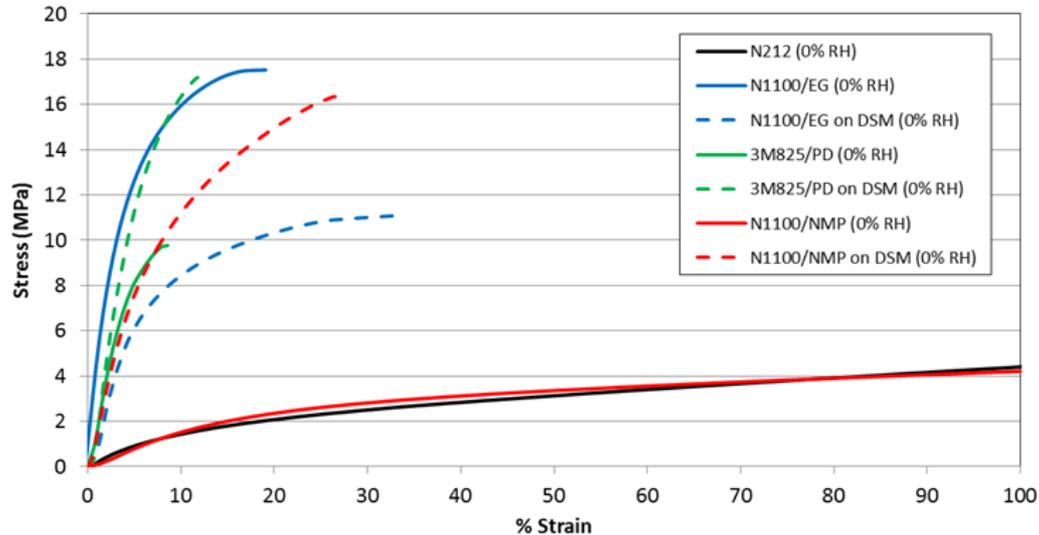



Stress-strain behavior at 90° C: 100% RH

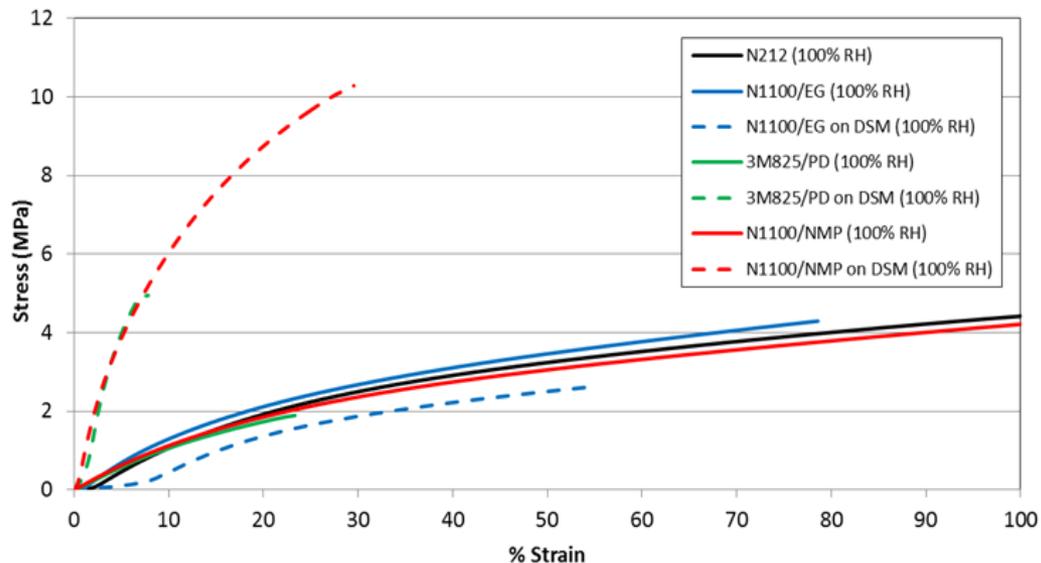

- The integration of ionomer with DSM improves the membrane mechanical properties;
- The stress at fixed strain varies from solvent to solvent even with DSM
 - PD comparable to EG
 - EG better than NMP
- EG-dispersed N1100EW performed well even without DSM

Voltage and RH Cycling

Cell conditions: EG based N1100 EW in DSM (30 μm) and cathode; anode and cathode: 0.2 mg/cm² Pt (from Tanaka 46.7% Pt/C), 50cm² FCT hardware

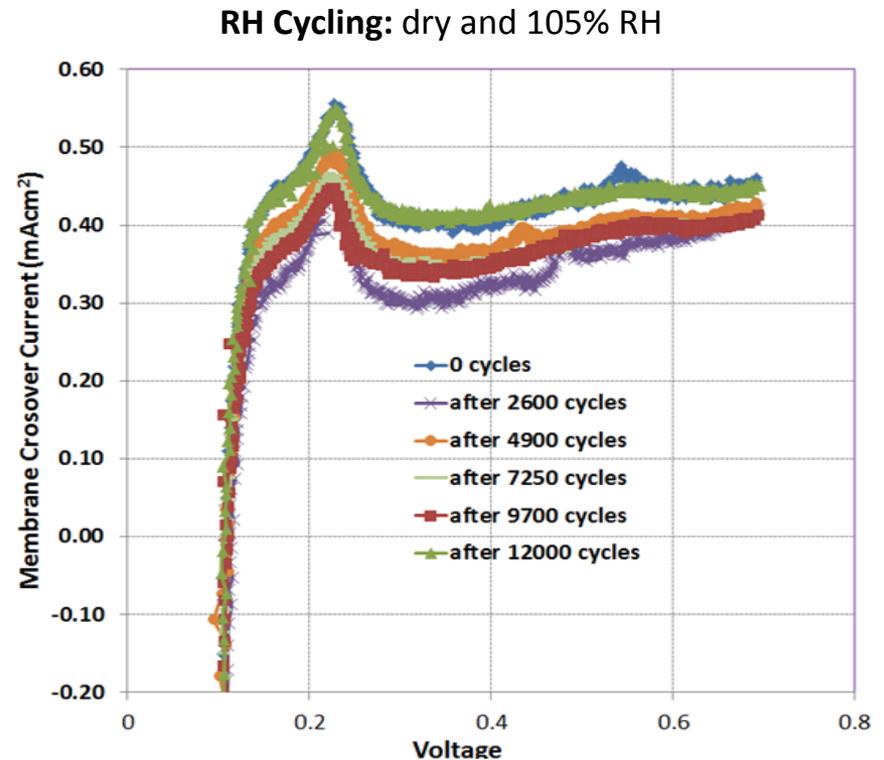
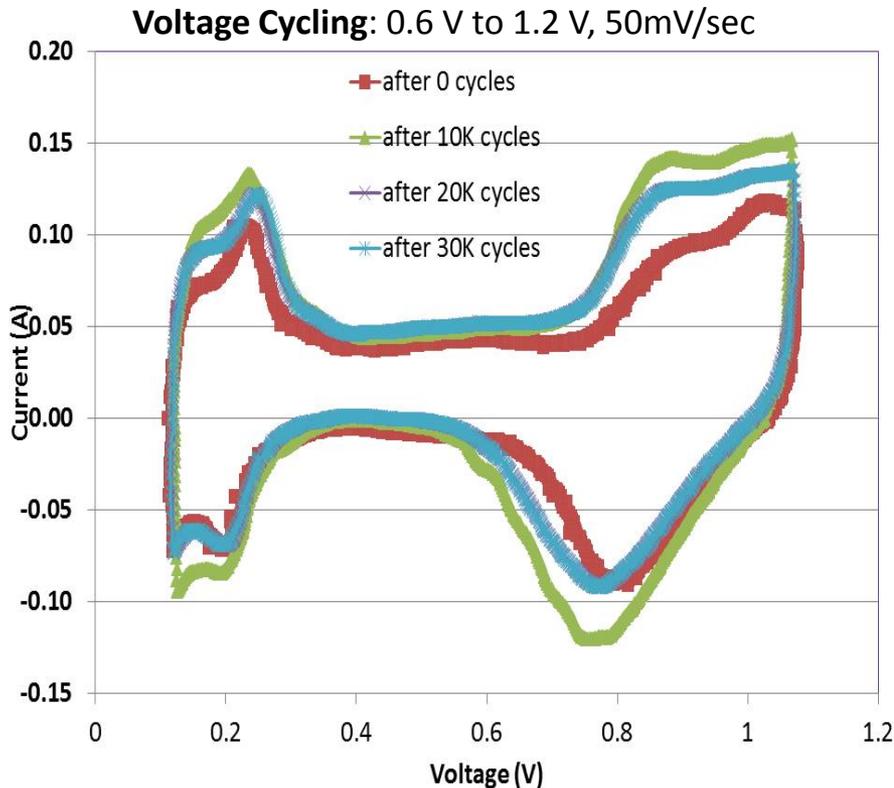


- ECSA calculated by H₂ adsorption/desorption decreased by 12% from 10k to 30k, upon voltage cycling (no change from 0 to 30k cycles)
- Extremely low H₂ crossover: 0.4 mA/cm² upon 12K RH cycling

Accomplishment 3: Fuel Cell Performance and Durability

H₂/air fuel cell performance at 80 °C at 30 psig backpressure;
Membrane: Nafion 212; Anode: 20 wt.% Pt/C (0.2 mg/cm²);
Cathode: 46.7 wt.% TKK Pt/C catalyst; Catalyst ink dispersing agent: water/2-propanol


H₂/air fuel cell performance at 80°C at 30 psig backpressure;
Membrane: Nafion 212; Anode: 20 wt.% Pt/C (0.2 mg/cm²);
Cathode: 46.7 wt.% TKK Pt/C; 20 and 10 wt.% ETEK Pt/X catalyst; Catalyst ink dispersing agent: water/2-propanol

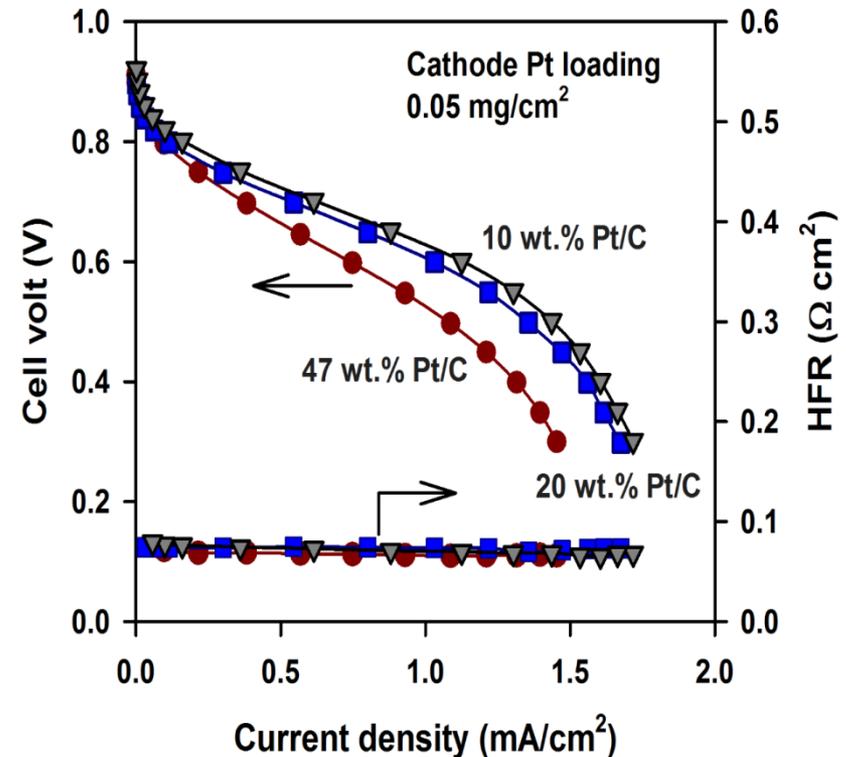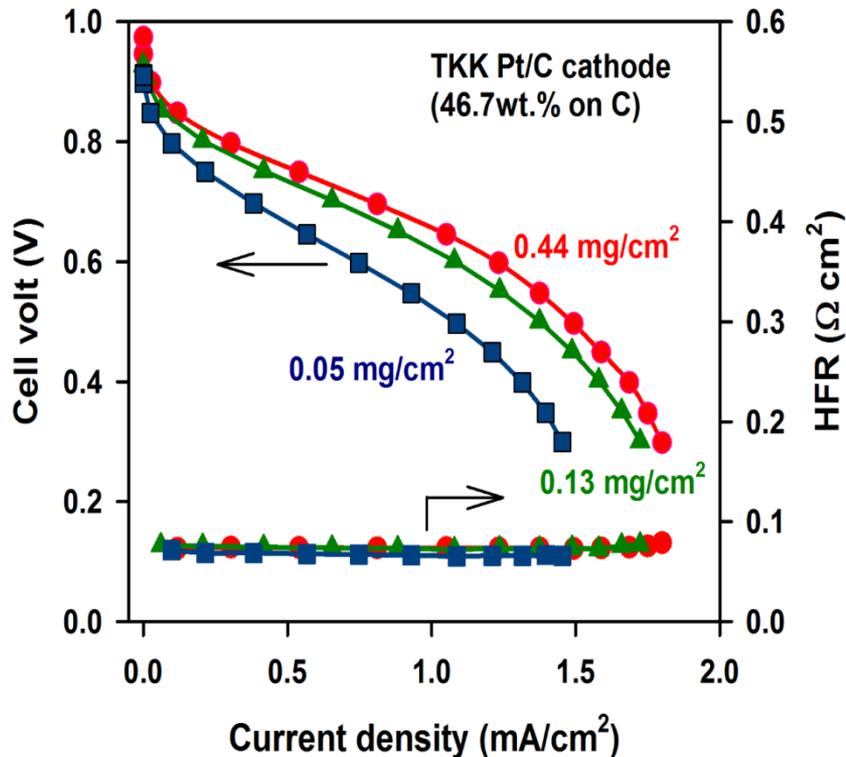

- More significant performance loss when Pt loading decreased from 0.13 to 0.05 mg_{Pt}/cm².
- Catalyst with low Pt to C ratio showed better performance for low loading cathode.

Solvent Impact on Low Pt loading Fuel Cell Performance

H₂/air fuel cell performance at 80°C at 30 psig backpressure; Membrane: Nafion 212; Anode: 20 wt.% Pt/C (0.2 mg/cm²); Cathode: 20 wt.% wt.% Pt/C catalyst; Catalyst ink dispersing agent: varied

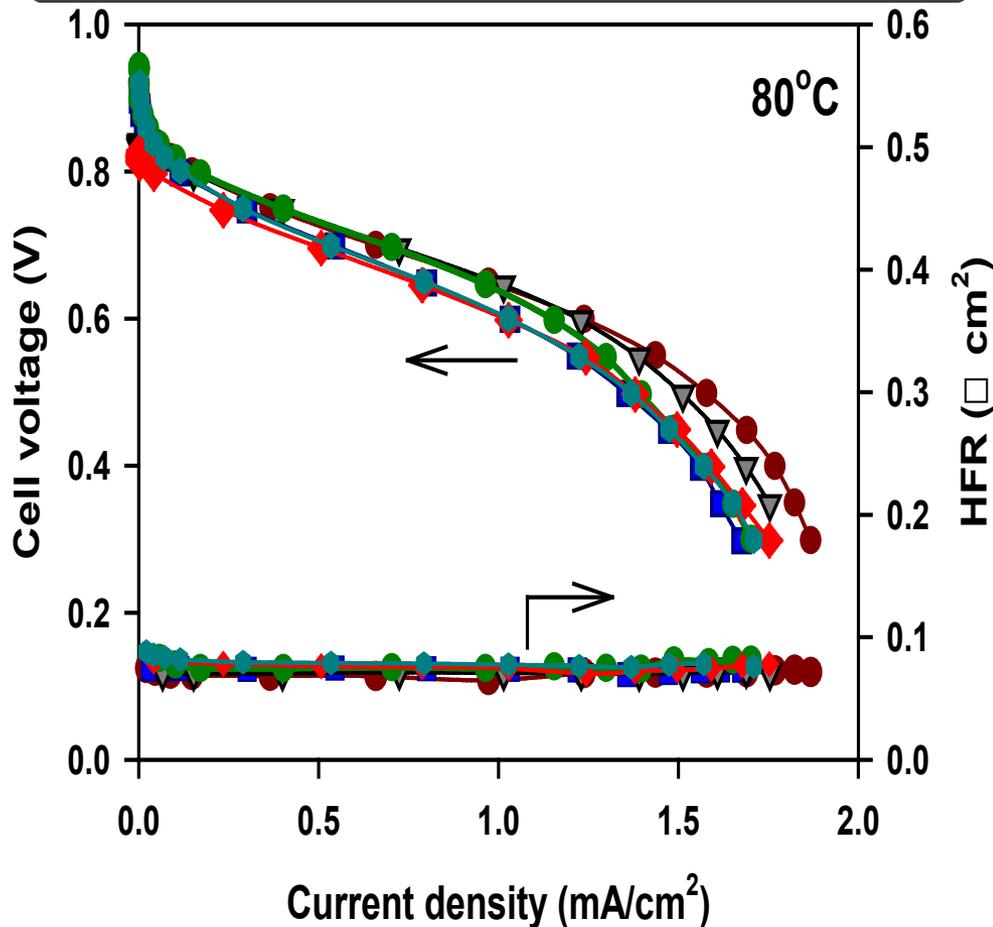

* Low loading Pt cathode needs longer break-in time (see complementary slide 2)


Cathode dispersing agent (cathode Pt loading)

- Water/IPA (0.054 mg_{Pt}/cm²)
- NMP (0.051 mg_{Pt}/cm²)
- DMAc (0.049 mg_{Pt}/cm²)
- Ethanol (0.049 mg_{Pt}/cm²)
- Pentanediol (0.051 mg_{Pt}/cm²)
- Glycerol (0.063 mg_{Pt}/cm²)

- Similar H₂/air fuel cell performance was obtained using different cathode dispersing agent after full break-in.*
- NMP and DMAc dispersing agents produced little better performance.

Solvent Impact on Low Pt loading Fuel Cell Durability


Cathode dispersing Solvent: varied; **ionomer:** Nafion or aquivion; **ionomer to pt/C composition:** 30wt.%; **Anode:** 0.2 mg_{Pt} cm⁻² (20 wt.% Pt/C, BASF), **Cathode:** 0.05-0.25 mg_{Pt} cm⁻² (20 wt.% Pt/C, BASF); **Membrane:** Nafion® 212; **Operating conditions:** cell temperature: 80°C, backpressure: 10 psi, Potential cycling: 0.6 – 1.0 V under H₂/N₂ at 80°C, Break-in: 12 h at 0.6 V H₂/air & 2 polarization curves at initial, 3, 10 and 30K potential cycles

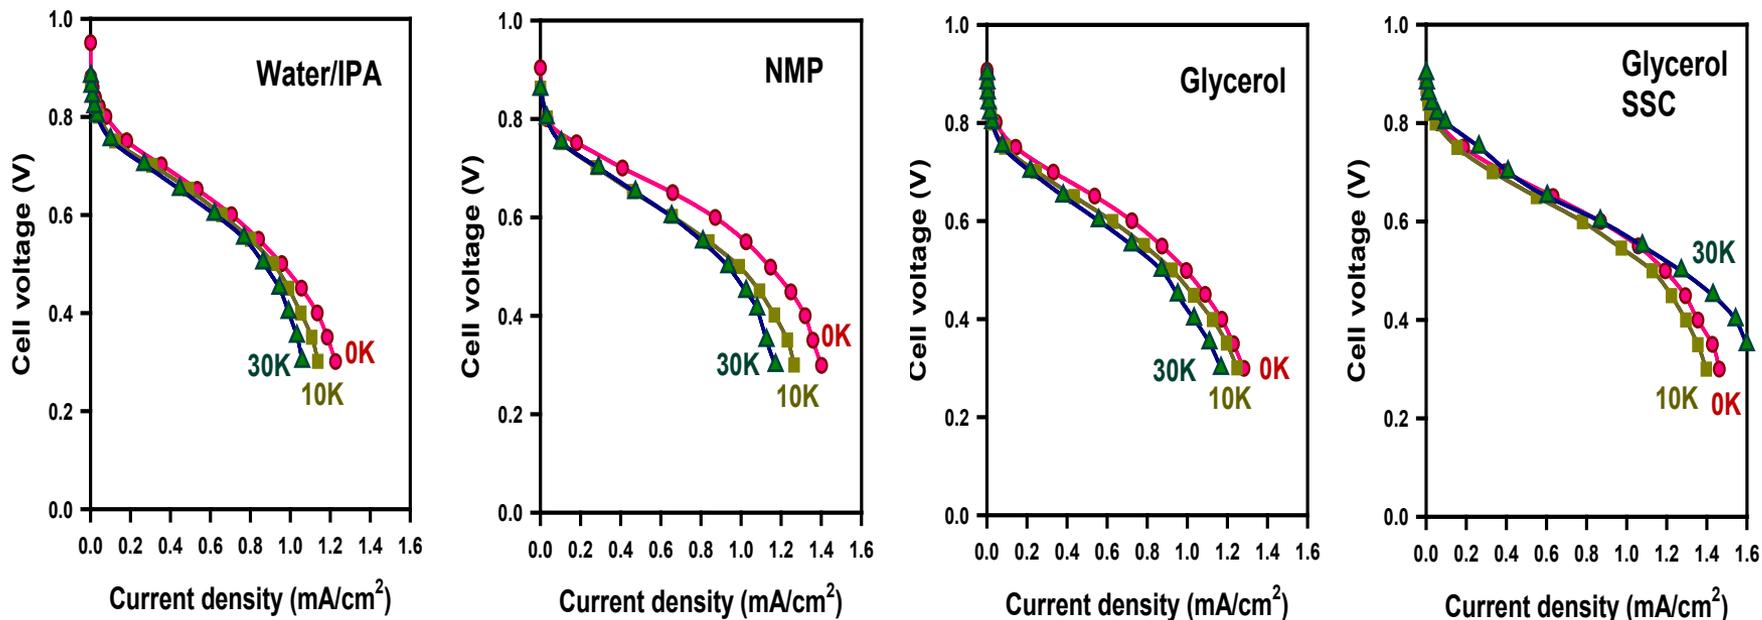


- Cathode catalyst inks were prepared from 7 different dispersing agents and tested (for other dispersing agents see Supplemental Slide).
 - MEAs prepared from glycerol based cathode catalyst ink showed superior durability.
- Highlight:** Short-side-chain Aquivion® ionomer prepared from glycerol based ink showed excellent performance and durability

Accomplishment 4: Electrolyzer Performance and Durability


- Apply non-aqueous ionomer dispersion to water electrolyzers to develop a scalable, durable, and high-performance MEA
 - Ir black + 15% ionomer in various solvents



Acetonitrile
(MeCN)



Acetone
(ACT)




g-butyrolactone
(GBL)




n-methylpyrrolidone
(NMP)




Dimethylformamide
(DMF)

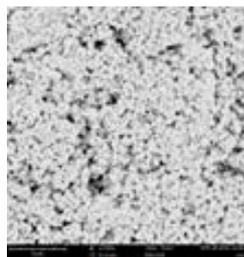


Aqueous solvent

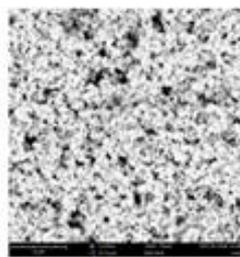

NMP

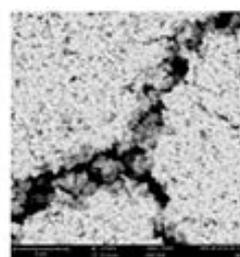



GBL

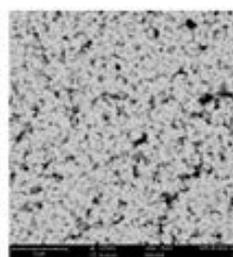

DMF

- Decals using GBL, NMP and DMF shows best morphology: uniform and little cracking
- Scalable for electrode mass production


Performance of Cast Anode Decals

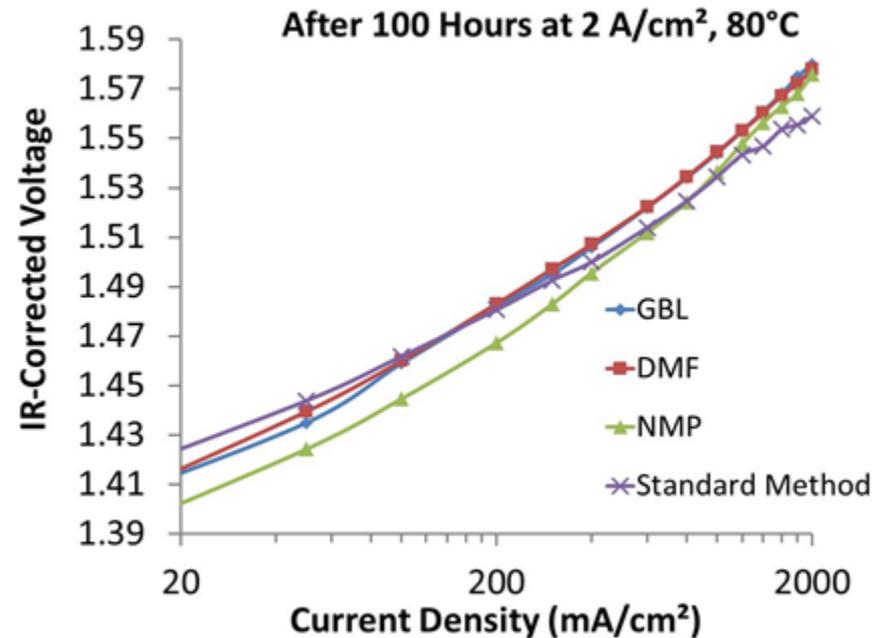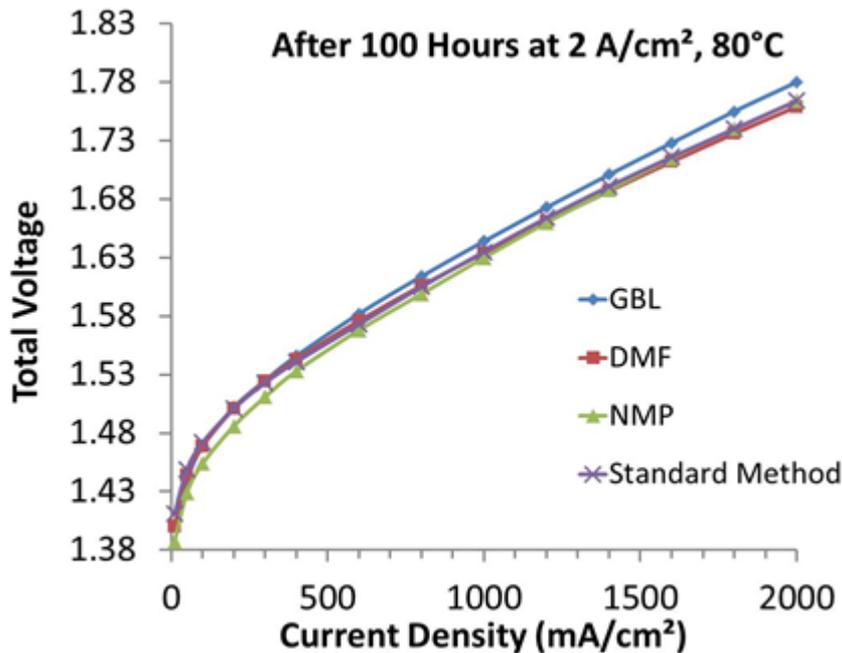


- All anodes using GBL, DMF and NMP-based ionomer performed as well as standard one using aqueous ionomer
- Using GBL, DMF or NMP enables the fabrication of electrodes in a processable and scalable level

Stability of Electrolyzer MEAs

Anode: 2 mg/cm² Ir Black;
Membrane: Nafion® 1110

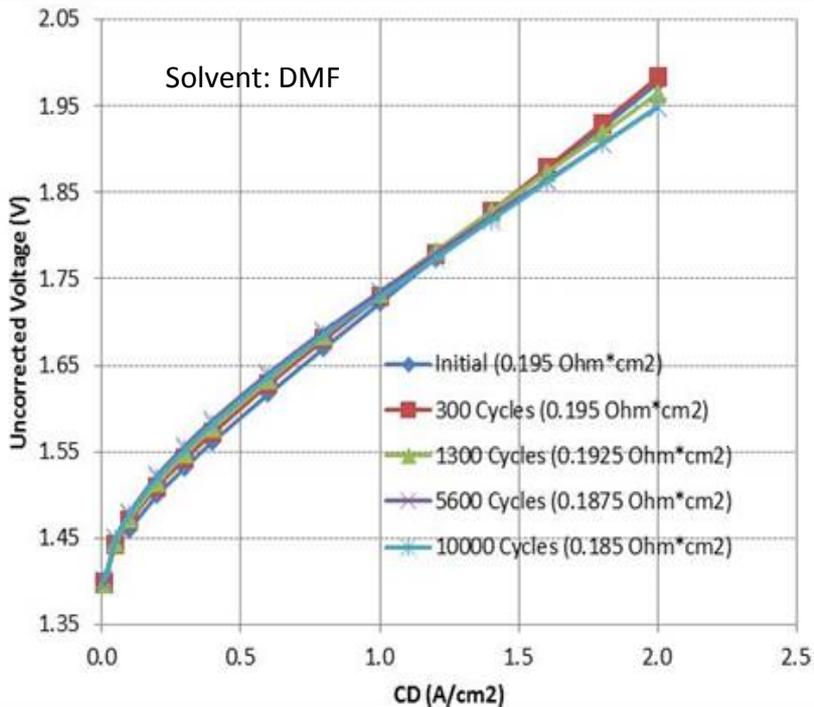

Anode: 0.4 mg/cm² Ir from Ir/W_xTi_{1-x}O₂;
Membrane: Nafion® 115

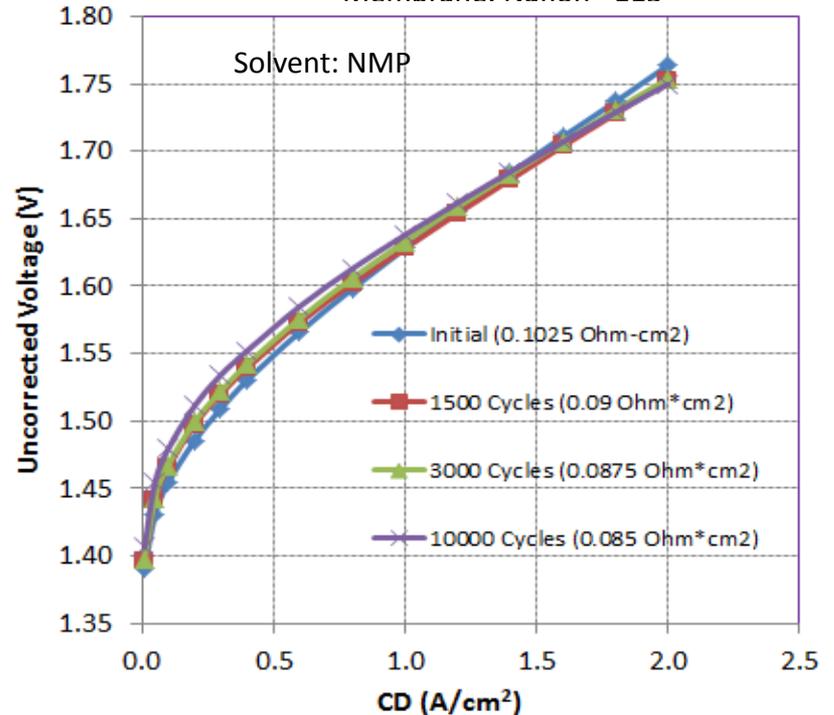

Voltage cycling from 1.4 V to 2.0 V, square wave, 30 second at each voltage

- Good compatibility between catalyst and ionomer
- Excellent MEA durability demonstrated upon voltage cycling (1.4 V to 2.0 V)

Summary

- A variety of non-aqueous ionomer dispersions were evaluated in terms of ionomer concentration, conductivity, dimensional expansion and mechanical properties of cast membranes
 - Selected solvents includes DMSO, GBL, NMP and MeOH
- Selected non-aqueous ionomer dispersions were impregnated in the DSM substrate and used in the fuel cell cathode, leading to mechanical and chemically stable MEAs
- Low Pt loading fuel cell electrodes using non-aqueous ionomer dispersions were developed, glycerol-based electrodes demonstrated a good trade-off between performance and durability
- Water electrolyzer electrodes using non-aqueous ionomer dispersions were investigated. GBL, NMP and DMF -based ionomer dispersions led to uniform electrodes with good performance and durability

Future Plans

- Further investigate the transport properties of fuel cell electrodes using low Pt loading and non-aqueous ionomer dispersions
- Use non-aqueous ionomer dispersions to develop fully scalable and processible electrode and MEA manufacturing platforms for Giner's water electrolyzer business

Acknowledgments

- Financial support from DOE SBIR/STTR Program
- Program Manager
Donna Ho
- Subcontractor
 - Dr. Yu- Seung Kim and David Langlois at LANL
- Giner Personnel
 - Brian Rasimick
 - Zach Green
 - Tom McCallum
 - Jason Willey
 - Dr. Corky Mittelsteadt