HyMARC Seedling: "Graphene-Wrapped" Complex Hydrides as High-Capacity, Regenerable H_2 Storage Materials

Di-Jia Liu (Lead) and Lina Chong

Argonne National Laboratory

Qingfeng Ge (Sub)

Southern Illinois University

2017 DOE Hydrogen and Fuel Cells Program Annual Merit Review and Peer Evaluation Meeting

Washington, D.C., June 5-9, 2017

Project ID ST136

This presentation does not contain any proprietary, confidential, or otherwise restricted information

Overview

Timeline

- Project start: Oct. 2016
- Phase I end: Sept. 2017
- Phase II end: Sept. 2019

Barriers

- Barriers addressed
  A. System Weight and Volume
  B. System cost
  C. Efficiency
  D. Durability/Operability

Budget

- Total project requested: $1.114 Million
  - DOE share: $1 Million
  - Contractor share: $114 K
- Funding in FY2017 (Phase I)
  - DOE fund received: $ 250 K
  - DOE Fund Spent*: $ 100 K

* **As of 3/31/2017**

Partners

- Interactions/collaborations
  - Argonne National Laboratory (Lead)
  - Southern Illinois University (Subcontractor)
  - HyMARC (SNL, LLNL, LBNL)
  - NREL
  - Shanghai Jiao Tong University

Relevance – Current Challenges for Onboard Hydrogen Storage Technologies

DOE Hydrogen Storage Technology Target

Storage Parameter	Units	2020	Ultimate
System Gravimetric Capacity:	kWh/kg (kg H_2/kg system)	1.8 (0.055)	2.5 (0.075)
System Volumetric Capacity:	kWh/L (kg H_2/L system)	1.3 (0.040)	2.3 (0.070)
Storage System Cost	$/kWh net	10	8

Advantages & Challenges of Complex Hydride Storage Materials

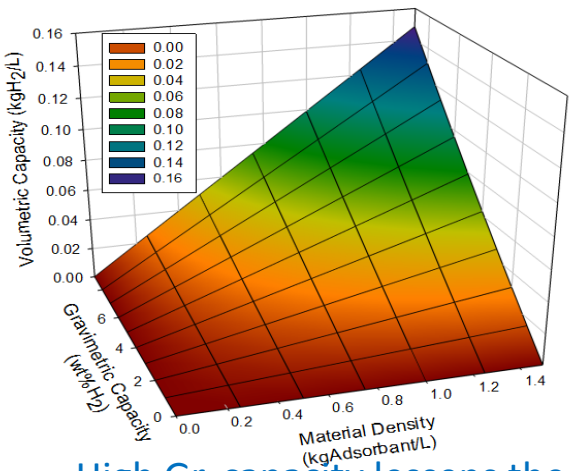

High Gr. capacity lessens the challenges on packing density

Advantages

- High gr. (10 ~14 wt.%) & vol. (0.08 ~0.15 kg/L) capacities
- Low storage pressure

Challenges

- Poor recyclability
- Poor H_2 Purity
- Poor DeH_2/ReH_2 Kinetics

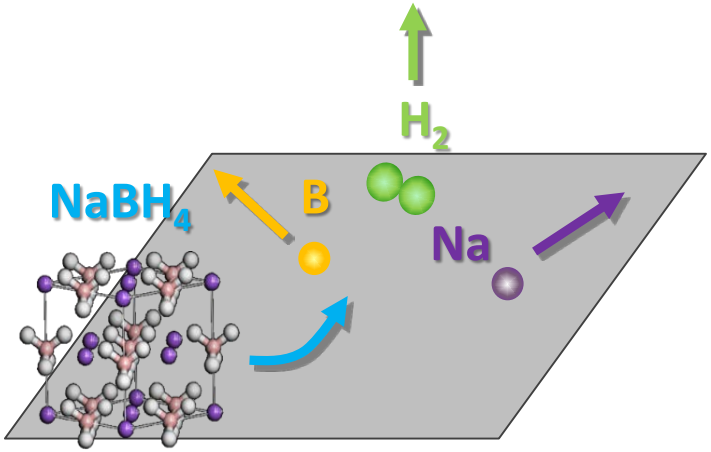

Encapsulating deH_2 products is essential for regeneration

Relevance - Objective

- ***Phase I –*** Deliver at least one "hydride@graphene" material with reversible total gravimetric capacity >8 wt% H_2 and total volumetric capacity >0.03 kg H_2/L at temperatures <400°C over at least five sorption/desorption cycles as validated by a DOE designated lab.
- ***Overall*** – To produce one or more hydride@graphene composite material with *regenerable / reversible* H_2 storage total gravimetric capacity >10wt.% and volumetric capacity greater than 0.055 kg H_2/L.

Potential Advantages of Hydride@Graphenes & Their Impact to Technology Barriers

- ***System Weight and Volume*** – Hydride@Graphenes have potential to reach both gravimetric and volumetric based on theory and preliminary experimental data
- ***System Cost*** – Hydride@Graphene is based on robust, solution based chemistry, scalable for industrial production.
- ***Efficiency*** – Hydride@Graphenes could significantly improve DeH_2/ReH_2 kinetics and temperatures compared to bulk hydrides.
- ***Durability/Operability*** – Hydride@Graphenes show promise to improve DeH_2/ReH_2 regenerability with cleaner hydrogen.

Approach – Complex Hydride Encapsulated by Graphene "Hydride@Graphene"

Concept developed through collaboration between Shanghai Jiao Tong U. & Argonne

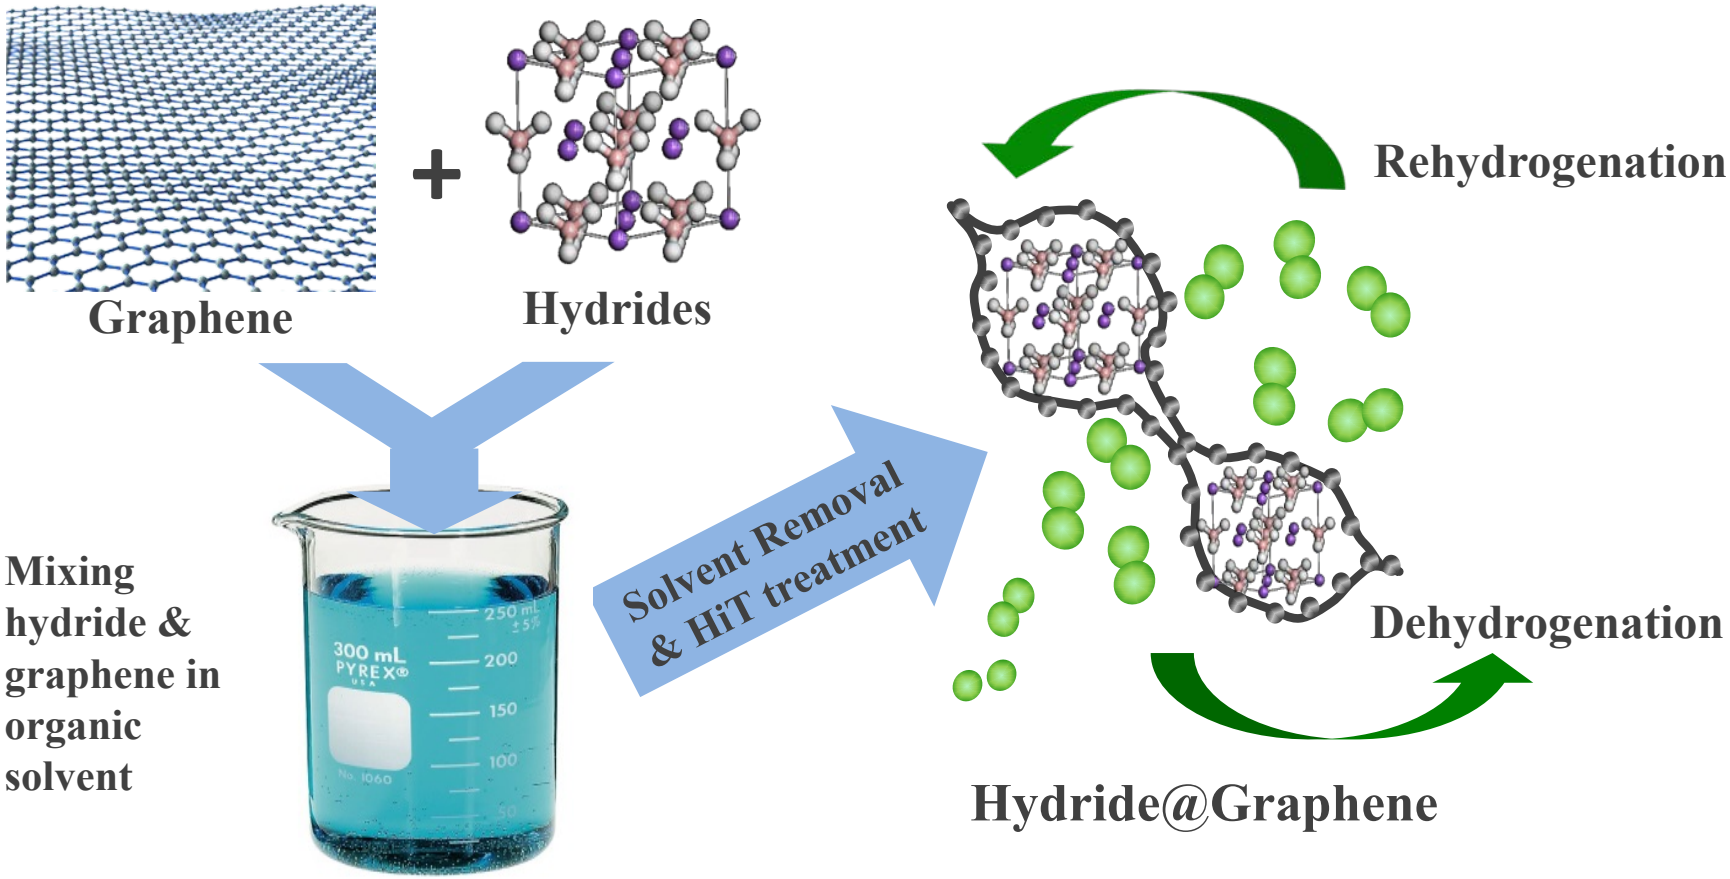

1. "NaBH4 in 'Graphene Wrapper': Significantly Enhanced Hydrogen Storage Capacity and Regenerability through Nano-encapsulation", L. Chong, X. Zeng, W. Ding, D-J Liu and J. Zou, Advanced Materials, **2015**, 27, 5070–5074
2. "Wrapped by graphene": An efficient way to achieve high capacity, reversible hydrogen storage through nanoencapsulated hydride, J. Zou, L. Chong, D-J Liu, X. Zeng, L. Peng, W. Ding, *Science*, **2016**, *351* (6278), 1223, Special issue

Approach –Advantages of Hydride@Graphene

$NaBH_4$@Graphene

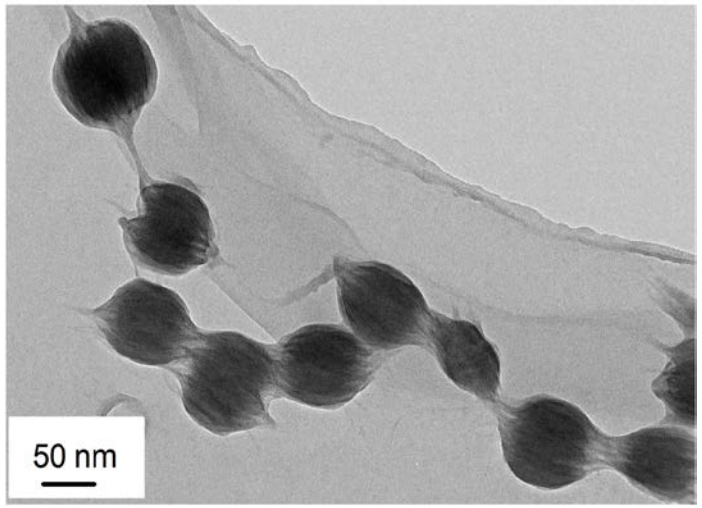

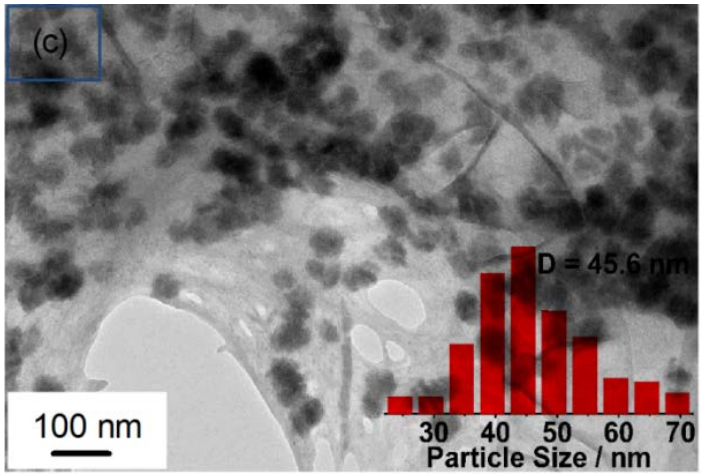

- Improved DeH_2/ReH_2 recyclability
  - Retention of DeH_2 byproducts facilitates hydride recovery during ReH_2
- Improved DeH_2/ReH_2 kinetics
  - Interaction between hydride and structurally conformable graphene and size control lead to lower DeH_2/ReH_2 temperatures
- Improved gravimetric capacity
  - Light weight, high surface area of graphene adds less parasitic weight
- Improved hydrogen purity
  - Only hydrogen can shuttle through graphene, reducing the release of byproducts to H_2 stream

Approach – Development Strategy

Hydride@Graphene Exploration (ANL)	Characterization & Optimization (ANL/HyMARC/HySCORE)	Modeling & Simulation (SIU/HyMARC)
▪ Refining existing and exploring new hydride@ graphene syntheses through rational design ▪ Structure characterization ▪ Post synthesis treatment	▪ H_2 storage capacity & reversibility measurements ▪ DeH_2/ReH_2 kinetics measurement ▪ Surface/structural property characterizations	▪ Computational guidance on size-dependent DeH_2/ ReH_2 activation energy ▪ Computational guidance on dopant catalytic effect

- New hydride@graphenes with enhanced H_2 storage capacities
- Reducing graphene usage in hydride@graphene for higher capacities
- Lowering DeH_2/ReH_2 temperatures through hydride crystallite size control
- Improving DeH_2/ReH_2 kinetics through interaction with graphene & additives
- Exploring the intrinsic storage capacity of graphene

Collaboration with HyMARC and leveraging existing experimental/ theoretical capabilities are essential to the project success!

Approach – Phase I Milestones/Go-NoGo Decision

Month/ Year	Milestones/Go-NoGo DP	Milestone Status
June/17	Regenerable DeH_2/ReH_2 storage capacity of > 8 wt.%	Storage capacities ranging from 9 wt.% to 7.4 wt.% achieved during six DeH_2/ReH_2 cycles
Sept/17	To produce sufficient quantity MgH_2@graphene as precursor for binary hydride@graphenes	To be started.
Sept/17	To complete structural & capacity characterization for modified $NaBH_4$@graphene	TPD, TGA, XRD, FTIR experiments are completed for the first batch of $NaBH_4$@graphene
Sept/17	Deliver a "hydride@graphene" with reversible total gr. capacity >8 wt% H_2 and total vol. capacity >0.03 kg H_2/L at T<400°C over 5 sorption/desorption cycles	To be delivered to a DOE designated lab for validation after initial measurement at ANL.

The focus of Phase I is to produce and demonstrate a hydride@graphene with reversible capacity of 8 wt.%.

Accomplishment – Update Since Project Inception

- New postdoc recruited and started in Jan, 2017
- Eight batches of $NaBH_4$@Graphene samples were synthesized.
- Dehydrogenation and rehydrogenation capacities and kinetics were measured and the capacity of 7.4 ~ 9 wt.% were observed
- Several characterizations including TPD, TGA, XRD, FTIR were performed on $NaBH_4$@graphene versus $NaBH_4$; insightful information on graphene-promoted DeH_2/ReH_2 recyclability and kinetics were obtained
- Preliminary computational simulations over hydride@graphene were carried out at SIU
- A number of collaborations with HyMARC team were initiated

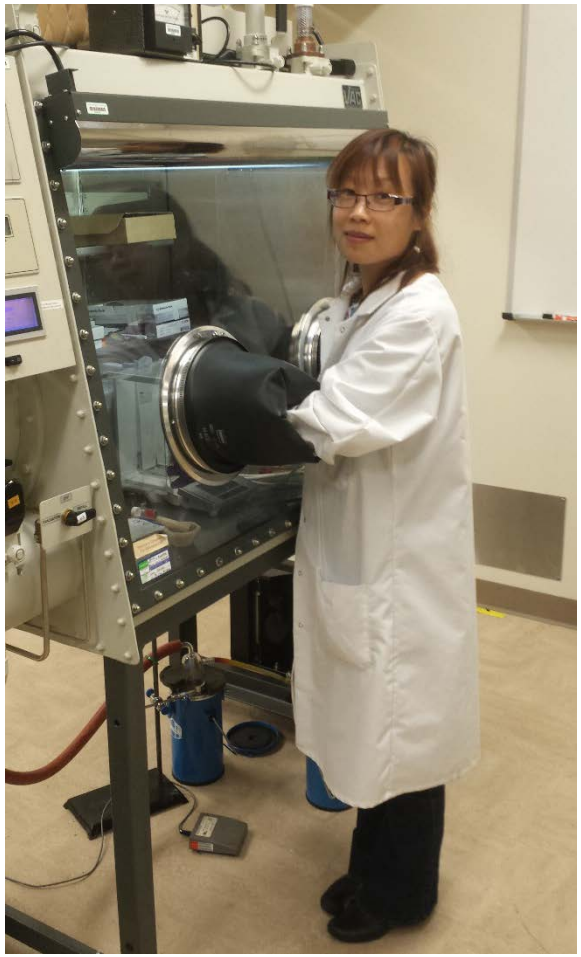

Accomplishment – Multiple Dehydrogenation (DeH_2) Cycles over $NaBH_4$@Graphene Demonstrated

Multiple DeH_2 Cycles Over a $NaBH_4$@Graphene Composite

Theoretical capacity = 9.1 w.t.% (86%$NaBH_4$ + 14% Graphene)

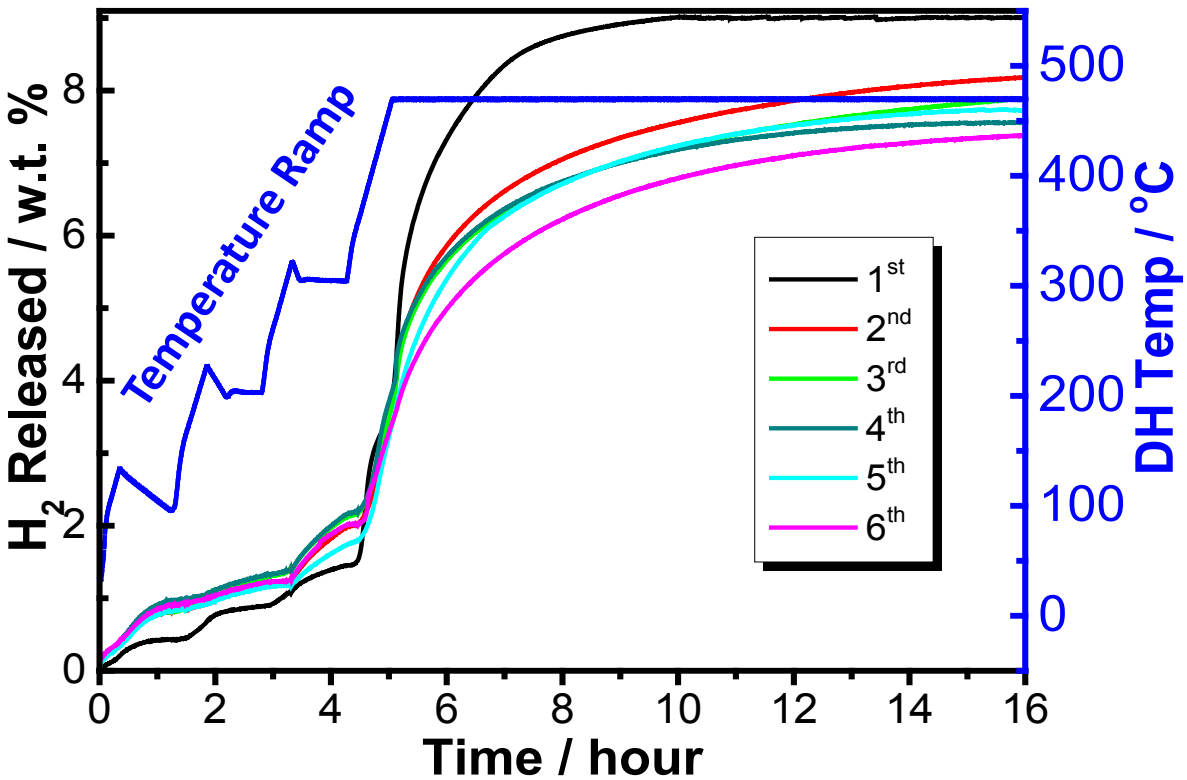

- Regenerable H_2 discharge was shown over 6 temperature programmed release cycles
- The first cycle demonstrates nearly 100% hydrogen discharge from $NaBH_4$@Graphene composite

Accomplishment – Multiple Rehydrogenation (ReH_2) Cycles Between DeH_2 over $NaBH_4$@Graphene Shown

Multiple ReH_2 Between DeH_2 Cycles of $NaBH_4$@Graphene Composite

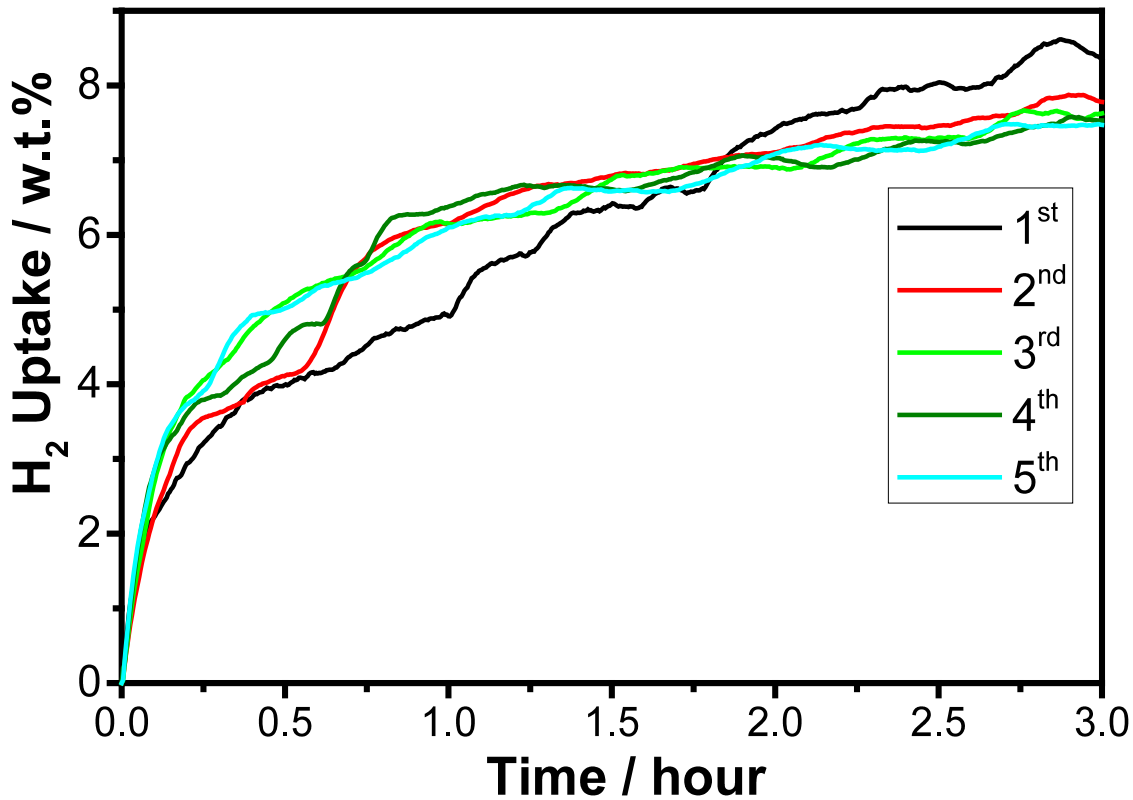

- One-step rehydrogenation at 350 °C under 4 MPa H_2 leads to recovery of majority hydride in graphene

Accomplishment – High Fraction of Hydride Regeneration over $NaBH_4$@Graphene Achieved

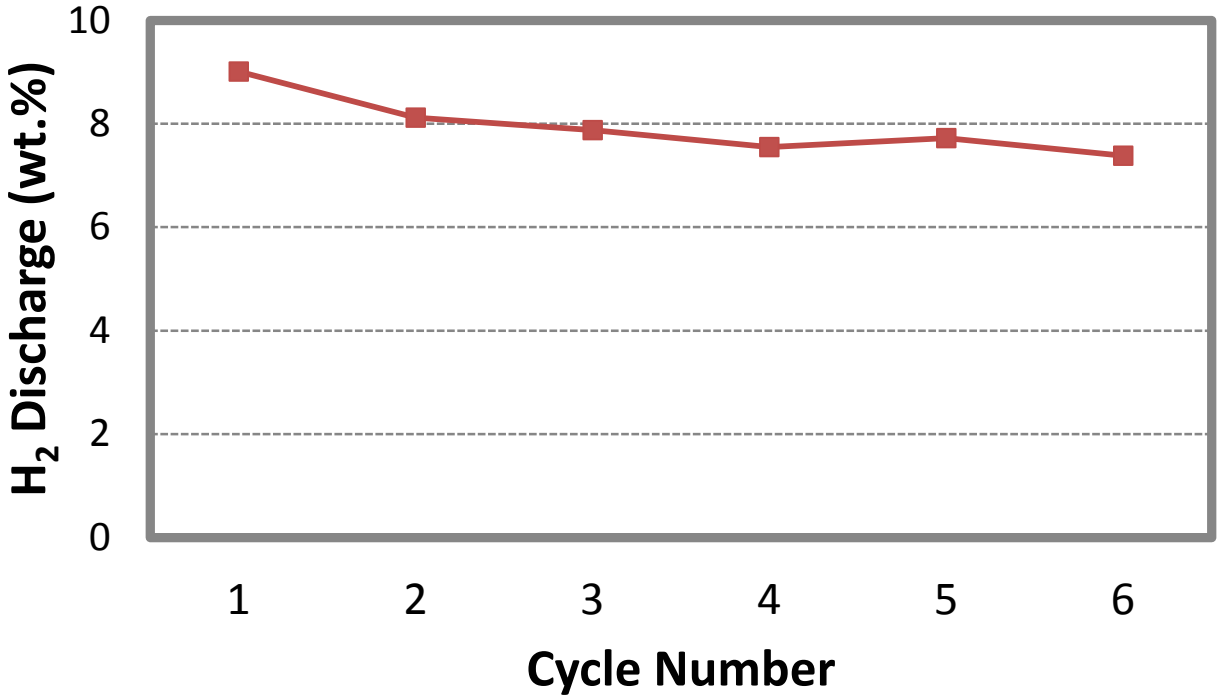

Cycle #	1	2	3	4	5	6
H2 Discharge (wt.%)	9.01	8.12	7.88	7.55	7.72	7.38
% to Theoretical Value	99%	89%	86%	83%	85%	81%

> 80% of hydride in $NaBH_4$@graphene was regenerated during multiple DeH_2/ReH_2 cycles

Accomplishment – Temperature Programmable Desorption (TPD) Showed Lower DeH_2 Temperature over $NaBH_4$@Graphene

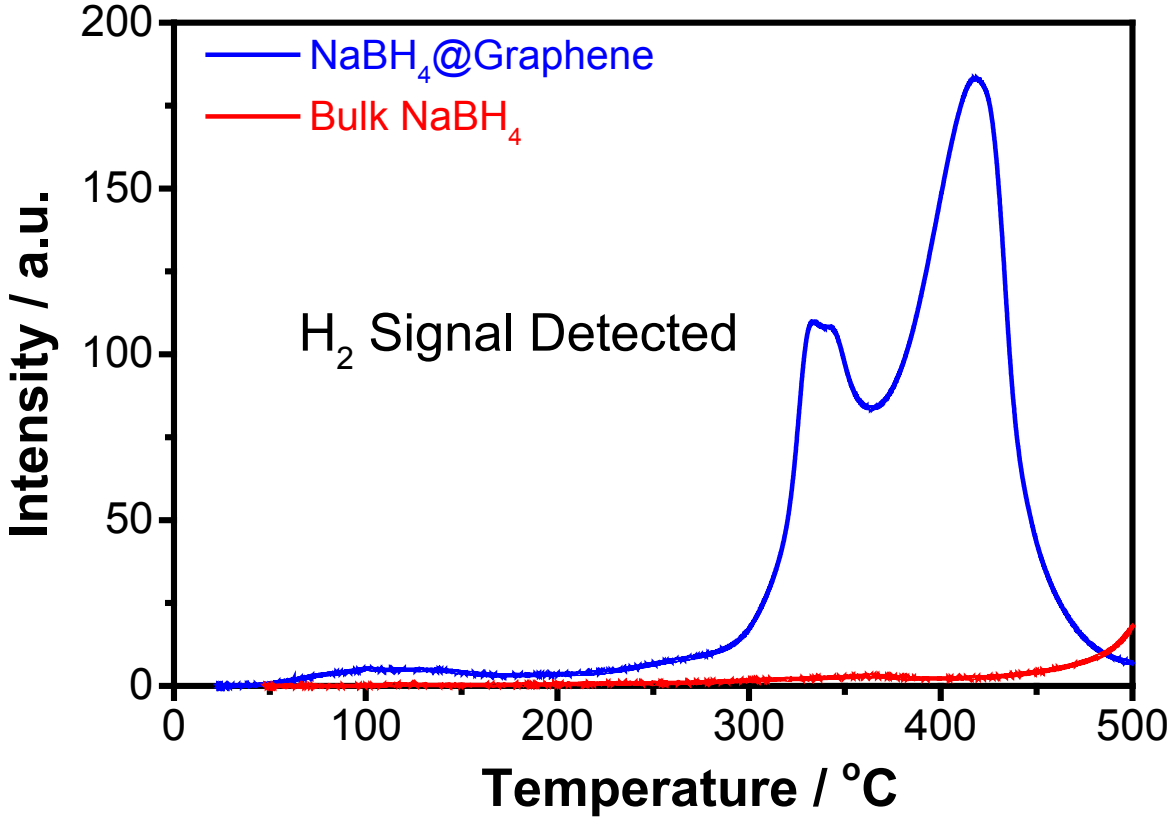

- TPD experiment showed a significant reduction of hydrogen discharge temperature in $NaBH_4$@Graphene over bulk $NaBH_4$
- A very low hydrogen release temperature (~50 °C) was observed for $NaBH_4$@Graphene, its root cause is yet to be identified

Accomplishment – Thermogravimetric Analysis (TGA) Confirmed Decrease of DeH_2 Temperature over $NaBH_4$@Graphene

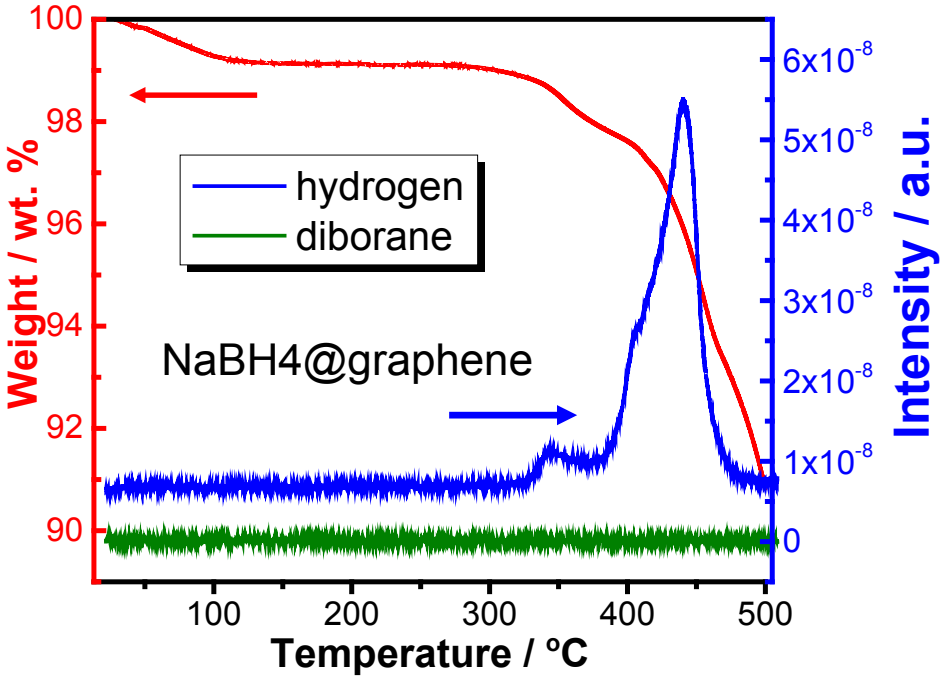

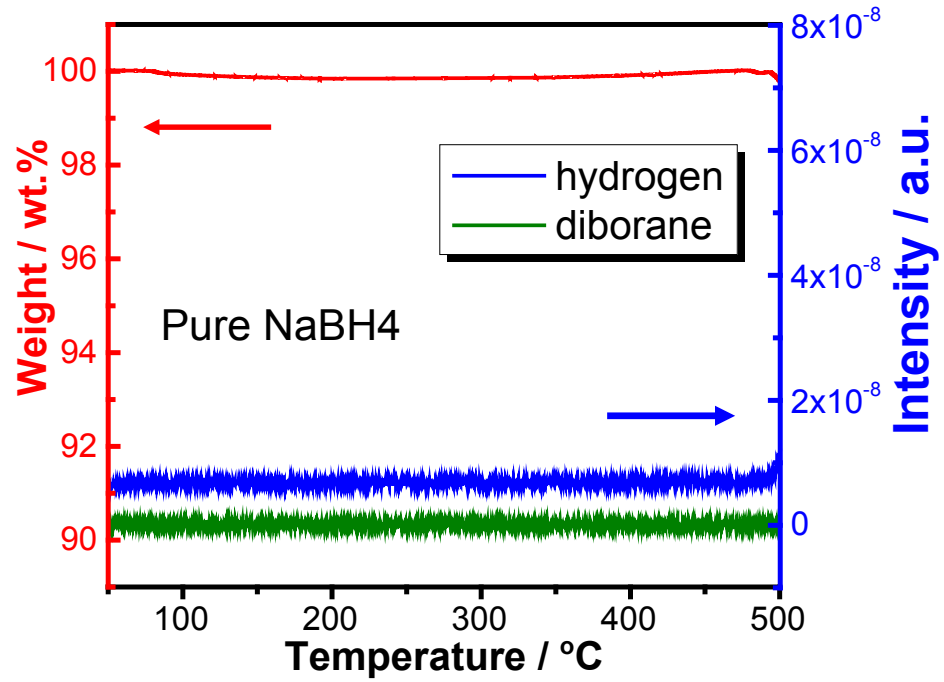

- Weight loss for $NaBH_4$@graphene matches that obtained from volumetric measurement. Weight loss at < 100 °C was again observed
- No appreciable weight loss for bulk $NaBH_4$ was observed, indicating the hydrogen release was promoted by graphene
- No other gas product such as diborane were observed

Accomplishment – X-ray Diffraction (XRD) Demonstrated Recovery of Hydride Crystallites in $NaBH_4$@Graphene after ReH_2

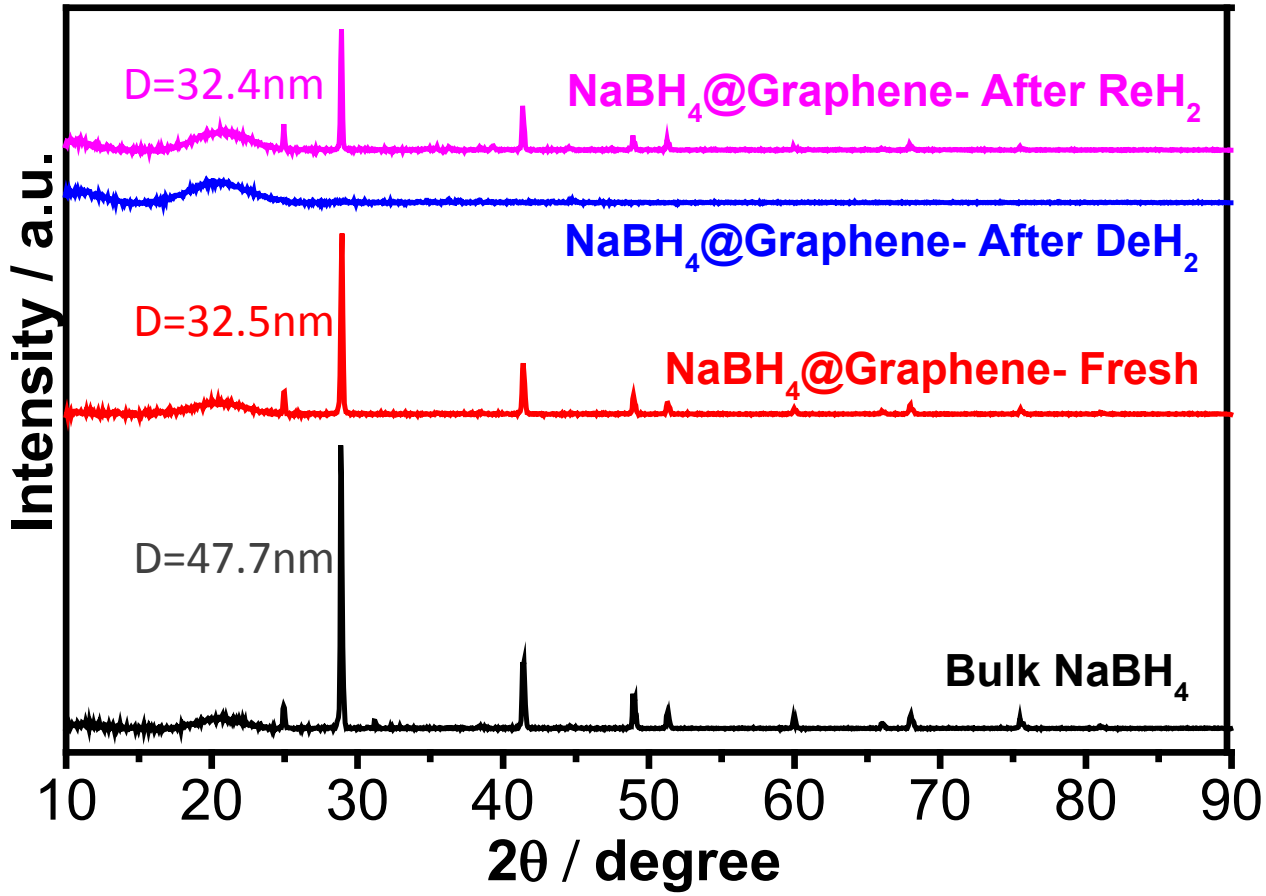

- XRD showed regeneration of crystalline hydride after rehydrogenation
- Hydride crystallite size in $NaBH_4$@graphene was reduced slightly compared to bulk hydride estimated based on Scherrer equation

Accomplishment – *In situ* FTIR Showed Reduction of B-H Band During DeH_2 over $NaBH_4$@Graphene

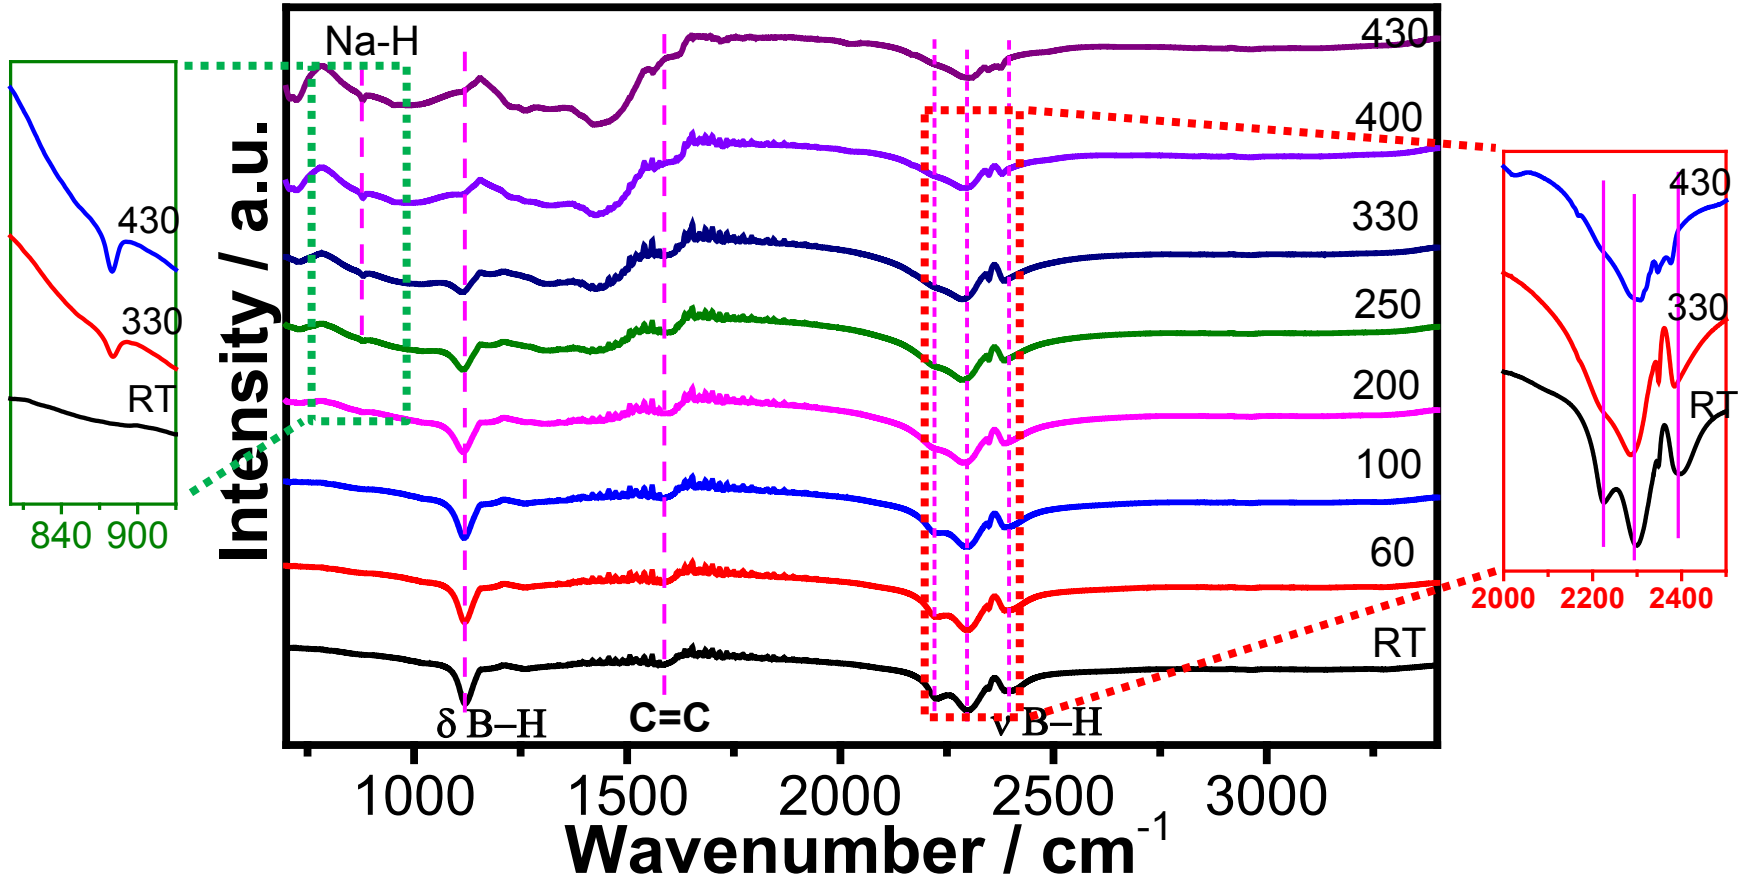

- *In situ* FTIR showed the loss of vibration peak associated with B-H and appearance of peak associated with Na-H as the temperature rose
- No other major chemical residual was found

Accomplishment – Computational Modeling Identified Two DeH_2 Pathways for Hydride@Graphene

Quantum Mechanical/Molecular Mechanical Calculation of $(MBH_4)_2$@Graphene

(M = Li, Na, K…, # of carbon used for graphene = 1928)

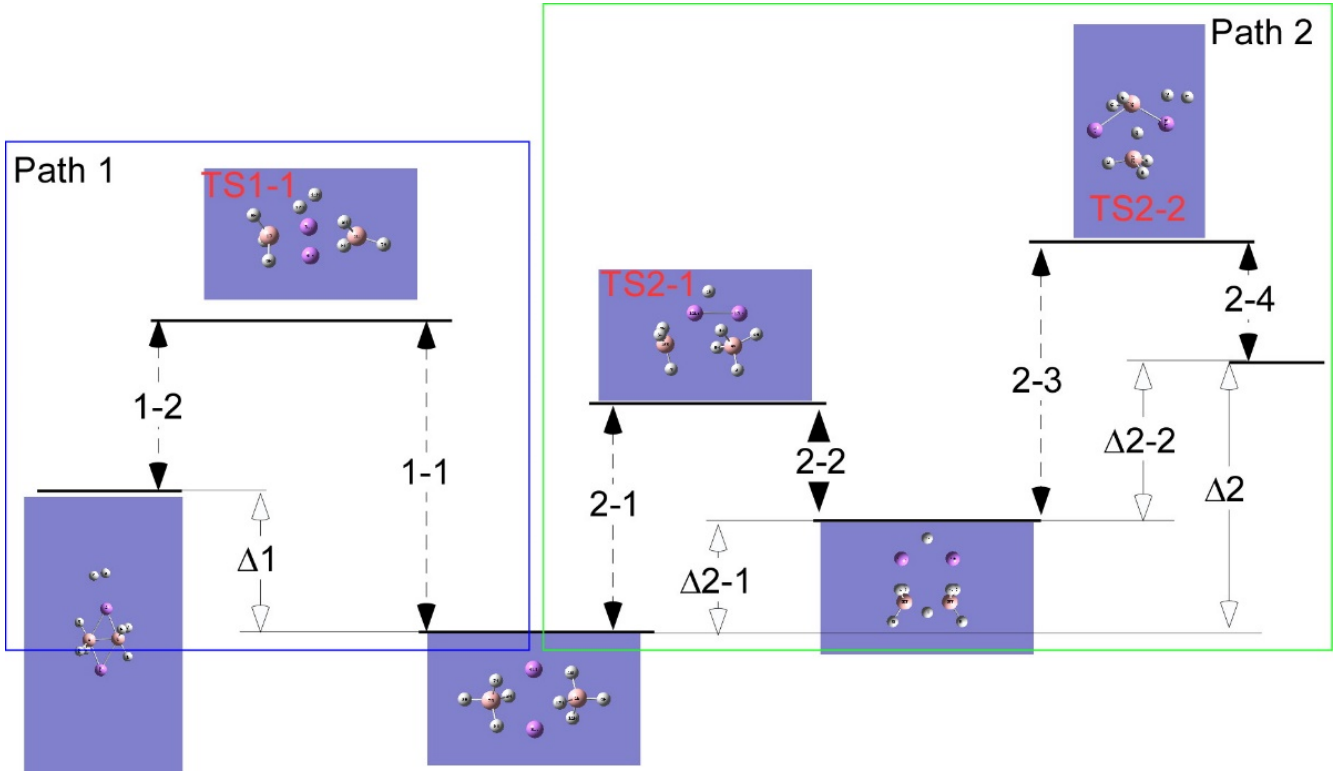

Path - 1 **Path - 2**

Accomplishment – Modeling Results Showed Limited Decreases of DeH_2 Barriers for Hydride@Graphene

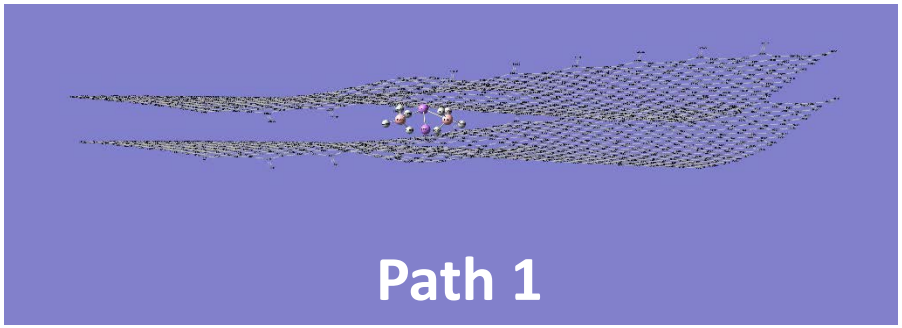

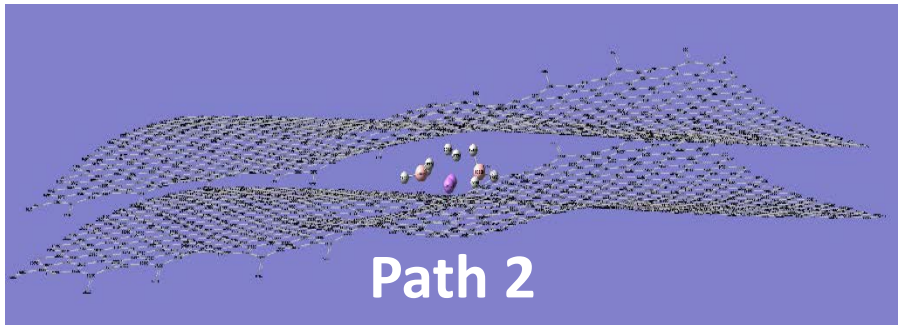

	Path 1			Path 2						
	1-1	1-2	Δ1	2-1	2-2	Δ2-1	2-3	2-4	Δ2-2	Δ2
$LiBH_4$	443.5	294.4	149.1	222.2	88.6	133.6	269.5	36.3	233.2	366.8
$LiBH_4$(Encap)	302.2	153.6	148.6	221.1	77.2	143.9	271.9	114.5	157.3	301.2
$NaBH_4$	407.7	222.0	185.6	229.8	96.4	133.4	267.4	215.1	52.3	185.6
$NaBH_4$(Encap)	388.7	208.9	179.8	220.3	84.1	136.1	267.9	219.4	48.5	184.6
KBH_4	418.6	210.7	207.9	259.1	100.4	158.7	252.6	203.4	49.2	207.9
KBH_4(Encap)	489.0	279.8	209.2				249.0	214.1	34.9	

- **Modeling shows only minor reduction of transition state barriers and overall reaction enthalpies for graphene encapsulated $NaBH_4$ in both reaction paths**
- **Major change in experimentally observed kinetics may be due to other effect**

Collaborations

- **HyMARC** – Computational modeling (solid mechanics) on encapsulated hydrides (in planning with Lawrence Livermore National Lab)
- **HyMARC** – Synchrotron X-ray absorption spectroscopic study on hydride under reaction (in planning with Lawrence Berkeley National Lab)
- **HyMARC** – Molecular Foundry for hydride synthesis optimization (in planning with Lawrence Berkeley National Lab)
- **HyMARC** – Collaborative investigations on the graphene promoted kinetics in hydrides (monthly meeting, Sandia National Lab)
- **HySCORE** – Hydrogen storage capacity certification (National Renewable Energy Lab, to be submitted)
- **Southern Illinois University** – Project subcontractor on the computational modeling (work initiated)
- **Shanghai Jiao Tong University** – Graphene/catalyst material exchange.

Proposed Future Work

Phase I

- Continue to increase overall H_2 storage capacity in $NaBH_4$@graphene through optimizing hydride/graphene ratio
- Improve DeH_2 and ReH_2 kinetics in $NaBH_4$@graphene through catalysis
  - Metal complex as added catalyst
  - Graphene defect / hetero-element incorporation as catalyst
- Continue to improve fundamental understanding of DeH_2 and ReH_2 mechanism through computational modeling and advanced characterization (collaborating with HyMARC)
- Initiate synthesis on binary complex hydrides encapsulated by graphene

Phase II

- Exploring new complex hydride@graphene with higher theoretical capacities
- Lowering DeH_2 and ReH_2 temperature and increase rate through the catalytic additives and hydride size control by synthesis
- Investigating DeH_2 and ReH_2 mechanism through advanced characterization & modeling to guide the design and improvement of hydride@graphene
- Engineering downselected hydride@graphene for transportation application

Summary

- Regenerable hydrogen storage capacities between 8.1 wt.% to 7.4 wt.% were demonstrated during six dehydrogenation/rehydrogenation cycles over $NaBH_4$@Graphene.
- Dehydrogenation/rehydrogenation kinetics and recyclability of $NaBH_4$ were significantly improved through “graphene wrapping”. Further improvement is still necessary and underway.
- A variety of structural characterizations confirmed the regeneration of hydride micro-crystallites assisted by graphene in the rehydrogenation cycle.
- Release of low level hydrogen at near ambient temperature was observed. Better understanding of the root cause could be important in improving dehydrogenation kinetics.
- Computational modeling for hydride@graphene was initiated.
- Several collaborations with HyMARC are underway.

Acknowledgement

- This work is supported by US DOE, Office of Energy Efficiency and Renewable Energy, Fuel Cell Technologies Office

- Project Manager: Jesse Adams

- Hydrogen Storage Program Manager: Ned Stetson

ADDITIONAL SLIDE

Accomplishment – Recent NMR Result

11B MAS-NMR spectra

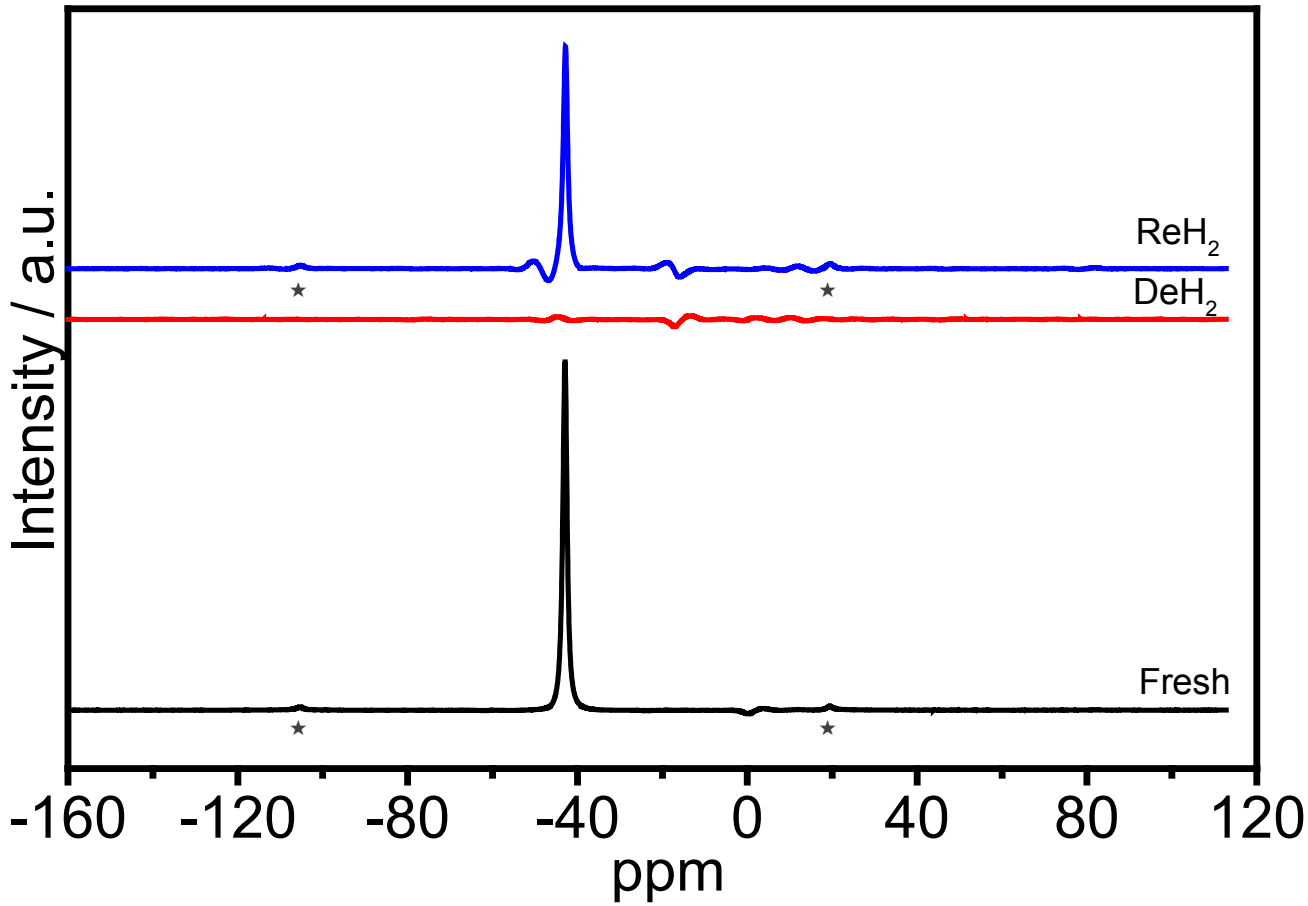

Asterisks indicate spinning sidebands