NREL
NATIONAL RENEWABLE ENERGY LABORATORY

Advanced Ionomers & MEAs for Alkaline Membrane Fuel Cells

PI Bryan Pivovar
National Renewable Energy Laboratory
June 15, 2018

DOE Hydrogen and Fuel Cells Program
2018 Annual Merit Review and Peer Evaluation Meeting

Project ID #FC147

This presentation does not contain any proprietary, confidential, or otherwise restricted information.

Overview

Timeline and Budget

- Project start: October 2015
- Project end: March 2019
- % complete: ~ 70%

- DOE Budget plan
  - FY 2016 - 2018 $ 2,600k
  - Cost Share Percentage – 0%

Barriers

- Durability
- Cost
- Performance

Partners

- LBNL – Adam Weber
- ORNL/UTK – Tom Zawodzinski
- Colorado School of Mines – Andy Herring
- (in-kind) 3M – Mike Yandrasits

Relevance/Impact
DOE (Preliminary) Milestones for AMFCs*

- **Q2, 2017:** Develop anion-exchange membranes with an area specific resistance ≤ 0.1 ohm cm^2, maintained for 500 hours during testing at 600 mA/cm^2 at T >60 ^oC.
- **Q4, 2017:** Demonstrate alkaline membrane fuel cell peak power performance > 600 mW/cm^2 on H_2/O_2 (maximum pressure of 1.5 atma) in MEA with a total loading of ≤ 0.125 mg_{PGM}/cm^2.
- **Q2, 2019:** Demonstrate alkaline membrane fuel cell initial performance of 0.6 V at 600 mA/cm^2 on H_2/air (maximum pressure of 1.5 atma) in MEA a total loading of < 0.1 mg_{PGM}/cm^2 , and less than 10% voltage degradation over 2,000 hour hold test at 600 mA/cm^2 at T>60 ^oC. Cell may be reconditioned during test to remove recoverable performance losses.
- **Q2, 2020:** Develop non-PGM catalysts demonstrating alkaline membrane fuel cell peak power performance > 600 mW/cm^2 under hydrogen/air (maximum pressure of 1.5 atma) in PGM-free MEA.

Impact/Team Project Goals

Novel Synthesis - Improve novel perfluoro (PF) anion exchange membrane (AEM) properties and stability.

Fuel Cell Optimization - Employ high performance PF AEM materials in electrodes and as membranes in alkaline membrane fuel cells (AMFCs).

Model Development - Apply models to AMFCs to determine and minimize losses (water management, electrocatalysis, and carbonate related).

*taken from D. Papageorgopoulos presentation AMFC Workshop, Phoenix, AZ, April 1, 2016

Approach

Membrane Synthesis, Electrode Optimization, and Fuel Cell Testing

Novel Polymer Synthesis



Gen 2 Synthesis

NREL: provide current material for further testing

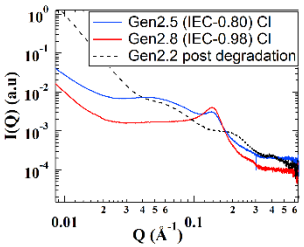

Characterization

NREL: conductivity, IEC

CSM: structure, carbonate

ORNL/UTK: microscopy, NMR

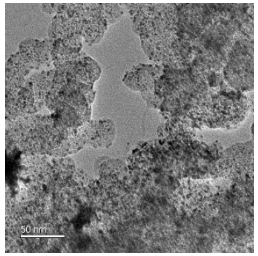

Gen 3 Synthesis

NREL: develop improved stability tether



Fuel Cell Optimization

MEA Fabrication/Optimization

NREL: composition, processing

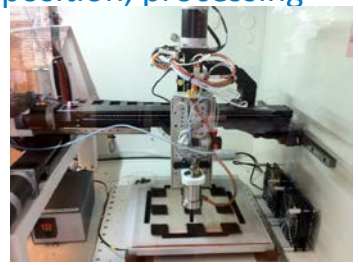

Fuel Cell Diagnostics

NREL: performance, durability, transport

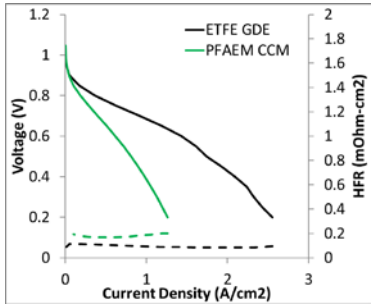

AMFC Modeling

LBNL: water, carbonate management, spatial effects

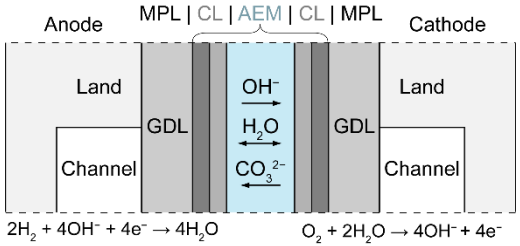

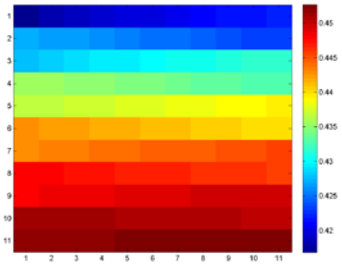

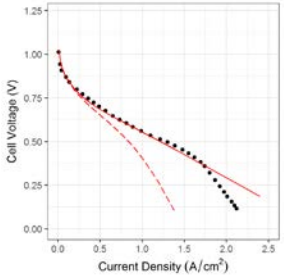

Approach

Project Schedule/Milestones

Name	Description	Criteria	Status
Mid-Project Decision Point (go/ no-go)	Meet FCTO MYPP 2017 Q2 Milestone for AEMFCs	Develop anion-exchange membranes with an area specific resistance of ≤0.1 ohm cm2 (after correction for cell electronic losses), maintained for 500 hours during testing at 600 mA/cm2 at T >60ºC.	Complete

Milestone Name/Description	End Date	Type	Status
Verify durability improvement toward hydroxide attack of Gen 3 chemistry in small molecule studies.	12/31/2017	Quarterly Progress Measure	Complete
Provide experimental results to LBNL for model verification of 1+2D model.	3/31/2018	Quarterly Progress Measure	Complete
Demonstrate capability of achieving Gen 3 chemistry in polymer membranes with greater than 80% conversion of side chains to cation form.	6/30/2018	Quarterly Progress Measure	TBD
Aligned with AEMFC Q2, 2019 milestone: Demonstrate alkaline membrane fuel cell initial performance of 0.6 V at 600 mA/cm2 on H2/air (maximum pressure of 1.5 atma) at T>60 C for >500 hr.	9/30/2018	Annual Milestone	TBD

Accomplishments and Progress

Continued Improvement and Supply of Gen 2 PF AEM

Gen 2 PF AEM Synthesis Optimization

Polymer Gen	Excess Linker	$IEC_{Theoretical}$ [mmol/g]	$IEC_{Measured}$ [mmol/g]	σ_{OH-} [mS/cm]
1.0	1.15	1.06	0.91	55
2.0	1.1	1.03	0.77	43
2.1	1.4	1.03	0.83	46.4
2.2	1.7	1.03	0.91	51.4

Gen 1 PF AEM Polymer

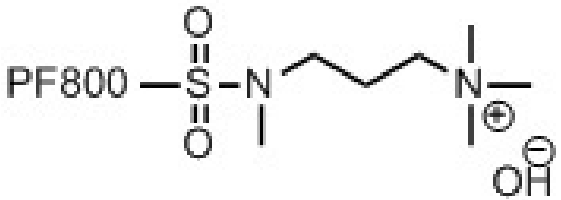

Gen 2 PF AEM Polymer

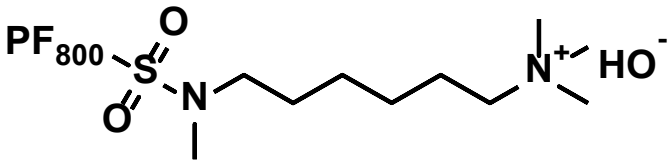

Synthesis scale and reproducibility

- >300 g Gen 2 PF AEM polymer has been produced to date
- Gen 2 production scale is ~12 g per batch, limited by reactor volume
- 7 batches of Gen 2.2 produced with reasonable reproducibility (IEC = 0.9 ± 0.04 mmol/g)
- Properties consistent with PFSA analogues

Polymer distribution ~20 entities, including:

- 3M
- Pajarito Powder
- Giner
- pH Matter
- Oak Ridge
- Lawrence Berkeley
- LSU
- Tennessee
- CO School of Mines
- UC-Merced
- South Carolina
- TUM

A.M. Park et al, *ECS Trans.* 2017 **80(8)**: 957-966; doi:10.1149/08008.0957ecst

Accomplishments and Progress

PF AEM Durability Studies

Accelerated degradation conditions (140 °C, 2:1 MeOH:H_2O, 2M KOH, 24 hr)
Chosen for solubility, reaction times

Gen 2 PF AEM Polymer

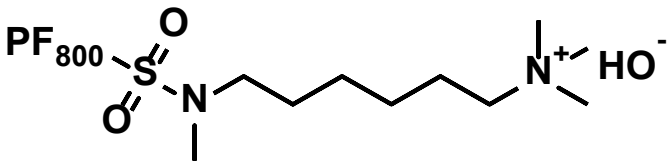

Gen	Small Molecule Analogue	QA Degradation [%]	Tether Degradation [%]
Gen 1		93.8	100
		74.4	70.7
		64.1	58.6
Gen 2		62.2	3.5
Gen 3		64.3	Not detected

Membrane Durability

- Membrane physically changed, conformed to reactor liner and became opaque and heterogeneous
- Couldn't be dissolved/recast, x-ray scattering showed significant change in structure, conductivity difficult to measure and low
- IEC decreased by only 13% compared to 62% of small molecule analogue

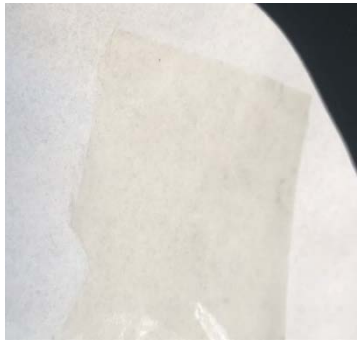

Pre Degradation

Post Degradation

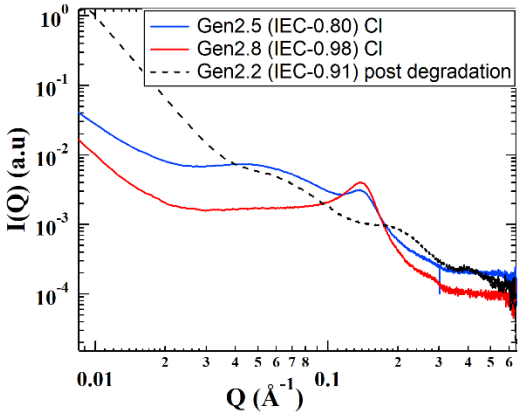

Accomplishments and Progress

PF AEMs Moving Forward

Gen 2 with increased stability cations

- Small molecule degradation indicates stability limitation of the quaternary ammonium cation
- Cations with enhanced stability being pursued: imidazolium, phosphonium, and heterocyclic cations have shown promising stability.

Gen 2 PF AEM Polymer

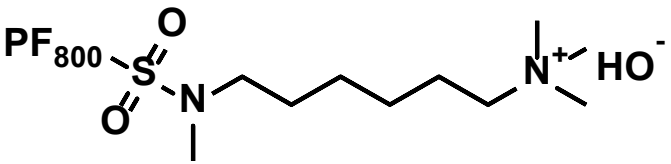

Imidazolium

1. Hugar et al. *J. Am. Chem. Soc.* **2015,** *137* (27), 8730-8737.
2. Price et al. *ACS Macro. Lett.* **2014,** *3* (2), 160-165.
3. Yang et al. *Int. J. Hydrogen Energy* **2015,** *40* (5), 2363-2370.

Phosphonium

4. Gu et al. *ChemSusChem* **2010,** *3* (5), 555-558.
5. Noonan et al. *J. Am. Chem. Soc.* **2012,** *134* (44), 18161-18164.

Heterocyclic

6. Gu et al. *Macromolecules* **2014,** *47* (19), 6740-6747.
7. Dang et al. *J. Mater. Chem. A* **2016,** *4* (30), 11924-11938.

Gen 3 PF AEM Polymer



Gen 3 chemistry

- Explore feasibility of a cation tether with an all carbon linkage (go/no-go 6/30/18)

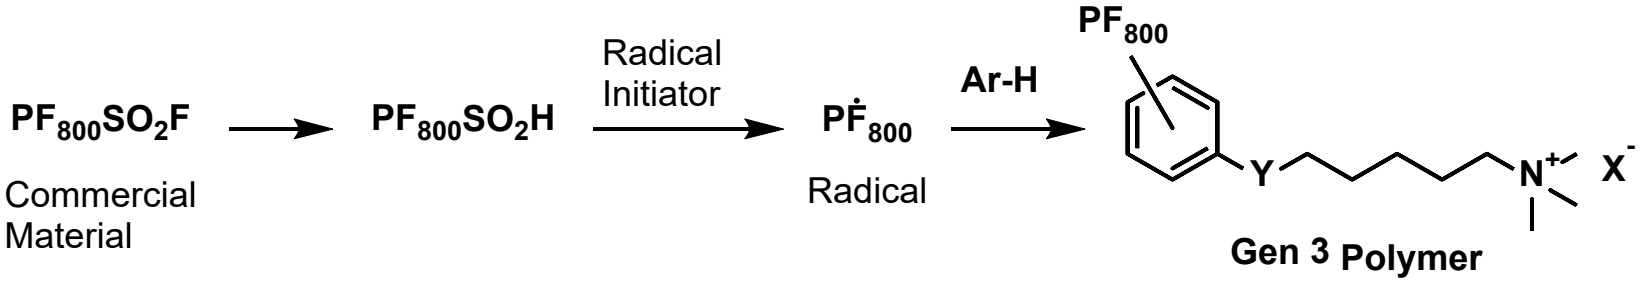

Accomplishments and Progress

Probing Carbonate Equilibrium

- Carbonate is critical for cell performance and is getting better quantified (modeled).

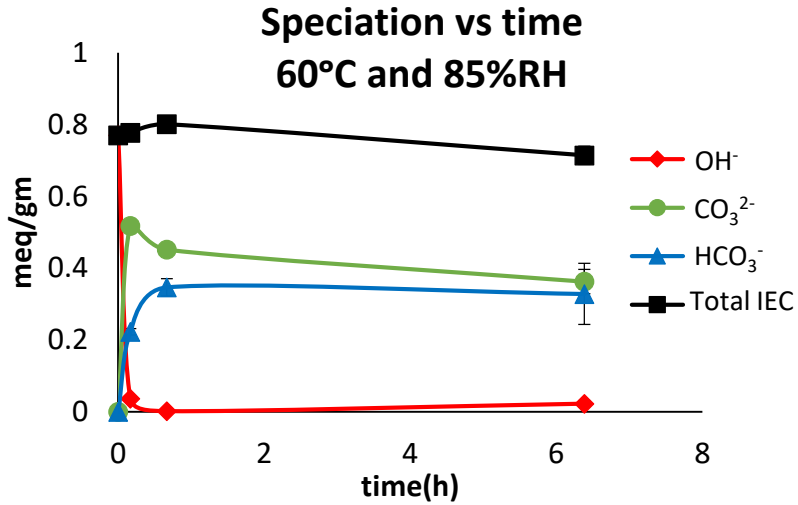

Carbonation happens quickly
Steady-state equilibrium between CO_3^{2-} and HCO_3^-
Reproducibility/Experimental error relatively large

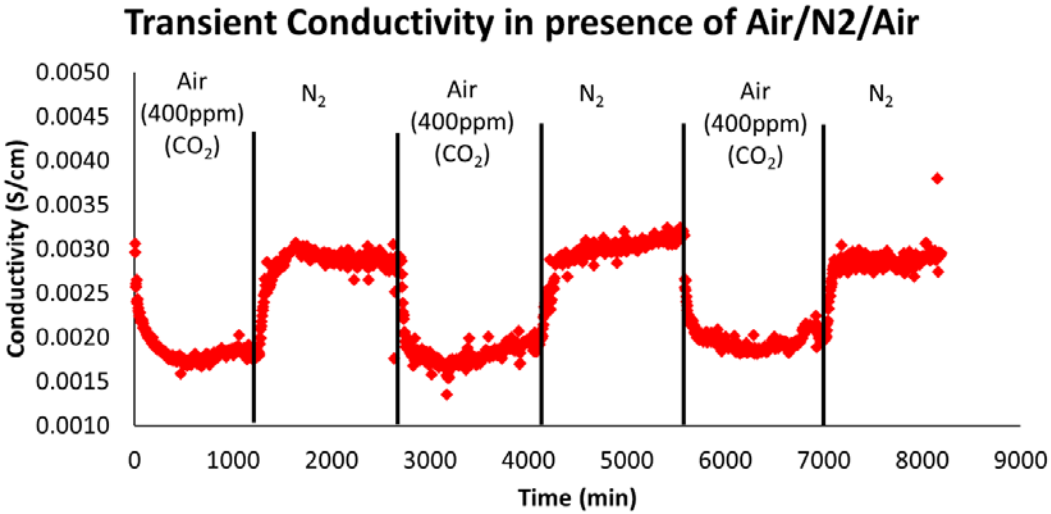

Transient conductivity of OH- sample in Air(400 ppm CO_2) & N_2(0 ppm CO_2)
60°C & 85%RH in a Bekktech cell

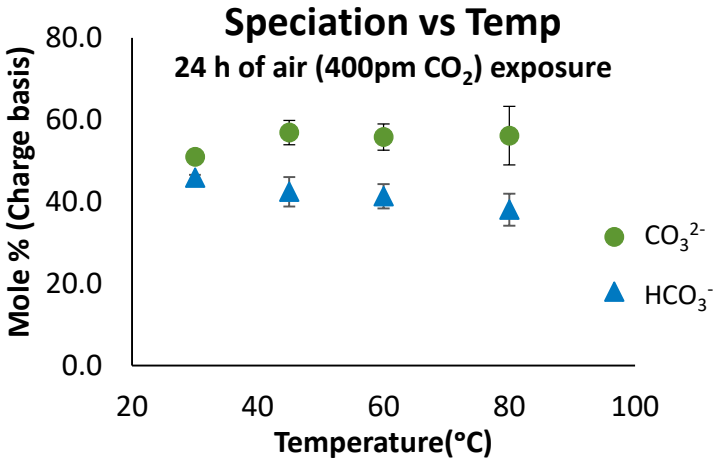

Slight decrease in HCO_3^-/CO_3^{2-} with increasing temperature

- Equilibrium with local conditions happens quickly
- Conductivity drops when exposed to CO_2 → absorption
- Conductivity rises when CO_2 removed → desorption
- Data reproducible between cycles

Equilibrium Reactions:

$$CO_{2(aq)} + OH^- \leftrightarrow HCO_3^-$$

$$HCO_3^- + OH^- \leftrightarrow CO_3^{2-} + H2O$$

Divekar et al.,, ECS Trans. 2017 80(8): 1005-1011; doi:10.1149/08008.1005ecst

Accomplishments and Progress

Electrode Preparation

- Few groups have shown high AMFC (~1W/cm2) performance.
- We have focused on two specific electrode approaches:

PF AEM Gen 2

- Employed NREL Gen 2 PF AEM dispersion properties fairly consistent with typical PFSA dispersions for PEM
- Performance fairly average (100's mW/cm^2), but durability very poor (~10 hours)

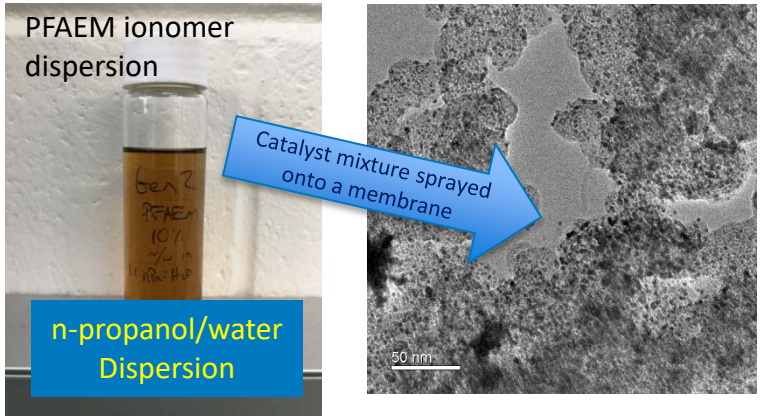

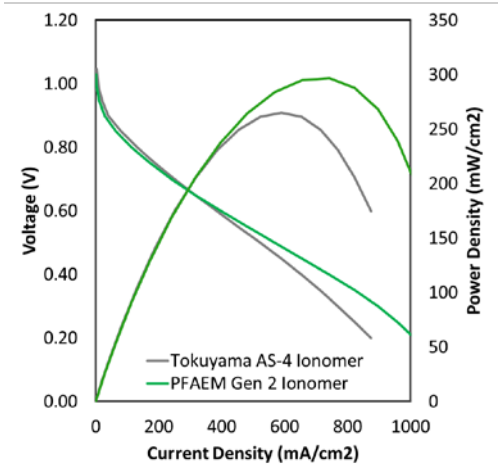

ETFE - based

- Solid ionomer powder (Prof. John Varcoe, Univ. of Surrey), dry mixed with catalyst, sprayed on GDL
- Electrode fabrication and optimization by Mustain, U. So. Carolina)
- Have demonstrated record performances in AMFCs (~2W/cm^2, 5A/cm^2), with good durability

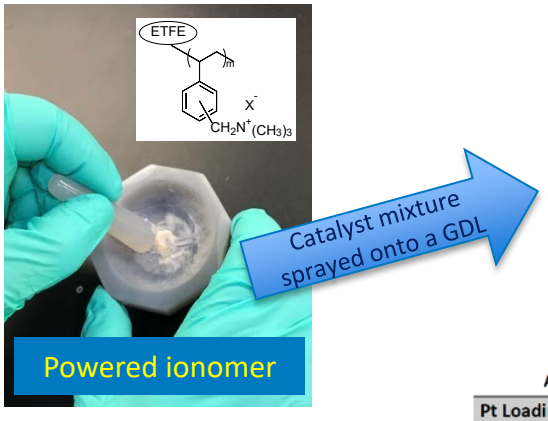

Anode Type:	IC	BC	EC
Pt Loading, mg cm^{-2}	0.47	0.47	0. 50
C Loading, mg cm^{-2}	0.75	1.07	1.76
Carbon weight %	41.4 %	48.0 %	56.0 %
AEI weight %	17.2 %	**20.0 %**	**20.0 %**
AEI:C ratio	***0.417**	***0.417**	0.357

L. Wang et al, *Green Chem.*, 2017, **19**, 831
T.J. Omasta, et al., *Journal of Power Sources* (2017)
T.J. Omasta, et al., *Energy Environ. Sci.*, 2018, **11**, 551

Accomplishments and Progress

High Performance AMFCs (2017 AMR Status)

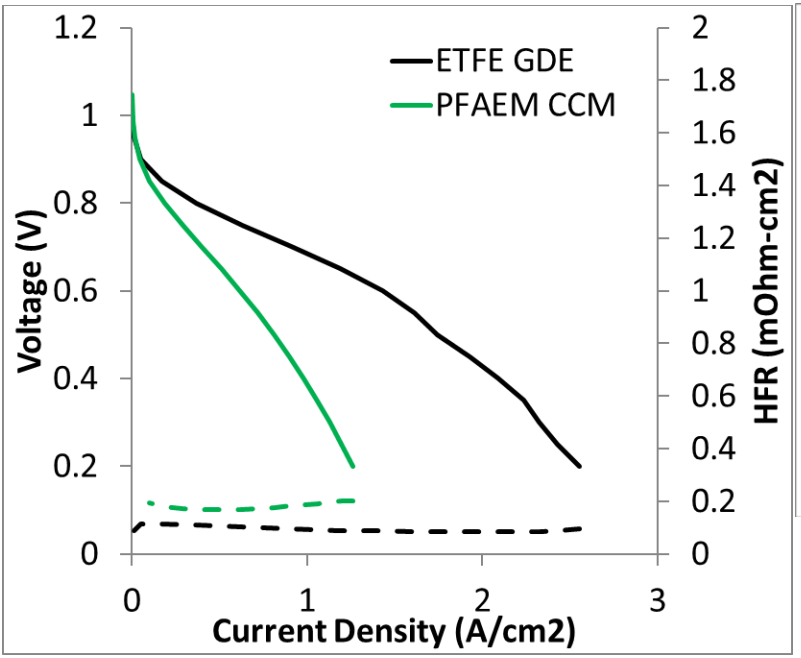

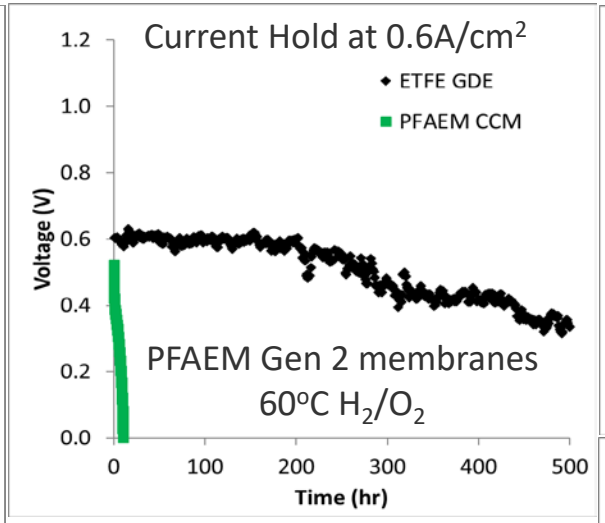

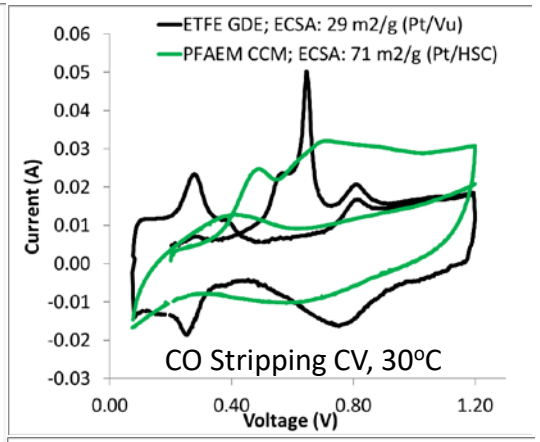

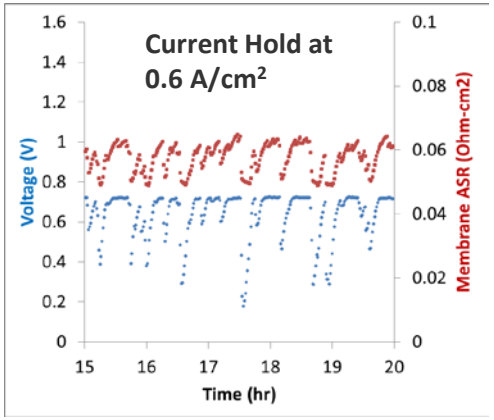

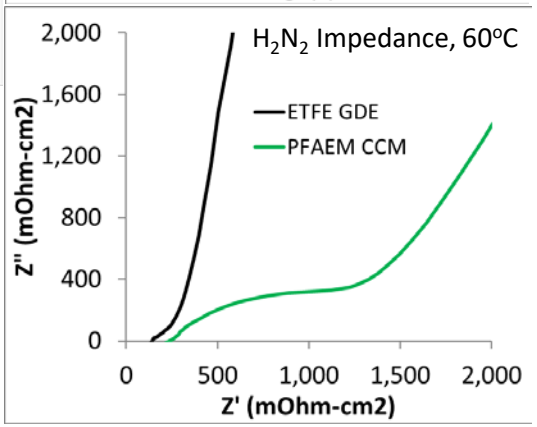

Membrane Electrode Assembly

- Cell Temp: 60°C
- Membrane: Gen 2 PFAEM (32 µm)
- Ionomer: ETFE or PFAEM
- GDL: Toray H-060 or SGLBC29
- Gases: H_2 var°C, O_2 var°C, 1.0 slpm
- Active Area: 5 cm^2
- Pressure: 121 kPa abs
- Anode: 0.5 mg/cm^2 Pt/HSC
- Cathode: 0.5 mg/cm^2 Pt/HSC
- Relative Humidity: 80% RH

- PF AEM Gen 2 membrane used in both cases, only difference is electrodes.
- Performance and durability of ETFE electrodes much higher than PF AEM.
- Performance, durability, voltammetry, and impedance all show strong dependence on electrodes.
- Extreme sensitivity to RH/water management for ETFE GDEs.

Accomplishments and Progress

Continuing Work with Gen 2 PF AEM

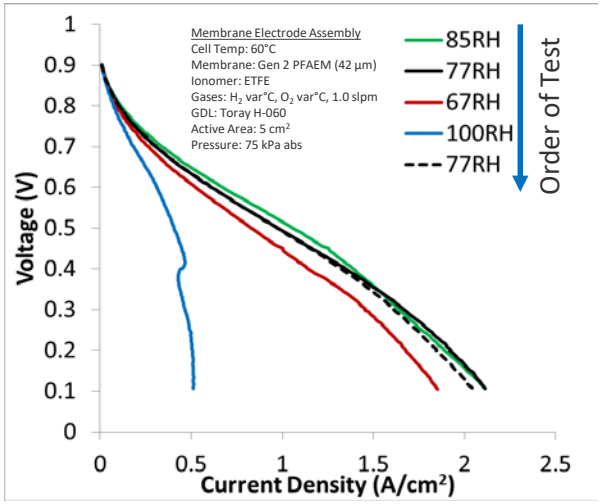

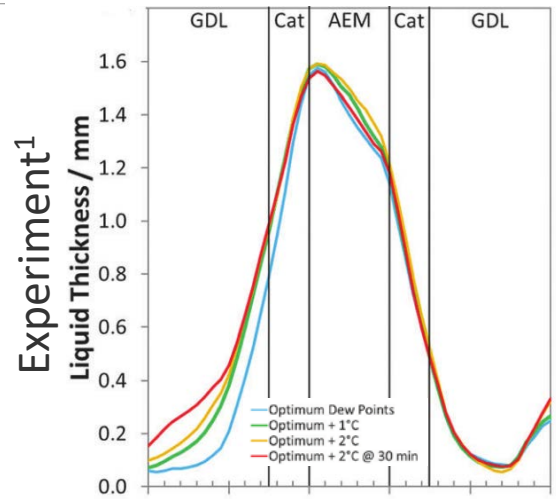

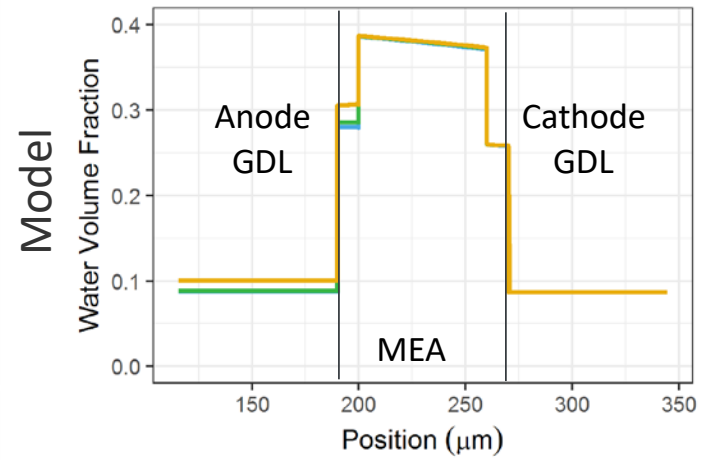

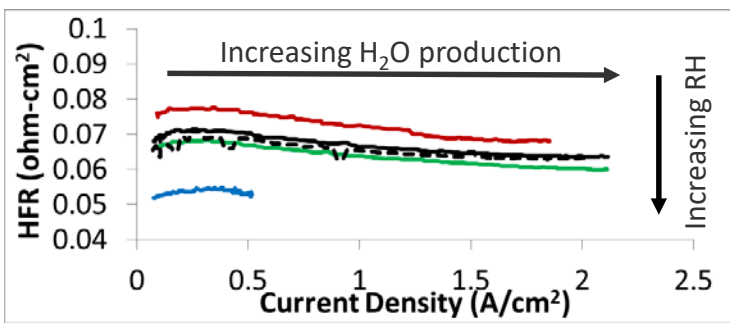

- These findings are consistent with experimental results[1] and modeling efforts (see back up slide 31). The importance of anode mass transport ('flooding') and back diffusion of water are key findings for optimal performance.

- Fully humidified and low RH (67%) showed lowest performance.
- HFR shows expected trend with RH, 100% RH shows much lower HFR but suffers due to (anode) mass transport limitation.
- HFR decreases with increasing current density, as water produced at anode back diffuses to cathode.

[1]Omasta, T. J. *et al. Energy Environ. Sci.* **11,** 551–558 (2018).

Accomplishments and Progress

ETFE GDE/PFAEM CCM Asymmetric MEAs

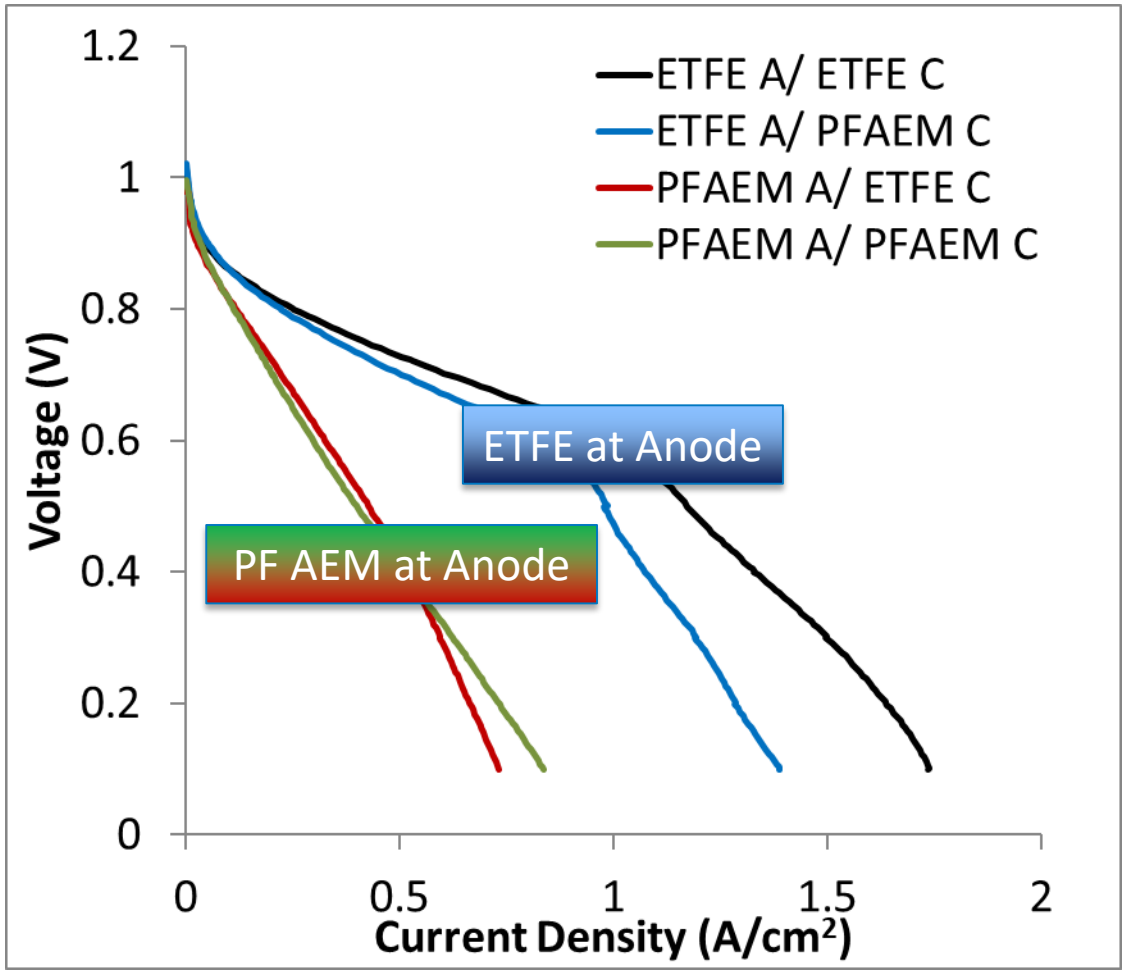

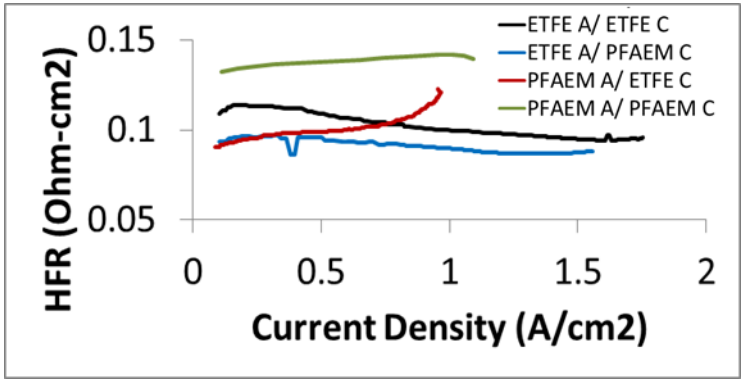

- HFR trends are also insightful, they show increasing HFR for PF AEM at anode and decreasing HFR for ETFE at anode with current density.
- Input provided for modeling efforts.

- ETFE electrodes at anode enables high initial performance

Membrane Electrode Assembly

- Cell Temp: 60°C
- Membrane: Gen 2 PFAEM (32 µm)
- Ionomer: ETFE or PFAEM
- GDL: Toray H-060 or SGLBC29
- Gases: H_2 var°C, O_2 var°C, 1.0 slpm
- Active Area: 5 cm^2
- Pressure: 121 kPa abs
- Anode: 0.5 mg/cm^2 Pt/HSC
- Cathode: 0.5 mg/cm^2 Pt/HSC
- Relative Humidity: 80% RH

Accomplishments and Progress

ETFE GDE/PFAEM CCM Asymmetric MEAs

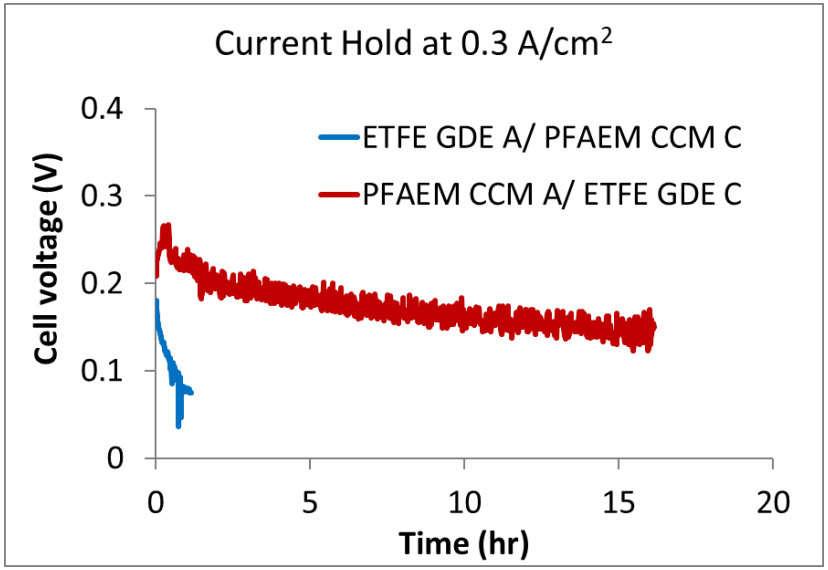

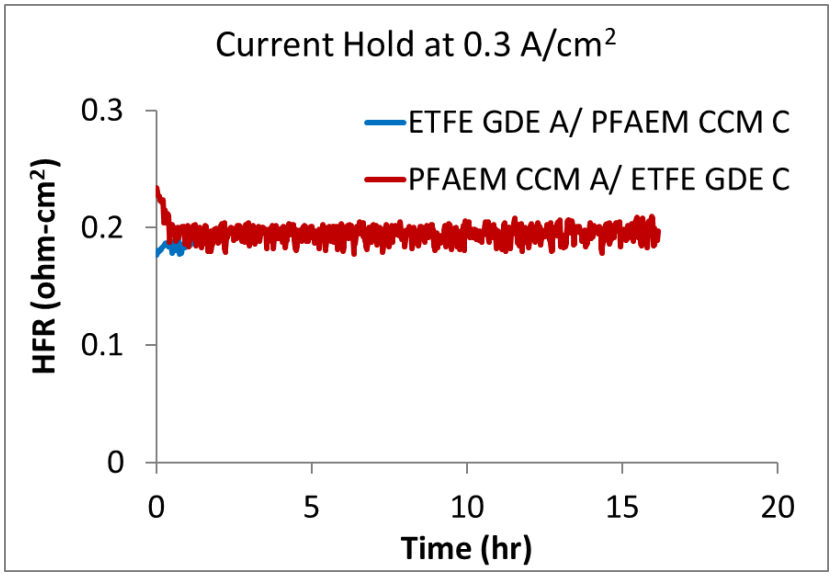

- Asymmetric MEAs also interesting for looking at durability trends.
- PF AEM at cathode shows extremely poor durability, while ETFE at cathode even with PF AEM at anode show better durability.
- HFR not impacted by durability over the time investigated, not correlated to performance loss.

- **ETFE electrode necessary at anode for performance**
- **ETFE electrode necessary at cathode for durability**

Membrane Electrode Assembly

- Cell Temp: 60°C; RH: 80% RH
- Membrane: Gen 2 PFAEM (32 µm)
- Ionomer: Varcoe AEI or PFAEM
- Gases: H_2 var°C, O_2 var°C, 1.0 slpm
- Active Area: 5 cm^2
- GDE: 0.35 mg/cm^2 Pt/HSC
- CCM: 0.40 mg/cm^2 Pt/HSC

Accomplishments and Progress

Performance Losses and Carbon Corrosion Concerns

As-prepared PF AEM CCM

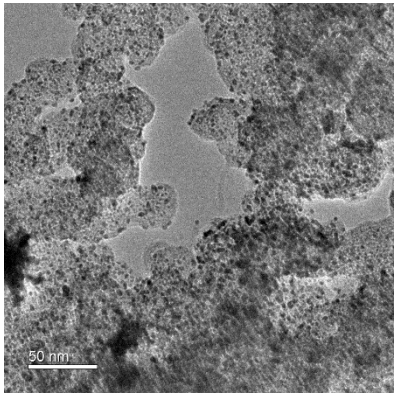

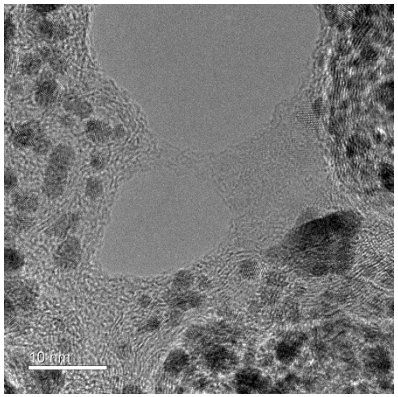

Post-test Cathode (13 hours)

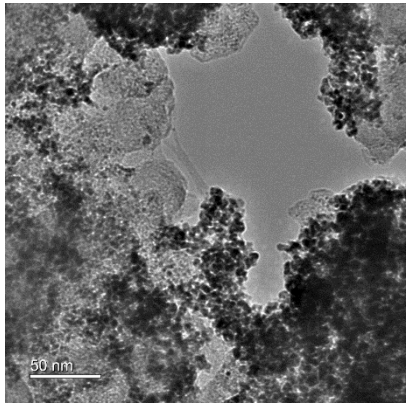

Post-test Anode (13 hours)

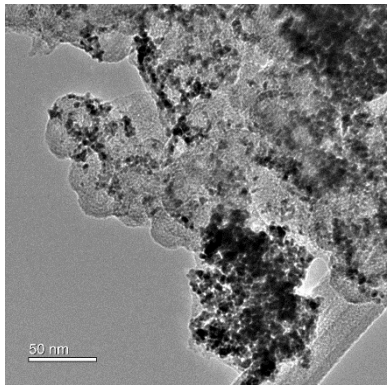

Clear signs of Pt agglomeration and carbon corrosion in both anode or cathode, but more pronounced in cathode. Major changes in voltammetry and impedance observed.

As- prepared PF AEM electrodes look like standard PFSA PEMFC electrodes

Cathode

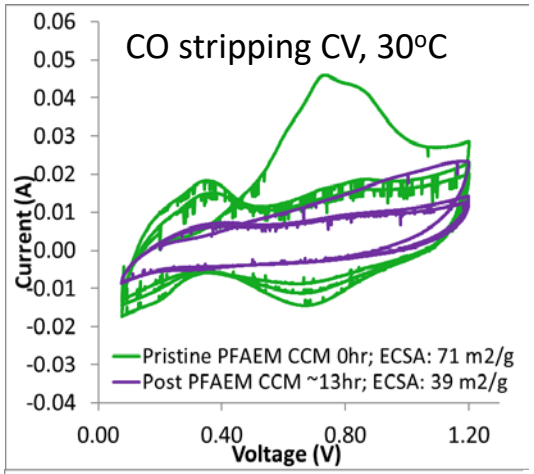

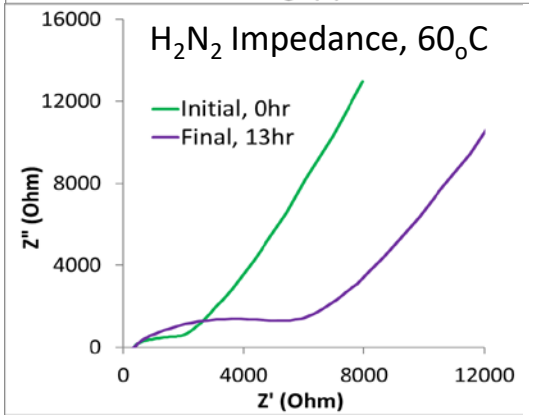

Accomplishments and Progress

AMFC Modeling (2017 AMR Status)

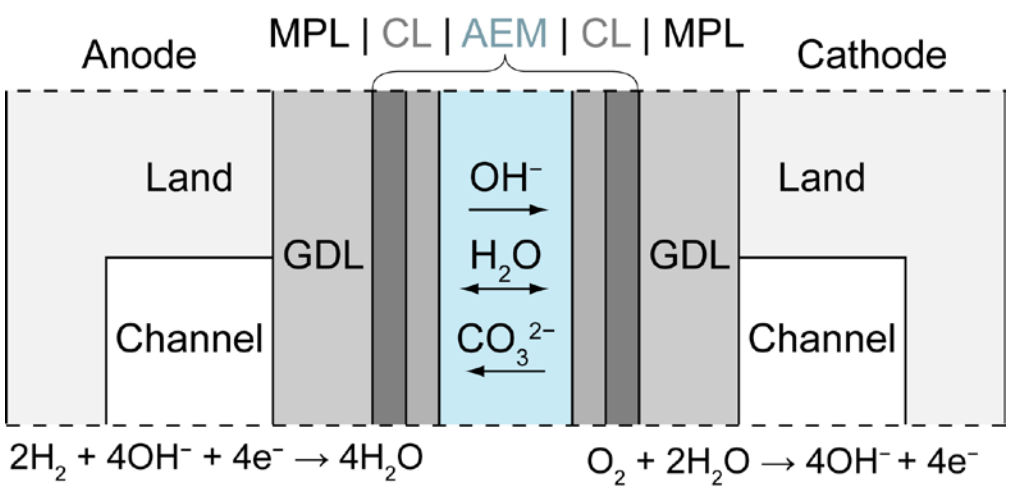

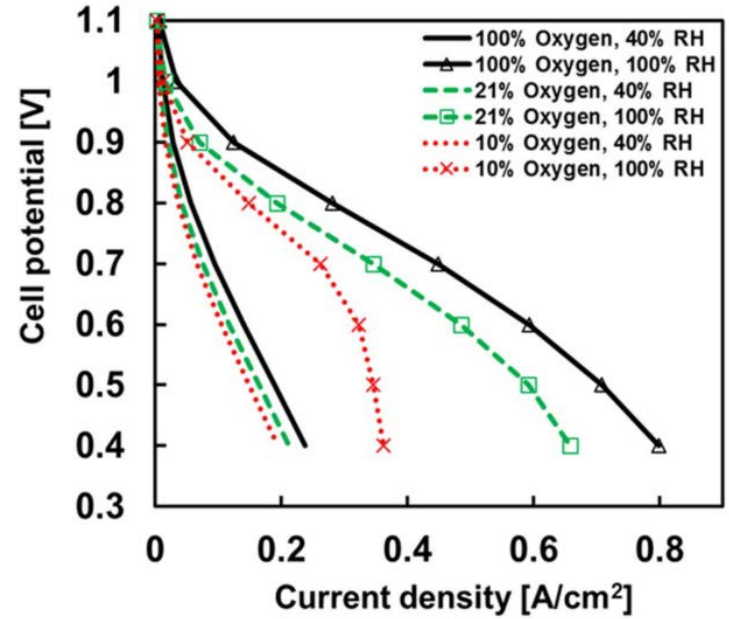

- 2017 AMR Status:
  - 2D model developed to explore water and carbonate management
  - Performance is highly sensitive to RH variations

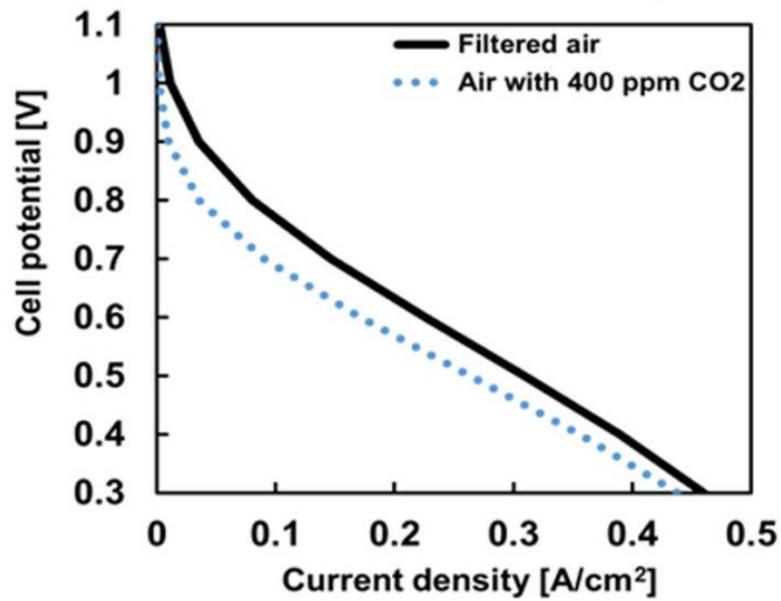

Accomplishments and Progress

Role of Water Back Diffusion

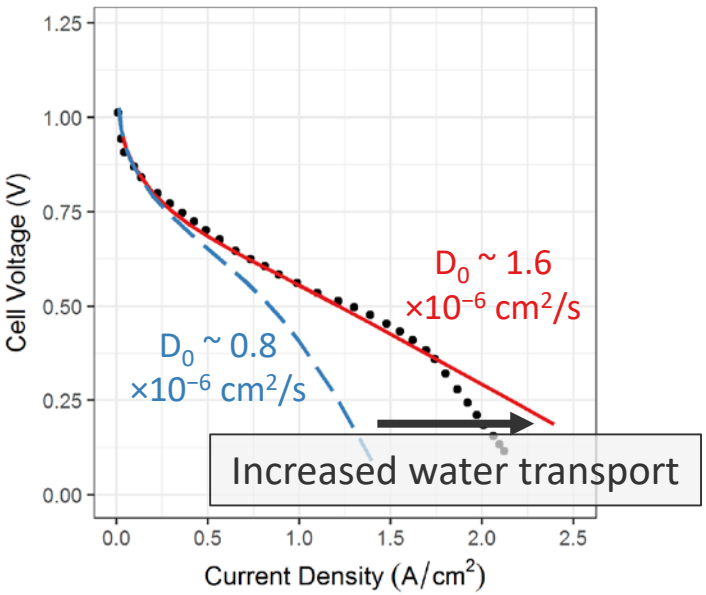

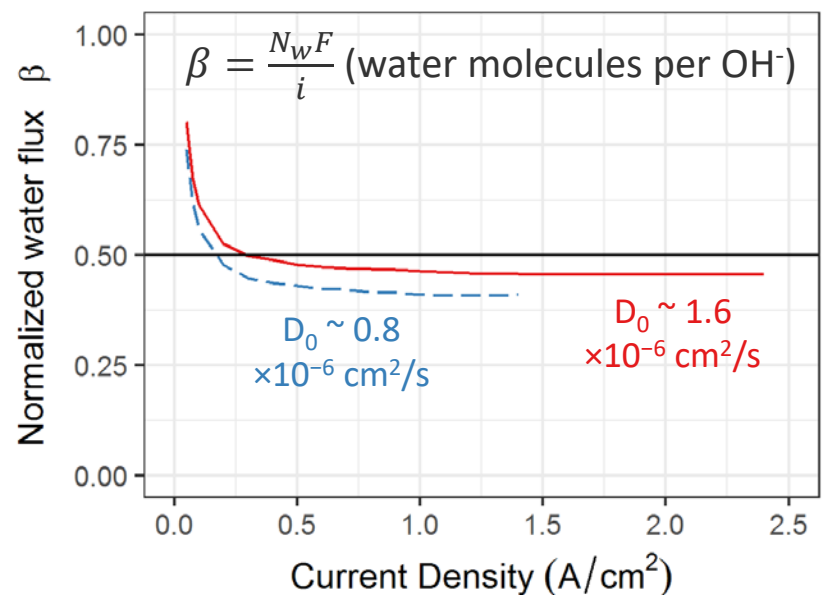

- Feedback from NREL experiments: cathode RH does not need to be very high for good performance
- Water back-diffusion replaces consumed water at AEMFC cathode
  - At $\beta = 0.5$, water flux from anode to cathode equals water consumption by ORR
- Faster water diffusion allows for more even catalyst utilization in cathode CL

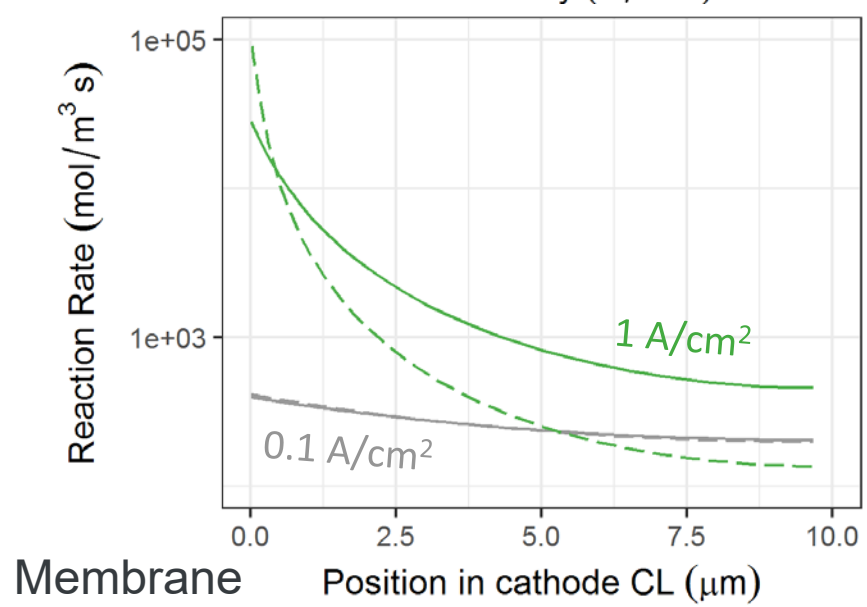

Data from:
Omasta, T. J. *et al. J. Power Sources* **375,** 205–213 (2018).

Accomplishments and Progress

Effects of CO_2 contamination

Polarization curve from 2-D model

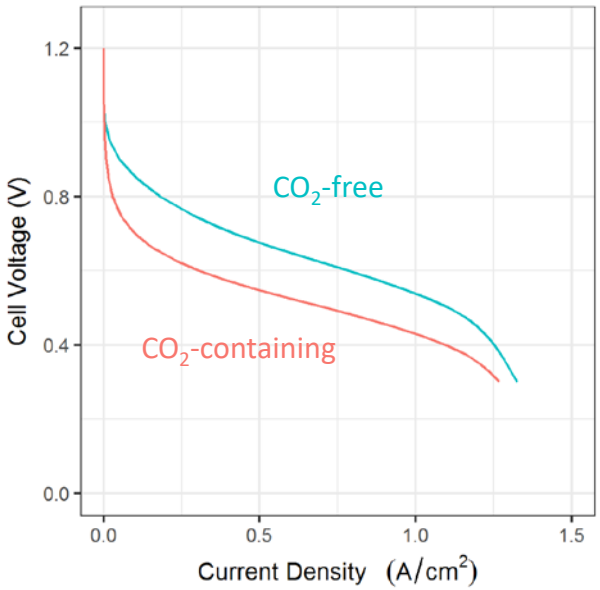

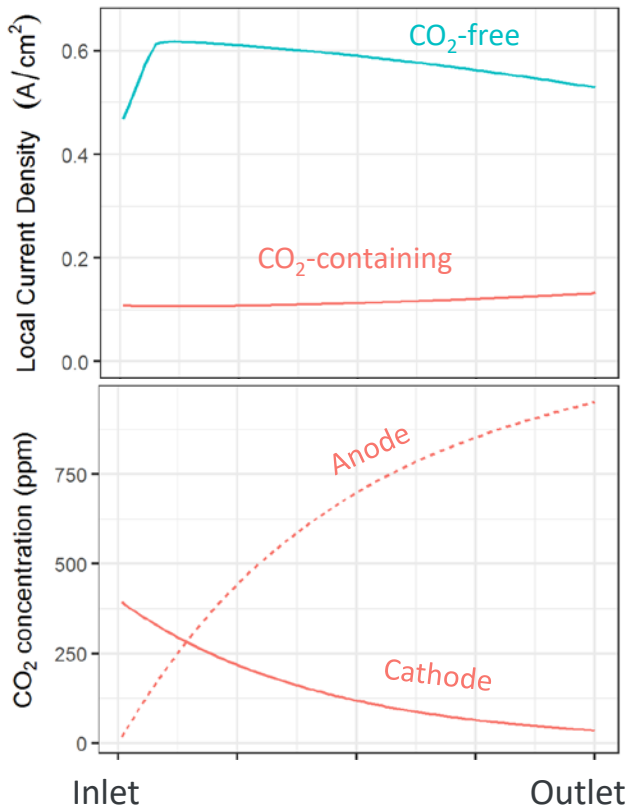

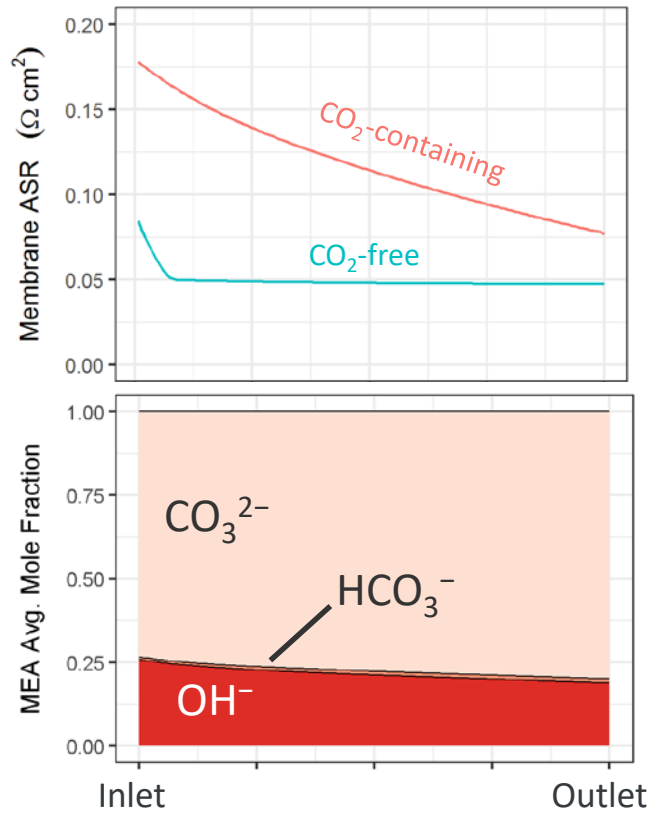

- NREL demonstrated rapid reduction in conductivity when OH-form PFAEM exposed to air containing CO_2
  - Model uses high CO_2 absorption and desorption rates suggested by NREL expt.
- Down the channel, average CO_3^{2-} concentration in MEA increases slightly, but ASR decreases overall due to hydration effects.

Models use air cathode (+400 ppm CO_2), H_2 anode, 80% RH.
Cell voltage of 0.7 V, temperature 60 °C.

Accomplishments and Progress

Responses to Previous Year (2017 AMR) Reviewer's Comments

- Reviewer Comment: Cost has been ignored. Analogies, or at least attempts to compare and rationalize cost improvements, should be presented. Cost mock-up through film formation should be taken into account.
- Response: While the primary focus of this work has not been cost, the use of perfluorinated ionomers tends to have much higher cost than that of hydrocarbon ionomers. The premise of using the PFSA precursor in these tests was to focus on an established larger scale production as a platform for evaluating the technology, specifically the potential benefits as a durable, high conductivity, high water transport membrane or as an ionomer. While advantages in water transport and conductivity have been demonstrated, durability and electrode performance are still lacking. These factors, plus the in flux of hydrocarbon polymers with high performance may limit our pursuit of these materials to the remaining time of this project. We have already pivoted toward a higher focus on the electrodes for the impact that they have shown on device performance.

- Reviewer Comment: The project still utilizes PGM catalysts, while the raison d'etre for alkaline fuel cell work is the potential for PGM-free fuel cells.
- Response: We have done this because this has been a polymer development project, but have followed work of others showing very positive strides in this direction and have included some preliminary work on backup slide 30. This area is of high interest but would merit another project of similar scale.

- Reviewer Comment: The only deficit: had a fuel cell fluoropolymer chemist(s) been involved, the compositional design/progression of the tether could have been identified immediately, and unnecessary work would have been eliminated.
- Response: Our team has world class chemists, and some of the best fluoropolymer chemists through our interactions with 3M that is highly active in the project. While significant experience in this area has greatly aided the project, one of the biggest surprises has been some of the difficulties associated with solubility and reactivity of the approaches employed. One of the easiest areas to overlook was the significant synthetic challenges to perform the select chemistries employed on the polymers used. While we respect the reviewers comment, we think this is a greater reflection of the difficulties of our chosen routes and perhaps limitations or mistakes made in the literature when employing similar approaches rather than a lack of involvement or skill on our team's part.

Collaborations

Institutions	Role
National Renewable Energy Laboratory (NREL): Bryan Pivovar (PI), Andrew Park, Derek Strasser, Chris Antunes, Ami Neyerlin, K.C. Neyerlin, Shaun Alia, Hai Long, Zbyslaw Owczarczyk	**Prime; Oversees the project, PF AEM synthesis and stability characterization, MEA optimization, and fuel-cell testing**
Lawrence Berkeley National Laboratory (LBNL) Adam Weber, Huai-Suen Shiau, Mike Gerhardt	**Sub; Fuel cell modeling including water transport and carbonate issues**
Oak Ridge National Laboratory/University of Tennessee (ORNL/UT): Tom Zawodzinski, Ramez Elgammel, Zhijiang Tang	**Sub; Polymer characterization (water self-diffusion coefficient and electro-osmotic drag)**
Colorado School of Mines (CSM): Andy Herring, Ashutosh Divekar	**Sub; Membranes characterization (water uptake, conductivity, structure).**
3M (3M): Mike Yandrasits, Krzysztof Lewinski, Steve Hamrock	**In-kind; Consulting on novel chemistries; preparation of solutions and dispersions; membrane fabrication.**

University of South Carolina: Bill Mustain, Travis Omasta; advanced electrode/GDE
University of Surrey: John Varcoe, ETFE membrane and ionomer
Many others whom have used/studied Gen 2 PF AEM

Remaining Challenges and Barriers/Future Work

- Polymer Synthesis:
  - Increased stability
  - Focus on increased stability cations and Gen 3 polymer development
- Characterization:
  - Membrane and electrode properties (including stability)
  - Continuing studies on stability, structure, water transport, carbonate
- AMFC implementation, Modeling, and Diagnostics:
  - Improved performance and durability in cells, closing the gap between experimental and modeling efforts
  - Electrode optimization and diagnostic studies focused on further characterization of electrodes and elucidating performance loss and durability.
    - In-situ: limiting current, RH studies, CV, segmented cell, air performance, and impedance
    - Ex-situ: microscopic, electrochemical, and spectroscopic analysis
  - Continued integration of modeling efforts with cell testing
    - Further elucidation of the impact of operating conditions (T, RH, current density, CO_2 concentration)

Any proposed future work is subject to change based on funding levels

Technology Transfer Activities

- Highly focused on engagement of project partner 3M, leaders in the areas of PF membranes and materials. Through technical advances, the materials being developed could lead to commercial products.

- Involvement with multiple projects leveraging core membrane technology being developed (Incubator projects with Giner, Inc (Reversible Fuel Cells) and University of Delaware (Redox Flow Battery) and SBIR Project with pHMatter, Inc (Reversible Fuel Cells). SBV project with Midwest Energy Group. As well as supply of polymer materials to ~20 entities.

- Co-led AMFC Workshop, May 1, 2016 involving over 50 participants from academia, industry and government. Contributed to/Co-led Workshop Report. Participation with ARPA E IONICS program.

2016 AMFC Workshop Report
http://energy.gov/eere/fuelcells/downloads/2016-alkaline-membrane-fuel-cell-workshop

Summary

- **Relevance:** AMFCs offer promise for improved performance and decreased cost.
- **Approach:** Synthesize, characterize and optimize membrane and fuel cell performance and durability using modeling and advanced diagnostic/ characterization techniques.
- **Accomplishments and Progress**: This year saw significant advances in technology by quantify the degradation of Gen 2 and Gen 3 small molecule analogues. The focus on electrodes has allowed us to elucidate the importance of water management on performance, particularly the role of back diffusion of water. Durability improvements due to ETFE electrodes were found to be significant. Model development provided insight into the role of water and carbon dioxide allowing the performance potential and limitations of AMFCs to be better understood.
- **Collaborations:** We have a diverse team of researchers including 3 national labs, 2 universities, and 1 industry participant that are leaders in the relevant fields of PF polymer electrolytes (3M), characterization (ORNL/UTK, CSM), and modeling (LBNL).
- **Proposed Future Research:** Focused on further improving polymer properties, and improving fuel cell performance and durability with an emphasis on electrode issues.

Technical Backup Slides

Accomplishments and Progress

Small Molecule Gen 3 durability

Gen 3 PF AEM Polymer Target

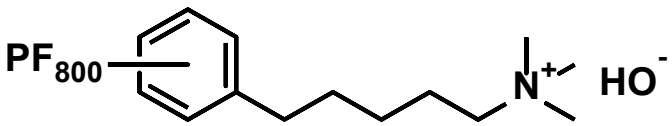

- *Para* substitution is projected to be one of two major products (*meta* position being the other) in the modified polymer
- *Ortho* substitution is presumed to be minor due to steric hindrance with the polymer
- Durability is presumed to be highest at the *meta* position
- Gen 3 small molecule degradation
  - After heating at 140 °C for 24 hrs in 2:1 methanol-d_3:KOH 1H NMR indicated the QA cation degraded 64%

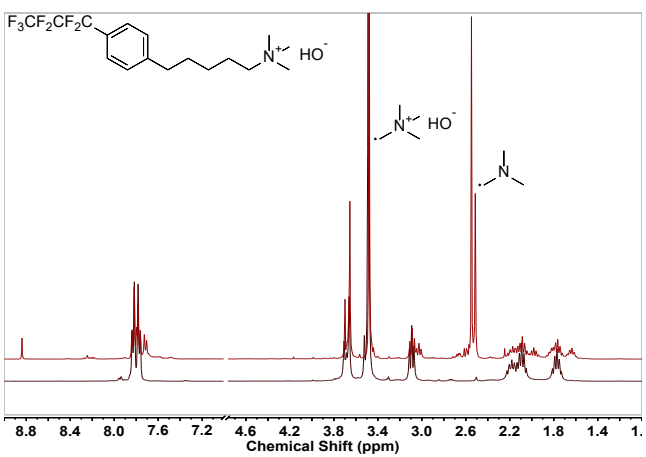

- ^{19}F NMR employed to detect changes in fluorine environments
  - Spectra indicates three fluorine signals with integration values proportional to the number of fluorine atoms in each environment.
  - Post degradation the integration values indicated the same proportionality and the addition of a peak for fluoride

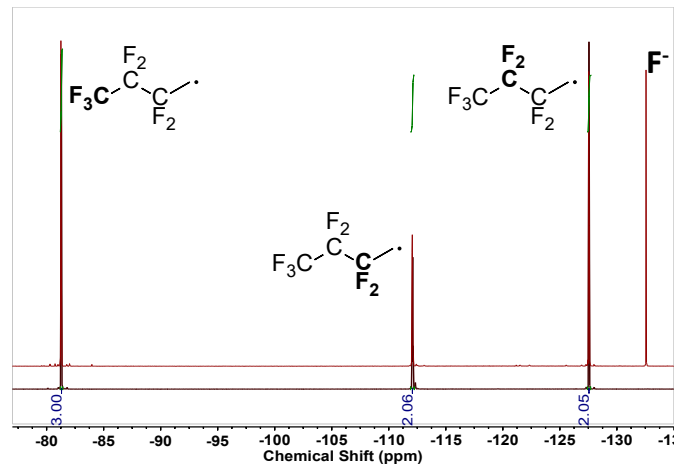

- Gen 3 small molecule conclusions
  - QA cation stability is comparable to the sulfonamide
  - Gen 3 tether linkage indicates enhanced stability

Accomplishments and Progress

Change in Morphology due to CO2 Uptake

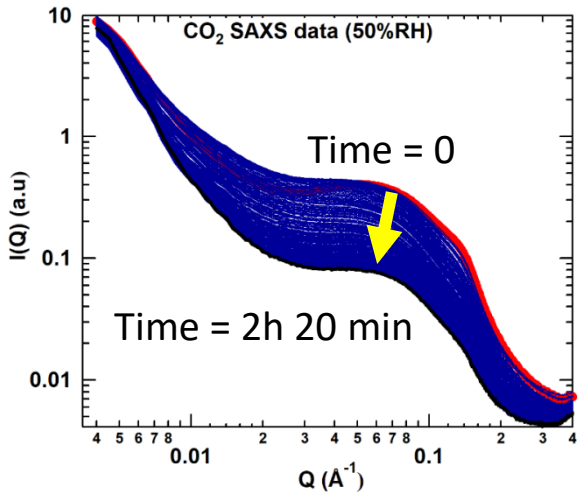

Transient SAXS data of OH^- PFAEM exposed to air at 60°C,**50%RH**[1]

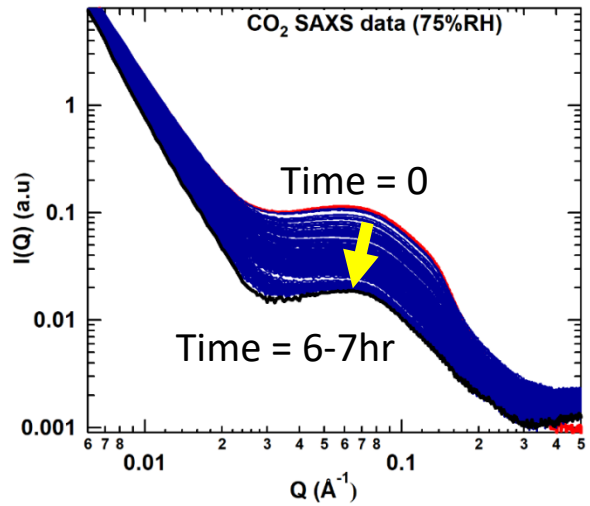

Transient SAXS data of OH^- PFAEM exposed to air at 60°C,**75%RH**

Intensity and d-spacing of the spectrum drops when exposed to air indicating CO_2 reaction and loss of water

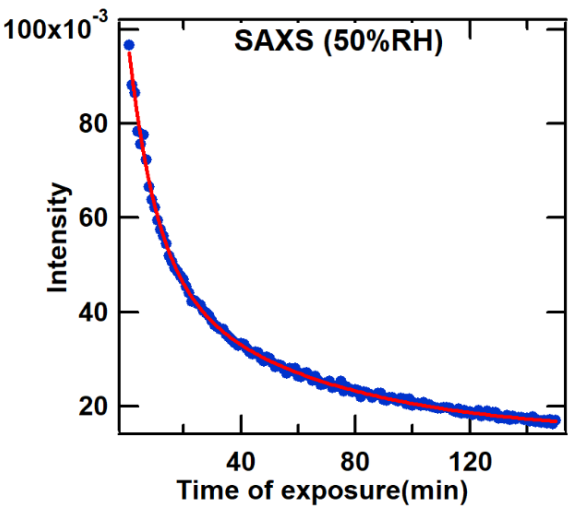

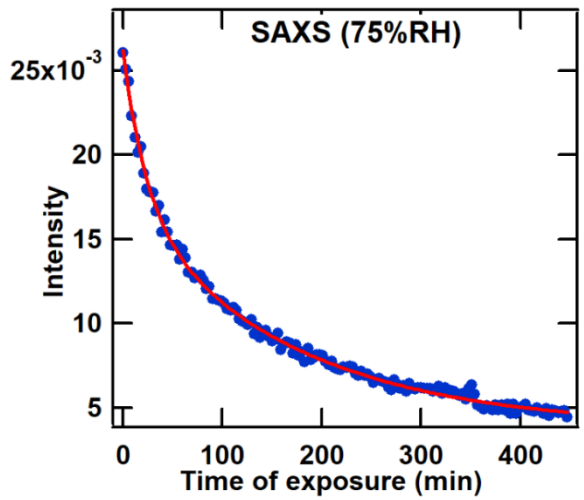

- Drop in intensity follows a double exponential decay behavior.
- The time of equilibration is faster at lower %RH

[1] Divekar et.al,ECS Transactions,80,8(2017)

Accomplishments and Progress

MEA Diagnostics for ETFE GDE/PFAEM CCM Asymmetric MEAs

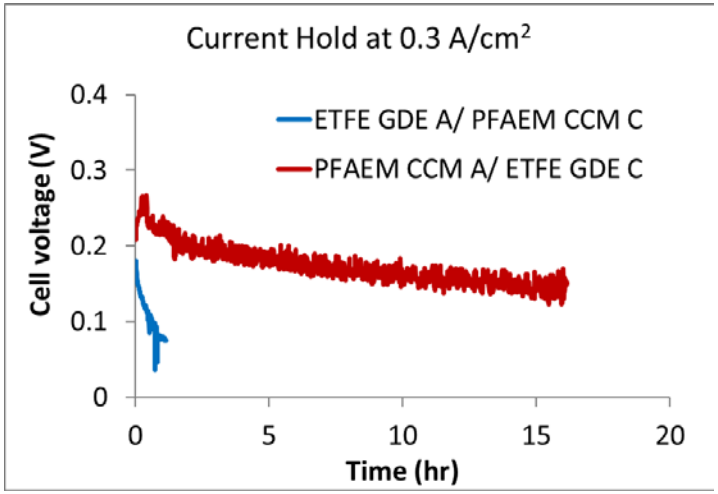

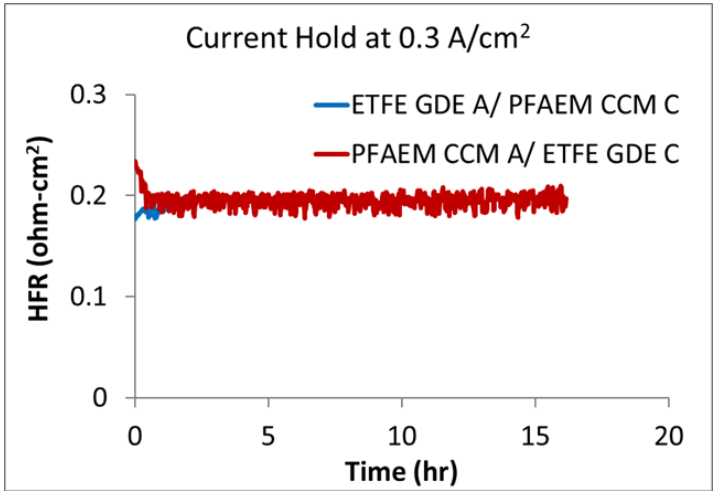

Membrane Electrode Assembly
Cell Temp: 60°C
Membrane: Gen 2 PFAEM (32 µm)
Ionomer: Varcoe AEI or PFAEM
GDL: Toray H-060 or SGLBC29
Gases: H_2 var°C, O_2 var°C, 1.0 slpm
Active Area: 5 cm²
Pressure: 121 kPa abs
Anode: 0.5 mg/cm² Pt/HSC
Cathode: 0.5 mg/cm² Pt/HSC
Relative Humidity: 80% RH

ETFE GDE A/ PFAEM CCM C
Pristine MEA 0hr

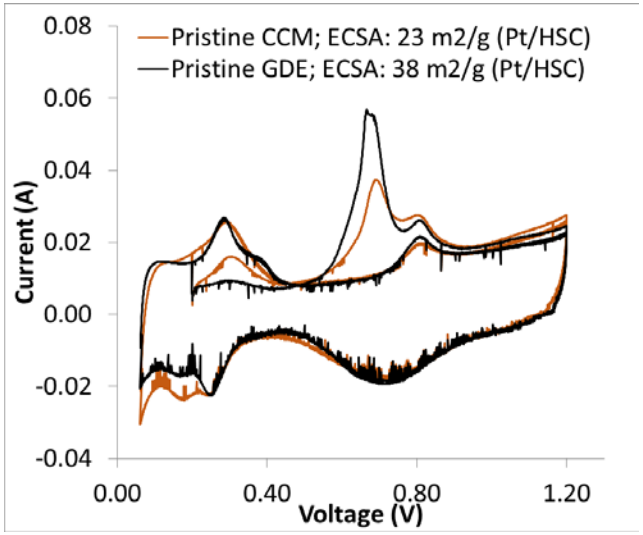

ETFE GDE A/ PFAEM CCM C
1hr

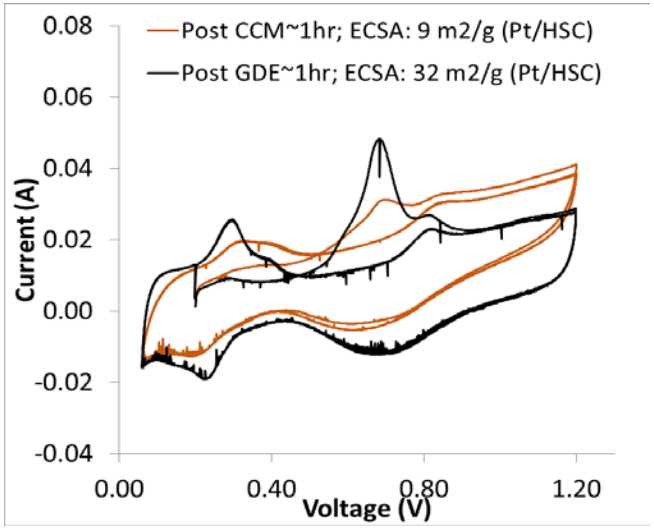

PFAEM CCM A/ ETFE GDE C
16hr

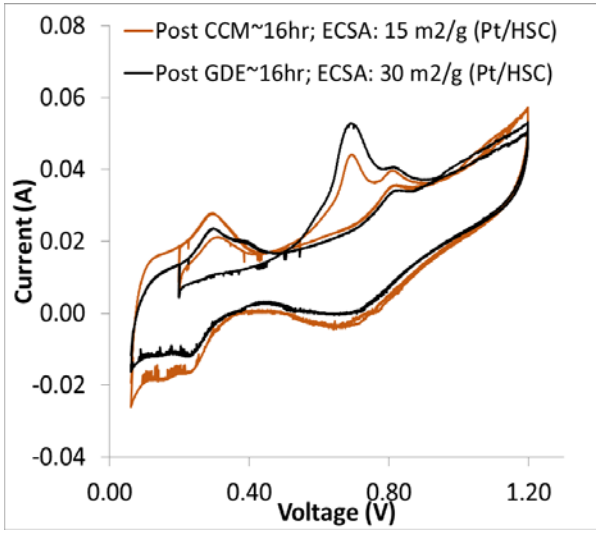

Surface area decreases after durability tests

Accomplishments and Progress

ETFE GDE MEAs

ETFE optimized electrodes yield 1.4 W/cm^2

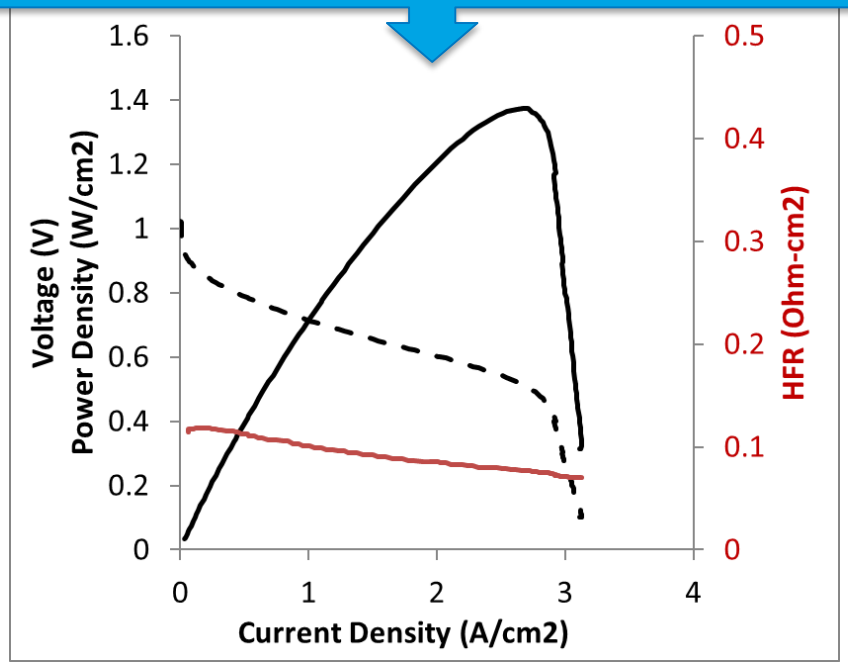

H_2N_2 Impedance, 60°C

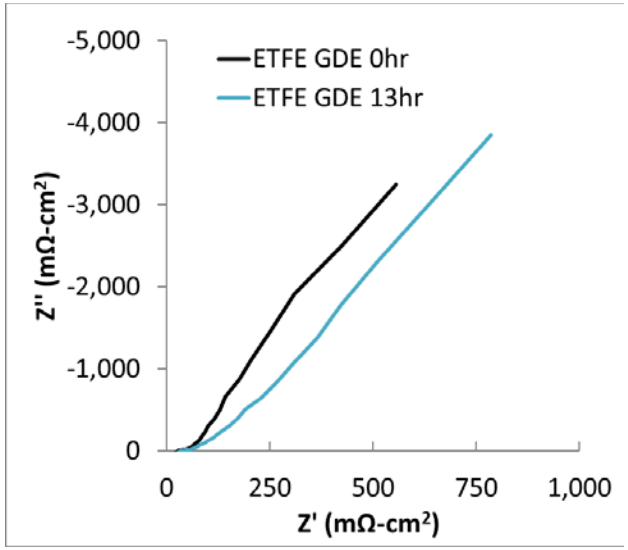

- Highest performance obtained with PF AEM Gen 2 membrane is 1.4 W/cm^2.
- Impedance showing slight change after 13 hour test.

Accomplishments and Progress

MEA Performance: PFAEM Solid Ionomer GDE vs PFAEM Dispersion Ionomer CCM

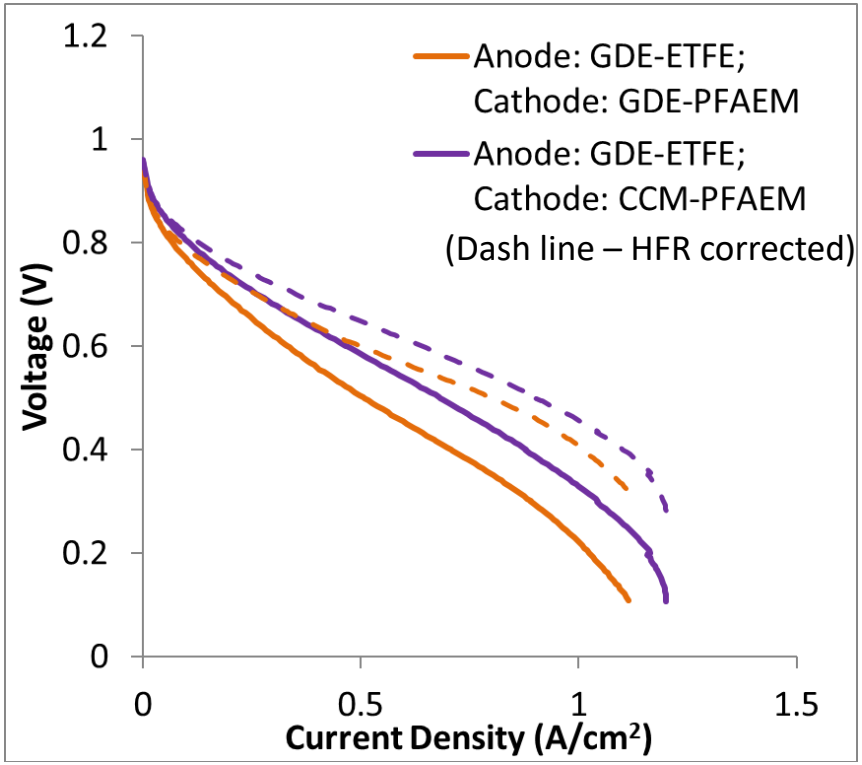

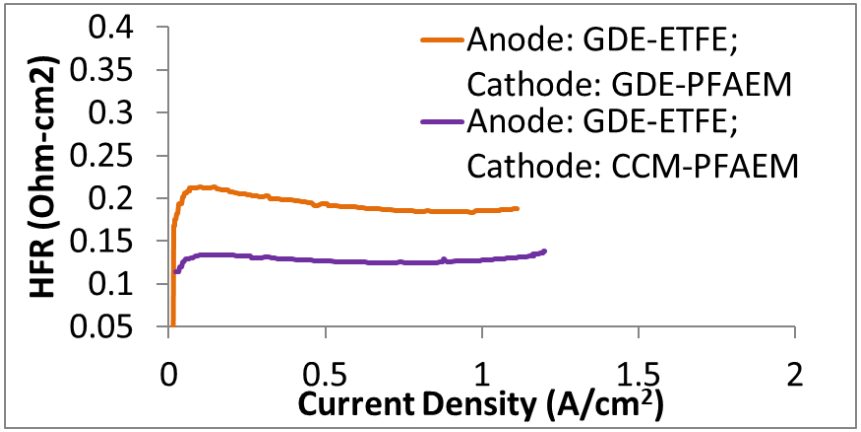

Membrane Electrode Assembly

- Cell Temp: 60°C
- Membrane: Gen 2 PFAEM (33 µm)
- GDL: Toray H-060
- Gases: H_2 , O_2 1.0 slpm
- Active Area: 5 cm^2
- Pressure: 121 kPa abs

- Anode is controlled with Mustain/Varcoe ETFE GDEs, 0.6 Ptmg/cm2 Pt/HSC.

- Cathode:
- C: 0.25 mg/cm^2 Pt/Vu, PFAEM dispersion ionomer (CCM), 100RH
- C: 0.25 mg/cm^2 Pt/Vu, PFAEM solid ionomer (GDE), 90RH

- PFAEM GDE cathode has almost twice higher HFR than PFAEM CCM cathode

Accomplishments and Progress

Silver Cathode GDE Performance

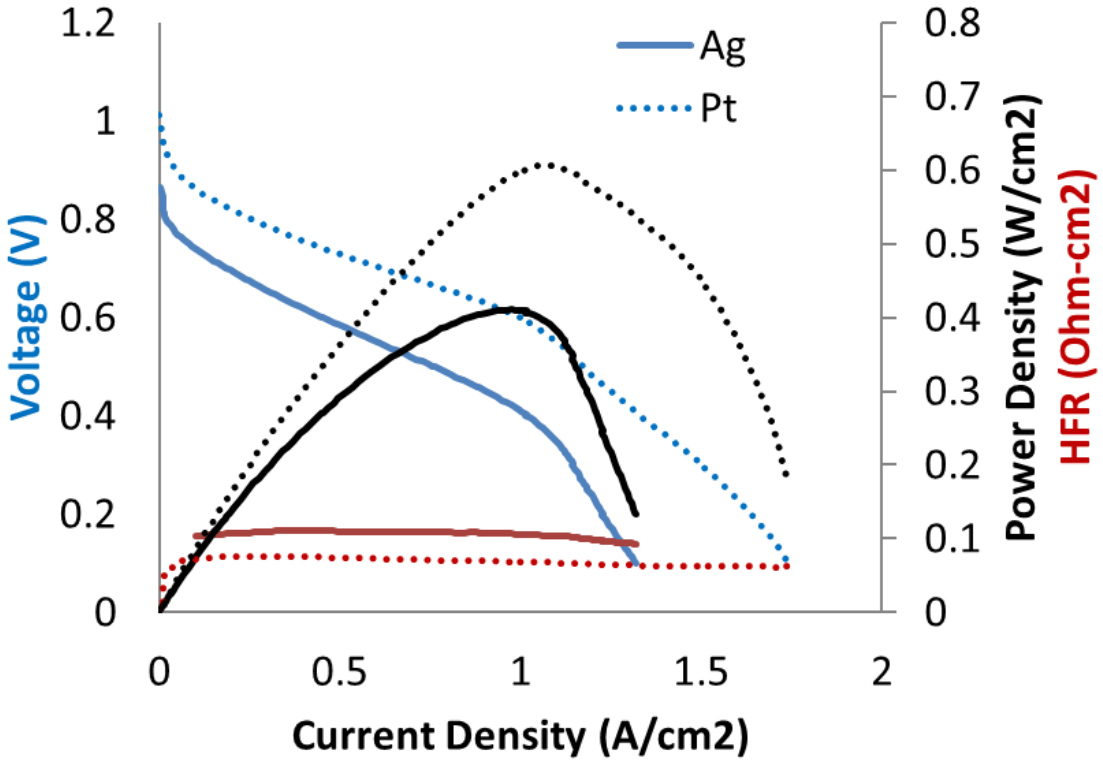

Membrane Electrode Assembly

- Cell Temp: 60°C
- Membrane: Gen 2 PFAEM (29 µm)
- Ionomer: Varcoe AEI
- GDL: Toray H-060
- Gases: H_2 50°C, O_2 53°C, 1.0 slpm
- Active Area: 5 cm^2
- Pressure: 121 kPa abs
- Anode: 0.5 mg/cm^2 Pt/Vu
- Cathode: ~1.0 mg/cm^2 Ag/Vu

- Ag cathode yields reasonable performance, but with low OCV

Accomplishments and Progress

Coupling Modeling and Experimental Results

Experiment

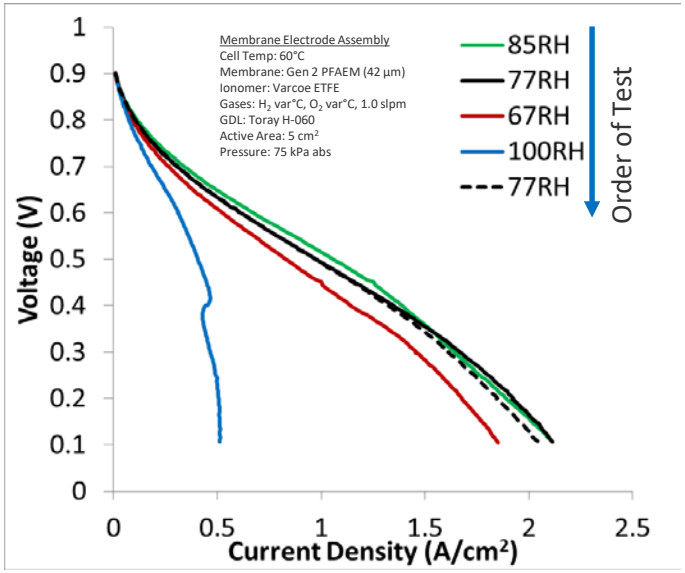

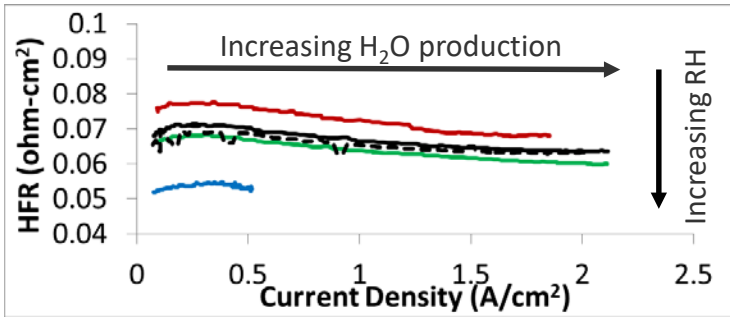

Model

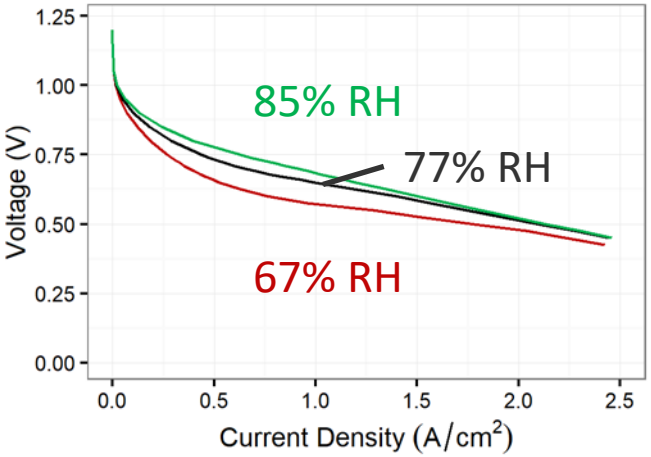

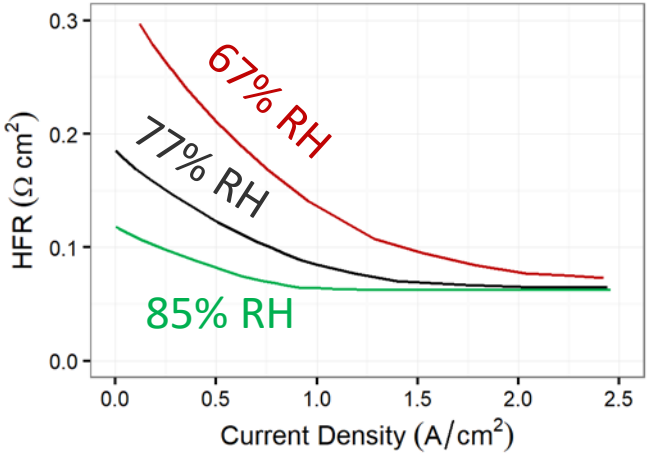

- Similar trend to experiment for polarization curve performance
- HFR decreases at high current density as the membrane hydrates
- Model currently seems to overestimate HFR increase at low RH

Accomplishments and Progress

Modeling Down-the-channel Effects in AEM Fuel Cells

Iterate 2-D model along channel

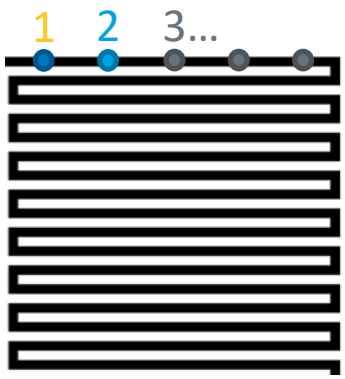

Model used O_2 cathode, H_2 anode, 60% RH. 0.1 std L/min flow rate. Cell voltage of 0.7 V, temperature 60 °C.

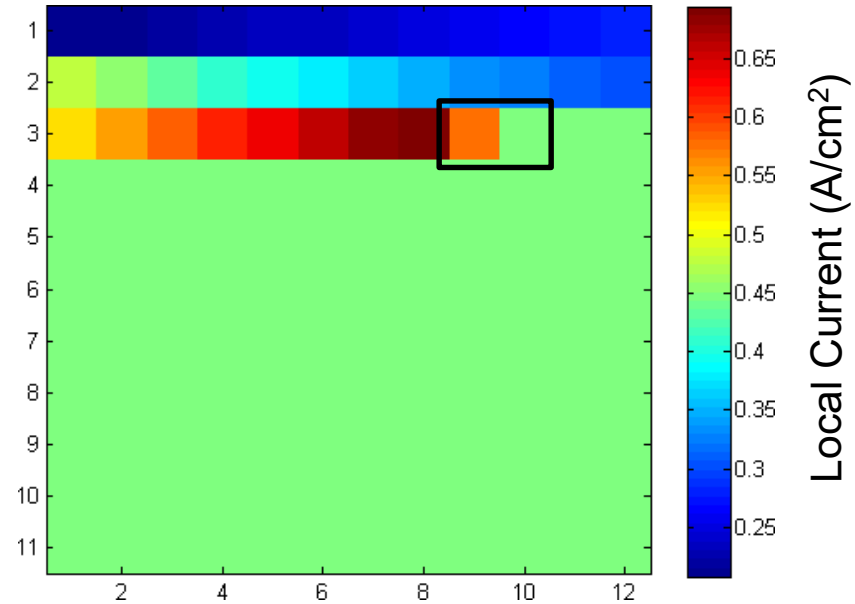

- Iterate 2-D model down the channel for cell-scale impacts
- NREL experiments demonstrated flooding on anode *and* cathode depending on operating conditions. Updated water transport modeling in membrane to match observations.
- Cell self-hydrates down the channel, leading to reduced membrane resistance
- High flow rates avoid flooding but reduce membrane water content, leading to reduced conductivity

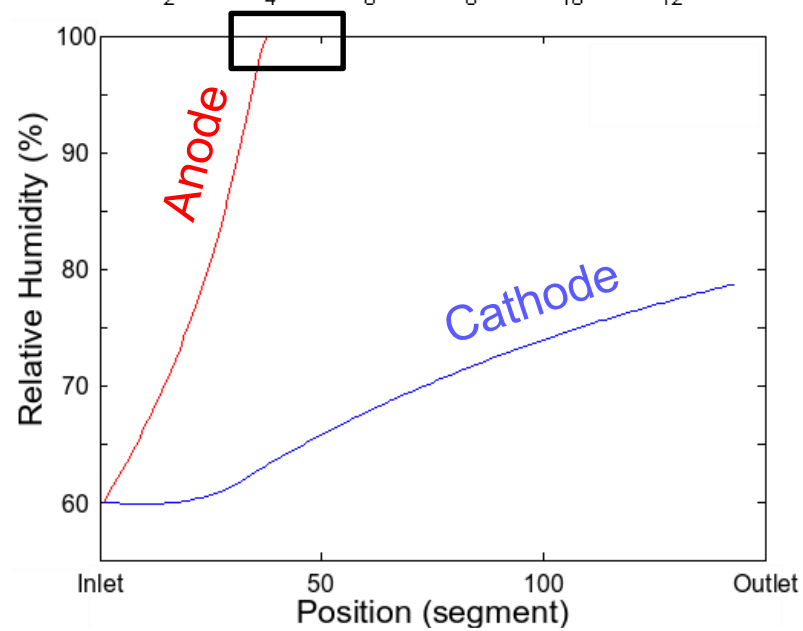

Accomplishments and Progress

Modeling Down-the-channel Effects in AEM Fuel Cells

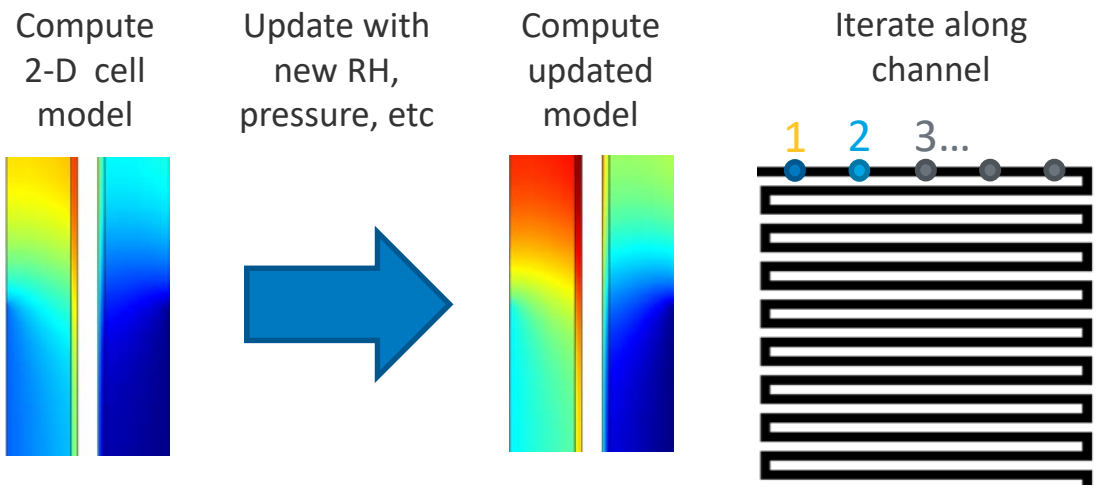

- Iterate 2-D model down the channel for cell-scale impacts
- NREL experiments demonstrated flooding on anode *and* cathode depending on operating conditions. Updated water transport modeling in membrane to match observations.
- Cell self-hydrates down the channel, leading to reduced membrane resistance
- High flow rates avoid flooding but reduce membrane water content, leading to reduced conductivity

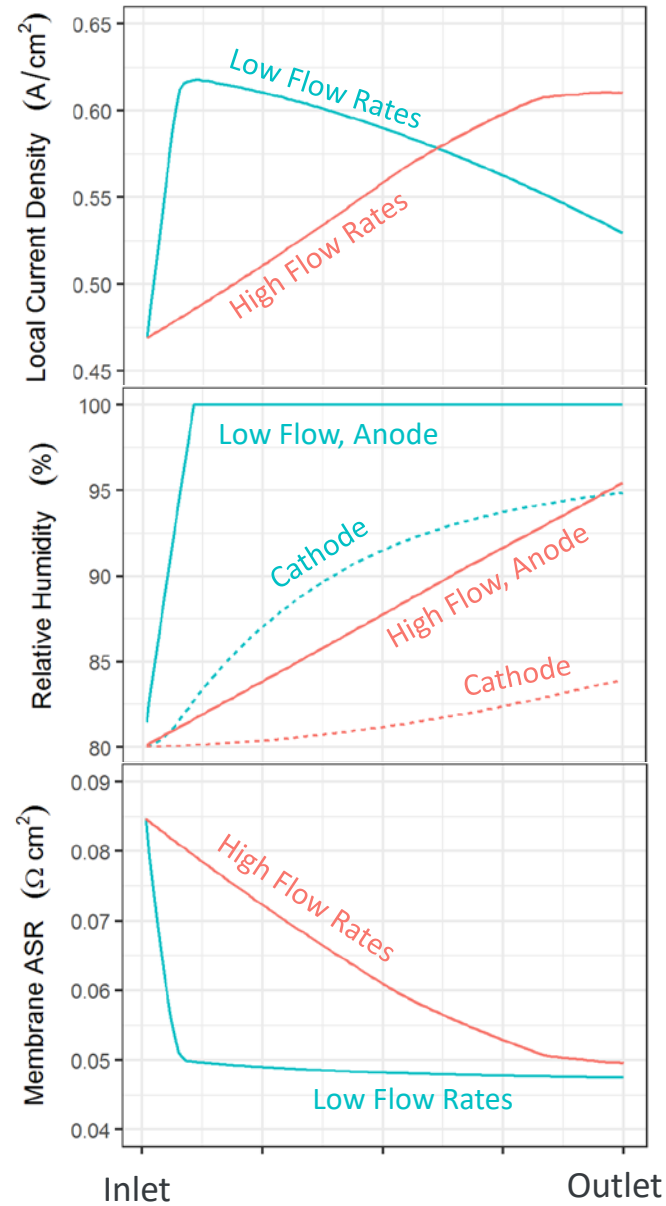

Models use air cathode, H_2 anode, 80% RH.
Cell voltage of 0.7 V, temperature 60 °C.