

Spirocyclic Anion Exchange Membranes for improved Performance and Durability

Bryan Pivovar
National Renewable Energy Laboratory
May 1, 2019

DOE Hydrogen and Fuel Cells Program
2018 Annual Merit Review and Peer Evaluation Meeting

Project ID: FC178

Overview

Timeline and Budget

- Project start date: 01/01/18
- Project end date: 09/30/19
- Total project budget: \$300k
 - Total recipient share: \$0K
 - Total federal share: \$300K
 - Total DOE funds spent*: \$170K

Barriers

- Cost
- Performance
- Durability

Partners

- NREL only project
- Multiple interactions across AEM space, leverage significant effort at NREL on related projects

* As of 3/31/19

Relevance/Impact

DOE (Preliminary) Milestones for AMFCs*

- **Q2, 2017:** Develop anion-exchange membranes with an area specific resistance ≤ 0.1 ohm cm^2 , maintained for 500 hours during testing at 600 mA/cm^2 at $T > 60$ °C.
- **Q4, 2017:** Demonstrate alkaline membrane fuel cell peak power performance > 600 mW/cm^2 on H_2/O_2 (maximum pressure of 1.5 atma) in MEA with a total loading of ≤ 0.125 $\text{mg}_{\text{PGM}}/\text{cm}^2$.
- **Q2, 2019:** Demonstrate alkaline membrane fuel cell initial performance of 0.6 V at 600 mA/cm^2 on H_2/air (maximum pressure of 1.5 atma) in MEA a total loading of < 0.1 $\text{mg}_{\text{PGM}}/\text{cm}^2$, and less than 10% voltage degradation over 2,000 hour hold test at 600 mA/cm^2 at $T > 60$ °C. Cell may be reconditioned during test to remove recoverable performance losses.
- **Q2, 2020:** Develop non-PGM catalysts demonstrating alkaline membrane fuel cell peak power performance > 600 mW/cm^2 under hydrogen/air (maximum pressure of 1.5 atma) in PGM-free MEA.

Impact/Team Project Goals

Synthesize novel spirocyclic ionomers to membranes and ionomers in Alkaline Membrane Fuel Cells (AMFCs).





Optimize performance to meet DOE AMFC targets

*taken from D. Papageorgopoulos presentation AMFC Workshop, Phoenix, AZ, April 1, 2016

Relevance/Objectives

Alkaline exchange membranes continue to be challenged with cation degradation at high temperature and pH conditions

- State of the art trimethyl ammonium cations exhibit limited durability under fuel cell operating condition
- Research has indicated that cations with a spirocyclic structure have improved durability
 - Higher activation energy for both Hoffman elimination and substitution degradation mechanisms
- Incorporation of spirocyclic ammonium cations into alkaline exchange membranes to improve durability


Quaternary Ammonium	Abbreviation	Half-life [hr]
	ASU	110
	DMP	87.3
	DMPy	37.1
	ASN	28.4
	BTMA	4.18

Marino, M. G.; Kreuer, K. D., Alkaline Stability of Quaternary Ammonium Cations for Alkaline Fuel Cell Membranes and Ionic Liquids. *ChemSusChem* **2015**, 8 (3), 513-523.

Approach

Synthesis

- Diallyl monomers undergo ring closing radical polymerization
- Polymerization of diallylpiperidinium chloride produces repeat units that of an ASU/ASN hybrid structure

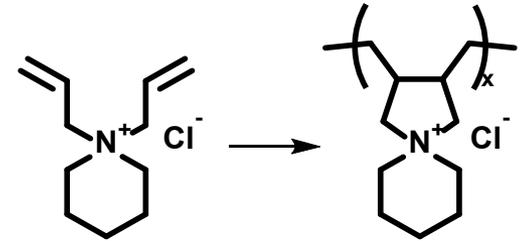

Polymer & copolymer characterization

- Structure
- IEC
- Conductivity

Accelerated aging

- Polymer & AEM durability
- Degradation pathways and rates

MEA fabrication and characterization

- Fuel cell performance
- Long term durability

Leverage NREs in-house expertise and MEA testing equipment

- Previous work generated multiblock copolymers of polydiallylpiperidinium segments in a high performance polysulfone backbone
- Current synthesis focuses on scaling synthetic procedure for production of larger (>20 g) batches
 - Provide ample material for complete MEA characterization and durability studies



Approach - Milestones

	Milestone Name/Description	End Date	Type
Q1	In alignment with DOE 2019, Q2 AEM target, Demonstrate AEM fuel cell initial performance of 0.6 V at 600 mA/cm ² on H ₂ /air (maximum pressure of 1.5 atma) in MEA, and less than 10% voltage degradation over 1,000 hour hold test at 600 mA/cm ² at T>60 oC.	12/31/2018	Milestone - Met at 500 hours
Q2	Develop ionomer solutions based on spirocyclic AEM polymers.	3/31/2019	Progress Measure - Met
Q3	Quantify fuel cell performance of at least 3 different MEAs using spirocyclic ionomers and compare to baseline AMFC performance.	6/30/2019	Progress Measure – On track
Q4	Optimize fuel cell performance based on a fully spirocyclic system where cathode and anode ionomer and membrane are spirocyclic based.	9/30/2019	Progress Measure – On track

AEM FC durability	In alignment with DOE 2019, Q2 AEM target, Demonstrate AEM fuel cell initial performance of 0.6 V at 600 mA/cm ² on H ₂ /air (maximum pressure of 1.5 atma) in MEA, and less than 10% voltage degradation over 1,000 hour hold test at 600 mA/cm ² at T>60 °C.	12/31/2018 – conditionally met

Accomplishments and Progress

Synthesis/Characterization

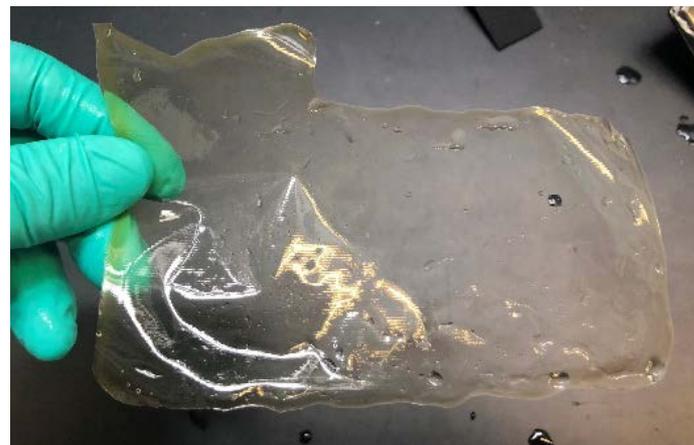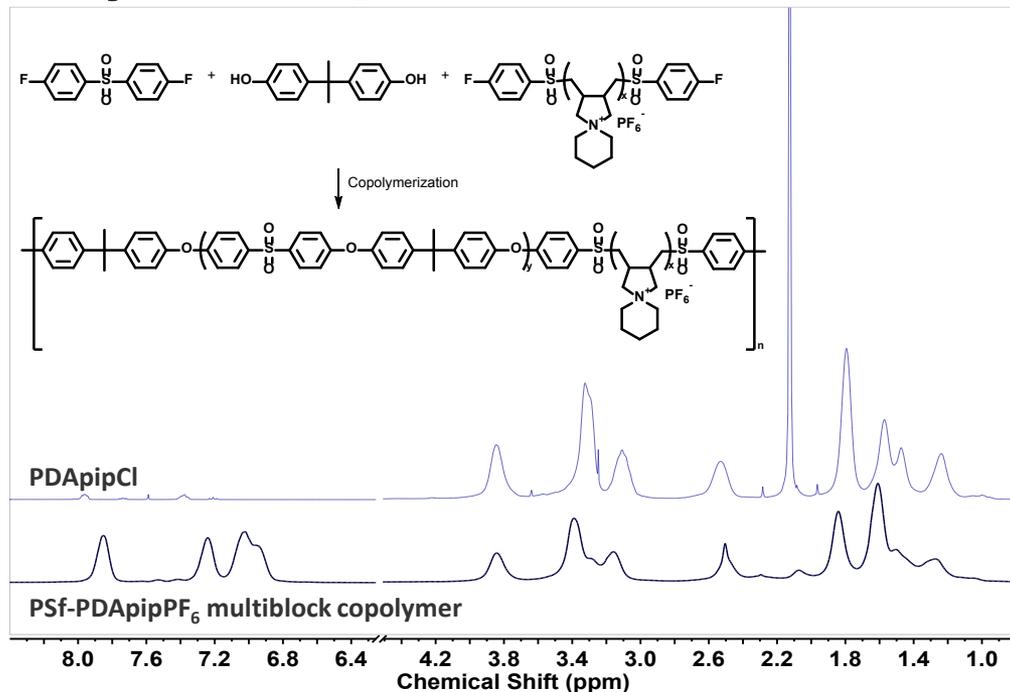

Polymer	IEC (measured) [mmol/g]	Cl ⁻ Conductivity @RT in Water [mS/cm]	Water Uptake (%)	Peak Power Density (W/cm ²)
SpiroCyclic AEM	1.3	14.0	22	0.85
SpiroCyclic AEM	1.5	13.8	42	1.22
SpiroCyclic AEM	1.7	16.1	80	1.48
Gen 2 PF AEM	0.9	13.4	18	1.10

Accomplishments and Progress

Durability

Before and (where possible) after Degradation

- Teflon-lined Parr reactors (20 mL)
- Dry samples of ~100 mg in Cl⁻ form
- 1 M KOH (10 mL)
- 80 °C in oven for 1000 h
- Room Temperature, Liquid H₂O, Cl⁻ Conductivity and IEC tested before/after



Gen 2



- More opaque color
- Still soft/flexible
- Broken/tears easily
- IEC ↓ 2.8%
- Conductivity ↓ 21%

PSF-1.7



- Darker orange color
- Hard/inflexible
- Breaks easily
- IEC ↓ 50%
- Conductivity ↓ 4%

PSF-1.5



- Orange/brown color
- Hard/inflexible
- Broken/tears easily
- IEC ↓ 66%
- Conductivity ↓ 60%


Accomplishments and Progress

Spirocyclic AEM in-situ Fuel Cell Performance

Membrane Electrode Assembly

- Cell Temp: 60°C
- Active Area: 5 cm²
- Pressure: 121 kPa_{abs}
- Ionomer: Varcoe ETFE AEI ionomer
- GDL: Toray H-060
- Gases: H₂ var°C, O₂ var°C, 1.0 slpm
- Anode: 0.8 mg/cm² PtRu/Vu
- Cathode: 0.5 mg/cm² Pt/Vu

Membrane: Spirocyclic IEC 1.7 mmol/g (55 μm)

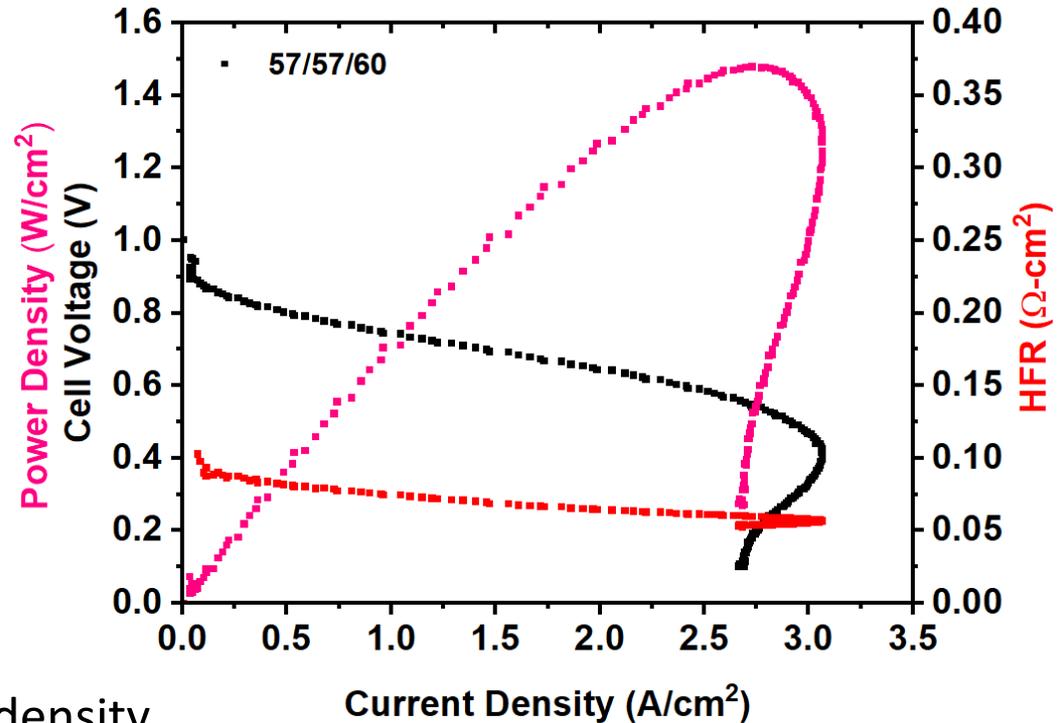


- ~ 1.48 W/cm² in peak power density
- ASR ~ 0.007 Ω (0.036 Ω-cm²)
- Close to state-of-the-art performance


Accomplishments and Progress

In-situ Fuel Cell Durability: Spirocyclic VS PF AEM


Durability 600mA/cm² hold, H₂/Air, 122 kPa_{abs}

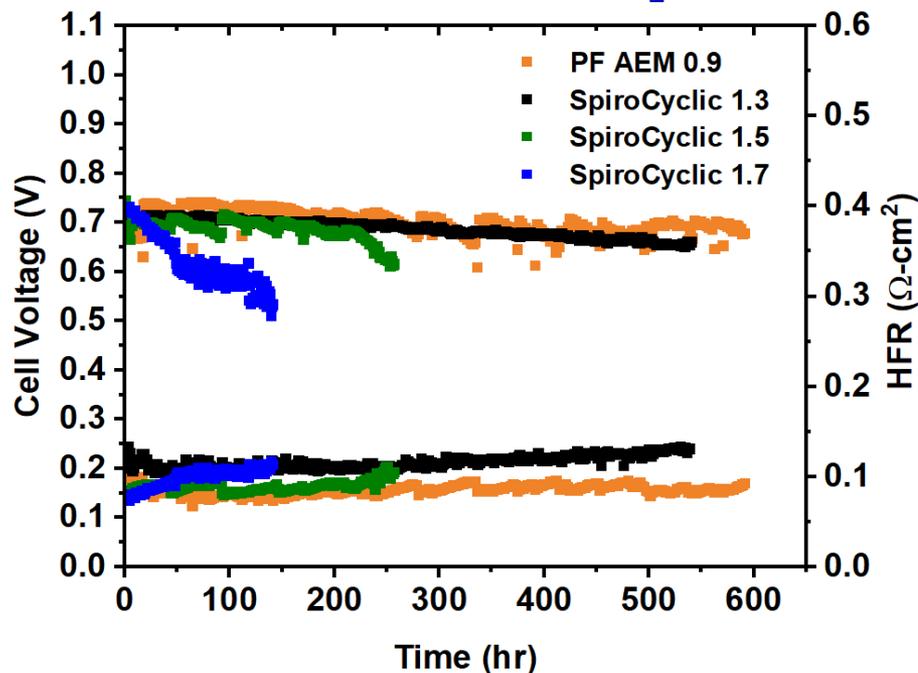

Spirocyclic

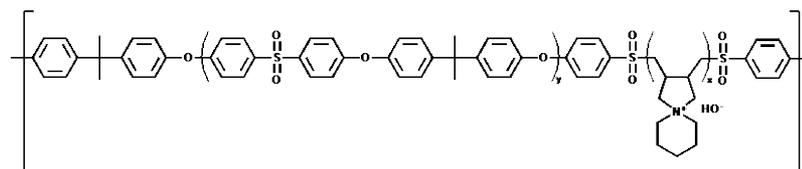

Gen 2 PF AEM

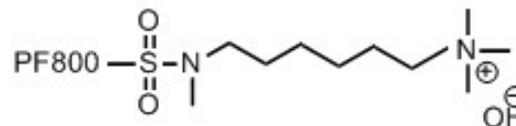


AEM	IEC (measured) [mmol/g]	Cl ⁻ Conductivity @RT in Water [mS/cm]	Water Uptake (%)	Peak Power Density (W/cm ²)
SpiroCyclic AEM	1.3	14.0	22	0.85
SpiroCyclic AEM	1.5	13.8	42	1.22
SpiroCyclic AEM	1.7	16.1	80	1.48
Gen 2 PF AEM	0.9	13.4	18	1.40

Accomplishments and Progress

Spirocyclic AEM in-situ Fuel Cell Durability

Durability 600mA/cm² hold

Membrane: Spirocyclic IEC 1.3 mmol/g (10 μm)

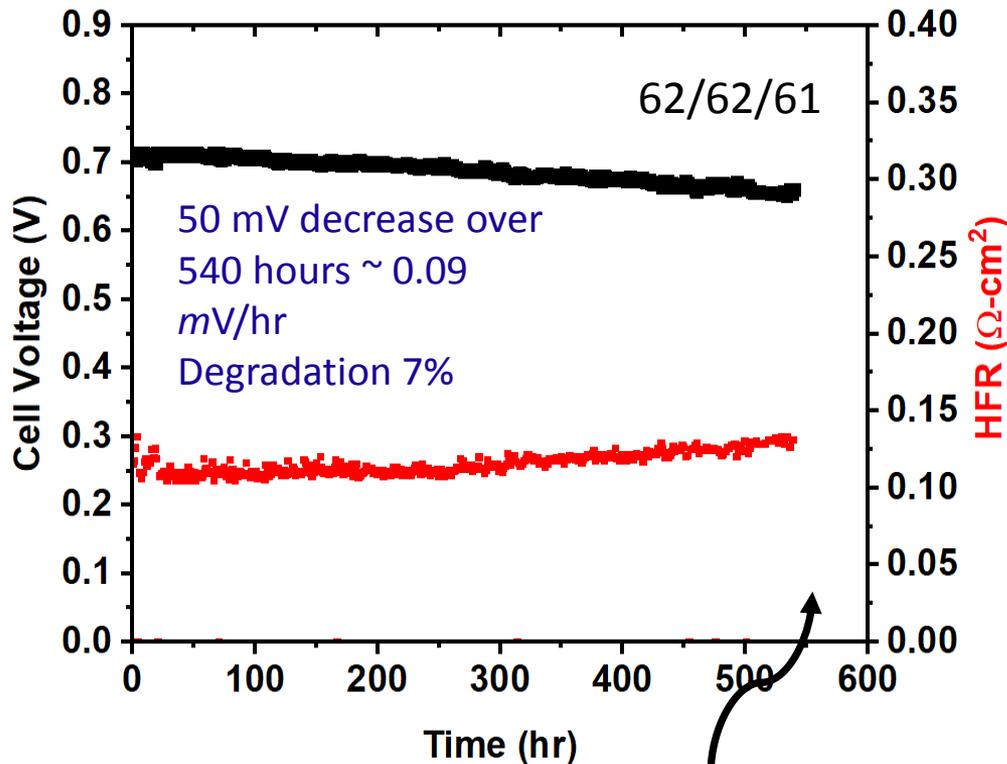


Cell shut down due to house
H₂ outage @ 540th hour

Membrane Electrode Assembly

- Cell Temp: 61°C
- Active Area: 5 cm²
- Pressure: 122 kPa_{abs}
- Ionomer: Varcoe ETFE AEI ionomer
- GDL: Toray H-060
- Durability: H₂ var°C, Air var°C, 1.0 slpm
- Anode: 0.8 mg/cm² PtRu/Vu
- Cathode: 0.5 mg/cm² Pt/Vu

Performance Stability

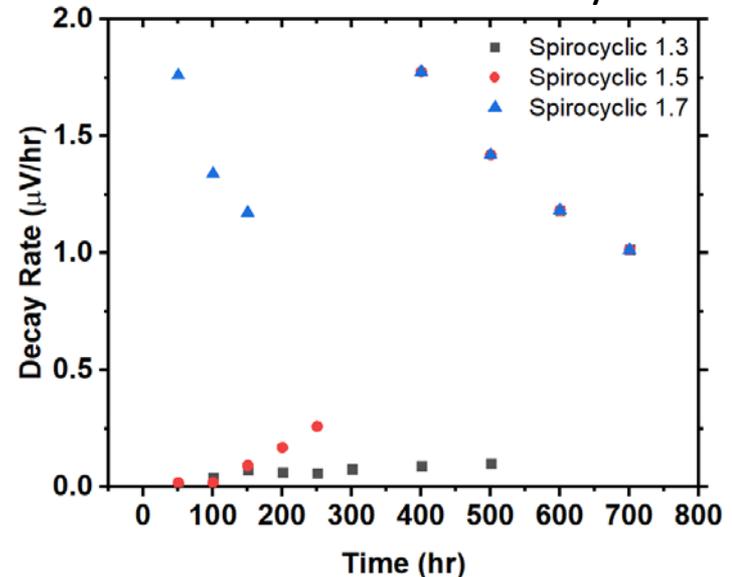

Accomplishments and Progress

PGM-free Cathode, Low loading Spirocyclic AEM MEA



Go/No-Go Decisions: **Completed.**

Demonstrate AEM fuel cell initial performance of 0.6 V at 600 mA/cm² on H₂/air (max. 1.5 atma) in MEA at T > 60°C with loading < 0.1 mg PGM/cm².

Membrane Electrode Assembly

- Cell Temp: 70°C
- Active Area: 5 cm²
- Pressure: 132 kPa_{abs}
- GDL: Toray H-060
- Anode: 0.1 mg/cm² PtRu/Vu
- Cathode: 2.2 mg/cm² Ag/Vu
- Membrane: Spirocyclic, 1.7mmol/g, (42μm)



600 mA/cm², H₂/air, 70°C

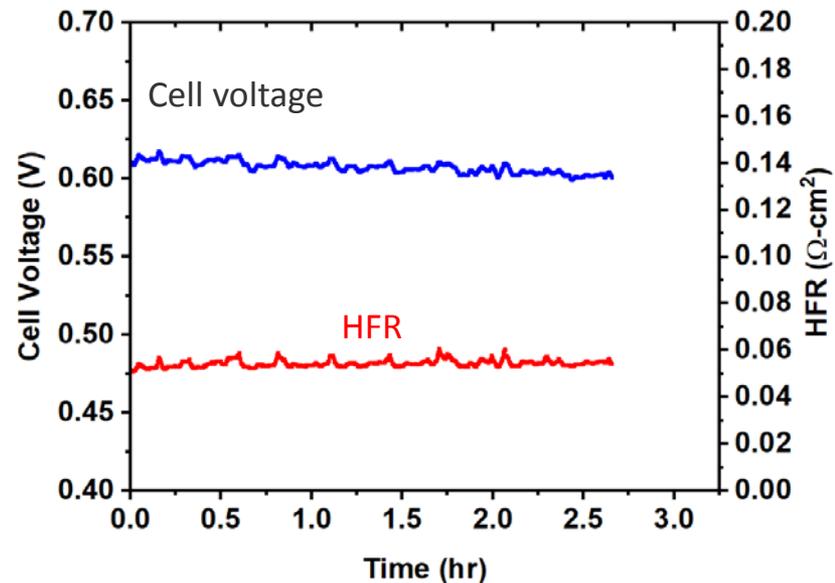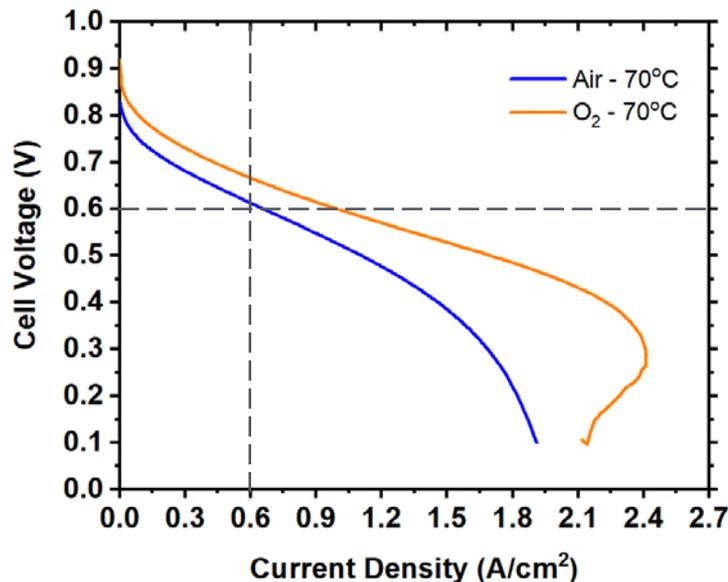

Accomplishments and Progress

Spirocyclic as Ionomer Incorporated into Electrodes

PF AEM Gen2 AEM, Spirocyclic ionomer

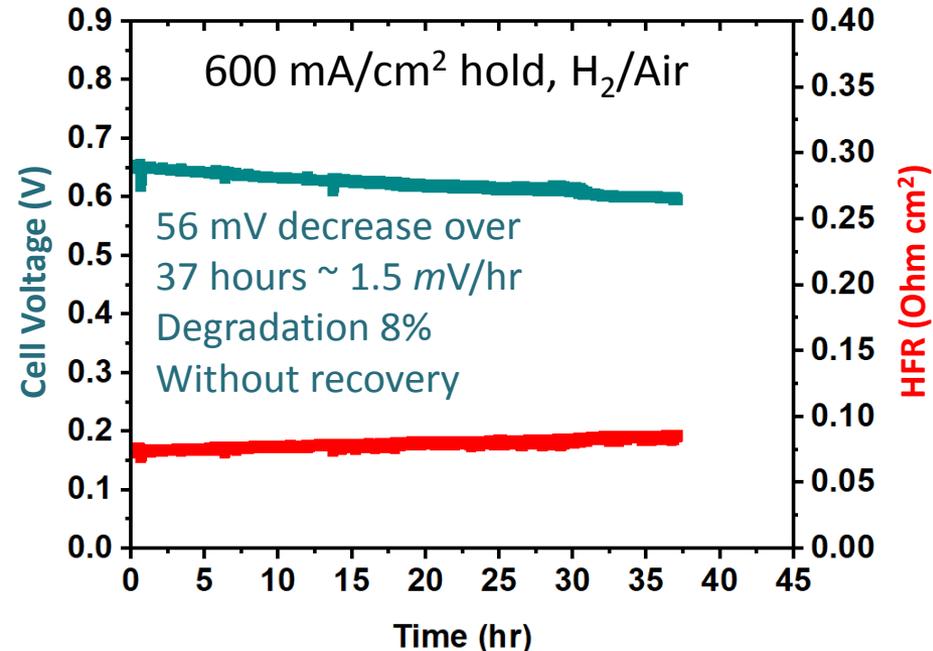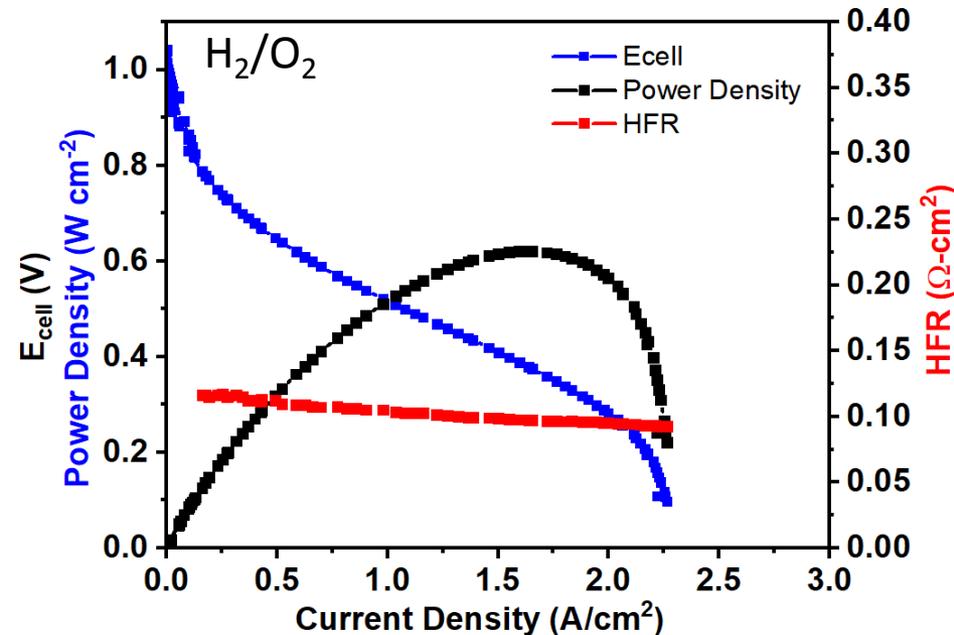

Membrane Electrode Assembly

- Cell Temp: 60°C
- Active Area: 5 cm²
- Pressure: 121 kPa_{abs}
- GDL: Toray H-060
- Anode: 0.5 mg/cm² Pt/Vu
- Cathode: 0.5 mg/cm² Pt/Vu
- Membrane: Gen 2 PF AEM (40μm)
- Dew points: 60/60/60

- Spirocyclic serves as a good ionomer with high performance and durability.
- At 37 hours of durability test, cell shut down occurred due to H₂ outage.

Collaborations and Coordinations

- NREL only (limited-funds) project that highly leverages significant effort at NREL on related projects including
 - PF AEM project (FC 142)
 - Membrane Working Group (FC 301)
 - ARPA-E efforts
 - FCTO HydroGEN AWSM (EMN) efforts

Summary

- We synthesized spirocyclic polymers of multiple ion exchange capacity (IEC)
- Lower IEC polymers were synthesized due to trends witnessed for increased durability with decreasing IEC.
- Thinner membranes were employed to limit the impact of lower IEC membranes in fuel cell tests.
- With optimized membranes greater than 500 hours of durability above 0.6V at 600 mA/cm² was demonstrated.
- High performance with low total PGM loading was shown using spirocyclic membranes.
- Initial performance and durability of spirocyclic ionomer based electrodes showed promise.

Response to Reviewers comments: Project presented last year but not reviewed.

Remaining Challenges and Barriers/Future Work

Remaining Challenges and Barriers

- Polymer stability remains an issue as IEC and conductivity losses in ex-situ testing were high, but fuel cell durability was reasonable when used as a membrane and in initial studies as an ionomer
- Further optimization as an electrode ionomer
 - Ink composition and processing
 - Specific IEC of ionomer material

Future Work


- Focus on ionomer implementation of spirocyclic polymer with a focus on probing cation-catalyst interactions
- Further investigation of low PGM-loaded MEAs

Technical Backup Slides

Accomplishments and Progress

Degradation Pathways – Accelerated testing

- After 144 hours some insoluble material was left behind in the reactor
- Insolubility indicates crosslinking resulting from ring opening attack of hydroxyl degradation products

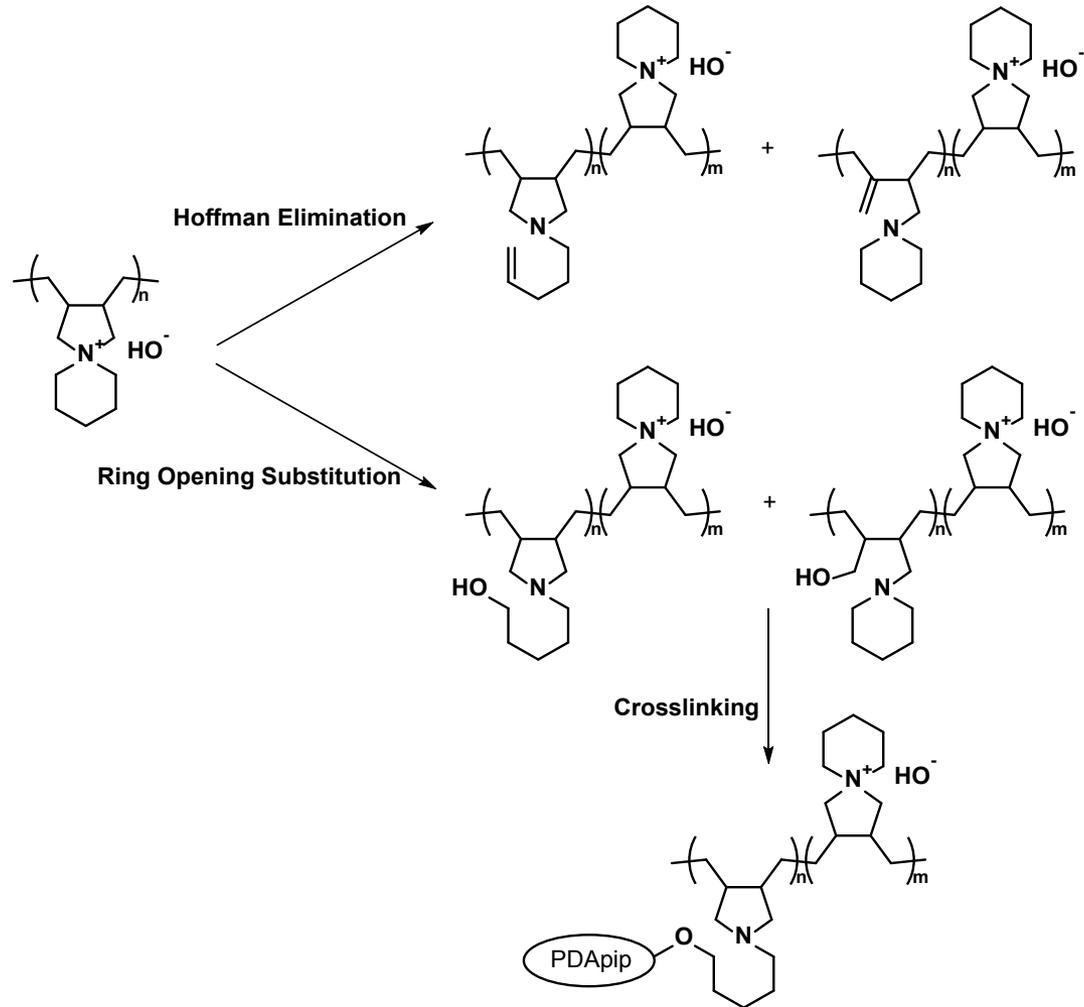


Accomplishments and Progress


Characterization - conductivity





Gen 2 - Cl⁻

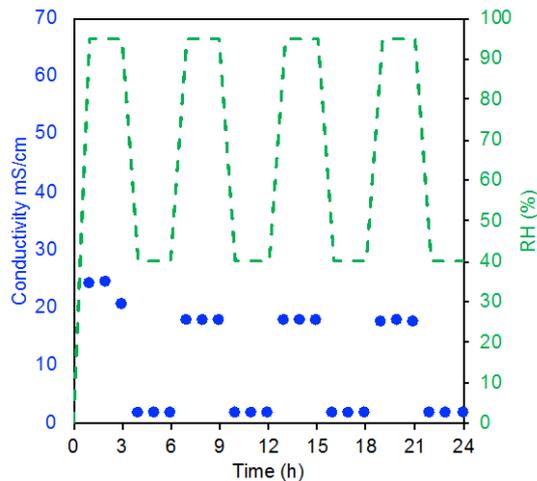

PSF 1.7 - Cl⁻


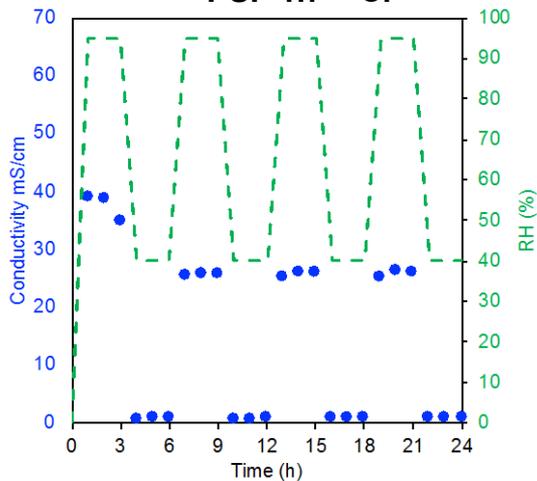


PSF 1.5 - Cl⁻

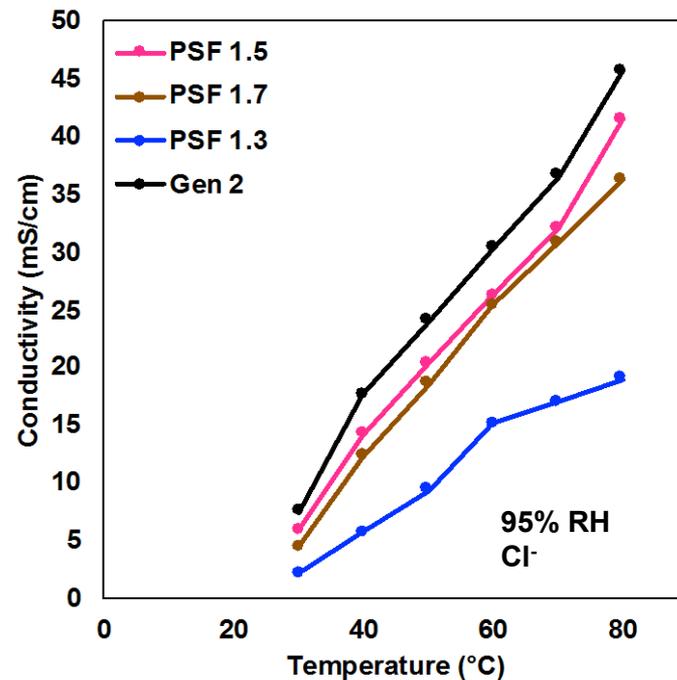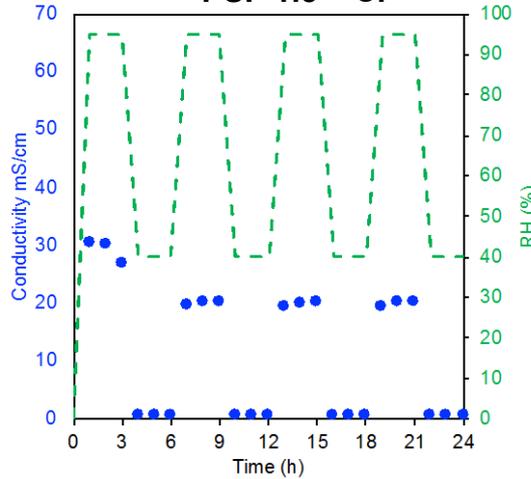




Accomplishments and Progress

Characterization – water uptake

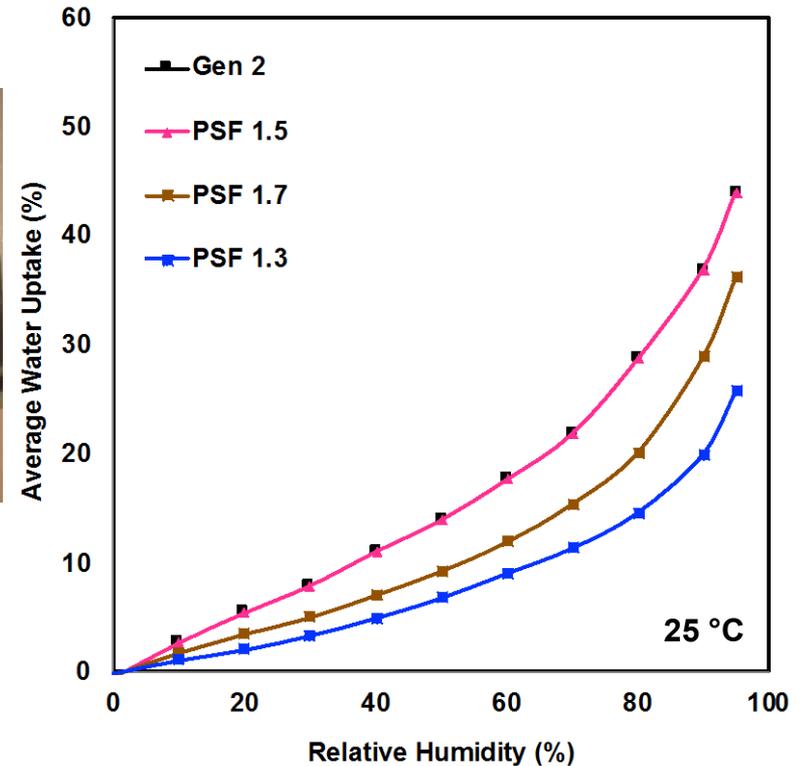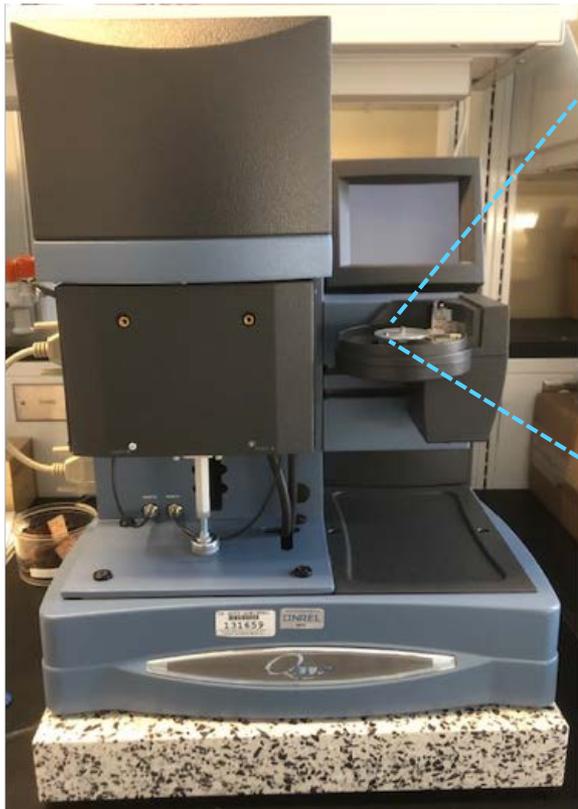

Accomplishments and Progress



Characterization

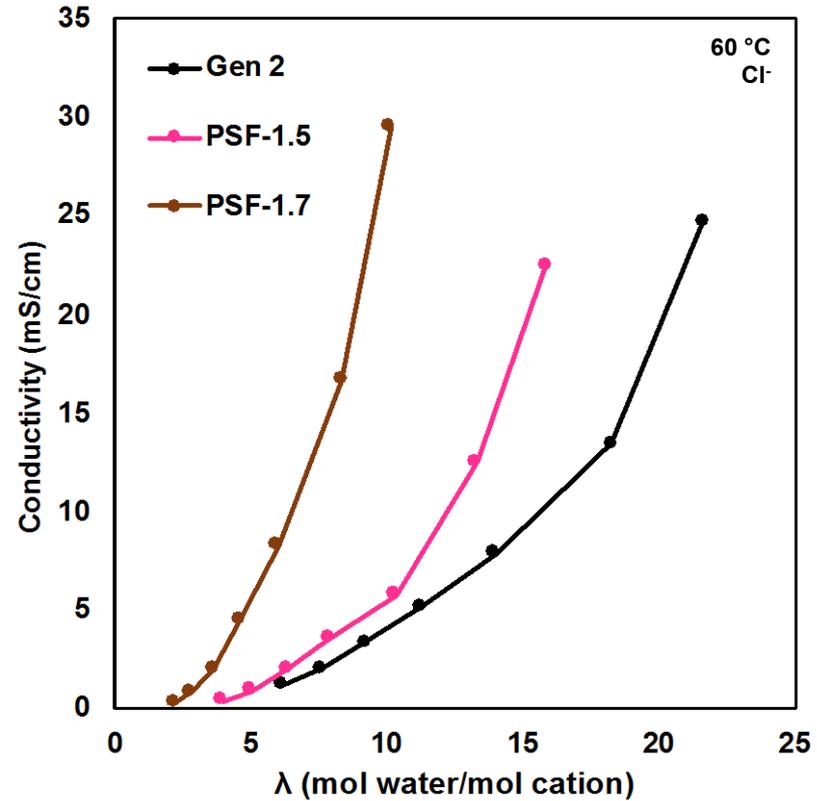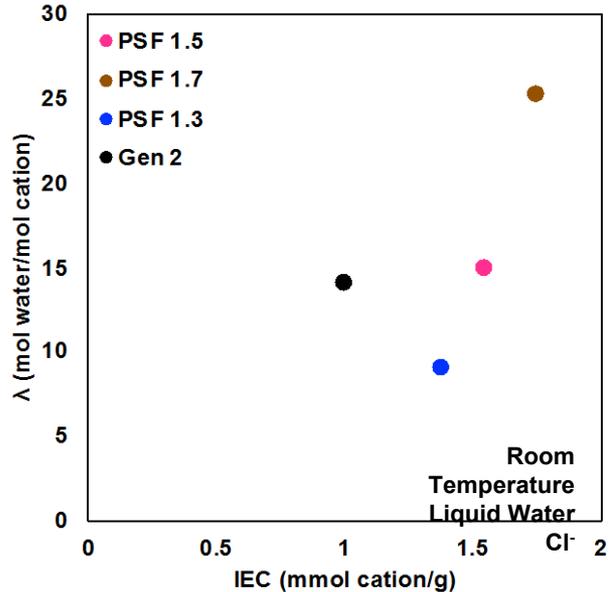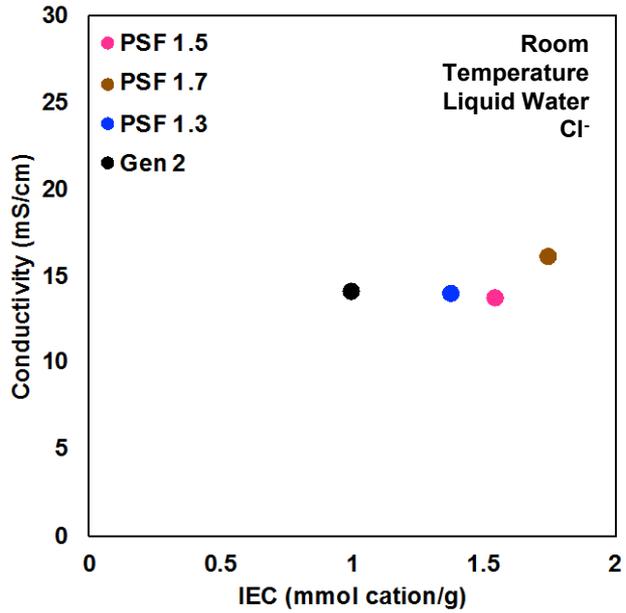

Accomplishments and Progress

Durability

Post 1000 h, 80°C Degradation Testing

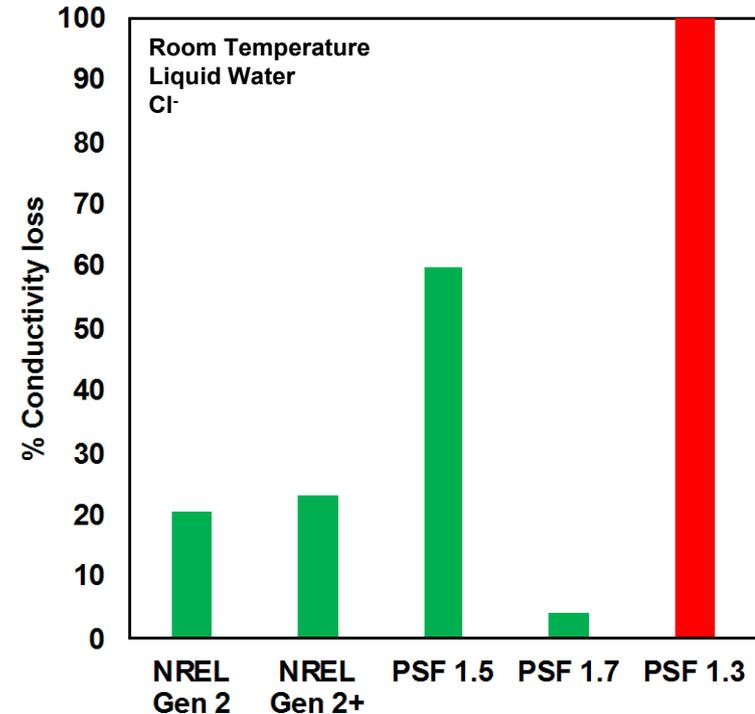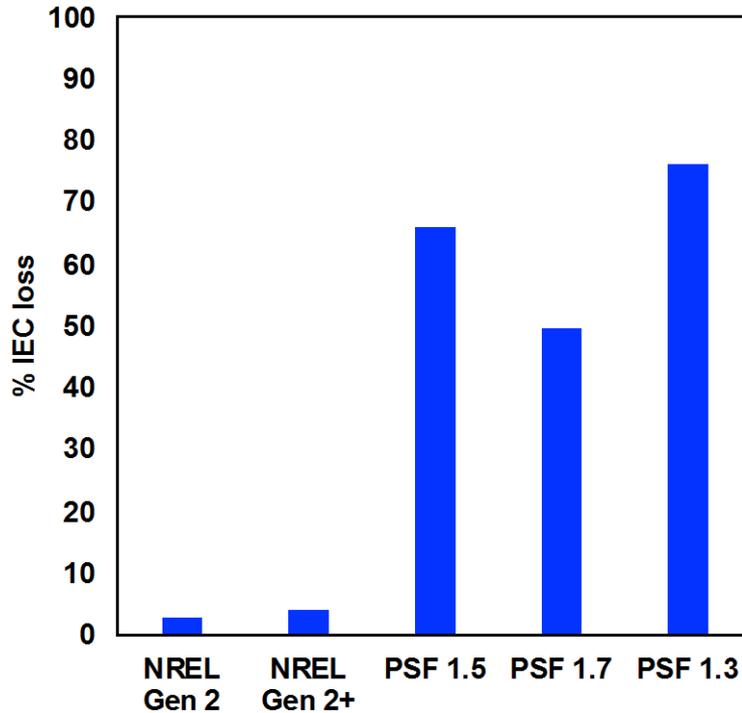

- PSF 1.7 shows improved stability relative to PSF 1.5 and PSF 1.3

- PSF-1.3 could not be measured
- Some correlation between IEC and conductivity loss, however morphology changes also seem significant